



Recovery of silver (I) using a thiourea-modified chitosan resin

Lin Wang^{a,b}, Rong Xing^a, Song Liu^a, Huahua Yu^a, Yukun Qin^{a,b}, Kecheng Li^{a,b}, Jinhua Feng^{a,b}, Rongfeng Li^{a,b}, Pengcheng Li^{a,*}

^a Institute of Oceanology, The Chinese Academy of Sciences, Qingdao, 266071, China

^b Graduate School of the Chinese Academy of Sciences, Beijing, 100039, China

ARTICLE INFO

Article history:

Received 22 January 2010

Received in revised form 9 April 2010

Accepted 15 April 2010

Available online 24 April 2010

Keywords:

Recovery

Chitosan

Thiourea

Resin

Silver

Adsorption

ABSTRACT

This work describes the preparation of a chelating resin from chemically modified chitosan. The resin was synthesized by using O-carboxymethylated chitosan to cross-link a polymeric Schiff's base of thiourea/glutaraldehyde and characterized by IR. Batch method was applied for testing the resin's adsorption behavior. Adsorption experiments showed the resin had good adsorption capacity and high selectivity for Ag(I) in aqueous solution. The maximum uptake of Ag(I) exhibited was 3.77 mmol/g, at pH 4.0. The results also indicated that the adsorption process was exothermic and fit well with the pseudo-second-order kinetic model. Ag(I) desorption could reach 99.23% using 0.5 M thiourea–2.0 M HCl solution.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Increasing industrialization and urbanization worldwide had caused serious pollution all around the world, especially in the aquatic environment. Wastewaters produced by humans are frequently laden with toxic heavy metals such as copper, silver, mercury, etc. The soluble form of these heavy metals is very dangerous because it is easily transported and more readily available to plants and animals. For humans, poisoning by these metals can result in severe dysfunction of kidney, reproduction system, liver, brain and central nervous systems [1]. Hence, to remove the toxic heavy metals from wastewaters has become increasingly focused. Furthermore, recovery of the precious metals like silver, gold and platinum will not only solve the environmental problems but also have profitable potential.

Silver is a precious metal widely used in the photographic, electrical, electronics, chemical and jewellery industries. Even though it is not as expensive as gold or platinum, silver is still only present in limited amounts in nature, which contributes to the need for efficient methods of recycling silver from waste generated by the above industries [2]. Most world silver is recovered from scraps such as photographic films, X-ray films and jewellery [3]. During the past

three decades, many methods have electrolysis [4], precipitation [5], ion flotation [6], ion-exchange [7], adsorption [8] and reverse osmosis [9], etc. Among all the above methods, adsorption using low-cost adsorbents is recognized as an emerging technique and a large variety of adsorbents have been developed and tested. For instance, activated carbon [10], polymeric adsorbents [11], clarified sludge [12] and biomaterials such as chitosan [13–15], konjac glucomannan [16], seaweed [17] and lignin [18], etc.

Chitosan, as one of the most frequently reported biosorbents, has been investigated by many researchers for recovery of heavy metals from aqueous solution. Modifications of chitosan can make it more selective and effective for several metal ions, especially heavy metal ions. Carboxymethylation was regarded as a simple and efficient way to facilitate the adsorption capacity of chitosan for many heavy metals [19]. In addition, grafting new functional groups such as thiourea [20], thiourea/rubanic acid [21], L-lysine [13] and glycine [22] onto cross-linked chitosan backbone can also improve its selectivity and adsorption ability. To date, no report has been identified on chitosan resin modified by using the two methods carboxymethylation and grafting sulfur groups (thiourea) together. In this work, a thiourea-modified chitosan resin was synthesized and characterized by Fourier transform infrared (FT-IR) spectroscopy. The adsorption behavior of the resin towards silver in aqueous solution was investigated and examined by ICP-OES. Both kinetic and thermodynamic analyses for adsorption process were reported.

* Corresponding author. Tel.: +86 532 82898707; fax: +86 532 82968951.

E-mail addresses: pcli@ms.qdio.ac.cn, wanglin@ms.qdio.ac.cn (P. Li).

2. Experimental

2.1. Instrumentation

Inductively Coupled Plasma Optical Emission Spectrometry (ICP-OES, Thermo-Fisher) was used to determine the concentration of metal ions. Fourier transform infrared spectroscopy was used to analyze the functional groups in the synthesized resin and the original chitosan.

2.2. Chemicals

Chitosan with 80 mesh, 96% degree of deacetylation and average-molecular weight of 6.36×10^5 was purchased from Qingdao Baicheng Biochemical Corp. (China). Glutaraldehyde, thiourea and other chemicals and reagents were from Sigma Chemicals Co. All the other reagents were analytical grade and distilled water was used to prepare all the solution. Standard solution of silver (1000 mg/l) for ICP-OES was obtained from Beijing NCS Analytical Instruments Co. Ltd. Metal ions of nitrate form were used and 0.1 M HNO_3 and 0.1 M NaOH were used for pH adjustment.

2.3. Synthesis of the thiourea-modified chitosan resin

O-carboxymethyl-chitosan was prepared following the method of Zhu et al. [23]. 2 g chitosan was immersed in 25 ml of 50 wt% NaOH solution to swell and alkalinize for 24 h. Five grams of monochloroacetic acid was dissolved in 25 ml of isopropanol, and then added drop-wise to the flask containing the alkalinized chitosan after filtration for 20 min. The reaction continued 8 h at room temperature and then the mixture was filtered to remove the solvent. The filtrate obtained was dissolved in 100 ml of water, and 2.5 M HCl was added to it to adjust its pH to 7. After this solution was centrifuged to remove the precipitate, 400 ml of anhydrous ethanol was added to it and the precipitate was O-carboxymethyl-chitosan.

3.0 g of thiourea was dissolved in 60-ml distilled water. 17.1 ml of (50%) glutaraldehyde solution was added to thiourea solution in a round flask. The mixture was heated on a water bath for 3 h at 323 K. After completion of the reaction, 1.36 g of carboxymethyl-chitosan was dissolved in 30-ml distilled water, and the solution was then added to the mixture of the flask and heated for 8 h at 343 K. A large quantity of resin was formed, and washed several times with dilute sodium hydroxide, distilled water and acetone respectively. The resin was dried at 333 K for 3 h and weighed about 2.96 g, and then sieved where the particle size fraction 0.1–0.4 mm was used in this study.

2.4. Characterization of the resin

FT-IR-spectra were used to identify the structure of the synthesized resin. The sample was prepared mixing 1 mg of the material with 100 mg of spectroscopy grade KBr. The FT-IR-spectra were recorded using Nicolet Magne-Avatar 360 equipment.

2.5. Preparation of solution

A stock solution of silver nitrate (1×10^{-2} M) was prepared in distilled water. 0.1 M HNO_3 and 0.1 M NaOH were used to change the acidity of the medium.

2.6. pH study of Ag(I) adsorption onto the modified chitosan resin

The experiments performed to determine the effect of pH on Ag(I) adsorption were carried out by placing 0.1 g of dry resin in a series of flasks containing 100 ml 1×10^{-2} M metal ion solution. The desired pH was adjusted using 0.1 M HNO_3 and 0.1 M NaOH. The

flasks were shaken at 300 rpm for 12 h at 298 K. After adsorption, the filtrate of each flask was obtained and the metal ion concentration was determined by ICP-OES.

2.7. Adsorption kinetics

The effect of contact time on the uptake of Ag(I) by the resin was done by placing 0.1 g of dry resin in a series of flasks. To each flask, 100 ml of Ag(I) at pH 4.0 with initial concentration of 1×10^{-2} M was added. The flasks were shaken at 298 K. Samples of 5 ml solution were withdrawn at scheduled time intervals and analyzed for Ag(I) concentration.

2.8. Adsorption isotherms

0.1 g dry resin was swelled in a series of 250-ml flasks containing 50 mL of distilled water for 1 h. In each flask, 50 mL of metal ion solution at desired concentration was added to the flask, and the pH value was recorded. The flasks were shaken at 300 rpm while keeping the temperature at 298, 308, 318 and 328 K for 12 h. Later on, the concentration of solution was determined by ICP-OES and the metal ion uptake was calculated.

2.9. Metal ions co-adsorption experiment

The selective separation of Ag(I) from binary mixtures with Cu(II), Ni(II), Cd(II), Zn(II) and Ca(II) was carried at pH 1.0 with the same other adsorption conditions in Section 2.6. After adsorption equilibrium, the concentration of each metal ion in the solution was measured by ICP-OES.

2.10. Desorption and reusability

Ag(I)-loaded modified chitosan resin was collected and washed with deionized water to remove any unadsorbed metal ions. Then batch desorption experiments were carried out using various concentrations of thiourea, HCl and thiourea-HCl solutions. The resin after desorption was rinsed with deionized water, dried and then reused in adsorption experiment. The process was repeated for five times.

3. Results and discussions

3.1. Characteristics of the resin

As seen from Fig. 1, the adsorption band around 3300 cm^{-1} in all spectrums, revealed the stretching vibration of $-\text{NH}_2$ and $-\text{OH}$ groups in chitosan, and the bands near 1641 and 1555 cm^{-1} in the spectrum of the resin are assigned to $\nu \text{ C}=\text{N}$ of Schiff's base moiety and $\nu \text{ C}-\text{N}$ of thiourea moiety, respectively [24]. The spectrum of the resin also displays new bands near 1108 and 1053 cm^{-1} corresponding to $\nu \text{ C}-\text{O}$, one of the characteristics of O-carboxymethyl-chitosan [25]. Besides, a lot of differences in the spectra before and after silver sorption were observed. The bands at 2917 cm^{-1} strengthened. The intensity of the band around 1400 cm^{-1} which is assigned to $>\text{N}-\text{C}=\text{S}$ group [22] was substantially decreased after Ag(I) binding, which confirms that sulfur groups were involved in silver binding. In the spectrum of silver adsorbed onto the modified resin, the peak at 1641 cm^{-1} disappeared and a new peak around 1703 cm^{-1} came out. Additionally, the changes in the spectra around 3300 cm^{-1} and the decreasing intensity at 1053 cm^{-1} also indicated that the nitrogen atoms as well as oxygen atoms in the $-\text{OH}$ and $-\text{CO}$ groups were involved in silver adsorption.

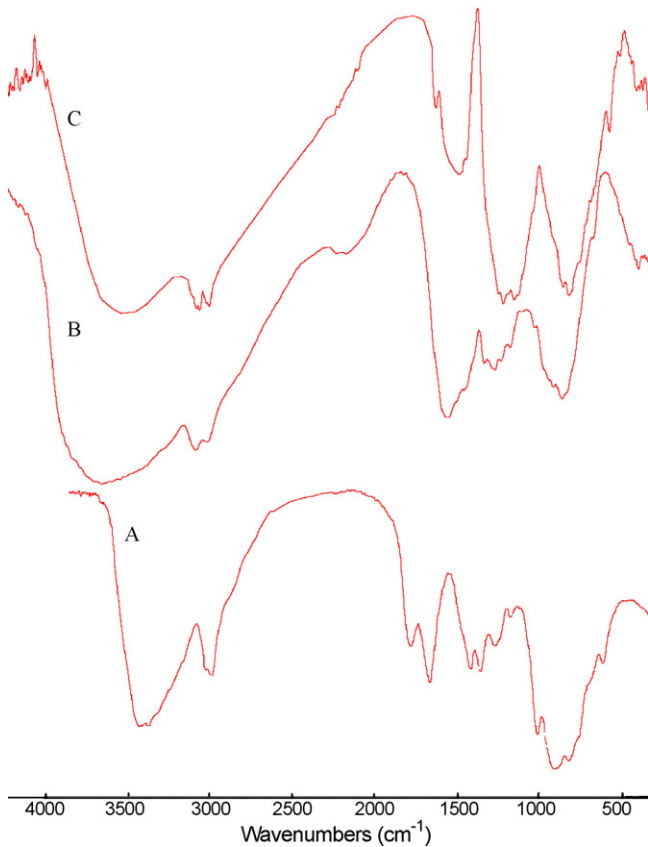


Fig. 1. FT-IR spectra of chitosan (A), the thiourea-modified chitosan resin before (B) and after (C) Ag(I) adsorption.

3.2. The pH effect on Ag(I) sorption

In Fig. 2, it is clearly seen that the uptake of Ag(I) increases as the pH increases till reaching a maximum value around pH 4.0. The pH value of solution increased after adsorption equilibrium. At the initial pH < 4.0, the increase of pH was more obvious and the final pH could reach above 6.0, while at the initial pH > 4.0, the final pH slightly elevated and did not go beyond 8.0. As reported by Chassary et al. [20], at lower pH, part of metal sorption can be explained by electrostatic attraction of anion metal complexes by protonated amine groups. With pH reaching about 4.0, the higher adsorption capacity might be due to the presence of free lone pairs

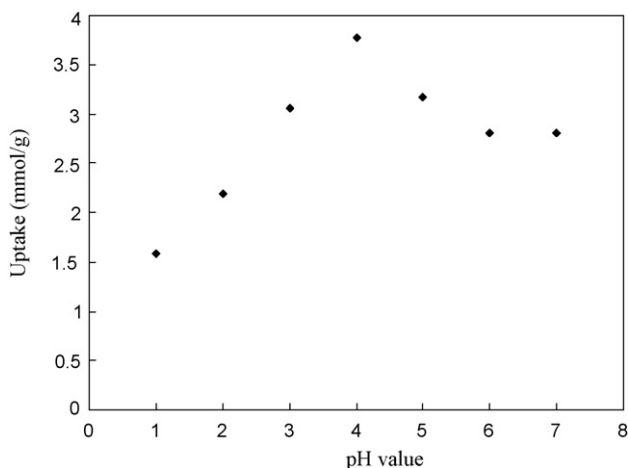


Fig. 2. Effect of the initial pH on the uptake of Ag(I) by the studied resin.

Table 1

Parameters of the pseudo-first-order, pseudo-second-order kinetic models and intra-particle diffusion model for recovery of Ag(I) on the studied resin.

Metal ion	Pseudo-first-order		
	k_1 (min ⁻¹)	q_e (mmol/g)	R^2
Ag(I)	0.016	1.87	0.9857
Metal ion	Pseudo-second-order		
	k_2 (g/mmol min)	q_e (mmol/g)	R^2
Ag(I)	0.126	4.1	0.9979
Metal ion	Intra-particle diffusion		
	k_{id} (mmol/gmin ^{0.5})	Intercept	R^2
Ag(I)	1.368	0.313	0.99

of electrons on nitrogen and sulfur atoms that are suitable for coordination with Ag(I) to give the corresponding resin–metal complex. At higher pH, the decreased adsorption of precious metals observed may be due to precipitation and the electrostatic repulsion between surface sites of adsorbent and metal ions [22].

3.3. Adsorption kinetics

The effect of contact time on the adsorption of Ag(I) is shown in Fig. 3a. Experimental results suggested that the silver adsorption could reach equilibrium within 4 h. The reaction kinetic parameters for the adsorption process were studied by batch method. The pseudo-first-order [26], pseudo-second-order [27] and intra-particle diffusion [28] kinetic models were selected to elucidate the adsorption kinetic process in this work.

The Lagergren pseudo-first-order kinetic model is represented as:

$$\log(q_e - q_t) = \log q_e - \left(\frac{k_1}{2.303}\right) t \quad (1)$$

where k_1 is the pseudo-first-order rate constant (min⁻¹) of adsorption, q_e and q_t (mmol/g) are the amounts of metal ion adsorbed at equilibrium and time t (min), respectively. The q_e and rate constant k_1 were calculated by plotting the $\log(q_e - q_t)$ versus t . The plots for pseudo-first-order model are presented in Fig. 3b.

The pseudo-second order model can be written as:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \left(\frac{1}{q_e}\right) t \quad (2)$$

where k_2 is the pseudo-second-order rate constant of adsorption (g/(mmol min⁻¹)). The kinetic parameters for pseudo-second-order model are determined from the linear plots of (t/q_t) versus t . The plots for pseudo-second-order model are presented in Fig. 3c.

The parameters for pseudo-first and pseudo-second order models were all shown in Table 1. Accordingly as shown in Table 1, the calculated q_e value of pseudo-second-order kinetic model is in good agreement with experimental q_e value (3.77 mmol/g) and could fit the adsorption of Ag(I) on the resin very well. To further test whether the adsorption rate is controlled by intra-particle diffusion, the intra-particle diffusion model was used.

The initial adsorption rate (h) can be determined from k_2 and q_e values using

$$h = k_2 q_e^2 \quad (3)$$

The linear form of the intra-particle diffusion equation can be described as:

$$\ln q_t = \ln k_{id} + 0.5 \ln t \quad (4)$$

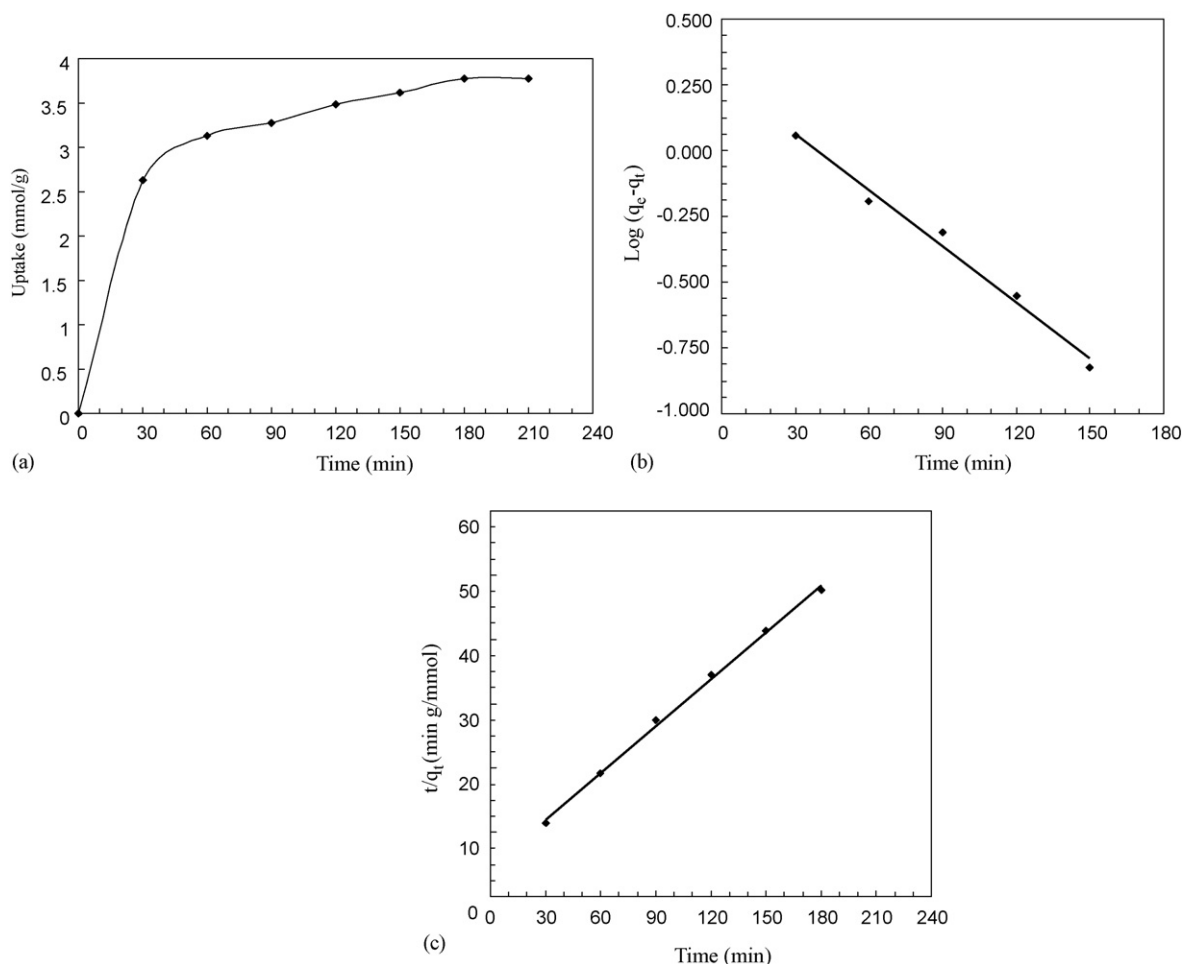


Fig. 3. (a) Effect of adsorption time on the uptake of Ag(I). (b) Pseudo-first-order kinetic plots for the adsorption of Ag(I). (c) Pseudo-second-order kinetic plots for the adsorption of Ag(I).

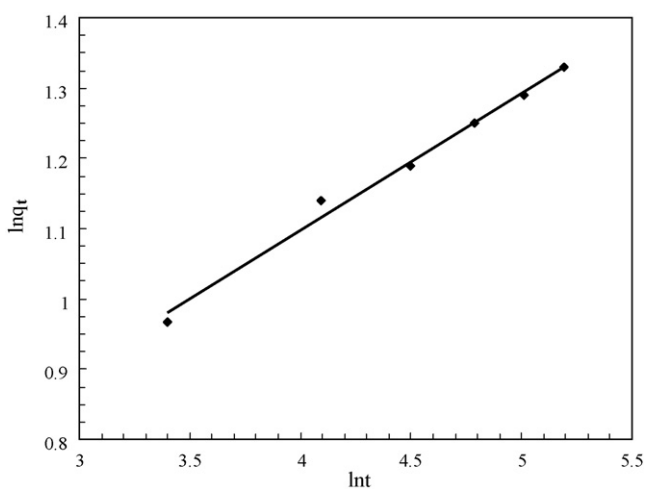


Fig. 4. Plots for intra-particle diffusion.

where k_{id} ($\text{mmol}/(\text{g min}^{1/2})$) is the intra-particle diffusion rate constant, which can be obtained from the slope of the plot $\ln q_t$ versus $\ln t$ in Fig. 4. The kinetic parameters from this model are also given in Table 1. From the experimental results, the main adsorption mechanism may be chemical sorption and consist of the external surface adsorption and the gradual adsorption stage. In gradual adsorption stage, intra-particle diffusion is rate controlling step.

3.4. Adsorption isotherms

Fig. 5 shows the isotherms of adsorption of Ag (I) on the thiourea-modified chitosan resin. The results illustrated that the

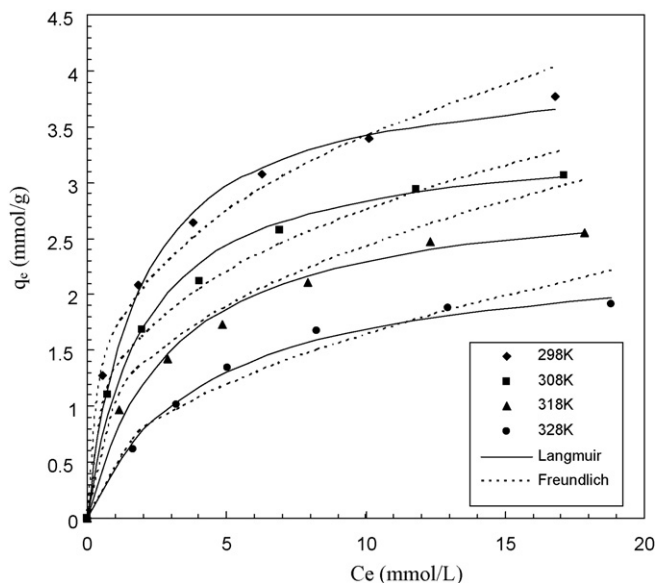


Fig. 5. Plots of Langmuir and Freundlich models at different temperatures.

Table 2
Langmuir and Freundlich constants for adsorption of Ag(I) by resin.

Temperature (K)	Langmuir model		
	Q_{\max} (mmol/g)	K_L (L/mmol)	R^2
298	4.09	0.564	0.9963
308	3.40	0.506	0.9975
318	2.98	0.335	0.9954
328	2.41	0.236	0.9928
Temperature (K)	Freundlich model		
	k_f (l/g)	n	R^2
298	1.64	3.140	0.9802
308	1.30	3.065	0.9813
318	1.05	2.732	0.9866
328	1.79	2.134	0.9310

adsorption capacity decreased with elevated temperature. To interpret the adsorption experimental data, the Langmuir and Freundlich isotherm models were used.

The Langmuir model can be expressed as:

$$\frac{C_e}{q_e} = \frac{C_e}{Q_{\max}} + \frac{1}{K_L Q_{\max}} \quad (5)$$

where C_e is the equilibrium concentration of metal ions in solution (mmol/l), q_e the adsorbed value of metal ions at equilibrium concentration (mmol/g), Q_{\max} (mmol/g) and K_L (l/mmol) are the Langmuir constants which are related to the adsorption capacity and energy of adsorption, respectively, and can be calculated from the intercept and slope of the linear plot, with C_e/q_e versus C_e . The values of K_L and Q_{\max} at different temperatures for adsorption of Ag (I) were reported in Table 2. It is seen that the value of Q_{\max} at 298 K (obtained from Langmuir plots) is consistent with that experimentally obtained (3.77 mmol/g), indicating that the adsorption process mainly monolayer.

The adsorption curves showed that the maximum uptake value for Ag (I) was 3.77 mmol/g. In former study, chitosan's maximum uptake value for Ag (I) was 42.0 mg/g [29]. Compared to chitosan, the higher maximum adsorption capacity obtained for Ag (I) on this resin is because of the fact that the carboxymethylation and incorporation of thiourea in chitosan increase the number of sorption sites, which enhances the adsorption capacity.

The degree of suitability of resin towards Ag (I) was estimated from the values of the separation factor constant (R_L) which can be calculated from the equation:

$$R_L = \frac{1}{1 + K_L C_0} \quad (6)$$

where K_L (l/mmol) is the Langmuir equilibrium constant and C_0 (mmol/l) is the initial concentration of metal ion. $R_L > 1.0$ unsuitable; $R_L = 1$ linear; $0 < R_L < 1$ suitable; $R_L = 0$ irreversible. The values of R_L lie between 0.151 and 0.298 confirming the suitability of the resin for the recovery of Ag (I).

The Freundlich model assumes heterogeneous adsorption due to the diversity of the adsorption sites or the diverse nature of the metal ions adsorbed, free or hydrolyzed species.

The Freundlich model is expressed as:

$$q_e = k_f C_e^{1/n} \quad (7)$$

where k_f ($l^{(1-1/n)}/g$) is the Freundlich constant related to adsorption capacity of adsorbent and n is the Freundlich exponent related to adsorption intensity. k_f and n can be calculated from the slope and intercept of the linear plot of $\log q_e$ versus $\log C_e$.

The adsorption data fit with Freundlich isotherm model is also shown in Table 2. The R^2 values and the plots in Fig. 5 indicated

Table 3
Thermodynamic parameters at different temperatures.

Temperature (K)	ΔG° (kJ/mol)	ΔH° (kJ/mol)	ΔS° (J/mol K)
298	-14.13	-24.77	-35.70
308	-13.77		
318	-13.41		
328	-13.06		

that the Langmuir model fits the experimental data better than the Freundlich model.

The values of K_L at different temperatures were treated according to van't Hoff equation [30],

$$\ln K_L = -\frac{\Delta H^\circ}{RT} + \frac{\Delta S^\circ}{R} \quad (8)$$

where ΔH° (J/mol) and ΔS° (J/mol K) are enthalpy and entropy changes, respectively, R is the universal gas constant (8.314 J/mol K) and T is the absolute temperature (in Kelvin). Plotting $\ln K_L$ against $1/T$ gives a straight line with slope and intercept equal to $-\Delta H^\circ/R$ and $\Delta S^\circ/R$, respectively.

Gibbs free energy of adsorption (ΔG° (J/mol)) was calculated from the following relation.

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (9)$$

The values of ΔH° , ΔS° and ΔG° were reported in Table 3. The negative values of ΔH° confirm the exothermic nature of adsorption process. The observed decrease in negative values of ΔG° with increasing temperature implies that the adsorption becomes less favorable at higher temperature.

Table 4 compares the maximum adsorption capacity of the thiourea-modified chitosan resin for Ag(I) with other adsorbents reported in the literature. The result demonstrated that the adsorption capacity of this resin was relatively higher than several other adsorbents.

3.5. Metal ions co-adsorption

Selective separation of Ag(I) from binary mixtures with Cu(II), Ni(II), Cd(II), Zn(II) and Ca(II) was studied at pH 1.0 and the other adsorption conditions was following Section 2.6. The uptake obtained for Ag(I) in the presence of Cu(II), Ni(II), Cd(II), Zn(II) and Ca(II) was 2.26, 0.3, 0.1, 0.02, 0.5 and 0.0 mmol/g, respectively. The especially higher uptake of Ag(I) compared to other metal ions at relatively lower pH value (1.0) may be useful in the selective separation of Ag(I) from other metal ions.

3.6. Desorption and reusability

Desorption efficiency of the modified resin was studied by the batch method using various concentrations of thiourea, HCl and thiourea-HCl solutions. The results are presented in Table 5. It was found that 0.5 M thiourea-2.0 M HCl solution can effectively desorbed the Ag(I) (>98%) from adsorbent material. The

Table 4
Maximum adsorption capacities for adsorption of Ag(I) onto various adsorbents.

Absorbent	Adsorption capacity (mmol/g)
Surface molecular-imprinted biosorbent [31]	1.846
Chemically modified melamine resins [32]	0.95
Chemically modified chitosan with magnetic properties [24]	2.1
Resin derived from 3-amino-1,2,4-triazole-5-thiol and glutaraldehyde [33]	3.6
Thiourea-modified chitosan resin (this work)	3.77

Table 5
Desorption process.

Desorption agent	Desorption efficiency (%)
0.1 M Thiourea	32.37
0.3 M Thiourea	71.25
0.5 M Thiourea	86.31
1.0 M Thiourea	92.60
0.5 M HCl	33.72
1.0 M HCl	60.14
1.5 M HCl	67.29
2.0 M HCl	72.38
0.5 M Thiourea–2.0 M HCl	99.23

high desorption efficiency obtained when 0.5 M thiourea–2.0 M HCl solution was used may be explained by the electrostatic interactions between the silver(I) species and charged species from elution, through the comparison of the electric double layer, which would weaken the interaction between the adsorbent and silver(I), promoting desorption. Also the resin can be reused after desorption with 0.5 M thiourea–2.0 M HCl solution. The resin reused for 5 cycles and the uptake of Ag(I) was 3.73, 3.71, 3.66, 3.65 and 3.63 mmol/g, respectively. These results showed that the adsorption capacity of this modified chitosan resin was not significantly changed up to 5 cycles and the desorption efficiencies were above 95%. Therefore, the resin had good durability and could be successfully applied for the recovery of Ag(I).

4. Conclusions

The recovery of silver (I) from aqueous medium was studied using a thiourea-modified chitosan resin. The FT-IR picture confirmed the efficient modification of this chitosan resin. The results suggested that the adsorption process was dependent on contact time, initial metal ion concentration, solution pH and temperature. The data also indicated that the adsorption reaction followed the pseudo-second-order kinetic model and fit well with the Langmuir isotherm equation as well as the simplified intra-particle diffusion equation. The 0.5 M thiourea–2.0 M HCl solution can effectively desorb silver (I) from the resin and this resin could be reused up to 5 times without obvious change in the uptake of silver (I).

Acknowledgements

This work was supported by the National High Technology Research and Development Program (“863” Program) of China (2007AA091600), the foundation of Special Prize of President Scholarship for Postgraduate Students of Chinese Academy of Sciences and a grant from the Applied Basic Research Programs of Science and Technology Bureau of Qingdao (no. 09-1-3-23-jch).

References

- [1] J.P. Chen, L.L. Lim, Key factors in chemical reduction by hydrazine for recovery of precious metals, *Chemosphere* 49 (2002) 363–370.
- [2] R. Dimeska, P.S. Murray, S.F. Ralph, G.G. Wallace, Electroless recovery of silver by inherently conducting polymer powders, membranes and composite materials, *Polymer* 47 (2006) 4520–4530.
- [3] V.I.E. Ajiwe, I.E. Anyadiegwu, Recovery of silver from industrial wastes, cassava solution effects, *Sep. Purif. Technol.* 18 (2000) 89–92.
- [4] K.C. Pillai, S.J. Chung, Il-Shik Moon, Studies on electrochemical recovery of silver from simulated waste water from Ag(II)/Ag(I) based mediated electrochemical oxidation process, *Chemosphere* 73 (2008) 1505–1511.
- [5] G. Pfrepper, R. Pfrepper, M. Knothe, Recovery of palladium and silver from process solutions by precipitation with thiocyanates and iron cyanides, *Hydrometallurgy* 21 (1989) 293–304.
- [6] A.I. Zouboulis, Silver recovery from aqueous streams using ion flotation, *Miner. Eng.* 8 (1995) 1477–1488.
- [7] S. Pavlinic, I. Piljac, Electrolytic desorption of silver from ion-exchange resins, *Water Res.* 32 (1998) 2913–2920.
- [8] K.G. Adani, R.W. Barley, R.D. Pascoe, Silver recovery from synthetic photographic and medical X-ray process effluents using activated carbon, *Miner. Eng.* 18 (2005) 1269–1276.
- [9] H. Koseoglu, M. Kitis, The recovery of silver from mining wastewaters using hybrid cyanidation and high-pressure membrane process, *Miner. Eng.* 22 (2009) 440–444.
- [10] D. Mohan, C.U. Pittman Jr., Activated carbons and low cost adsorbents for remediation of tri- and hexavalent chromium from water, *J. Hazard. Mater.* 137 (2006) 762–811.
- [11] K. Zheng, B. Pan, Q. Zhang, W. Zhang, B. Pan, Y. Han, Q. Zhang, D. Wei, Z. Xu, Q. Zhang, Enhanced adsorption of p-nitroaniline from water by a carboxylated polymeric adsorbent, *Sep. Purif. Technol.* 57 (2007) 250–256.
- [12] A.K. Bhattacharya, T.K. Naiya, S.N. Mandal, S.K. Das, Adsorption, kinetics and equilibrium studies on removal of Cr(VI) from aqueous solutions using different low-cost adsorbents, *Chem. Eng. J.* 137 (2008) 529–541.
- [13] K. Fujiwara, A. Ramesh, T. Maki, H. Hasegawa, K. Ueda, Adsorption of platinum (IV), palladium (II) and gold (III) from aqueous solutions onto l-lysine modified crosslinked chitosan resin, *J. Hazard. Mater.* 146 (2007) 39–50.
- [14] S.T. Lee, F.L. Mi, Y.J. Shen, S.S. Shyu, Equilibrium and kinetic studies of copper(II) ion uptake by chitosan-tripolyphosphate chelating resin, *Polymer* 42 (2001) 1879–1892.
- [15] C.Q. Qin, Y.M. Du, Z.Q. Zhang, Y. Liu, L. Xiao, X.W. Shi, Adsorption of chromium (VI) on a novel quaternized chitosan resin, *J. Appl. Polym. Sci.* 90 (2003) 505–510.
- [16] C. Niu, W. Wu, Z. Wang, S. Li, J. Wang, Adsorption of heavy metal ions from aqueous solution by crosslinked carboxymethyl konjac glucomannan, *J. Hazard. Mater.* 141 (2007) 209–214.
- [17] K.N. Ghimire, K. Inoue, K. Ohto, T. Hayashida, Adsorption study of metal ions onto crosslinked seaweed *Laminaria japonica*, *Bioresour. Technol.* 99 (2008) 32–37.
- [18] X. Guo, S. Zhang, X.-q. Shan, Adsorption of metal ions on lignin, *J. Hazard. Mater.* 151 (2008) 134–142.
- [19] C. Jeon, W.H. Holl, Chemical modification of chitosan and equilibrium study for mercury ion removal, *Water Res.* 37 (2003) 4770–4780.
- [20] P. Chassary, T. Vincent, E. Guibal, Metal anion sorption on chitosan and derivative materials: a strategy for polymer modification and optimum use, *React. Funct. Polym.* 60 (2004) 137–149.
- [21] E. Guibal, N. Von Offenbergen Sweeney, T. Vincent, J.M. Tobin, Sulfur derivatives of chitosan for palladium sorption, *React. Funct. Polym.* 50 (2002) 149–163.
- [22] A. Ramesh, H. Hasegawa, W. Sugimoto, T. Maki, K. Ueda, Adsorption of gold(III), platinum(IV) and palladium(II) onto glycine modified crosslinked chitosan resin, *Bioresour. Technol.* 99 (2008) 3801–3809.
- [23] A. Zhu, M.B. Chan-Park, S. Dai, L. Li, The aggregation behavior of O-carboxymethylchitosan in dilute aqueous solution, *Colloids Surf., B* 43 (2005) 143–149.
- [24] A.M. Donia, A.A. Atia, K.Z. Elwakeel, Recovery of gold(III) and silver(I) on a chemically modified chitosan with magnetic properties, *Hydrometallurgy* 87 (2007) 197–206.
- [25] X.-G. Chen, H.-J. Park, Chemical characteristics of O-carboxymethyl chitosans related to the preparation conditions, *Carbohydr. Polym.* 53 (2003) 355–359.
- [26] S. Lagergren, Zur theorie der sogenannten adsorption gelöster Stoffe, *K. Sven. Vetenskapsakad. Handl.* 24 (1898) 1–39.
- [27] Y.S. Ho, G. McKay, The kinetics of sorption of divalent metal ions onto sphagnum moss peat, *Water Res.* 34 (2000) 735–742.
- [28] W.J. Weber, J.C. Morris, Kinetics of adsorption of carbon from solutions, *J. Sanit. Eng. Div. Am. Soc. Civ. Eng.* 89 (1963) 31–63.
- [29] A. Bhatnagar, M. Sillanpää, Applications of chitin- and chitosan-derivatives for the detoxification of water and wastewater—a short review, *Adv. Colloid Interface Sci.* 152 (2009) 26–38.
- [30] J. Tellinghuisen, Van't Hoff analysis of K° (T): How good...or bad? *Biophys. Chem.* 120 (2006) 114–120.
- [31] H. Huo, H. Su, T. Tan, Adsorption of Ag⁺ by a surface molecular-imprinted biosorbent, *Chem. Eng. J.* 150 (2009) 139–144.
- [32] M.A. Abd El-Ghaffar, Z.H. Abdel-Wahab, K.Z. Elwakeel, Extraction and separation studies of silver(I) and copper(II) from their aqueous solution using chemically modified melamine resins, *Hydrometallurgy* 96 (2009) 27–34.
- [33] M.A. Abd El-Ghaffar, M.H. Mohamed, K.Z. Elwakeel, Adsorption of silver(I) on synthetic chelating polymer derived from 3-amino-1,2,4-triazole-5-thiol and glutaraldehyde, *Chem. Eng. J.* 151 (2009) 30–38.