

Enzymatic deinking of secondary fibers: cellulases/hemicellulases versus laccase-mediator system

David Ibarra · M. Concepción Monte ·
Angeles Blanco · Angel T. Martínez ·
María J. Martínez

Received: 15 December 2010 / Accepted: 12 May 2011 / Published online: 4 June 2011
© Society for Industrial Microbiology 2011

Abstract The use of enzymes has been suggested as an environmentally friendly alternative to complement conventional chemical deinking in the recycling of recovered paper. This study compares the use of cellulases/hemicellulases versus the laccase-mediator system for deinking printed fibers from newspapers and magazines. For this purpose, two commercial enzyme preparations with endoglucanase and endoxylanase activities (Viscozyme Wheat from *Aspergillus oryzae* and Ultraflo L from *Humicola insolens*, Novozymes) and a commercial laccase (NS51002 from *Trametes villosa*, Novozymes), the latter in the presence of synthetic or natural (lignin-related) mediators, were evaluated. The enzymatic treatments were studied at the laboratory scale using a standard chemical deinking sequence consisting of a pulping stage; an alkaline stage using NaOH, sodium silicate and fatty acid soap; and a bleaching stage using hydrogen peroxide. The handsheets

were then prepared and their brightness, residual ink concentration, and strength properties were measured. Among the different enzymatic treatments assayed, both carbohydrate hydrolases were found to deink the secondary fibers more efficiently. Brightness increased up to 3–4% ISO on newspaper fibers, being Ultraflo 20% more efficient in the ink removal. Up to 2.5% ISO brightness increase was obtained when magazine fibers were used, being Viscozyme 9% more efficient in the ink removal. Regarding the laccase-mediator system, alone or in combination with carbohydrate hydrolases, it was ineffective in deinking both newspaper and magazine fibers, resulting in pulps with worse brightness and residual ink concentration values. However, pulp deinking by the laccase-mediator system was displayed when secondary fibers from printed cardboard were used, obtaining up to 3% ISO brightness increase and lower residual ink concentrations.

Keywords Cellulases · Deinking · Laccase-mediator system · Recycling · Secondary fibers · Hemicellulases

D. Ibarra (✉) · A. T. Martínez · M. J. Martínez (✉)
Centro de Investigaciones Biológicas,
Environmental Biology Department, CSIC,
Ramiro de Maeztu 9, 28040 Madrid, Spain
e-mail: david.ibarra@ciemat.es

M. J. Martínez
e-mail: mjmartinez@cib.csic.es

M. Concepción Monte · A. Blanco
Chemical Engineering Department,
Universidad Complutense, Avenida Complutense s/n,
28040 Madrid, Spain

Present Address:

D. Ibarra
CIEMAT, Renewable Energy Division,
Biofuels Unit, Avenida Complutense 22, 28040 Madrid, Spain

Introduction

Recovered paper is an important source of raw material for the pulp and paper industry. Indeed, the utilization of these secondary fibers is increasing all over the world, the deinking being an important step in the recycling process for white grade papers. In the traditional deinking process, large quantities of chemicals are used [29], which makes the method expensive, environmentally damaging, and also increases the release of contaminants. In this context, enzymes could reduce the demand of chemicals and would also lower the process costs and the environmental impact [1, 31]. These enzymes include cellulases, hemicellulases,

pectinases, amylases, lipases, esterases, and laccases [6, 10, 22, 24, 25, 37].

Among the different enzymes assayed, the enzymatic deinking using carbohydrate hydrolases, with activities involved in cellulose and hemicellulose hydrolysis, has been widely demonstrated on different secondary fibers [10, 14, 17, 18, 20, 24, 25, 32, 36] being applied in several paper mills [11]. The mechanism of deinking by these enzymes has not been completely elucidated, although some hypotheses have been described [11, 14]. The cellulose and hemicellulose hydrolysis on the surface of the fibers leads to a removal of small fibrils, a phenomenon known as “peeling-off fibers”, which facilitates ink detachment from the surface. It has also been suggested that the alteration of the ink particles hydrophobicity because of the removal of small fibrils enhances their separation (fiber/ink separation) in the flotation/washing step.

The interest in the use of laccases, alone or in combination with cellulases and/or hemicellulases, for deinking secondary fibers has been greatly increased in the last years [15–17, 21, 26, 35]. Laccases in the presence of redox mediators, the so-called laccase-mediator system described 20 years ago [2], has been largely used to delignify, and bleach, different types of pulps [3, 7, 12, 13, 28]. This fact offers the possibility for deinking secondary fibers rich in lignin, such as fibers based on mechanical pulps [1]. With the removal of lignin, the bonds between the fiber and ink particles became loose, facilitating ink detachment. Moreover, successful transformation of recalcitrant dyes by the laccase-mediator system has been recently described [8, 9], which has supposed a new way for secondary fibers deinking by direct decolorization of the inks.

In the present study, two different strategies for enzymatic deinking of secondary fibers were evaluated: one using cellulases/hemicellulases for removing inks in an indirect way by peeling-off fibers, and other using the laccase-mediator system for removing inks in an indirect way by the removal of surface lignin or in a direct way by decolorizing the inks. For this purpose, different raw materials (secondary fibers from newspapers and magazines) were used. Brightness, residual ink concentration, and strength properties of the handsheets formed from the resulting deinked pulps were tested.

Materials and methods

Recovered paper

Secondary fibers from newspapers and magazines, procured locally, were used. Prior to the treatments, the dried

raw materials were shredded and maintained in distilled water for 24 h. In addition, secondary fibers from printed cardboard (corrugated containers) were also used to evaluate the laccase-mediator system. The lignin content, referred to as acid-insoluble lignin, was determined by the Klason 72% sulfuric acid digestion procedure.

Enzymes and mediators

Carbohydrate hydrolases used in this work, Viscozyme Wheat (from *Aspergillus oryzae* and designated as EV) and Ultraflo L (from *Humicola insolens* and designated as EU), were obtained from Novozymes. Their activities involved in cellulose hydrolysis (exoglucanase, EC.3.2.1.91; endoglucanase, EC.3.2.1.4; and β -glucosidase, EC.3.2.1.21) were measured on: Avicel (Merck) for total cellulose activity (exoglucanase); and the specific substrates carboxymethyl cellulose (Serva) and *p*-nitrophenyl glucoside (Sigma) for endoglucanase and β -glucosidase activities, respectively [34]. Their activities involved in hemicellulose hydrolysis (endoxylanase, EC. 3.2.1.8; and β -xylosidase, EC. 3.2.1.37) were measured on birch xylan (Sigma) and *p*-nitrophenyl xyloside (Sigma) for endoxylanase and β -xylosidase activities, respectively [34]. Their activities involved in starch hydrolysis (α -amylase, EC. 3.2.1.1; and glucoamylase, EC.3.2.1.3) were studied on soluble starch (Calbiochem) and *p*-nitrophenyl glucoside (Sigma) for α -amylase and glucoamylase activities, respectively [35]. The endoglucanase, exoglucanase, endoxylanase, and α -amylase activities, determined in 50 mM sodium acetate buffer (pH 5) at 50°C, were followed by the release of reducing sugars estimated as glucose or xylose at 540 nm [23]. The β -glucosidase, β -xylosidase, and glucoamylase activities, determined in 50 mM sodium acetate buffer (pH 5) at 50°C, were followed by the release of *p*-nitrophenol (ϵ_{412} 15 200 M⁻¹ cm⁻¹). Their optimum pH was investigated on the different substrates in 100 mM citrate-phosphate-borate buffer (pH range from 3–8) at 24°C, determining the activities as described above.

A Novozymes commercial laccase NS51002 (from *Trametes villosa*) was used. Laccase activity was determined by measuring the oxidation of 5 mM 2,2'-azino-bis(3-ethylbenzothiazoline-6-sulphonic acid) (ABTS) buffered with 100 mM sodium acetate (pH 5) at 24°C. Formation of the ABTS cation radical was monitored (ϵ_{436} 29,300 M⁻¹ cm⁻¹).

Proteins were determined according to the Bradford method [4], using bovine albumin as standard and Bio-Rad kit assay.

One unit of enzyme activity was defined as the amount of enzyme that transforms 1 μ mol of substrate per minute. All spectrophotometric measurements were carried out on a Shimadzu UV-vis 160.

The compounds used as redox mediators, 1-hydroxybenzotriazole (HBT), violuric acid (VIO), sinapic acid (SIN), ferulic acid (FER), and *p*-coumaric acid (PCO) were purchased from Sigma.

Deinking pulp sequences

A standard (industrial type) deinking sequence P–D–B (Fig. 1) was performed in laboratory scale including: (1) pulping stage (P), carried out in a lab disintegrator ENJO-D-33.73/D at 3% consistency, room temperature and 3,000 rev/min, according to the ISO standard 5263-1:2004; (2) alkaline deinking stage (D) using 1.5% NaOH, 3% Na₂Si₂O₃ and 0.06% of fatty acid soap for 60 min at 60°C and 5% consistency; and (3) alkaline peroxide bleaching stage (B) using 3% H₂O₂ and 1.5% NaOH for 120 min at 90°C and 5% consistency (above percentages referred to dry weight pulp). To facilitate the separation of ink particles detached from the fibers (fiber/ink separation), the pulp samples were exhaustively washed with distilled water through a 200-mesh wire.

Enzymatic treatments were assayed at the standard deinking sequence by: (1) incorporating a cellulase/hemicellulase stage (C), using EV or EU enzymes (sequence P–C–D–B); (2) incorporating a laccase-mediator (L) stage (sequence P–L–D–B); and (3) incorporating a cellulase/hemicellulase stage, using EV or EU, followed by a laccase-HBT stage (sequence P–C–L–D–B) (Fig. 1).

Both EV and EU treatments were carried out in duplicate with 10 g (dry weight) of pulp at 3% consistency in 50 mM sodium tartrate buffer (pH 4) or sodium citrate

buffer (pH 7), respectively. Two enzymatic dosages, 10 or 30 U/g dry weight pulp, were tested. The treatments were carried out in flasks, at 160 rev/min and 50°C, for 1 h. Laccase-mediator treatments were carried out in duplicate with 10 g (dry weight) of pulp at 3% consistency in 50 mM sodium tartrate buffer (pH 4), using 20 U/g dry weight pulp of laccase and 0.5% (w/w) (referred to dry weight pulp) of different mediators. Tween 80 (0.05% w/v) was added as surfactant. The treatments were carried out in flask under O₂ atmosphere (continuous bubbling) at 160 rev/min and 50°C, for 5 h. In all cases, pulps were also treated under identical conditions without enzymes or mediators.

Optical and mechanical property measurements of the handsheets

Three handsheets per tested sequence with a grammage of 60 g/m² were prepared using a Rapid-Kothen sheet former according to ISO 5269/2. The handsheets were characterized measuring the tensile index by an extensometer according to ISO 1924, and the tear index by Elmendorf equipment according to ISO 6383 and ISO 1974.

Brightness (% ISO) and residual ink concentration (ppm) of the handsheets were measured by a Datacolor Elrepho 2000 spectrophotometer. The ink removal index was calculated using the following equation:

$$\text{Ink removal index (\%)} = \frac{(C_{\text{controlpulp}} - C_{\text{enzymesdeinkedpulp}})}{C_{\text{controlpulp}}} \times 100$$

where *C* is the residual ink concentration.

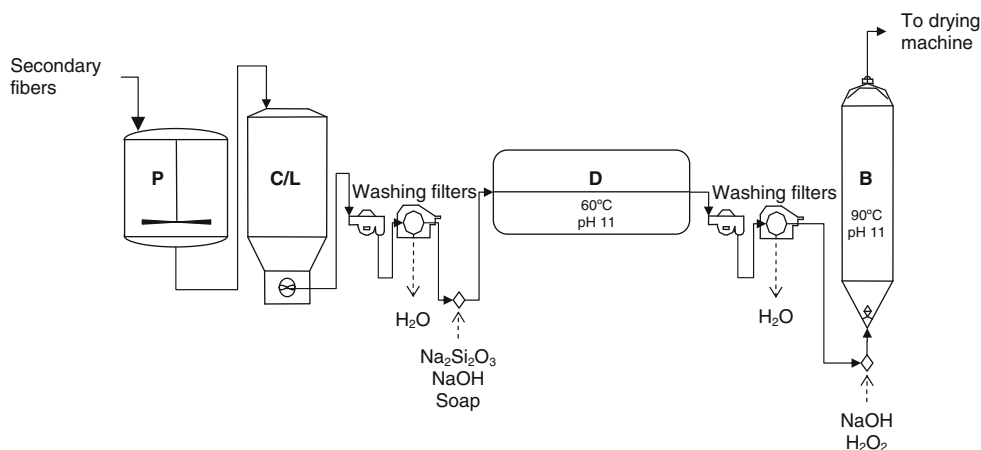


Fig. 1 Scheme of a standard deinking sequence including: (1) pulping stage (P), (2) alkaline deinking stage (D), and (3) alkaline peroxide bleaching stage (B). Enzymatic treatments were assayed in laboratory scale using this standard sequence by: (a) incorporating a cellulase/hemicellulase (C) stage (sequence P–C–D–B), (b) incorporating a laccase-mediator (L) stage (sequence P–L–D–B), and

(c) incorporating a cellulase/hemicellulase stage followed by the laccase-mediator (C–L) stage (sequence P–C–L–D–B). In order to facilitate the removal of ink particles detached from secondary fibers (fiber/ink separation), the pulp samples were exhaustively washed with distilled water through a 200-mesh filter

Results and discussion

Deinking using cellulases/hemicellulases

Optical properties of the handsheets

Figure 2 shows the changes of brightness and residual ink concentration in deinked pulps from newspaper and magazine fibers after a cellulase/hemicellulase-containing deinking sequence (P–C–D–B), using EV or EU enzymes, and their corresponding control sequences. In general, control deinked pulp from newspaper fibers showed optical properties slightly better than those of deinked pulp from magazine fibers (Fig. 2); obtaining brightness values higher and residual ink concentrations lower. Moreover, control deinking sequence at pH 7 (optimum pH for endoglucanase and endoxylanase activities determined in EU preparation) resulted in slightly higher brightness (1.5–2% ISO brightness higher) and lower residual ink concentration (130–150 units residual ink concentration lower) than obtained when the control deinking sequence was carried out at pH 4 (optimum pH for endoglucanase and endoxylanase activities determined in EV preparation). Conventional deinking process employs sodium hydroxide in combination with a range of other chemicals [29]. High pH values favor fibers swelling, increasing their flexibility, and consequently facilitating the detachment of the adhered ink

[33]. Furthermore, it may also act directly on the printed ink film and weaken its structure, leading to fragmentation [29]. For these reasons, the slight alkaline pH could explain the better optical properties for control deinked pulps obtained at pH 7.

Using 10 U/g dry weight pulp of both carbohydrate hydrolases the brightness of deinked pulp from newspaper fibers increased 3–4 units, reaching 56% ISO and 59% ISO brightness with EV and EU, respectively (Fig. 2). Moreover, EU was 20% more efficient than EV in the ink removal, i.e., ink detachment (Fig. 3). By contrast, an increment of 2.5 units was obtained when magazine fibers were used, reaching 53% ISO and 55% ISO brightness with EV and EU, respectively (Fig. 2). In this case, EV was 9% more efficient than EU in the ink removal (Fig. 3). As mentioned above, the enzymatic deinking using cellulases/hemicellulases has been successfully demonstrated [10, 14, 17, 18, 20, 24, 25, 32, 36]. Among the different carbohydrate hydrolase activities, endoglucanase and/or endoxylanase activities seems to play an important role in the deinking efficiency, although it is difficult to know the contribution of each one to the deinking process. Some authors support the idea that the main contribution is given by endoglucanases [10, 32], which attack the less-ordered cellulose between, and on the surface of, the fibrils, leading to fiber wall swelling and loosening of short fibers, and consequently dislodging the inks. Other authors consider

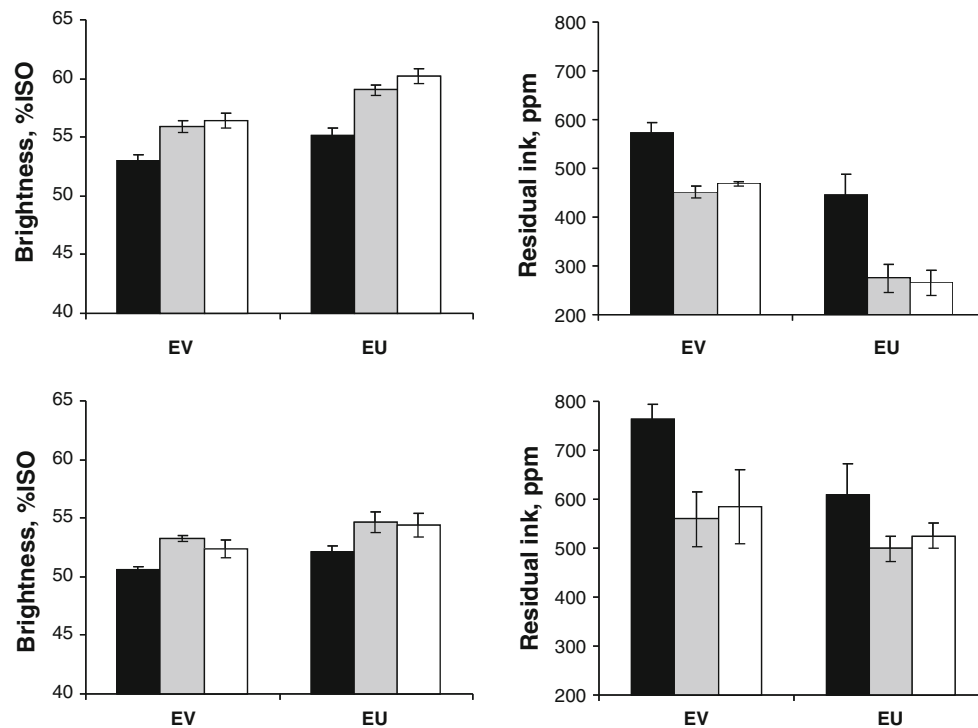


Fig. 2 ISO brightness (*left*) and residual ink concentration (*right*) of deinked pulps from newspaper (*top*) and magazine (*bottom*) fibers after a cellulase/hemicellulase-containing deinking sequence

(P–C–D–B). Enzyme dosages: 0 (*black bars*), 10 (*gray bars*), and 30 U/g (*white bars*) dry weight pulp. Mean values and 95% confidence limits are shown

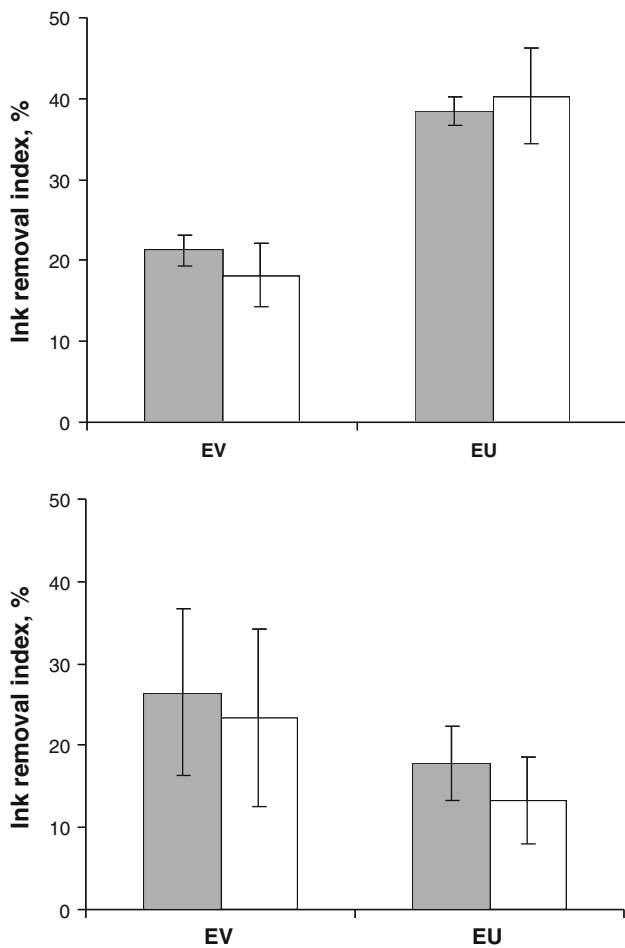


Fig. 3 Ink removal indices of deinked pulps from newspaper (*top*) and magazine (*bottom*) fibers after a cellulase/hemicellulase-containing deinking sequence (P–C–D–B). Enzyme dosages: 10 (gray bars), and 30 U/g (white bars) dry weight pulp

that endoxylanases provide the main activity [24], promoting ink detachment due to hemicellulose hydrolysis on the fibers surface. In any case, the combined action of the two activities has shown better deinking efficiencies [10, 18]. In this sense, EV (containing 17 U/mg endoglucanase activity estimated from glucose release from carboxymethyl cellulose and 65 U/mg endoxylanase activity estimated from xylose release from birch xylan, see Table 1) and EU (containing 23 U/mg endoglucanase activity estimated from glucose release from carboxymethyl cellulose and 61 U/mg endoxylanase activity estimated from xylose release from birch xylan, Table 1) showed mainly both endoglucanase and endoxylanase activities, explaining their effectiveness deinking secondary fibers from newspapers and magazines. In addition, EV also showed a slight glucoamylase activity (1 mU/mg), which could explain its better efficiency in the ink removal of magazine fibers (with a hypothetical higher starch amount than newspaper fibers). Increment of dosage from 10 to 30 U/g dry weight

Table 1 Summary of different enzymatic activities detected in both EV and EU preparations

Type of enzyme activity	EV		EU	
	U/ml	U/mg	U/ml	U/mg
Cellulase				
Exoglucanase	135	4	90	13
Endoglucanase	520	17	160	23
β -Glucosidase	5,500 ^a	177 ^b	7,630 ^a	1,090 ^b
Hemicellulase				
Endoxylanase	2,000	65	430	60
β -Xylosidase	21,000 ^a	680 ^b	2,630 ^a	380 ^b
Amylase				
α -Amylase	nd	nd	nd	nd
Glucoamylase	25 ^a	1 ^b	nd	nd

nd not detected

^a Activity expressed as mU/ml

^b Activity expressed as mU/mg; protein concentration (mg/ml) according to the Bradford method: 31 and 7 mg/ml for EV and EU preparations, respectively

pulp of both enzymes did not enhance significantly the optical properties (Figs. 2, 3).

Mechanical properties of the handsheets

Table 2 shows the mechanical properties (tensile and tear indexes) of the handsheets from deinked pulps from newspaper and magazine fibers, after a cellulase/hemicellulase-containing deinking sequence (P–C–D–B), using EV or EU, and their corresponding control sequences. The integration of both enzymes resulted in strength properties practically unaltered, being even slightly improved, especially using 10 U/g dry weight pulp of EV on newspaper, or scarcely worsened using EU. In contrast to use of multicomponent carbohydrate hydrolases, which often have a detrimental effect on paper properties [30], several studies sustain the idea that the use of monocomponent enzymes, endoglucanases and/or endoxylanases, maintains or even enhances the strength properties [10, 20, 32]. Our results support this assumption. The losing of small fibrils from the surface fibers by the action of monocomponent carbohydrate hydrolases employed improves the interfibrillar bonding and consequently enhances the strength properties [32].

Deinking using the laccase-mediator system

Optical properties of the handsheets

Figure 4 shows the changes of brightness and residual ink concentration in deinked pulps from newspaper and

Table 2 Mechanical properties of the handsheets from deinked pulps from newspaper and magazine fibers after a cellulase/hemicellulase-containing deinking sequence (P–C–D–B) with two different enzyme

	Newspaper						Magazine					
	EV			EU			EV			EU		
	C ^a	10	30	C ^a	10	30	C ^a	10	30	C ^a	10	30
Tensile index (Nm/g)	20.1	26.8	21.8	25.5	23.8	23.2	27.8	28.2	30.3	29.8	29.5	28.6
Tear index (mNm ² /g)	2.35	2.35	2.35	2.15	2.35	2.15	2.75	3.10	3.10	2.60	2.35	2.35

^a Secondary fibers treated under the same enzymatic conditions (1 h, 50°C at pH 4 for EV or pH 7 for EU) but without enzymes

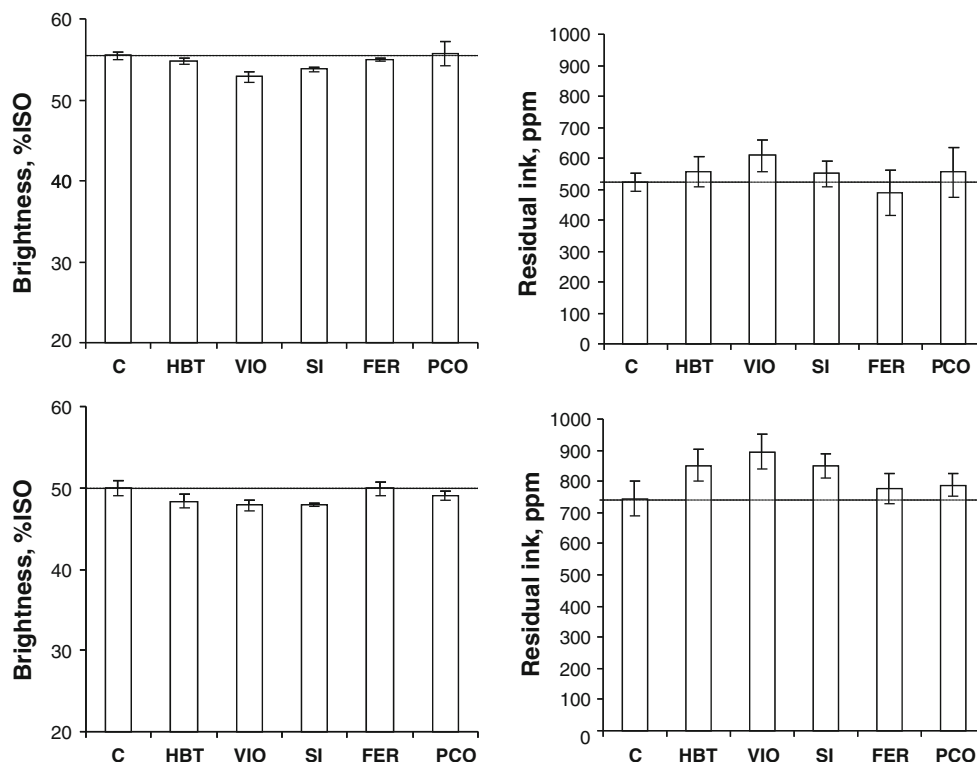


Fig. 4 ISO brightness (*left*) and residual ink concentration (*right*) of deinked pulps from newspaper (*top*) and magazine (*bottom*) fibers after a laccase-mediator-containing deinking sequence (P–L–D–B) using 0.5% (referred to pulp dry weight) HBT (1-hydroxybenzotriazole), VIO

(violuric acid), SI (sinapic acid), FER (ferulic acid) and PCO (*p*-coumaric acid). C (control pulp) treated under identical conditions but without enzyme and mediators. Mean values and 95% confidence limits are shown

magazine fibers after a laccase-mediator-containing deinking sequence (P–L–D–B), and the corresponding control deinking sequence. In spite of their high lignin contents (around 12% of acid-insoluble lignin), the laccase-mediator system was ineffective in deinking both secondary fibers. Compared to carbohydrate hydrolases, no significant differences were found when the laccase-mediator system, using 0.5% w/w of different synthetic (HBT and VIO) and natural (SIN, FER and PCO) mediators, was integrated in the deinking sequence. In fact, deinked pulps with slightly lower brightness and different color tones were obtained depending of the mediator used. No improvement of the deinked pulp properties was observed when mediator

concentrations were increased (1.5 and 3% w/w) (data not shown). These results disagree with those reported recently [15–17, 21, 26, 35] describing the capacity of laccases and laccase-mediator systems (using different synthetic mediators) for the deinking of secondary fibers. Moreover, some of these studies have also displayed the enzymatic synergistic deinking combining cellulases or hemicellulases with the laccase-mediator system [15, 26]. In this sense, enzymatic deinking sequences containing a cellulase/hemicellulase stage, EV or EU, followed by laccase-HBT stage (P–C–L–D–B) were tested on both newspaper and magazine fibers. No synergistic effect was observed between EV/EU and laccase-HBT system (Table 3). Even the

Table 3 Optical properties of the handsheets from deinked pulps from newspaper and magazine fibers after a cellulase/hemicellulase followed by a laccase-mediator-containing deinking sequence (P–C–L–D–B) compared to cellulase/hemicellulase-containing (P–C–D–B) and laccase-mediator-containing (P–L–D–B) deinking sequences

	Newspaper		Magazine	
	Brightness (% ISO)	Residual ink (ppm)	Brightness (% ISO)	Residual ink (ppm)
Control ^a , *	53 ± 0.02	545 ± 53.5	51 ± 0.2	665 ± 13
P–C–D–B ^a	55.8 ± 0.03	445 ± 9.5	53.5 ± 0.4	480 ± 16
P–L–D–B	52.6 ± 0.25	570 ± 5.5	50.3 ± 0.8	680 ± 16
P–C–L–D–B ^a	51.4 ± 0.05	600 ± 53.5	49.7 ± 0.6	680 ± 52
Control ^b , *	54.5 ± 0.20	470 ± 12.5	52.1 ± 0.4	615 ± 40
P–C–D–B ^b	58.3 ± 0.35	340 ± 35	55 ± 0.5	470 ± 19
P–L–D–B	52.8 ± 0.40	560 ± 15	51.5 ± 0.9	620 ± 26
P–C–L–D–B ^b	52.3 ± 0.30	575 ± 28	51 ± 0.45	640 ± 31

P pulping stage, *D* alkaline deinking stage, *B* alkaline bleaching stage, *C* cellulase/hemicellulase stage using 10 U/g dry weigh pulp of ^a EV or ^b EU; *L* laccase-mediator stage using 0.5% of 1-hydroxybenzotriazole (HBT) as mediator.* Secondary fibers treated under the same enzymatic conditions (1 h, 50°C at pH 4 for EV or pH 7 for EU, and 5 h, 50°C at pH 4 for laccase-HBT) without enzymes and mediator

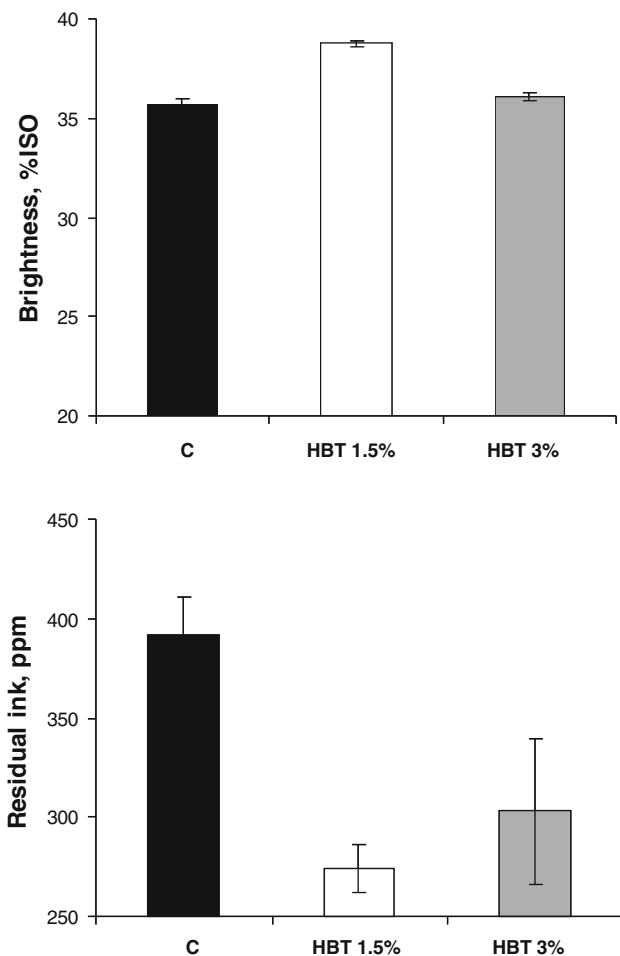


Fig. 5 ISO brightness (*top*) and residual ink concentration (*bottom*) of deinked pulps from printed cardboard after a laccase-mediator-containing deinking sequence (P–L–D–B) using 1.5 and 3% (referred to pulp dry weight) HBT (1-hydroxybenzotriazole). C (control pulp) treated under identical conditions but without enzyme and mediator. Mean values and 95% confidence limits are shown

enhanced optical properties attained after the cellulase/hemicellulase-containing deinking sequences (P–C–D–B) were negatively affected when the laccase-HBT system was integrated after the cellulase/hemicellulase stage (P–C–L–D–B), as shown in Table 3.

When a secondary fiber with higher lignin content (21% of acid-insoluble lignin), such as printed cardboard, was assayed in a deinking P–L–D–B sequence, using HBT as mediator, the optical properties were enhanced (Fig. 5). Using 1.5% w/w of mediator the brightness of deinked pulp increased 3 units, reaching 39% ISO brightness, and the ink residual concentration was reduced 200 units. In contrast to newspaper and magazine fibers, in printed cardboard fibers, these results could be explained by delignification phenomenon. With the removal of surface lignin from printed cardboard by the laccase-mediator system, the bindings between fiber and ink particles attached of the fiber became loose, facilitating ink detachment [1]. No improvement of the optical properties was observed when HBT concentration was increased to 3% w/w.

Further work is necessary to proceed towards the applicability of the laccase-mediator system for fiber deinking. In addition to the secondary fiber types and mediators used, other parameters could have importance in the treatment, such as the nature of different inks, hardly degradable, employed in the printing of these fiber types.

Mechanical properties of the handsheets

Table 4 shows the mechanical properties (tensile and tear indexes) of the handsheets from deinked pulps from newspaper and magazine fibers after a laccase-mediator-containing deinking sequence (P–L–D–B), and the

Table 4 Mechanical properties of the handsheets from deinked pulps from newspaper and magazine fibers and printed cardboard after a laccase-mediator containing deinking sequence (P–L–D–B)

	Newspaper						Magazine						Printed cardboard	
	C ^a	HBT	VIO	SI	FER	PCO	C ^a	HBT	VIO	SI	FER	PCO	C ^a	HBT
Tensile index (Nm/g)	24.7	25.6	31.6	35	32.2	36.2	22.1	21.5	19.9	17.4	14.5	13.3	28.6	32.5
Tear index (mNm ² /g)	2.55	2.35	3.15	3.00	3.00	3.55	2.35	2.35	2.10	1.70	1.15	1.75	3.15	3.25

^a Secondary fibers treated under the same enzymatic conditions (5 h, 50°C at pH 4) without laccase and mediators; *HBT* 1-hydroxybenzotriazole, *VIO* violuric acid, *SI* sinapic acid; *FER* ferulic acid, and *PCO* *p*-coumaric acid

corresponding control deinking sequence. The effect of the laccase-mediator system on these properties differed depending of the secondary fiber type and mediator used. The laccase-HBT system did not affect substantially the strength properties of the resulting deinked pulps from both newspaper and magazine fibers. However, contradictory results were observed with the other mediators used. On the one hand, significant increments of tensile and tear indexes for deinked pulps of newspaper fibers; on the other hand, important drops for deinked pulps of magazine fibers. Few studies have reported the effect of the laccase-mediator system on physico-mechanical properties of fibers with scarce residual lignin content. Mohandass et al. [21] described an improvement of tensile index, with a little increment of tear index, in recycled blue office paper after laccase-TEMPO treatment. In the same way, Cadena et al. [5] reported increments of both indexes in ECF (elementally chlorine-free) and TCF (totally chlorine-free) bleached *Eucalyptus globulus* pulps after laccase-HBT treatment. These positive effects have been ascribed to alterations in electrokinetic properties. Changes on pulp surface charge due to a reduction of the content in ionizable groups (carboxylic and hexenuronic acids) by the laccase-mediator system improve the physico-mechanical properties by increasing the number of bonds between fibrils with both reduced ionic charge and repulsive forces. This assumption could be accepted to explain the beneficial effects observed for the strength properties of newspaper fibers after the laccase-mediator system in the presence of violuric, sinapic, ferulic and *p*-coumaric acids. However, other reasons should be explored to explain the negative effects observed in magazine fibers.

Printed cardboard treated with laccase-HBT resulted in deinked pulps with tensile index increased up to 4% and tear index slightly enhanced (Table 4). Similar results have often been described on unbleached chemical pulps with high lignin content [7, 19, 27]. They suggested that both the releasing lignin and chemically modified lignin, i.e., more hydrophilic, by the laccase-HBT system might lead to an increase in the formation of interfibrillar bonds and consequently an improvement of strength properties.

Conclusions

According to this study, the effectiveness of enzymatic deinking depends to a large extent on both the different enzymatic activities selected and the secondary fiber types employed. In this sense, a great variability in the results of properties tested, i.e., brightness, residual ink concentration, and strength properties, was obtained after evaluating two enzymatic deinking strategies on different types of secondary fibers. Carbohydrate hydrolases, mainly containing endoglucanase and endoxylanase activities, enhanced the optical properties of resulting deinked pulps from both newspaper and magazine secondary fibers, maintaining or slightly improving the strength properties. By contrast, the laccase-mediator system was ineffective deinking both secondary fibers, resulting in deinked pulps with worse brightness and residual ink concentration values. In addition, both significant increments and drops of physico-mechanical properties were attained in function of fibers types and mediators used. Pulp deinking by the laccase-mediator system was displayed when secondary fibers with higher lignin content, i.e., printed cardboard, were used, obtaining both enhanced optical and strength properties. Nevertheless, in addition to the different enzymatic activities selected and secondary fiber types used, other factors such as printing methods, ink types, and fiber/ink separation process should be taken into account in order to proceed towards the applicability of enzymatic deinking processes.

Acknowledgments This work was supported by the PROLIPAPEL projects S-0505/AMB0100 and S-2009AMB-1480 of the Community of Madrid. Novozymes (Denmark) is acknowledged for supplying enzymes. Holmen Paper (Spain) is acknowledged for optical and mechanical properties tests.

References

1. Bajpai P, Bajpai PK (1998) Deinking with enzymes: a review. *Tappi J* 81:111–117
2. Bourbonnais R, Paice MG (1990) Oxidation of non-phenolic substrates: an expended role for laccase in lignin biodegradation. *FEBS Lett* 267:99–102

3. Bourbonnais R, Paice MG (1996) Enzymatic delignification of kraft pulp using laccase and a mediator. *Tappi J* 79:199–204
4. Bradford MM (1976) A rapid and sensitive method for the quantitation of microgram quantities of proteins utilizing the principle of protein-dye binding. *Anal Biochem* 72:248–254
5. Cadena EM, Vidal T, Torres AL (2010) Can the laccase mediator system affect the chemical and refining properties of the eucalyptus pulp? *Bioresour Technol* 101:8199–8204
6. Call HP, Strittmatter G (1992) Application of ligninolytic enzymes in the paper and pulp industry—recent results. *Papier* 46:32–37
7. Camarero S, García O, Vidal T, Colom J, del Río JC, Gutiérrez A et al (2004a) Efficient bleaching of non-wood high paper pulp using laccase-mediator system. *Enzyme Microb Technol* 35:113–120
8. Camarero S, Ibarra D, Martínez MJ, Martínez AT (2004b) Lignin-derived compounds as efficient laccase mediators for decolorization of different types of recalcitrant dyes. *Appl Environ Microbiol* 71:1775–1784
9. Claus H, Farber G, König H (2002) Redox-mediated decolorization of synthetic dyes by fungal laccases. *Appl Microbiol Biotechnol* 59:672–678
10. Gübitz GM, Mansfield SD, Böhm D, Sessler JN (1998) Effect of endoglucanases and hemicellulases in magnetic and flotation deinking of xerographic and laser-printed papers. *J Biotechnol* 65:209–215
11. Heise OU, Unwin JP, Klungness JH, Fineran WG, Sykes M, Abubark S (1996) Industrial scale up of enzyme-enhanced deinking of non-impact printed toner. *Tappi J* 79:207–212
12. Herpoël I, Jeller H, Fang G, Petit-Conil M, Bourbonnais R, Rober JL et al (2002) Efficient enzymatic delignification of wheat straw pulp by a sequential xylanase-laccase mediator treatment. *J Pulp Paper Sci* 28:67–71
13. Ibarra D, Romero J, Martínez MJ, Martínez AT, Camarero S (2006) Exploring the enzymatic parameters for optimal delignification of eucalypt pulp by laccase-mediator. *Enzyme Microb Technol* 39:1319–1327
14. Jeffries TW, Klungness JH, Sykes MS, Rutledge CK (1994) Comparison of enzyme enhanced with conventional deinking of xerographic and laser printed paper. *Tappi J* 77:173–179
15. Kapoor M, Kapoor RK, Kuhad RC (2007) Differential and synergistic effects of xylanase and laccase mediator system (LMS) in bleaching soda and waste pulps. *J Microbiol* 103:305–317
16. Knutson K, Ragauskas A (2004) Laccase-mediator biobleaching applied to a direct yellow dyed paper. *Biotechnol Prog* 6:1893–1896
17. Kuhad RC, Mehta G, Gupta R, Sharma KK (2010) Fed batch enzymatic saccharification of newspaper cellulose improves the sugar content in the hydrolysates and eventually the ethanol fermentation by *Saccharomyces cerevisiae*. *Biomass Bioenerg* 34:1189–1194
18. Lee CK, Darah I, Ibrahim CO (2007) Enzymatic deinking of laser printed office waste papers: some governing parameters on deinking efficiency. *Bioresour Technol* 98:1684–1689
19. Lund M, Felby CF (2001) Wet strength improvement of unbleached kraft pulp through laccase catalyzed oxidation. *Enzyme Microb Technol* 28:760–765
20. Marques S, Pala H, Alves L, Amaral-Collaco MT, Gama FM, Gírio FM (2003) Characterisation and application of glycanases secreted by *Aspergillus terreus* CCM1 498 and *Trichoderma viride* CCM1 84 for enzymatic deinking of mixed office wastepaper. *J Biotechnol* 100:209–219
21. Mohandass C, Knutson K, Ragauskas A (2008) Laccase-treatment of recycled blue dyed paper: physical properties and fiber charge. *J Ind Microbiol Biotechnol* 35:1103–1108
22. Morkbak AL, Degn P, Zimmermann W (1999) Deinking of soybean oil based ink-printed paper with lipases and a neutral surfactant. *J Biotechnol* 67:229–236
23. Nelson N (1944) A photometric adaptation of the Somogyi method for the determination of glucose. *J Biol Chem* 152:375–380
24. Pala H, Mota M, Gama FM (2004) Enzymatic versus chemical deinking of non-impact ink printed paper. *J Biotechnol* 108:79–89
25. Pelach MA, Pastor FJ, Puig J, Vilaseca F, Mutje P (2003) Enzymatic deinking of old newspaper with cellulase. *Proc Biochem* 38:1063–1067
26. Qinghua X, Yingjuan F, Yang G, Menghua Q (2009) Performance and efficiency of old newspaper deinking by combining cellulase/hemicellulase with laccase-violuric acid system. *Waste Manag* 29:1486–1490
27. Saparrat MCN, Mocchiutti P, Liggieri CS, Aulicino MB, Caffini NO, Balatti PA, Martínez MJ (2008) Ligninolytic enzyme ability and potential biotechnology applications of the white-rot fungus *Grammothele subargentea* LPSC no. 436 strain. *Process Biochem* 43:368–375
28. Sealey J, Ragauskas AJ, Elder TJ (1999) Investigations into laccase-mediator delignification of kraft pulps. *Holzforschung* 53:498–502
29. Shrinath A, Szewczak JT, Bowen IJ (1991) A review of ink-removal techniques in current deinking technology. *Tappi J* 74:85–93
30. Suurnakki A, Tenkanen M, Siika-Aho M, Niku-Paavola ML, Viikari L, Buchert J (2000) *Trichoderma reesei* cellulases and their core domains in the hydrolysis and modification of chemical pulp. *Cellulose* 7:189–209
31. Thomas WJ (1994) Comparison of enzyme-enhanced with conventional deinking of xerographic and laser-printed paper. *Tappi J* 77:173–179
32. Vyas S, Lachke A (2003) Biodeinking of mixed office waste paper by alkaline active cellulases from alkalotolerant *Fusarium* sp. *Enzyme Microb Technol* 2003:236–245
33. Wielen LCV, Panek JC, Pfromm PH (1999) Fracture of toner due to paper swelling. *Tappi J* 82:115–121
34. Wood TM, Bhat KM (1988) Methods for measuring cellulase activities. *Methods Enzymol* 160:87–112
35. Xu QH, Qin MH, Shi SL, Zhang AP, Xu Q (2004) Deinking of old newsprint with laccase-mediator system. *Trans China Pulp Paper* 19:48–51
36. Zhang X, Renaud S, Paice M (2008) Cellulase deinking of fresh and aged recycled newsprint/magazines (ONP/OMG). *Enzyme Microb Technol* 43:103–108
37. Zollner HK, Schroeder LR (1998) Enzymatic deinking of non-impact printed white office paper with α -amylase. *Tappi J* 81:166–170