

This article was downloaded by:

On: 24 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Macromolecular Science, Part A

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713597274>

Novel Copolymers of Methoxy Ring-Substituted Methyl 2-cyano-3-phenyl-2-propenoates

Gregory B. Kharas^a; Allison L. Crawford^a; Katherine J. Payne^a; Maria N. T. Sanidad^a; Matthew W. Sims^a; Debbie Leung^a; John Loumbardias^a; Sarah Yazdani^a; Celeste A. Diener^a; Xue Tian^a; Kenneth Watson^b

^a Chemistry Department, DePaul University, Illinois ^b Lanxess Inc., Sarnia, Ontario, Canada

To cite this Article Kharas, Gregory B. , Crawford, Allison L. , Payne, Katherine J. , Sanidad, Maria N. T. , Sims, Matthew W. , Leung, Debbie , Loumbardias, John , Yazdani, Sarah , Diener, Celeste A. , Tian, Xue and Watson, Kenneth(2005) 'Novel Copolymers of Methoxy Ring-Substituted Methyl 2-cyano-3-phenyl-2-propenoates', *Journal of Macromolecular Science, Part A*, 42: 6, 683 – 690

To link to this Article: DOI: 10.1081/MA-200058623

URL: <http://dx.doi.org/10.1081/MA-200058623>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Novel Copolymers of Methoxy Ring-Substituted Methyl 2-cyano-3-phenyl-2-propenoates

GREGORY B. KHARAS,¹ ALLISON L. CRAWFORD,¹
KATHERINE J. PAYNE,¹ MARIA N. T. SANIDAD,¹
MATTHEW W. SIMS,¹ DEBBIE LEUNG,¹
JOHN LOUMBARDIAS,¹ SARAH YAZDANI,¹ CELESTE A.
DIENER,¹ XUE TIAN,¹ AND KENNETH WATSON²

¹Chemistry Department, DePaul University, Illinois

²Lanxess Inc., Sarnia, Ontario, Canada

Electrophilic trisubstituted ethylene monomers, methoxy ring-substituted methyl 2-cyano-3-phenyl-2-propenoates, $RC_6H_3CH=C(CN)CO_2CH_3$, (where R is 2,3-(CH₃O)₂, 2,4-(CH₃O)₂, 2,5-(CH₃O)₂, 2,6-(CH₃O)₂, 3,4-(CH₃O)₂, 3,5-(CH₃O)₂, 2,4,5-(CH₃O)₃, and 2,4,6-(CH₃O)₃), were synthesized by the piperidine catalyzed Knoevenagel condensation of ring-substituted benzaldehydes and methyl cyanoacetate, and characterized by CHN elemental analysis, IR, ¹H- and ¹³C-NMR. Copolymerization of the propenoates and vinyl acetate in solution with radical initiation (AIBN) at 70°C yielded equimolar alternating copolymers. The composition of the copolymers was calculated from nitrogen analysis, and the structures were analyzed by IR, ¹H- and ¹³C-NMR, GPC, DSC, and TGA. High T_g of the copolymers in comparison with that of polyvinyl acetate indicates a substantial decrease in chain mobility of the copolymer due to the high dipolar character of the trisubstituted ethylene monomer unit. The gravimetric analysis indicated that the copolymers decompose in the 240–400°C range.

Keywords trisubstituted ethylenes, radical copolymerization, alternating copolymers, vinyl acetate copolymers

Introduction

Early studies of substituted ethylenes showed that the reactivity of the monomers in radical polymerization depends on their polarity, resonance stabilization and steric factors. Although steric difficulties preclude homopolymerization of most tri- and tetrasubstituted olefins, their copolymerization with a monosubstituted alkene makes it possible to overcome these steric problems (1). Copolymerization of trisubstituted ethylenes (TSE, $CHR^1=CR^2R^3$) having double bonds substituted with halo, cyano, and carbonyl groups and electron-rich monosubstituted ethylenes such as ST, *N*-vinylcarbazole, and vinyl acetate (2, 3) show a tendency toward the formation of alternating copolymers.

Received and Accepted 1 January 2005

Address correspondence to Gregory B. Kharas, Chemistry Department, DePaul University, IL 60614-3214. Fax: 773-325-7421; E-mail: gkharas@depaul.edu

In continuation of our studies of the monomer structure-reactivity correlation in the radical copolymerization of TSE monomers (4–6), we have prepared di and trimethoxy ring-substituted methyl 2-cyano-3-phenyl-2-propenoates, $\text{RC}_6\text{H}_3\text{CH}=\text{C}(\text{CN})\text{CO}_2\text{CH}_3$ (where R is 2,3-(CH_3O)₂, 2,4-(CH_3O)₂, 2,5-(CH_3O)₂, 2,6-(CH_3O)₂, 3,4-(CH_3O)₂, 3,5-(CH_3O)₂, 2,4,5-(CH_3O)₃, and 2,4,6-(CH_3O)₃), and explore the feasibility of their copolymerization with vinyl acetate.

Experimental

General Procedures

Infrared spectra of the TSE monomers (NaCl plates) and polymers (KBr pellets) were determined with a Nicolet Avatar 360 FT-IR spectrometer. The melting points of the monomers, the glass transition temperatures (T_g), and thermal stability of the copolymers were measured by using a TA Instruments model DSC 2010 and TGA 2090. The molecular weight of polymers was determined relative to polystyrene standards in CHCl_3 solutions with sample concentrations 0.8% (wt/vol) by gel permeation chromatography using an Alltech 526 HPLC pump at an elution rate of 1.0 mL/min through Styragel HR 0.5, 1, 3, and 4 columns (Waters) at 25°C, a Model 410 refractive index and Viscotek T50A differential viscometer detectors. ^1H and ^{13}C NMR spectra of 2–4% CDCl_3 solutions of monomers and polymers were obtained on a Bruker DRX-500 spectrometer operating at 500.13 MHz for ^1H and 125.76 MHz for ^{13}C . Chemical shifts are reported referenced to TMS as 0 ppm. Proton spectra utilized 64 K data points with a sweep width of 31.4 kHz, a pulse delay of 10 s and 5000 scans accumulated. Elemental analyses were performed by Quantitative Technologies Inc. (New Jersey).

Synthesis of Monomers

2,3-Dimethoxy, 2,4-dimethoxy, 2,5-dimethoxy, 2,6-dimethoxy, 3,4-dimethoxy, 3,5-dimethoxybenzaldehydes, 2,4,5-trimethoxy, and 2,4,6-trimethoxybenzaldehydes, methyl cyanoacetate, DMF, and piperidine supplied from Aldrich Chemical Co., were used for monomer synthesis as received. The preparation procedure was essentially the same for all of the TSE monomers. In a typical synthesis, equimolar amounts of methyl cyanoacetate and an appropriate ring-substituted benzaldehyde were mixed with a small amount of DMF in an Erlenmeyer flask. A few drops of piperidine were added with stirring. The crystalline product of the reaction was isolated by filtration and purified by recrystallization from 2-propanol.

Methyl 2-cyano-3-(2,3-dimethoxyphenyl)-2-propenoate

Yield: 94%; mp 130°C; ^1H NMR δ 8.7 (s, 1H, $\text{CH}=\text{C}$), 7.9, 7.2, 7.1, 6.9 (m, 3H, phenyl), 3.94, 3.92 (s, 6H, phenyl- OCH_3), 3.89 (s, 3H, OCH_3); ^{13}C NMR δ 163 ($\text{C}=\text{O}$), 153 ($\text{HC}=\text{C}$), 149, 125, 124, 120, 117 (phenyl), 115 (CN), 103 ($\text{C}=\text{C}$), 62, 56 (phenyl- OCH_3), 53 (OCH_3); IR (NaCl): 2977 (m, C–H), 2219 (m, CN), 1729 (s, $\text{C}=\text{O}$), 1590 ($\text{C}=\text{C}$), 1228 (s, C–O– CH_3), 785 (s, C–H out of plane). Anal. Calcd. for $\text{C}_{13}\text{H}_{13}\text{NO}_4$: C, 63.15; H, 5.30; N, 5.66; Found: C, 62.85; H, 5.27; N, 5.60.

Methyl 2-cyano-3-(2,4-dimethoxyphenyl)-2-propenoate

Yield: 68%; mp 156°C; $^1\text{H-NMR}$ δ 8.7 (s, 1H, CH=), 7.1, 6.6, 6.5, 6.4 (m, 3H, phenyl), 3.94, 3.92 (s, 6H, phenyl-OCH₃), 3.88 (s, 3H, OCH₃); $^{13}\text{C-NMR}$ δ 166 (C=O), 153 (HC=), 150, 130, 126, 120, 97 (phenyl), 114 (CN), 106 (C=), 62, 56 (phenyl-OCH₃), 53 (OCH₃); IR (NaCl): 3060 (m, C-H), 2215 (m, CN), 1719(s, C=O), 1608 (C=C), 1268 (s, C-O-CH₃), 782 (s, C-H out of plane). Anal. Calcd. for C₁₃H₁₃NO₄: C, 63.15; H, 5.30; N, 5.66; Found: C, 63.12; H, 5.17; N, 5.55.

Methyl 2-cyano-3-(2,5-dimethoxyphenyl)-2-propenoate

Yield: 88%; mp 132°C; $^1\text{H-NMR}$ δ 8.7 (s, 1H, CH=), 7.9, 7.1, 6.9 (m, 3H, phenyl), 3.93, 3.86 (s, 6H, phenyl-OCH₃), 3.82 (s, 3H, OCH₃); $^{13}\text{C-NMR}$ δ 163 (C=O), 154 (HC=), 149, 122, 120, 112 (phenyl), 116 (CN), 101 (C=), 56, 55 (phenyl-OCH₃), 53 (OCH₃); IR (NaCl): 2956 (m, C-H), 2223 (m, CN), 1716(s, C=O), 1612 (C=C), 1233 (s, C-O-CH₃), 762 (s, C-H out of plane). Anal. Calcd. for C₁₃H₁₃NO₄: C, 63.15; H, 5.30; N, 5.66; Found: C, 63.03; H, 5.07; N, 5.53.

Methyl 2-cyano-3-(2,6-dimethoxyphenyl)-2-propenoate

Yield: 59%; mp 106°C; $^1\text{H-NMR}$ δ 8.6 (s, 1H, CH=), 7.2, 7.0 (m, 3H, phenyl), 3.81 (s, 6H, phenyl-OCH₃), 3.77 (s, 3H, OCH₃); $^{13}\text{C-NMR}$ δ 161 (C=O), 154 (HC=), 148, 120, 119, 113 (phenyl), 116 (CN), 102 (C=), 56 (phenyl-OCH₃), 52 (OCH₃); IR (NaCl): 2952 (m, C-H), 2224 (m, CN), 1726(s, C=O), 1600 (C=C), 1266 (s, C-O-CH₃), 764 (s, C-H out of plane). Anal. Calcd. for C₁₃H₁₃NO₄: C, 63.15; H, 5.30; N, 5.66; Found: C, 63.16; H, 5.17; N, 5.58.

Methyl 2-cyano-3-(3,4-dimethoxyphenyl)-2-propenoate

Yield: 56%; mp 126°C; $^1\text{H-NMR}$ δ 8.1 (s, 1H, CH=), 7.8, 7.5, 6.9 (m, 3H, phenyl), 3.97, 3.94 (s, 6H, phenyl-OCH₃), 3.91 (s, 3H, OCH₃); $^{13}\text{C-NMR}$ δ 163 (C=O), 154 (HC=), 149, 127, 124, 111, 110 (phenyl), 116 (CN), 98 (C=), 56, 55 (phenyl-OCH₃), 52 (OCH₃); IR (NaCl): 2959 (m, C-H), 2218 (m, CN), 1732(s, C=O), 1589 (C=C), 1232 (s, C-O-CH₃), 761 (s, C-H out of plane). Anal. Calcd. for C₁₃H₁₃NO₄: C, 63.15; H, 5.30; N, 5.66; Found: C, 62.75; H, 4.95; N, 5.53.

Methyl 2-cyano-3-(3,5-dimethoxyphenyl)-2-propenoate

Yield: 82%; mp 106°C; $^1\text{H-NMR}$ δ 8.2 (s, 1H, CH=), 7.0, 6.5 (m, 3H, phenyl), 3.8 (s, 6H, phenyl-OCH₃), 3.6 (s, 3H, OCH₃); $^{13}\text{C-NMR}$ δ 164 (C=O), 156 (HC=), 146, 120, 118, 112 (phenyl), 116 (CN), 101 (C=), 57 (phenyl-OCH₃), 53 (OCH₃); IR (NaCl): 2958 (m, C-H), 2226 (m, CN), 1722(s, C=O), 1604 (C=C), 1268 (s, C-O-CH₃), 762 (s, C-H out of plane). Anal. Calcd. for C₁₃H₁₃NO₄: C, 63.15; H, 5.30; N, 5.66; Found: C, 63.01; H, 5.14; N, 5.60.

Methyl 2-cyano-3-(2,4,5-trimethoxyphenyl)-2-propenoate

Yield: 82%; mp 194°C; $^1\text{H-NMR}$ δ 8.4 (s, 1H, CH=), 7.0, 6.7 (m, 3H, phenyl), 3.8 (s, 9H, phenyl-OCH₃), 3.7 (s, 3H, OCH₃); $^{13}\text{C-NMR}$ δ 163 (C=O), 152 (HC=), 153, 144, 114,

96 (phenyl), 116 (CN), 114 (C=), 56 (phenyl-OCH₃), 52 (OCH₃); IR (NaCl): 2954 (m, C-H), 2211 (m, CN), 1716(s, C=O), 1574 (C=C), 1224 (s, C-O-CH₃), 762 (s, C-H out of plane). Anal. Calcd. for C₁₄H₁₅NO₅: C, 60.64; H, 5.45; N, 5.05; Found: C, 60.66; H, 5.41; N, 5.05.

Methyl 2-cyano-3-(2,4,6-trimethoxyphenyl)-2-propenoate

Yield: 84%; mp 147°C; ¹H-NMR δ 8.3 (s, 1H, CH=), 7.1, 6.8 (m, 3H, phenyl), 3.8 (s, 9H, phenyl-OCH₃), 3.7 (s, 3H, OCH₃); ¹³C NMR δ 164 (C=O), 152 (HC=), 152, 145, 113, 95 (phenyl), 116 (CN), 112 (C=), 57 (phenyl-OCH₃), 53 (OCH₃); IR (NaCl): 2952 (m, C-H), 2220 (m, CN), 1718(s, C=O), 1593 (C=C), 1223 (s, C-O-CH₃), 768 (s, C-H out of plane). Anal. Calcd. for C₁₄H₁₅NO₅: C, 60.64; H, 5.45; N, 5.05; Found: C, 60.58; H, 5.37; N, 4.93.


Copolymerization

Vinyl acetate (Aldrich) was distilled at 72°C before use. Ethyl acetate (Aldrich) was used as received. 1,1'-Azobis(cyclohexanecarbonitrile) (ABCN) (Aldrich) was recrystallized twice from ethyl alcohol and then dried under reduced pressure at room temperature. Copolymers of the TSE monomers and vinyl acetate were prepared in 25-ml Pyrex screw cap ampoules at VAC/TSE = 2/1 molar ratio of the monomer feed using 0.12 mol/l of ABCN at an overall monomer concentration 2.44 mol/l in 10 ml of ethyl acetate. The copolymerization was conducted at 70°C. After a predetermined time, the mixture was cooled to room temperature, and precipitated dropwise in petroleum ether. The crude copolymers were purified by reprecipitation from chloroform solution into an excess of petroleum ether. The composition of the copolymers was determined based on the nitrogen content.

Results and Discussion

Monomer Synthesis

The TSE monomers were synthesized by Knoevenagel condensation (7) of a ring-substituted benzaldehyde with an active hydrogen compound, methyl cyanoacetate, catalyzed by a base, piperidine:



The condensation reaction proceeded smoothly, yielding crystalline products, which were purified by conventional techniques.

Homopolymerization

An attempted homopolymerization of the TSE monomers in the presence of AIBN did not produce any polymer as indicated by the lack of a precipitate in methanol. The inability of the monomers to polymerize is associated with steric difficulties encountered in the homopolymerization of 1,1- and 1,2-disubstituted ethylenes. This type of steric hindrance would increase the activation energy required for addition and slow down the rate of propagation to such an extent as to favor the occurrence of a chain transfer or termination instead.

Homopolymerization of VAC under conditions identical to those in the copolymerization experiments yielded 28.7% of polyvinyl acetate, when polymerized for 30 min.

Copolymerization

Copolymerization (Scheme 1) of VAC and the substituted methyl (*E*)-2-cyano-3-phenyl-2-propenoates resulted in the formation of copolymers (Table 1) with weight-average molecular masses 11.5×10^3 to 26.8×10^3 daltons. According to elemental analysis, the copolymerization of the propenoates with VAC results in equimolar copolymers, which is indicative of high reactivity of the monomers in cross-propagation reactions.

In an attempt to qualitatively correlate the observed monomer reactivities, we considered copolymer composition data obtained at VAC/TSE = 2 monomer feed. The relative reactivity of VAC in copolymerization with these monomers can be estimated by assuming applicability of the copolymer composition [Equation (1)] of the terminal copolymerization model (1):

$$m_1/m_2 = [M_1](r_1[M_1] + [M_2])/[M_2]([M_1] + r_2[M_2]) \quad (1)$$


m_1 and m_2 are the mole fractions of VAC and TSE monomer units in the copolymer, respectively; $[M_1]$ and $[M_2]$ are the concentrations of VAC and a TSE in the monomer feed, respectively; $r_1 = k_{11}/k_{12}$, and $r_2 = k_{22}/k_{21}$. In the absence of the self-propagation of TSE monomers ($k_{22} = 0$, $r_2 = 0$), and at monomer feed, ($[M_1]/[M_2] = 2$), Equation (1) yields:

$$r_1 = 0.5 (m_1/m_2 - 1) \quad (2)$$

Consideration of the copolymerization constants according to Equation (2) also involves the assumption of minimal copolymer compositional drift at this monomer feed and given conversion. This nonrigorous kinetic treatment nevertheless allows estimation of the reactivity of a vinyl acetate-ended polymer radical in reaction with electrophilic monomer. Very low values of r_1 , 0.01 for 2,3-(CH₃O)₂, 0.04 for 2,4-(CH₃O)₂, 0.00 for 2,5-(CH₃O)₂, 0.02 for 2,6-(CH₃O)₂, 0.02 for 3,4-(CH₃O)₂, 0.02 for 3,5-(CH₃O)₂, 0.03 for 2,4,5-(CH₃O)₃, and 0.01 for 2,4,6-(CH₃O)₃ substituted propenoates, suggest that VAC and TSE enter into the copolymer in equimolar amounts in a nonrandom, alternating arrangement along the copolymer chain.

Structure and Thermal Properties

The structures of the copolymers were characterized by IR and NMR spectroscopy. A comparison of the spectra of the copolymers and polyvinyl acetate shows that the reaction between the TSE monomers and VAC is a copolymerization. All the IR

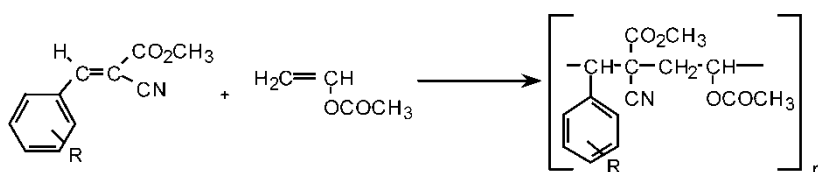

Scheme 1. VAC-TSE copolymer synthesis. R = 2,3-(CH₃O)₂, 2,4-(CH₃O)₂, 2,5-(CH₃O)₂, 2,6-(CH₃O)₂, 3,4-(CH₃O)₂, 3,5-(CH₃O)₂, 2,4,5-(CH₃O)₃, and 2,4,6-(CH₃O)₃.

spectra of the copolymers show overlapping bands in $3300\text{--}2600\text{ cm}^{-1}$ region corresponding to C–H vibrations. The absorptions of the VAC units appear at $1770\text{--}1650\text{ cm}^{-1}$ (carbonyl group), $1380\text{--}1360\text{ cm}^{-1}$ (wagging CH_3), $1250\text{--}1210\text{ cm}^{-1}$ (stretching COO), and $1030\text{--}1010$ and $1130\text{--}1110\text{ cm}^{-1}$ (stretching C–C–C). The bands for the TSE monomer unit are $2235\text{--}2245\text{ cm}^{-1}$ (w, CN), $1740\text{--}1748\text{ cm}^{-1}$ (s, C=O), and $1232\text{--}1238\text{ cm}^{-1}$ (m, C–O).

All NMR spectra show broad resonance signals. Broadening of the NMR signals in the spectra of the copolymers is apparently associated with head-to-tail and head-to-head structures, which formed through the attack of a VAC-ended radical on both sides of the TSE monomer unit. It was demonstrated that both head-to-tail and head-to-head structures TSE-styrene dyads exist in the copolymers of styrene and 2-phenyl-1,1-dicyanoethene (8). All spectra show a broad peak in the $6.5\text{--}8.0$ ppm region corresponding to the phenyl ring protons of the TSE. A broad signal in the $4.7\text{--}5.7$ ppm region is assigned to the VAC methine protons. The peaks in the range $3.5\text{--}4.5$ ppm and $3.2\text{--}3.5$ ppm are assigned to the methoxy and the methine protons of the TSE monomer unit. A signal in $1.7\text{--}2.7$ ppm range corresponds to VAC methyl group. Broad, overlapping resonances in the $0.9\text{--}2.5$ ppm region are assigned to the methylene proton of VAC monomer unit. The ^{13}C -NMR and DEPT spectra of the copolymers also support the suggested skeletal structure of the copolymers. Thus, the assignment of the peaks as follows: $167\text{--}175$ ppm (C=O), $120\text{--}140$ ppm (phenyl carbons), $115\text{--}120$ ppm (CN), $52\text{--}57$ ppm (OCH_3 and methine), $46\text{--}52$ ppm (quaternary carbon) of TSE unit. The peaks corresponding to the carbons of VAC monomer unit are at 170 ppm (C=O), $65\text{--}72$ ppm (methine), $35\text{--}47$ ppm (CH_2), and $20\text{--}30$ ppm (CH_3). The IR and NMR data showed that these are true copolymers, composed of both TSE and VAC monomer units.

The copolymers prepared in the present work are all soluble in methyl ethyl ketone, acetone, benzene, THF, DMF and CHCl_3 and insoluble cyclohexane, and in ethyl and petroleum ethers. High T_g of the copolymers (Table 1), in comparison with that of polyvinyl acetate ($T_g = 28\text{--}31^\circ\text{C}$) indicates a decrease in the chain mobility of the copolymer due to the high dipolar character of the TSE structural unit. Information on the degradation of the copolymers was obtained from thermogravimetric analysis. The TGA in nitrogen and air produce similar traces. The decomposition of the copolymers occurs in two steps, presumably acetic acid elimination in the $209\text{--}360^\circ\text{C}$ range followed by very slow decomposition of the formed at about 400°C residue ($20\text{--}17\%$). Such a two-step degradation, acetic acid elimination followed by polyacetylene degradation is known for polyvinyl acetate (9). The continued heating up to 950°C brings down the weight of the residue to about 10% . The decomposition products were not analyzed in this study and the mechanism has yet to be investigated.

Conclusions

Trisubstituted ethylenes, methoxy ring-substituted methyl 2-cyano-3-phenyl-2-propenoates, were prepared via a base-catalyzed condensation of appropriate substituted benzaldehyde and methyl cyanoacetate. The copolymerization of the propenoates with vinyl acetate results in equimolar alternating copolymers. The compositions of the copolymers were calculated from nitrogen analysis and the structures were analyzed by IR, ^1H - and ^{13}C -NMR. High glass transition temperatures of the copolymers, in comparison with that of polyvinyl acetate, indicate a substantial decrease in the chain mobility of the copolymers due to the high dipolar character of the trisubstituted ethylene monomer unit. The gravimetric analysis indicated that the copolymers decompose in the range $200\text{--}400^\circ\text{C}$.

Acknowledgements

We are grateful to acknowledge that the project was partly supported by the Coatings Industry Education Foundation and Chicago Society of Coatings Technology. XT was supported by a CIEF graduate fellowship.

References

1. Odian, G. (1991) *Principles of Polymerization*, 3rd Ed.; Wiley: New York.
2. Hall, H.K., Jr. and Daly, R.C. (1975) Electron-deficient trisubstituted olefins. A new class of reactive comonomers. *Macromolecules*, 8: 22–31.
3. Kharas, G.B. (1996) Trisubstituted ethylene copolymers. In *Polymeric Materials Encyclopedia*; Salamone, J.C., ed.; CRC Press: Boca Raton; Vol. 11, 8405–8409.
4. Kharas, G.B., Fuerst, A.M., Feitl, E.L., Pepper, M.E., Prillaman, F.C., Pyo, J.R., Rogers, G.M., Tadros, A.Z., Umek, L.G., and Watson, K. (2004) Novel copolymers of trisubstituted ethylenes and styrene. II. Halogen ring-substituted ethyl 2-cyano-1-oxo-3-phenyl-2-propenylcarbamates. *J. Macromol. Sci.*, A41: 629–635.
5. Kharas, G.B., Mc Colough, K.E., Heiskell, J.R., Herrman, J.E., Levun, J.A., Lucchetta, E.M., Villaseñor, G., Parish-Chafey, L.A., Schreiber, P.J., O'Malley, P.A., Starkman, B.G., Verdoorn, G., Passe, L.B., and Watson, K. (2003) Synthesis and copolymerization of ring-substituted N-(aminocarbonyl)-2-cyano-3-phenyl-2-propenamides with Styrene. *Designed Monomers and Polymers*, 6: 103–113.
6. Kharas, G.B., Fuerst, A.M., Scola, A., III, Bavirsha, D.J., Bernau, B.M., Brown, S.K., Ece, P., Dabrowski, A.N., De Angelo, P., Fatemi, F.R., and Watson, K. (2002) Novel copolymers of trisubstituted ethylenes and styrene. I. Alkyl and alkoxy ring-substituted ethyl 2-cyano-1-oxo-3-phenyl-2-propenylcarbamates. *J. Macromol. Sci., Pure Appl. Chem.*, A39: 1383–1391.
7. Smith, M.B. and March, J. (2001) Addition to carbon-hetero multiple bonds. In *March's Advanced Organic Chemistry*; J. Wiley & Sons: New York; Ch. 16, 1225.
8. Kharas, G.B., Murau, P.A., Watson, K., and Harwood, H.J. (1992) Microstructure of styrene copolymers with 2-phenyl-1,1-dicyanoethene. *Polym. Int.*, 28: 67–74.
9. Holland, B.J. and Hay, J.N. (2002) The thermal degradation of poly(vinyl acetate) measured by thermal analysis-fourier transform infrared spectroscopy. *Polymer*, 43: 2207–2211.