

This article was downloaded by:

On: 24 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Macromolecular Science, Part A

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713597274>

Grafting of Methyl Acrylate onto PET Initiated by Diperoxidocuprate(III)

Yinghai Liu^a; Shengxian Li^a; Jianping Zhang^a; Weiqi Zhou^a; Rongyue Zhang^a

^a College of Chemistry and Environmental Science, Hebei University, Baoding, P. R. China

To cite this Article Liu, Yinghai , Li, Shengxian , Zhang, Jianping , Zhou, Weiqi and Zhang, Rongyue(2006) 'Grafting of Methyl Acrylate onto PET Initiated by Diperoxidocuprate(III)', *Journal of Macromolecular Science, Part A*, 43: 8, 1255 – 1263

To link to this Article: DOI: 10.1080/10601320600737625

URL: <http://dx.doi.org/10.1080/10601320600737625>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Grafting of Methyl Acrylate onto PET Initiated by Diperoxidocuprate(III)

YINGHAI LIU, SHENGXIAN LI, JIANPING ZHANG,
WEIQI ZHOU, AND RONGYUE ZHANG

College of Chemistry and Environmental Science, Hebei University, Baoding,
P. R. China

A novel system, potassium diperoxidocuprate(III) (DPC)-Poly(ethylene terephthalate) (PET), was employed to initiate the graft copolymerization of methyl acrylate (MA) onto PET in alkali medium. The effects of reaction conditions, such as the initiator concentration, ratio of MA to PET, and temperature and time, were investigated. Graft copolymers with high grafting parameters were obtained ($E\% > 80\%$), which indicated that the DPC-PET system is an efficient initiator for this graft copolymerization. The structures and the thermal stability of PET-g-PMA were characterized by scanning electron microscope (SEM), infrared spectroscopy (IR) and thermogravimetric analysis (TGA). A mechanism is proposed to explain the generation of radicals and the initiation of graft copolymerization. The SEM photographs show that the graft copolymer greatly improved the compatibility of the PET/PMMA blends. The moisture regain (MR) of PET-g-PMA is found to increase compared with PET.

Keywords potassium diperoxidocuprate(III) (DPC), poly(ethylene terephthalate) (PET), methyl acrylate (MA), transfer initiated, Graft copolymerization

Introduction

There is widespread use of synthetic fibers in the textile industry today. PET have a prominent place among these synthetic fibers. However, in spite of many superior properties of PET fibers, some of their poor features such as low MR, difficulty of dyeing, and poor antistatic properties limit their usage. One of the most common ways reported to give new properties or improve poor features of PET, is grafting various monomers onto them by graft copolymerization. It is generally thought that, as a result of graft copolymerization, the properties of PET backbone are not affected and the fibers acquire new properties, depending upon the monomer grafted. The graft copolymerization can be chemically initiated using initiators such as benzoyl peroxide (1, 2), hydrogen peroxide (3) and ceric ion (4–6). In addition, supernormal valence transition-metals have received considerable attention and the feasibility of their applications to radical polymerization appeals to more and more attention of researchers. Noticeably, some achievements on the polymerization and graft copolymerization of vinyl monomer

Received November 2004; Accepted January 2006.

Address correspondence to Yinghai Liu, College of Chemistry and Environmental Science, Hebei University, Baoding 071002, P. R. China. E-mail: yhliu2004@163.com

initiated by supernormal valence transition-metals have obtained by our group since 1990s (7–10).

In this paper, DPC-PET system was used to initiate the grafting copolymerization of MA onto PET backbone. The effects of reaction conditions, such as the initiator concentration, the ratio of MA to PET, temperature and time, were investigated, and the grafting conditions were optimized. At the same time, the structures and properties of PET and PET-g-PMA were characterized by SEM, IR and TGA. The SEM photographs show that the graft copolymer greatly improved the compatibility of the PET/PMMA blends. The moisture regain (MR) of PET-g-PMA is found to increase compare with PET.

Experimental

Materials

PET (300–400 mesh, Boye Chemical Factory, Boye, China) was washed with acetone to remove any adhering impurity before use and then dried under vacuum at 60°C. MA (Tianjin Huadong Chemical Reagent Station) was washed successively with aqueous sodium hydroxide solution, distilled water, then distilled under reduced pressure. The other solvents were all of analytical reagent and used without any further purification.

Synthesis and Measurement of DPC

DPC was synthesized and measured according to the reported procedure (11). DPC was synthesized and measured according to the reported procedure (10). $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$ (5.53 g), KIO_4 (6.80 g), KOH (9.0 g) were added to about 250 ml of water. The mixture was shaken thoroughly and heated on a hot plate. In about 20 min, the boiling mixture turned intensely red and the boiling was continued for another 20 min more for the completion of the reaction. The mixture was then cooled, filtered through sintered glass crucible (G4) and diluted to 250 ml with doubly distilled water. The concentration of DPC was obtained by its absorption at $\lambda = 414 \text{ nm}$ using a Shimadzu UV-265 spectrophotometer (Japan). The concentration of base DPC was calculated as $1.67 \times 10^{-2} \text{ mol/L}$.

Graft Copolymerization and Treatment of Copolymer

Required amounts of PET, MA and water were added in the reaction tube. Eliminating oxygen was performed by injecting pure nitrogen into it and the reaction system was maintained at certain temperature in a thermostatic reservoir. Then, appropriate amounts of DPC were added under a stream of dry N_2 gas. After a given time, the reaction was terminated by adding hydrochloric acid. The formed polymer was filtered, washed well with water, and then dried under vacuum at 60°C to constant weight. The homopolymer of MA (PMA) was removed from the crude graft copolymer by Soxhlet extraction with acetone for 48 h. The titled copolymer was then obtained after drying to a constant weight under vacuum at 60°C.

Definition of the Grafting Parameters

The grafting parameters were defined and calculated in the following manner:

$$C\% = (\text{total weight of PMA}/\text{weight of MA charged}) \times 100\%$$

$$E\% = (\text{weight of PMA grafted}/\text{total weight of PMA}) \times 100\%$$

$$P\% = (\text{weight of PMA grafted}/\text{weight of PET}) \times 100\%$$

Measurements

AMKAY-1000B was used to observe the morphologies of PET and PET-g-PMA. The FTIR spectra of PET and PET-g-PMA were recorded on an FTS-40 spectrometer (BIO RAD Co., USA) using potassium bromide pellets technique. The TGA curves of PET and PET-g-PMA were carried out on a Shimadzu apparatus (DGC-40 DTA-TG) at a heating rate of 10°C/min in a static air atmosphere.

Results and Discussion

Effect of DPC Concentration

As shown in Figure 1, when the total volume, the ratio of MA/PET as well as reaction temperature and time are kept invariably, by changing the DPC concentrations, C%, E% and P% increase significantly first, reach a maximum value, and then decrease. The initial increasing trend may be due to the fact that in this concentration range, DPC attacks grafting sites of PET backbone directly, and creates a great deal of macroradicals which will initiate the grafting in the presence of MA, leading to the increase of graft parameters. However, a further increase of the DPC concentration accelerates the reaction of DPC and radical, which terminates the chain propagation reaction, hence decreasing C% and P%. Meanwhile, at higher DPC concentration, the chance of chain transfer to monomer is enhanced, resulting in the decline of E%.

Effect of MA-to-PET Ratio

The effect of MA-to-PET (weight) ratio on graft copolymerization is depicted in Figure 2. It is observed from this Figure that the grafting parameters increase initially with the

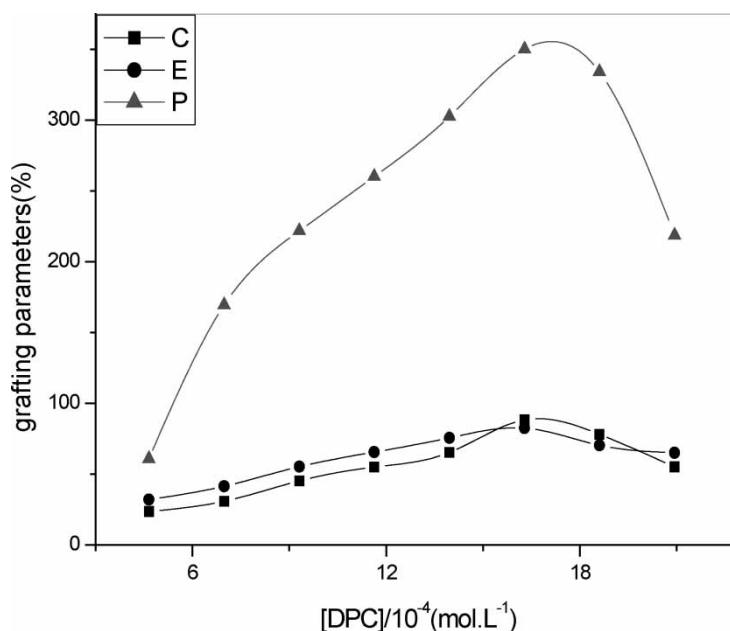


Figure 1. Effect of DPC concentration on grafting parameters MA/PET = 3.8, T = 35°C, Time = 60 min.

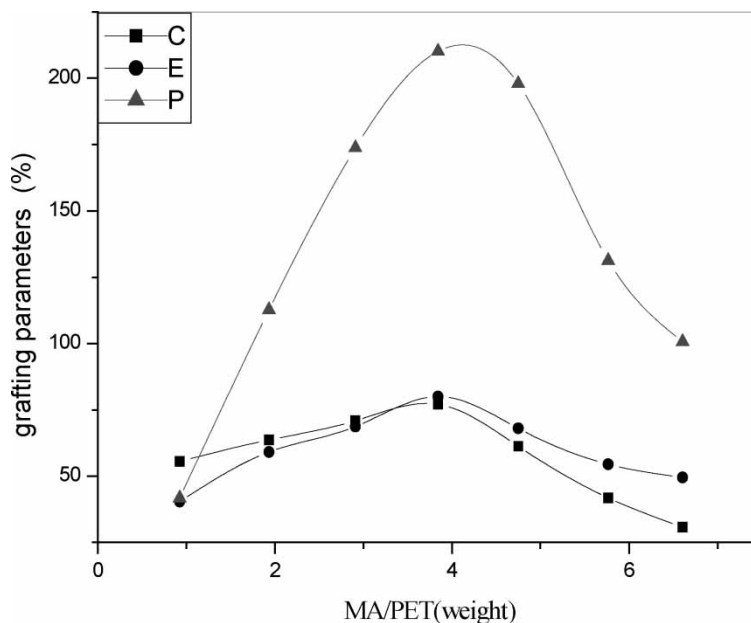


Figure 2. Effect of MA/PET ratio on grafting parameters [DPC] = 16.29×10^{-4} mol/L, Time = 60 min, T = 35°C.

increasing MA-to-PET ratio, this may be ascribed to the surface-activity and self-emulsifying properties of PET and MA-to-PET, which assists in the proximity of monomer to the growing chains and active sites on the PET. However, beyond MA/PET (weight) = 3.8, grafting parameters decline. This may be explained as follows: with the total volume fixed, an increase in ratio MA-to-PET means the higher DPC concentration in the water phase, thus the chain transfer reaction of radicals to MA is accelerated. Moreover, when the MA-to-PET ratio is higher, the obvious adsorption of monomers onto PET largely impeding the approach of between DPC and PET, which is necessary for initiation. Therefore, homopolymerization rate enhances and E% declines correspondingly.

Effect of Temperature

Keeping the other variables constant, the grafting reactions are carried out at different temperatures between 20°C and 45°C. In Figure 3, grafting parameters increase in the beginning up to 35°C, and then decrease to some extent with further increasing of temperature. The improvement in grafting parameters can be explained by the higher decomposing rate of initiator, producing more PET macroradicals (which attracts more DPC), as well as the quickened diffusion and mobility of the MA from the aqueous phase to the backbone with the increase of temperature. The decline of grafting parameters at high temperature can be ascribed to both the enhanced radical termination reaction through oxidation by DPC and the increased chance of chain transfer reaction.

Effect of Time

As shown in Figure 4, it can be seen that E% keep unchanged in a range of 20 min to 80 min, however, both C% and P% increase steadily with the reaction time prolonged

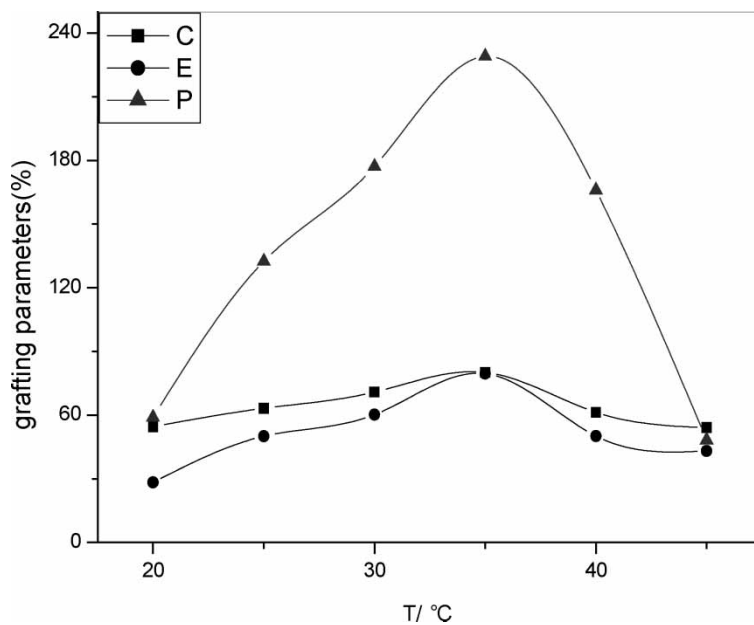


Figure 3. Effect of temperature on grafting parameters [DPC] = 16.29×10^{-4} mol/L, Time = 60 min, MA/PET = 3.8.

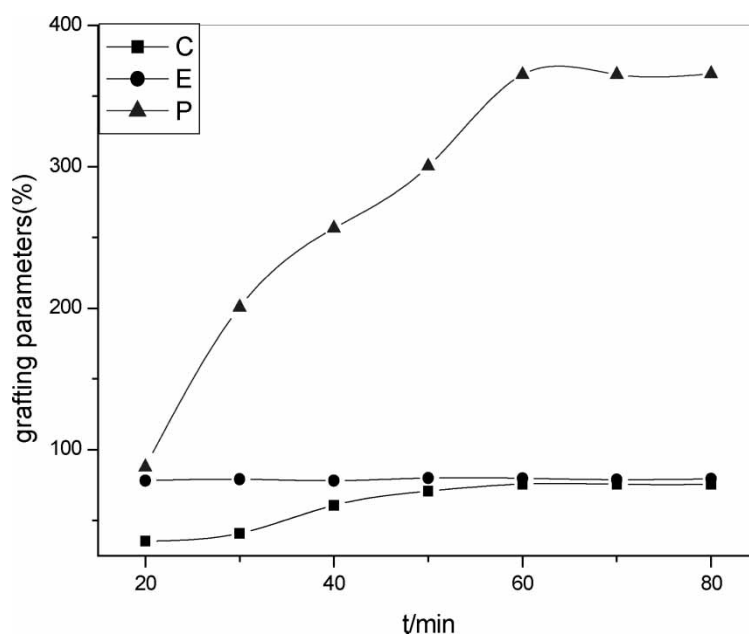


Figure 4. Effect of time on grafting parameters [DPC] = 16.29×10^{-4} mol/L, MA/PET = 3.8, T = 35°C.

up to 60 min, and then maintain a plateau, which is in consistent with the general rule of radical polymerization initiated by supernormal valence transition- metals (7–10).

Scanning Electron Microscopy

The SEM of PET(a), PET-g-PMA(b), PET/PMMA(c) and PET/PET-g-PMA/PMMA(d) are shown in Figure 5. It was found that the PET(a) shape is grain, whereas the PET-g-PMA almost turns into an entirety, which may be due to the incorporation of PMA with the PET backbone, there is no doubt that the graft reaction conveys these alterations. The surface of PET/PET-g-PMA/PMMA (d) is smoother than PET/PMMA(c)'s, this indicates that the graft copolymer greatly improved the compatibility of the PET/PMMA blends.

IR Spectroscopy

In the FTIR spectra of PET-g-PMA (Figure 6), some characteristic absorptions such as 1734 cm^{-1} , 1164 cm^{-1} and 826 cm^{-1} assigned to PMA and 1600 cm^{-1} , 1500 cm^{-1} for PET, respectively, have been recorded, indicating the successful grafting of MA onto PET. Additionally, the absorption intensity of phenyl moiety in the IR measurement of PET-g-PMA becomes weak, implying more evidence that PMA has been grafted onto PET under the above-mentioned reaction condition. Furthermore, the character

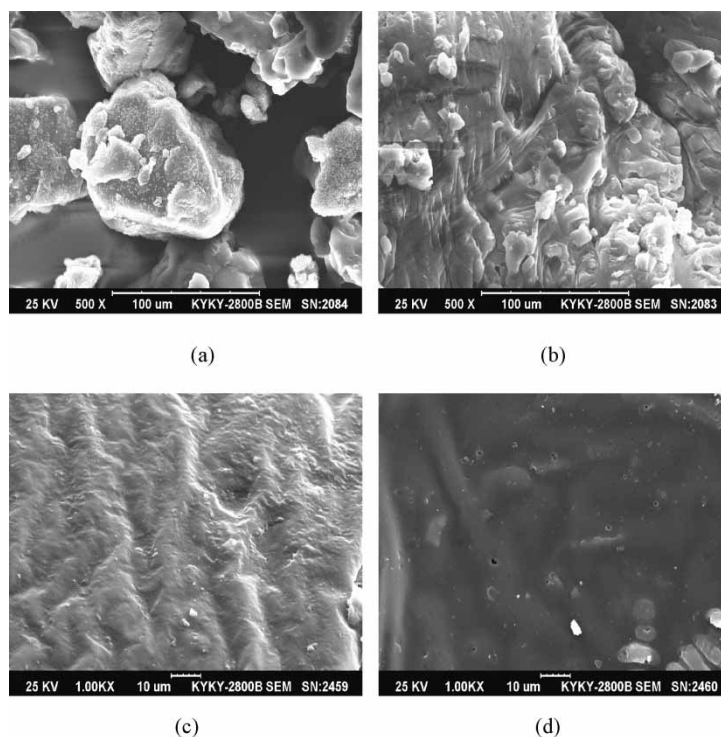


Figure 5. SEM of PET(a), PET-g-PMA(b), PET/PMMA(c), and PET/PET-g-PMA/PMMA (d).


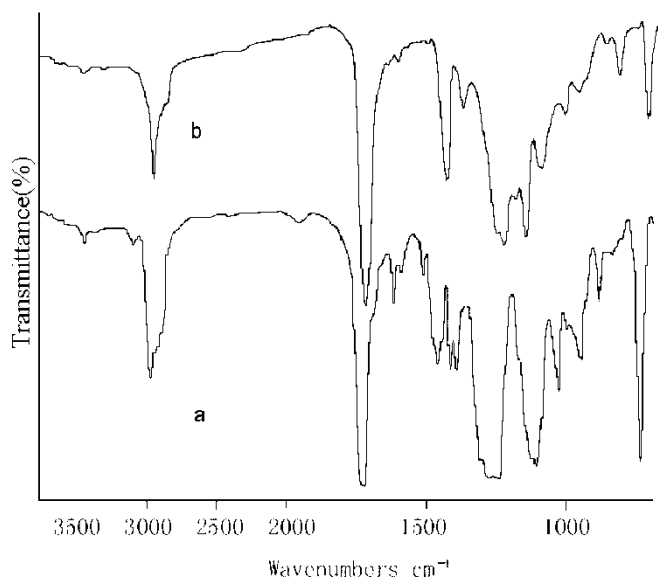


Figure 6. IR spectrum of PET (a) and PET-g-PMA(b).

absorption of $-\text{CH}_2$ at 2960 cm^{-1} for PET-g-PMA becomes weak, which indicates that the grafting reaction may be occurred at the segment of



Thermal Analysis

The thermograms from TGA are shown in Figure 7. In the TG curve of PET-g-PMA, an inflexion due to absorbed moisture lies between 45°C – 330°C . No such inflexions are observed in the TG curve of PET. This reveals that graft copolymer can increase the moisture absorption.

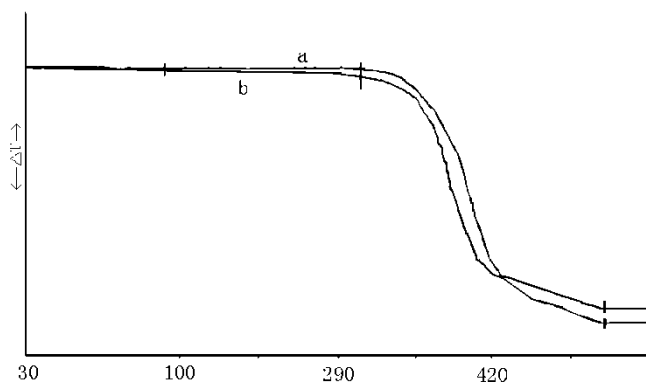


Figure 7. TGA curves of PET(a) and PET-g-PMA(b).

Determination of Moisture Regain


In the MR measurement, PET and PET-g-PMA were immersed in 36% H₂SO₄ solution and followed by placing them into desiccator for 48 h and then drying to a constant weight under 110°C. The MR was defined and calculated as follow:

MR = the added weight after moisture absorption/the weight of PET before moisture absorption.

The percentage of MR is found to increase with the increasing of E%, and the maximum value is 18.6%. While PET is highly hydrophobic in nature, the moisture content of the PET is very low under normal conditions of temperature and humidity. Grafting with MA not only brings about the opening of the structure to a certain extent, but also increases hydrophilicity of the fiber as a result of the introduction of the polar groups (an ester group) into the PET matrix. This shift in the hydrophobic nature is responsible for the enhancement of the MR with increasing the percentage of E%.

The Initiation Mechanism of Grafting Reaction

An initiation mechanism of transfer graft based on IR spectra and literature (10) was proposed as follows:

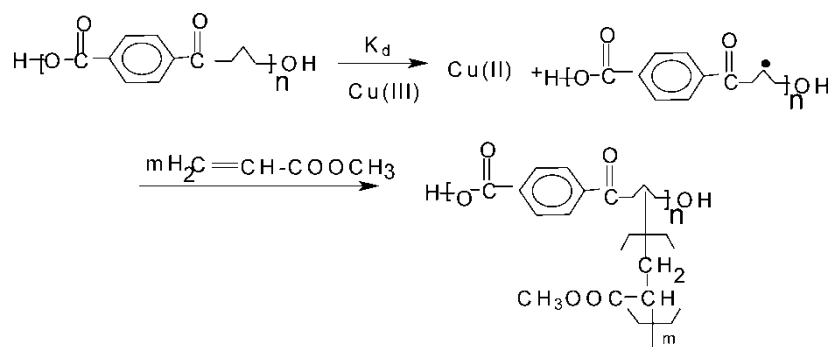

Conclusions

In this study, graft copolymers with high graft parameters have been successfully synthesized, using DPC-PET system as an efficient initiator for graft copolymerization. The optimal conditions have been evaluated and listed as follows: temperature (35°C), concentration of [DPC] (16.29×10^{-4} mol/L), weight ratio of MA/PET (3.8:1) and reaction time (60 min). The structure of the titled copolymer has been testified by a series of charactering techniques including SEM, IR and TGA. Meanwhile, DPC-PET system is expected to be a considerable foreground in its practical application due to the facile preparation of DPC from $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$ and the mild reaction conditions for the graft polymerization. Further work is now in progress.

Acknowledgement

The authors would like to express sincerely thanks to the Natural Science Foundation of He Bei Province for financial support of this research.

References

1. Mehmet, Sacak and Fazli, Ofaz. (1993) *Journal of Applied Polymer Science*, 50: 1909–1916.
2. Mehmet, Sacak, Filz, Sertkaya, and Muzaffer, Talu. (1992) *Journal of Applied Polymer Science*, 44: 1737–1742.
3. Hebeish, A., Shalaby, S.E., and Bayazeed, A.M. (1981) *Journal of Applied Polymer Science*, 26: 3253–3269.
4. Chansook, N. and Kiatkamjornwong, S. (2003) *Journal of Applied Polymer Science*, 89: 1952–1958.
5. Pradhan, Adwait K., Pati, Nrusingha C., and Nayak, Padma L. (1982) *Journal of Applied Polymer Science*, 27: 1873–1881.
6. Nayak, N.C., Das, H.K., and Singh, B.C. (1991) *Journal of Applied Polymer Science*, 42: 2391–2396.
7. Liu, Y.H., Liu, X.H., Deng, K.L., Liu, Z.J., and Yang, L.Y. (2003) *J. Mac. Sci. Part A—Pure and Appl. Chem.*, A40 (3): 211–223.
8. Liu, Y.H., Li, J.B., Yang, L.Y., and Shi, Z.Q.S. (2003) *J. Mac. Sci. Pure and Appl. Chem.*, 10: 1107–1117.
9. Liu, Y.H., Li, J.B., Yang, L.Y., and Shi, Z.Q.S. (2004) *J. Mac. Sci. Pure and Appl. Chem.*, A41 (3): 305–316.
10. Liu, Y.H., Liu, Z.H., Zhang, J.S., and Deng, K.L. (2002) *J. Macromol. Sci. Pure and Appl. Chem.*, A39 (1): 129–143.
11. Jaiswal, P.K. and Yadava, K.L. (1973) *Indian J. Chem.*, 11: 837–839.