

Tissue differentiation in an in vivo bioreactor: in silico investigations of scaffold stiffness

Hanifeh Khayyeri · Sara Checa · Magnus Tägil · Fergal J. O'Brien · Patrick J. Prendergast

Received: 3 August 2009 / Accepted: 9 December 2009 / Published online: 27 December 2009
© Springer Science+Business Media, LLC 2009

Abstract Scaffold design remains a main challenge in tissue engineering due to the large number of requirements that need to be met in order to create functional tissues in vivo. Computer simulations of tissue differentiation within scaffolds could serve as a powerful tool in elucidating the design requirements for scaffolds in tissue engineering. In this study, a lattice-based model of a 3D porous scaffold construct derived from micro CT and a mechano-biological simulation of a bone chamber experiment were combined to investigate the effect of scaffold stiffness on tissue differentiation inside the chamber. The results indicate that higher scaffold stiffness, holding pore structure constant, enhances bone formation. This study demonstrates that a lattice approach is very suitable for modelling scaffolds in mechano-biological simulations, since it can accurately represent the micro-porous geometries of scaffolds in a 3D environment and reduce computational costs at the same time.

1 Introduction

In tissue engineering, scaffolds play a critical role in regulating cell activities. They provide a volume in which

vascularisation and stem cell differentiation can occur [1]. By virtue of its stiffness and pore structure, the scaffold determines the mechanical environment and thereby modulates tissue differentiation. It is therefore critical to match scaffold mechanical properties to the graft environment not only to prevent mechanical failure of the scaffold but also to create an appropriate mechanical environment for the desired tissue differentiation pathway.

Biomaterials science has mainly used a trial-and-error approach to scaffold design [2]. In order to achieve improved cellular infiltration and better control of the mechanical conditions inside the constructs bioreactors have been designed [2, 3]. Although they have improved the reliability of in vitro scaffold experiments, it is essential that scaffolds perform in an in vivo environment to promote cellular infiltration and desired tissue formation. Steps towards this goal could be guided by the use of computational analysis.

Current computational models for predicting tissue formation adopt mechano-regulation theories that link mechanical forces to mesenchymal differentiation pathways. One of the earliest mechano-regulation theories was proposed by Pauwels [4]. He suggested that shear stress and hydrostatic pressure regulates tissue differentiation in fracture calluses. Later, Carter et al. [5] proposed an osteogenic index, described as a combination of distortional strain and hydrostatic pressure, to modulate the process of skeletal tissue differentiation. A more quantitative model was put forward by Claes and Heigele [6] who determined tissue formation by proposing different thresholds of hydrostatic pressure and local stress for bone, cartilage and fibrous tissue differentiation. By characterising the skeletal tissues as biphasic materials, Prendergast et al. [7] proposed that a biophysical stimulus (a combination of fluid flow and shear strain) regulated tissue

H. Khayyeri · S. Checa · F. J. O'Brien · P. J. Prendergast (✉)
Trinity Centre for Bioengineering, School of Engineering,
Trinity College, Dublin, Ireland
e-mail: pprender@tcd.ie

M. Tägil
Department of Orthopaedics, Lund University Hospital, Lund,
Sweden

F. J. O'Brien
Department of Anatomy, Royal College of Surgeons in Ireland,
Dublin, Ireland

formation. Although the mechano-regulation theories of Carter et al. [5], Claes and Heigele [6], and Prendergast et al. [7] have been able to capture the main aspects of tissue differentiation, the predictions by the theory of Prendergast et al. [7] have been most successfully correlated with experimental results [8–11]. Another key factor that regulates tissue differentiation is the formation of blood vessels. Newly formed blood vessels provide cells with oxygen and nutrients which are essential for cell proliferation and survival. Since the diffusion of oxygen is limited to a few hundred micrometers from the capillaries, the vascular morphology at the site may play a significant role in determining tissue differentiation patterns [12]. Previous tissue differentiation simulations adopting the mechano-regulation theory of Prendergast et al. [7] within a scaffold have been conducted; the effects of porosity, permeability, Young's modulus, dissolution rate [13] and angiogenesis [14] on tissue differentiation patterns were investigated. However, these studies used a conceptual graft environment/experiment—one of the aims of this paper is to report on how we have extended that work to deal with real scaffolds and their performance in existing mechano-regulated *in vivo* experiments.

Simulations of tissue differentiation inside a mechanically loaded *in vivo* bone chamber have achieved qualitative corroboration in previous studies [10, 11] and shown that the well defined and mechanically controlled environment make bone chambers very suitable for tissue differentiation experiments and simulations. In this study, a bone chamber developed by Tägil and Aspenberg [15] was used (Fig. 1a); consisting of a hollow cylinder with two ingrowth openings at the bottom (Fig. 1b). This bone chamber allows the application of known pressure loads on a defined

loading regime, which makes it appropriate for tissue differentiation simulations, particularly for investigating and evaluating the mechanical properties of a scaffold construct.

The objective of this work was to examine the effect of the mechanical properties (Young's modulus) of a scaffold with a known 3D geometry and material properties, on the tissue differentiation process inside a bone chamber, using a computer model. Specifically, we hypothesise that the scaffold can be represented using a lattice model, and that the complexity of the scaffold can thereby be included in the simulation. If this hypothesis can be confirmed then this presents a methodological approach for investigating the interrelationship between scaffold geometry and mechano-regulation in tissue engineering.

2 Methods

A finite element model of the bone chamber was created (Fig. 1c) to determine the local mechanical environment acting on the cells. Each element was divided into 1,000 lattice points (distance between lattice points 10 μm) (Fig. 1d) where each point represented a position a cell and its extracellular matrix [16] or scaffold material could occupy. The cells were allowed to migrate, proliferate, apoptose, differentiate and synthesise new extracellular matrices while new capillaries invaded the chamber, depending on the surrounding mechanical environment. The scaffold material was included in the chamber by superimposing cross-sections (pixels) of processed μCT scans of a highly porous (>90%) collagen GAG-scaffold, which has been used in bone tissue engineering [17–20], on the lattice points (Fig. 1e). The scaffold construct was

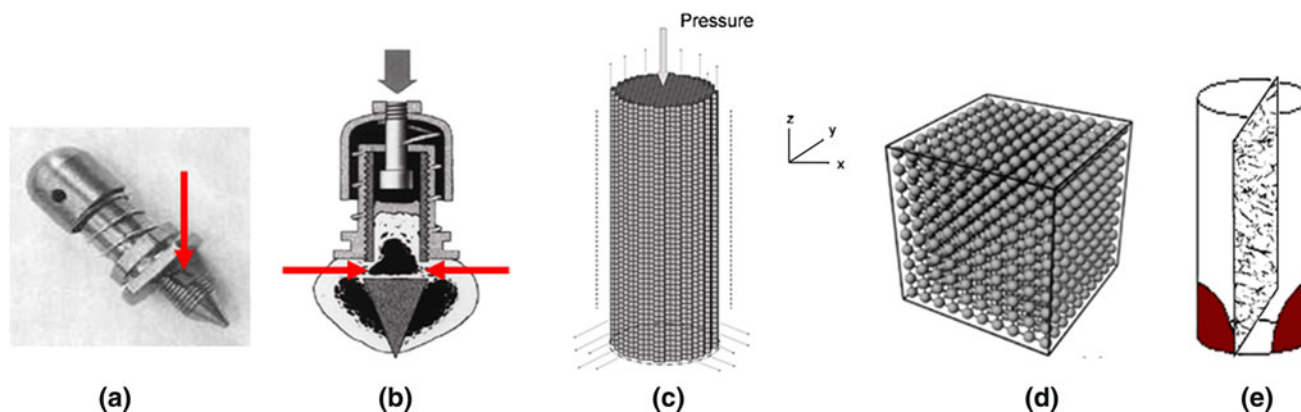


Fig. 1 **a** The bone chamber, where the *arrow* points at an ingrowth opening. **b** Cross-section of the bone chamber [15] where the *thin arrows* point at the ingrowth openings and the *thick arrow* points at the piston by which loading is applied. **c** FE-model of the interior of the bone chamber where the chamber wall was modelled as boundary conditions; ↑↑↑↑: free fluid flow; ↑↑↑↑: $u_x = u_y = 0$; ----:

$u_x = u_y = u_z = 0$. **d** A finite element containing $10 \times 10 \times 10$ lattice points for the simulation of cell activity [13]. **e** Sketch of the bone chamber illustrating the scaffold construct at the mid-cross-section of the chamber; ‘quadrants’ of the openings and the sections through the biomaterial are represented as dark patches in the cross-section

structured with pore size between 300 and 400 μm . Material data, for both tissues and scaffold, was modelled according to the literature [11, 21].

A random walk algorithm [16] was implemented for cell migration. Cell proliferation (mitosis) occurred by allowing mother and daughter cells to randomly occupy neighbouring free lattice points in 21 different states [22].

Cell differentiation also occurred in a random fashion but modulated by the site vascularity [12] and a biophysical stimulus described as a combination of fluid flow and shear strain [7]. Different levels of stimulus determined the differentiation of mesenchymal stem cells into osteoblasts, chondrocytes and fibroblasts which formed bone, cartilage and fibrous tissue, respectively. High levels of biophysical stimulus promoted differentiation of fibroblasts, whilst intermediate stimulus resulted in chondrocytes. Low levels of mechanical stimulation favoured osteoblastic differentiation but only in well vascularised areas where oxygen tension was high. Mesenchymal stem cells (MSCs) in regions under a mechanical stimulus favorable for osteoblast differentiation but with poor vascularity followed the chondrogenic pathway rather than the osteogenic [12].

Capillaries were described as a sequence of endothelial cells. Capillary tips could extend either in the previous direction (persistence), a random direction, or along a concentration gradient (e.g., VEGF that acts as an angiogenic factor and is assumed to be released by hypertrophic chondrocytes) [12]. Each vessel had a possibility to branch with a probability determined by the length of the vessel [12], where longer vessels had a higher probability. The growth of the vessels was restricted by anastomosis (the fusion of two sprouts) and a high mechanical stimulus [12].

The tissue differentiation process inside the bone chamber was modelled as an iterative process where each iteration corresponded to 12 h. The chamber was initially filled with scaffold material and granulation tissue. As an initial condition, MSCs and endothelial cells were seeded at the ingrowth openings. Next the cells began to infiltrate the chamber by migration and proliferation. After the MSCs reached a maturation age (6 days) they differentiated depending on the biophysical stimulus and the site-specific vascularity, with cell phenotype specific rates [23]. Since the lattice points in an element could not only represent different cell phenotypes which synthesize extracellular matrices with different material properties but also have material properties of the scaffold construct, a rule of mixtures was used to determine the material property of each element [24]. Also, in order to prevent an unphysiological rapid change in material properties, the values were averaged over 10 previous iterations.

Correspondingly with the experiments [15], the chamber was kept unloaded for 3 weeks allowing tissue to grow in and then subjected to 2 MPa loading, every 12 h,

for the 6 following weeks. The tissues and the scaffold inside the chamber were assumed to be under very low loading representing normal rat blood pressure during the unloaded time period and were subjected to 0.02 MPa [11]. The effect of scaffold Young's modulus on tissue differentiation patterns was investigated by varying the scaffold Young's modulus within experimentally reported values [25–27]: 0.001, 0.01, 0.1, 1.0, 10, 100 and 1000 MPa.


3 Results

After 9 weeks, for less stiff scaffolds (Young's modulus between 1 and 1,000 kPa) simulations predicted a large amount of fibrous tissue formation due to high fluid flows and shear strains inside the chamber and small amounts of chondrogenic and osteogenic differentiation (Table 1). By increasing the stiffness of the scaffold material, larger amounts of chondrocytes and osteoblasts were predicted and a decrease in fibroblast differentiation was observed, see Table 1 and Fig. 2. In the simulation where a rather stiff scaffold was considered ($E = 1,000$ MPa), a thick layer of chondrocytes surrounded by osteoblasts with no fibroblasts was predicted (Fig. 2). The results also showed a greater and higher endothelial cell invasion in the chamber due to the lower mechanical stimulus environment induced by stiffer scaffold material (a population increase from 6.6 to 8.2% of the chamber volume for $E = 0.001$ –1,000 MPa). However, this has no significant effect on the differentiation outcome since the high porosity of the scaffold and the initial low mechanical environment (3 weeks under no external mechanical load) provides easy access for the formation of the new capillaries in the entire chamber for all simulated scaffold Young's modulus. Therefore the predictions clearly indicate a crucial role for scaffold stiffness in bone regeneration.

Table 1 Percentages of the differentiated cell phenotypes inside the bone chamber for different scaffold stiffness

Scaffold Young's modulus (MPa)	Fibroblasts (%)	Chondrocytes (%)	Osteoblasts (%)
0.001	89.5	5.8	4.7
0.01	89.6	5.9	4.5
0.1	89.0	5.7	5.3
1.0	89.2	5.9	4.9
10	82.6	8.7	8.7
100	59.3	19.7	20.1
1000	1.6	32.7	65.7

Fig. 2 Mid-cross-sections of the chamber where the *coloured* lattice points illustrate endothelial cells (EC), mesenchymal stem cells (MSC), fibroblasts (FB), chondrocytes (CC) and osteoblasts (OB). The *black* lattice points scattered in the entire chamber denote the scaffold occupying the chamber

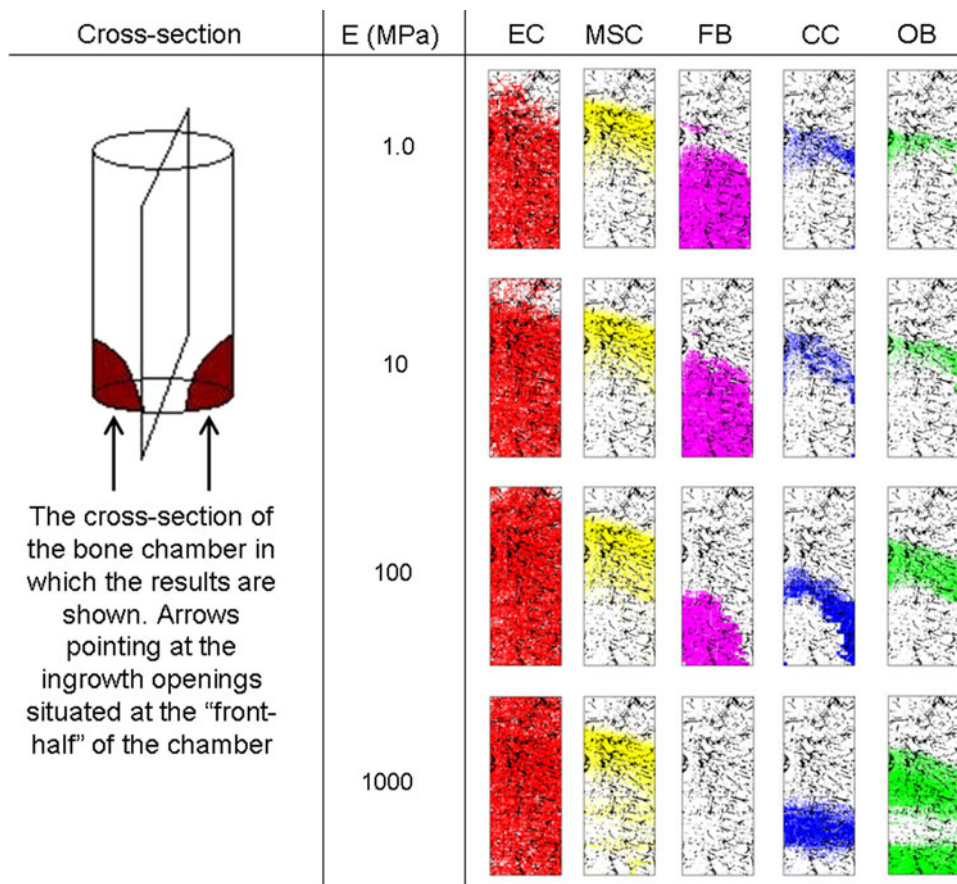

4 Discussion

This study shows that the lattice modelling approach has the benefit of being able to accurately include the microporous geometries of scaffolds in mechano-biological simulations that have previously been done using smaller mesh size [28]. The lattice points are successful in representing cells and their extracellular matrices as well as scaffold material and the high density of lattice points allows for explicit modelling of scaffold pore configurations that are otherwise difficult to capture in standard FE-models. The results obtained in this study indicate that the large pore size allows cells and blood vessels to easily enter and fill the scaffold and to supply sufficient nutrients and oxygen. The scaffold construct is very porous and only 10% of the chamber is filled with scaffold material. The simulations show that increasing scaffold mechanical stiffness from 1 to 1,000 kPa does not have a significant effect on the tissue differentiation outcome after 9 weeks whereas a higher mechanical stiffness ($E > 1$ MPa) enhances bone differentiation in highly porous constructs. This suggests a loading-specific scaffold stiffness threshold above which bone regeneration is facilitated.

Simulations of scaffold stiffness being ≥ 10 MPa showed a significant increase of bone and cartilage formation.

A large amount of fibrous tissue was however still predicted at the bottom of the chamber in the vicinity of the ingrowth openings, where the fluid flows and shear strains are high. When implementing $E = 1$ GPa, fibrous tissue was no longer found at the ingrowth openings and only bone and cartilage could be observed in the chamber. A further increase in scaffold stiffness ($E = 2$ GPa) concluded in very low biophysical stimulus and only bone differentiation (results not shown).

Although we have been careful to assign values to parameters consistent with literature [23] it is a limitation of the model that some parameters are difficult to define precisely, such as the permeability of different tissues, maturation age and cell process rates. The scaffold construct was not considered to be degradable which could be essential to the process of tissue differentiation. Moreover, the plastic deformation (buckling) of the scaffold struts was not taken into consideration. This might have a major effect on the cell access to the interior of the scaffold by clogging the openings. Although the simulations are non-deterministic in that they adopt stochastic modelling of cell processes, a previous study has shown that this cannot capture the inter-specimen variability found in experiments of the bone chamber [11]. Hence it must be noted that the simulations performed in this study are expected to be

subjected to a larger variability in an in vivo animal population.

Despite the above limitations, model predictions were able to capture the effect of scaffold stiffness on tissue differentiation patterns which corroborate with experimental observations [29, 30]. In contrast to previous models, this framework adopts not only a mechanistic approach but also considers the effect of angiogenesis on tissue differentiation patterns in a well controlled environment. It simulates an already existing in vivo experiment that has been successful in showing the significant effect of mechanical loading on the tissue differentiation process.

We conclude that our hypothesis is confirmed; that the lattice modelling approach is suitable for studies of tissue differentiation inside scaffolds, as this technique was not only able to represent cellular processes explicitly but captured also the complex micro-porous geometry of the scaffold. With the lattice model a smaller mesh size is not necessary for capturing the porous configuration of a scaffold which in turn reduces computational time and problems related to the meshing of the scaffold. The result of this study reaffirms the importance of the design of tissue engineering scaffolds and suggests a threshold for scaffold stiffness above which osteogenesis is enhanced. The successful implementation of the lattice model, for representing complex scaffold pore geometries, advances a novel approach for tissue engineering scaffolds, specifically for computational investigations of the relationship between scaffold pore geometries and mechano-regulation.

Acknowledgments The authors would like to acknowledge Amir Al-Munajjed for assisting with the acquisition of micro-CT images of the scaffold used in this study. This project was funded by Science Foundation Ireland Principal Investigator Award.

References

- Muschler GF, Nakamoto C, Griffith LG. Engineering principles of clinical cell-based tissue engineering. *J Bone Joint Surg Am*. 2004;86:1541–58.
- Lacroix D, Planell JA, Prendergast PJ. Computer-aided design and finite-element modeling of biomaterial scaffold for bone tissue engineering. *Philos Trans R Soc A*. 2009;367:1993–2009.
- Jaasma MJ, Plunket NA, O'Brien FJ. Design and validation of a dynamic flow perfusion bioreactor for use with compliant tissue engineering scaffolds. *J Biotechnol*. 2008;133:490–6.
- Pauwels F. A new theory on the influence of mechanical stimuli on the differentiation of supporting tissue. The tenth contribution to the functional anatomy and causal morphology of the supporting structure. *Z Anat Entwickl Gesch*. 1960;121:478–515.
- Carter D, Blenman P, Beaupré G. Correlations between mechanical stress history and tissue differentiation in initial fracture healing. *J Orthop Res*. 1988;6:736–48.
- Claes L, Heigele C. Magnitudes of local stress and strain along bony surfaces predicts the course and type of fracture healing. *J Biomech*. 1999;32:255–66.
- Prendergast PJ, Huiskes R, Søballe K. Biophysical stimuli on cells during tissue differentiation at implant interfaces. *J Biomech*. 1997;30:539–48.
- Isaksson H, van Donkelaar C, Huiskes R, Ito K. Corroboration of mechanoregulatory algorithms for tissue differentiation during fracture healing: comparison with in vivo results. *J Orthop Res*. 2006;24:898–907.
- Hayward LNM, Morgan EF. Assessment of a mechano-regulation theory of skeletal tissue differentiation in an in vivo model of mechanically induced cartilage formation. *Biomech Model Mechanobiol*. 2009. doi:10.1007/s10237-009-0148-3.
- Geris L, Vandamme K, Naert I, Vander Sloten J, Duyck J, Van Oosterwyck H. Application of mechanoregulatory models to simulate peri-implant tissue formation in an in vivo bone chamber. *J Biomech*. 2008;41:145–54.
- Khayyeri H, Checa S, Tägil M, Prendergast PJ. Corroboration of mechanobiological simulations of tissue differentiation in an in vivo bone chamber using a lattice-modeling approach. *J Orthop Res*. 2009;27:1659–66.
- Checa S, Prendergast PJ. A mechanobiological model for tissue differentiation that includes angiogenesis: a lattice-based modeling approach. *Ann Biomed Eng*. 2009;37:129–45.
- Byrne DP, Lacroix D, Planell JA, Kelly DJ, Prendergast PJ. Simulation of tissue differentiation in a scaffold as a function of porosity, Young's modulus and dissolution rate: application of mechanobiological models in tissue engineering. *Biomaterials*. 2007;28:5544–54.
- Checa S, Prendergast PJ. Effect of cell seeding and mechanical loading on vascularization and tissue formation inside a scaffold: a mechano-biological model using a lattice approach to simulate cell activity. *J Biomech*. 2009. doi:10.1016/j.jbiomech.2009.10.044.
- Tägil M, Aspenberg P. Cartilage induction by controlled mechanical stimulation in vivo. *J Orthop Res*. 1999;17:200–4.
- Pérez MA, Prendergast PJ. Random-walk models of cell dispersal included in mechanobiological simulations of tissue differentiation. *J Biomech*. 2007;40:2244–53.
- O'Brien FJ, Harley BA, Yannas IV, Gibson LJ. The effect of pore size on cell adhesion in collagen-GAG scaffolds. *Biomaterials*. 2005;26:433–41.
- Byrne EM, Farrell E, McMahon LA, Haugh MG, O'Brien FJ, Campbell VA, et al. Gene expression by marrow stromal cells in a porous collagen-glycosaminoglycan scaffold is affected by pore size and mechanical stimulation. *J Mater Sci: Mater Med*. 2008;19:3455–63.
- Tierney CM, Haugh MG, Liedl J, Mulcahy F, Hayes B, O'Brien FJ. The effect of collagen concentration and crosslink density on the biological, structural and mechanical properties of collagen-GAG scaffolds for bone tissue engineering. *J Mech Behav Biomed Mater*. 2009;2:202–9.
- Farrell E, O'Brien FJ, Doyle P, Fischer J, Yannas I, Harley BA, et al. A collagen-glycosaminoglycan scaffold supports adult rat mesenchymal stem cell differentiation along osteogenic and chondrogenic routes. *Tissue Eng*. 2006;12:459–68.
- McMahon LA, Reid AJ, Campbell VA, Prendergast PJ. Regulatory effects of mechanical strain on the chondrogenic differentiation of MSCs in a collagen-GAG scaffold: experimental and computational analysis. *Ann Biomed Eng*. 2008;36:185–94.
- Byrne DP, Prendergast PJ, Kelly DJ. Optimisation of scaffold porosity using a stochastic model for cell proliferation and migration in mechanobiological simulations. *J Biomech*. 2006;39:S413–4.
- Isaksson H, van Donkelaar C, Huiskes R, Ito K. A mechano-regulatory bone-healing model incorporating cell-phenotype specific activity. *J Theor Biol*. 2008;252:230–46.

24. Huiskes R, van Driel WD, Prendergast PJ, Sballo K. A biomechanical regulatory model for peri-prosthetic fibrous tissue differentiation. *J Mater Sci Mater Med*. 1997;8:785–8.
25. Harley BA, Leung JH, Silvia ECCM, Gibson LJ. Mechanical characterization of collagen-glycosaminoglycan scaffolds. *Acta Biomater*. 2007;3:463–74.
26. Lacroix D, Chateau A, Ginebra M, Planell JA. Micro-finite element models of bone tissue-engineering scaffolds. *Biomaterials*. 2006;27:5326–34.
27. Charriere E, Lemaitre J, Zysset P. Hydroxyapatite cement scaffolds with controlled macroporosity: fabrication protocol and mechanical properties. *Biomaterials*. 2003;24:809–17.
28. Sandino C, Planell JA, Lacroix D. A finite element study of mechanical stimuli in scaffolds for bone tissue engineering. *J Biomech*. 2008;41:1005–14.
29. Engler AJ, Sen S, Sweeney HL, Discher DE. Matrix elasticity directs stem cell lineage specification. *Cell*. 2006;126:677–89.
30. Erickson IE, Huang AH, Chung C, Li RT, Burdick JA, Mauck RL. Differential maturation and structure-function relationships in MSC- and chondrocyte-seeded hydrogels. *Tissue Eng Part A*. 2009;15:1041–52.