



ELSEVIER

Journal of Molecular Catalysis A: Chemical 107 (1996) 399–403

JOURNAL OF
MOLECULAR
CATALYSIS
A: CHEMICAL

The photocatalytic decomposition of nitric oxide on $\text{Ag}^+/\text{ZSM-5}$ catalyst prepared by ion-exchange

Masaya Matsuoka, Emi Matsuda, Kouji Tsuji, Hiromi Yamashita, Masakazu Anpo *

Department of Applied Chemistry, University of Osaka Prefecture, 1-1 Gakuen-cho, Sakai, Osaka 593, Japan

Abstract

Over $\text{Ag}^+/\text{ZSM-5}$ catalyst prepared by an ion-exchange the photocatalytic decomposition of NO into N_2 , N_2O , and NO_2 was affected by UV irradiation at a low temperature of 298 K. In situ X-ray absorption near edge structure (XANES), ESR, photoluminescence, and diffuse reflectance (DR) spectroscopy were applied to examine the $\text{Ag}^+/\text{ZSM-5}$ catalyst. The wavelengths of the effective UV irradiation was determined. Data suggest that electron transfer from excited Ag^+ ion into the π anti-bonding molecular orbital of NO molecule plays a significant role in the photocatalytic decomposition of NO.

Keywords: Photocatalysis; Nitric oxide; Decomposition; Silver; Zeolite

1. Introduction

Ion-exchanged copper/zeolite catalysts have attracted a great deal of attention as potential catalysts for the direct decomposition of NO into N_2 and O_2 [1]. We have reported that Cu^{2+} ions introduced into zeolites by an ion-exchange or doped in SiO_2 using the sol-gel method are easily and selectively reduced to Cu^+ ions on evacuation at temperatures higher than 573 K. UV irradiation of the thus formed $\text{Cu}^+/\text{zeolites}$ [2] or Cu^+/SiO_2 catalysts [3,4] in the presence of NO effects the photocatalytic decomposition of NO into N_2 and O_2 even at 275 K. Results of ESR, IR, and photoluminescence studies suggested that the excited state of the Cu^+ ion produced by UV irradiation ($3d^{10} \rightarrow 3d^9 4s^1$) plays a significant role in the reaction.

Ion-exchanged silver/zeolite catalysts have been reported to show very high activity for the disproportionation of ethylbenzene [5,6], photo-chemical/thermal cleavage of water to H_2 and O_2 [7], photo-oxygen production from water [8], photo-dimerization of alkanes [9], and the selective reduction of NO by ethylene at around 823 K [10] or by ethanol at around 723 K [11]. The present work shows that $\text{Ag}^+/\text{ZSM-5}$ catalyst is of remarkably high photocatalytic activity in the decomposition of NO compared with photocatalysts containing Cu^+ ions reported in our recent papers [2–4].

2. Experimental

ZSM-5 zeolite ($\text{SiO}_2:\text{Al}_2\text{O}_3$ mole ratio = 23.3:1.0) supplied by the TOSOH corporation was used. The $\text{Ag}^+/\text{ZSM-5}$ zeolite catalyst was prepared by ion exchange with an aqueous

* Corresponding author.

$\text{Ag}(\text{NH}_3)_2^+$ solution. After the ion exchange, the sample was washed with distilled water and dried in air at 373 K. Silver loading was determined as 6.9 wt% metal by an atomic absorption spectrometer. Prior to spectroscopic and photocatalytic measurements samples were degassed at 298 K for 1 h, calcined at 673 K in the presence of 20 Torr of O_2 for 1 h, then degassed at 473 K for 1 h. The $\text{Ag}^0/\text{ZSM-5}$ catalyst was prepared by heating the $\text{Ag}^+/\text{ZSM-5}$ in the presence of an $\text{H}_2/\text{H}_2\text{O}$ mixture at a total pressure of 20 Torr ($\text{H}_2/\text{H}_2\text{O} = 1$). Photocatalytic reactions were carried out at 298 K using a high pressure mercury lamp and water filter. An UV-cut filter ($\lambda > 250$ nm) was used to examine the effect of the irradiation wavelength upon the reaction. The reaction products were analyzed by gas chromatography and mass spectrometry. XANES spectra were obtained at the BL-10B facility of the Photon Factory at the National Laboratory for High-Energy Physics, Tsukuba. Si(311) channel-cut crystal was used to monochromatize the X-rays from the 2.5 GeV electron storage ring. The Ag K-edge absorption spectra were recorded in the transmission mode at 298 K. The ESR spectra were recorded at 77 K using a JES-RE2X spectrometer operating in the X-band mode. The photoluminescence spectra were recorded with a Shimadzu RF-5000 spectrofluorophotometer at 77 K. DR spectra were recorded with a Shimadzu UV-2200A spectrometer at 298 K.

3. Results and discussion

UV irradiation of the $\text{Ag}^+/\text{ZSM-5}$ catalyst in the presence of 10 Torr of NO at 298 K was found to lead to the formation of N_2 , N_2O and NO_2 . The reaction profiles of the formation of N_2 and N_2O are shown in Fig. 1. Formation of N_2 and N_2O is found only under UV irradiation and the yield of these products increases with a good linearity against the irradiation time, suggesting that the reaction proceeds photocatalytically. On the $\text{Ag}^0/\text{ZSM-5}$ and $\text{H}^+/\text{ZSM-5}$ cat-

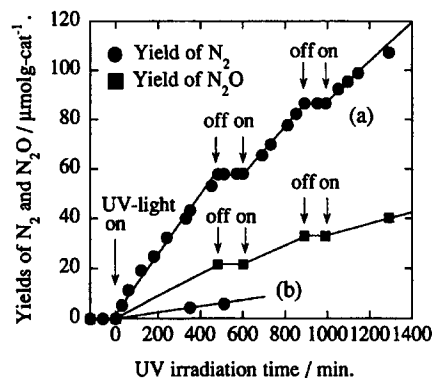


Fig. 1. The time profiles of the photocatalytic decomposition reaction of NO into N_2 and N_2O on the $\text{Ag}^+/\text{ZSM-5}$ catalyst (a) and $\text{Cu}^+/\text{ZSM-5}$ catalyst (b) at 298 K.

alysts formation of a minor amount of N_2 and N_2O was observed, but it was small and negligible compared to the yield of the reaction above UV irradiated $\text{Ag}^+/\text{ZSM-5}$ catalysts. These results clearly indicate that the Ag^+ ions of the catalyst play a significant role in the photocatalytic decomposition of NO.

As also shown in Fig. 1, the rate of N_2 formation on the $\text{Ag}^+/\text{ZSM-5}$ catalyst is 10 times faster than on the $\text{Cu}^+/\text{ZSM-5}$ catalyst [2], indicating that the photocatalytic decomposition of NO proceeds faster on the Ag^+ ions than on the Cu^+ ions. As for reaction products, N_2 , N_2O , and NO_2 were produced, suggesting that the decomposition of NO on the $\text{Ag}^+/\text{ZSM-5}$ catalyst proceeds in a different way from the reaction of NO on the $\text{Cu}^+/\text{ZSM-5}$ catalyst to produce N_2 and O_2 . (NO_2 was also produced on the $\text{Cu}^+/\text{ZSM-5}$ under the higher pressure of NO by the gas phase reaction of NO with O_2 .) Under UV-irradiation of the catalyst through the UV-25 filter ($\lambda > 250$ nm), the photocatalytic decomposition of NO proceeded at 15% of the rate without the UV-cut filter, i.e., with the full arc of the high pressure mercury lamp. This indicates that the UV-light effective for NO decomposition lies in the wavelength regions of 200 nm to 250 nm.

Fig. 2 shows the XANES spectra of the $\text{Ag}^+/\text{ZSM-5}$ catalyst (a), Ag foil (b), and bulk Ag_2O (c), respectively. As shown in Fig. 2, the

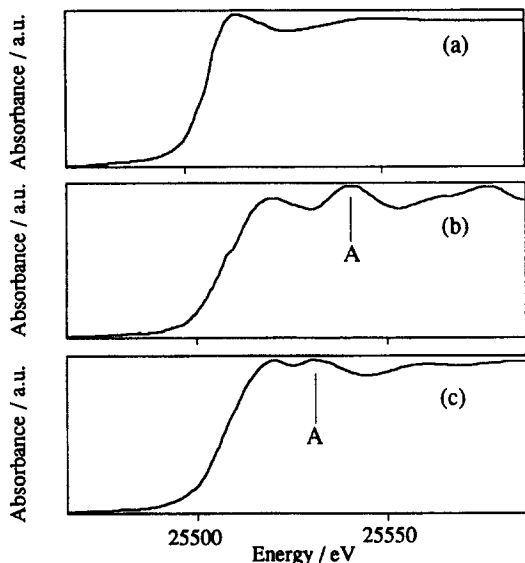


Fig. 2. The XANES spectra of the Ag^+ /ZSM-5 catalyst (a), Ag foil (b), and Ag_2O powder (c).

XANES spectra of the Ag foil and bulk Ag_2O exhibit several well-defined bands due to multiple scattering (A) at around 25530 eV and other bands arising from continuum resonances involving a multiple scattering effect in the region above 25550 eV, while the XANES spectrum of the Ag^+ /ZSM-5 catalyst scarcely exhibits any remarkable bands due to this effect. This implies that silver ions are anchored within the micropores of the ZSM-5 zeolite in a highly dispersed state forming neither clusters nor Ag metal or oxide crystals.

Fig. 3(a), (b), (c) shows the diffuse reflectance spectra of the Ag^+ /ZSM-5 (a), H^+ /ZSM-5 (b), and Ag^0 /ZSM-5 catalyst (c), respectively. The H^+ /ZSM-5 exhibits no intense absorption band in the 200–250 nm wavelength range. On the other hand, as shown in Fig. 3(a), the Ag^+ /ZSM-5 catalyst exhibits an intense absorption band at around 220 nm which is attributed to the $4d^{10} \rightarrow 4d^9 5s^1$ electronic transition of the Ag^+ ions [12–14]. The Ag^0 atoms, and Ag_n^0 and Ag_m^{n+} clusters are known to exhibit absorption bands at wavelength above 250 nm [15,16]. However, no absorption band of the Ag^+ /ZSM-5 appears in this region. Fur-

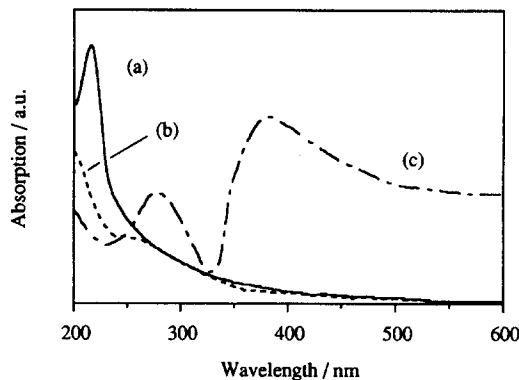


Fig. 3. The DR spectra of the Ag^+ /ZSM-5 catalyst (a), H^+ /ZSM-5 (b), and Ag^0 /ZSM-5 catalyst (c).

thermore, no EPR signals assigned to the Ag^0 atoms or Ag^{2+} species were observed with the Ag^+ /ZSM-5 catalyst. These results firmly support the conclusion that silver ions are included within the pore structure of the ZSM-5 zeolite as highly dispersed Ag^+ ions.

As shown in Fig. 3(c), after H_2 treatment of the Ag^+ /ZSM-5 catalyst, the intensity of the absorption band of Ag^+ ions at about 220 nm drastically decreases and broad absorption bands of Ag_n^0 or Ag_m^{n+} clusters appear above 250 nm, indicating that reduction and aggregation of the Ag^+ ions has occurred. Since Ag^0 /ZSM-5 did not show any photocatalytic activity for the decomposition of NO, it is concluded that the Ag_n^0 or Ag_m^{n+} clusters can not be associated with the reaction.

Fig. 4 shows the ESR signal obtained after the addition of 7 Torr of NO onto the

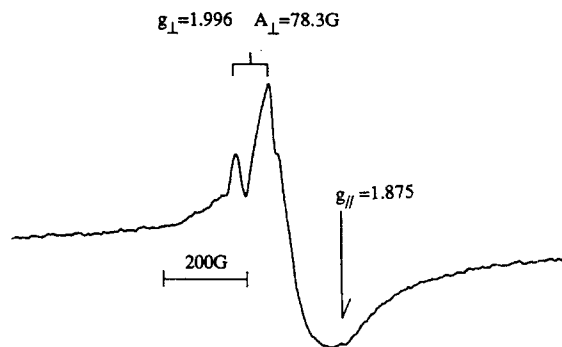


Fig. 4. The ESR signal obtained after the addition of 7 Torr of NO onto the Ag^+ /ZSM-5 catalyst at 77 K.

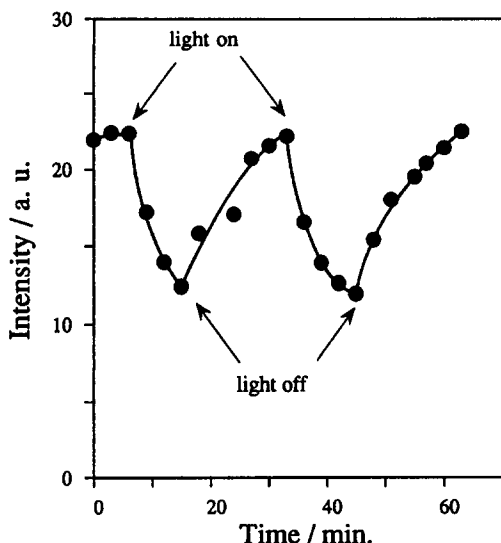


Fig. 5. The time profile of the intensity of the ESR signal due to $(\text{Ag-NO})^+$ species under UV irradiation.

$\text{Ag}^+/\text{ZSM-5}$ catalyst at 77 K. The hyperfine splitting of the signal shows that the electron spin interacts with a nucleus of Ag^+ ($I = 1/2$) suggesting that the NO molecules are adsorbed on the Ag^+ to form a nitrosylic adduct, i.e., $(\text{Ag-NO})^+$ [17]. The evacuation of the system led to the disappearance of the signal suggesting that the interaction of NO with the Ag^+ ion is weak. On evacuation no new EPR signal appeared indicating that the oxidation of Ag^+ to Ag^{2+} by the addition of NO at high pressures (> 1 Torr) did not occur.

Fig. 5 shows the effect of UV irradiation upon the intensity of the ESR signal under the same condition shown in Fig. 4. UV irradiation of the $\text{Ag}^+/\text{ZSM-5}$ catalyst having the $(\text{Ag-NO})^+$ species led to a decrease in the intensity of the ESR signal assigned to the $(\text{Ag-NO})^+$ species with UV irradiation time without the appearance of any new signal. After UV irradiation was stopped, the intensity of the signal returned to its original level. These reversible changes in the ESR signal assigned to the $(\text{Ag-NO})^+$ suggest not only that the $(\text{Ag-NO})^+$ species act as reaction precursors but also that the photo-induced decomposition of NO molecules proceeds catalytically.

Fig. 6 shows the photoluminescence spectrum (a) and its corresponding excitation spectrum (b) of the $\text{Ag}^+/\text{ZSM-5}$ catalyst. The excitation band at around 220 nm shows a good coincidence with absorption band which is attributed to the electronic transition $4d^{10} \rightarrow 4d^9 5s^1$ of Ag^+ ion on the $\text{Ag}^+/\text{ZSM-5}$ catalyst. Therefore, the excitation band at around 220 nm and photoluminescence band at around 340 nm can be attributed to the presence of the Ag^+ ion, i.e., to the excitation $4d^{10} \rightarrow 4d^9 5s^1$ and its reverse radiative deactivation $4d^9 5s^1 \rightarrow 4d^{10}$, respectively. Fig. 6 also shows the effect of the addition of NO on the photoluminescence of the $\text{Ag}^+/\text{ZSM-5}$ catalyst. The addition of NO onto the $\text{Ag}^+/\text{ZSM-5}$ catalyst leads to the efficient quenching of the photoluminescence due to the Ag^+ ion. As shown in Fig. 6(a), after the complete quenching the evacuation of the system leads to recovery of the photoluminescence to its original intensity. These results clearly suggest that the interaction of the NO molecule with the Ag^+ ion is weak, and that added NO molecules easily interact with Ag^+ species in ground and also in excited states. The photoluminescence of the $\text{Ag}^+/\text{ZSM-5}$ catalyst was more easily quenched by the added NO than

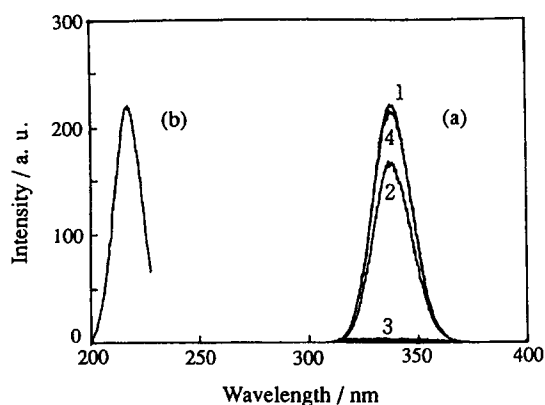


Fig. 6. The observed ordinary photoluminescence spectra (a) and its excitation spectrum (b) of the $\text{Ag}^+/\text{ZSM-5}$ catalyst, and the effect of the addition of NO on the photoluminescence. The addition of NO was carried out at 298 K. NO pressure (in Torr): 1, 0.0; 2, 0.2; 3, 4.0; 4, after the degassing of NO at 298 K. The excitation spectra were monitored at 342 nm emission.

that of the $\text{Cu}^+/\text{ZSM-5}$ catalyst suggesting that in photo-excited states Ag^+ ions interact with NO molecules more efficiently than Cu^+ ions.

The most effective wavelengths of UV light for the photocatalytic decomposition of NO (200–250 nm) was found to lie in the same wavelength region as the absorption band and excitation band of the $\text{Ag}^+/\text{ZSM-5}$ attributed to the presence of the Ag^+ ions (220 nm). $\text{Ag}^+/\text{ZSM-5}$ catalyst degassed at ambient temperature after UV-irradiation for a long period in the presence of 10 Torr of NO did not show any new absorption spectra which could have been attributed to the Ag^0 atoms, Ag_n^0 or Ag_m^{n+} clusters as well as any EPR spectra due to the Ag^{2+} ions. These results clearly indicate that the decomposition of NO molecules proceeds photocatalytically on the Ag^+ ions.

Furthermore, the EPR measurements indicated that the addition of O_2 or NO at high pressures (> 1 Torr) did not lead to the oxidation of Ag^+ to Ag^{2+} in the $\text{Ag}^+/\text{ZSM-5}$ catalyst in clear contrast to the easy oxidation of Cu^+ to Cu^{2+} in the $\text{Cu}^+/\text{ZSM-5}$ catalyst [18]. Since Ag^+ ions are chemically stable even in an oxidative atmosphere, the $\text{Ag}^+/\text{ZSM-5}$ catalyst is a potential photocatalyst for the direct decomposition of NO at ambient temperatures. Another advantage is that $\text{Ag}^+/\text{ZSM-5}$ needs lower-temperature pretreatment (473 K) than $\text{Cu}^{2+}/\text{ZSM-5}$ which requires evacuation at temperatures higher than 973 K in order to produce Cu^+ ions as active species.

From these various findings it was concluded that the photo-excited electronic state of highly dispersed Ag^+ ions ($4d^95s^1$) plays a significant role in the photocatalytic decomposition of NO while an electron transfer from the photo-excited Ag^+ into the π anti-bonding molecular orbital of NO leads to the weakening of the N–O bond and initiates the decomposition of the NO molecule. The remarkably high photo-

catalytic reactivity of the $\text{Ag}^+/\text{ZSM-5}$ catalyst can be attributed to the high chemical stability of the Ag^+ ion and the efficient interaction of the excited electronic state of the Ag^+ ion with NO molecules as compared with those properties of the Cu^+ ion on the $\text{Cu}^+/\text{ZSM-5}$ catalyst. The study of the excited electronic state of the Ag^+ ion on the $\text{Ag}^+/\text{ZSM-5}$ catalyst as well as a detailed study of the mechanisms behind the photocatalytic decomposition of NO will be the subject of our future work.

References

- [1] M. Iwamoto, H. Yahiro, K. Tanda, N. Mizuno, Y. Mine and S. Kagawa, *J. Phys. Chem.*, 95 (1991) 3727.
- [2] M. Anpo, M. Matsuoka, Y. Shioya, H. Yamashita, E. Giamello, C. Morterra, M. Che, H.H. Patterson, S. Webber, S. Ouellette and M.A. Fox, *J. Phys. Chem.*, 98 (1994) 5744.
- [3] M. Anpo, T. Nomura, T. Kitao, E. Giamello, D. Murphy, M. Che and M.A. Fox, *Res. Chem. Intermed.*, 15 (1991) 225.
- [4] N. Negishi, M. Matsuoka, H. Yamashita and M. Anpo, *J. Phys. Chem.*, 97 (1993) 5211.
- [5] T. Baba and Y. Ono, *Zeolites*, 7 (1987) 292.
- [6] Y. Ono, T. Baba, K. Kanae and S.G. Seo, *J. Chem. Soc. Jpn.*, 7 (1988) 985.
- [7] P.A. Jacobs, J.B. Uytterhoeven and H.K. Beyer, *J. Chem. Soc., Chem. Commun.*, (1977) 128.
- [8] G. Calzaferri, S. Hug, T. Hugentobler and B. Sulzberger, *J. Photochem.*, 26 (1984) 109.
- [9] G.A. Ozin and F. Hugues, *J. Phys. Chem.*, 86 (1982) 5174.
- [10] S. Sato, Y. Yu-u, H. Yahiro, N. Mizuno and M. Iwamoto, *Appl. Catal.*, 70 (1991) L1.
- [11] T. Miyadera, A. Abe, G. Muramatsu and K. Yoshida, *Proc. Symp. Environ. Conscious Mater.*, 3rd IUMRS Intern. Conf. on Adv. Mater., Tokyo, 1993, p. 405.
- [12] C.E. Moore, *Atomic Energy Levels*, Vol. 3, National Bureau of Standards, Washington, DC, 1971, pp. 48–54.
- [13] A.N. Truklin, S.S. Etsin and A.V. Shendrik, *Izv. Akad. Nauk. SSSR, Ser. Fiz.*, 40 (1976) 2329.
- [14] J. Texter, R. Kellerman and T. Gonsiorwski, *J. Phys. Chem.*, 90 (1986) 2118.
- [15] G.A. Ozin and H. Huber, *Inorg. Chem.*, 17 (1978) 155.
- [16] G.A. Ozin, F. Hugues, S.M. Matter and D.F. McIntosh, *J. Phys. Chem.*, 87 (1983) 3445.
- [17] C. Chao and J.H. Lunsford, *J. Phys. Chem.*, 78 (1974) 1174.
- [18] E. Giamello, D. Murphy, G. Magnacca, C. Morterra, Y. Shioya, T. Nomura and M. Anpo, *J. Catal.*, 136 (1992) 510.