

Synthesis of *endo,exo*-1,2,3,4,11,11-Hexachlorotricyclo[6.2.1.0^{5,10}]undec-2-en-7,8-dicarboxylic acid *N*-(2,4,6-Tribromophenyl)imide

M. S. Salakhov, B. T. Bagmanov, V. S. Umaeva, and M. I. Bagmanova

Institute of Polymer Materials, National Academy of Sciences of Azerbaidzhan, Sumgait, Az5004 Azerbaidzhan

Received May 24, 2006. Revised version January 5, 2007

Abstract—A preparation method was developed for *endo,exo*-1,2,3,4,11,11-hexachlorotricyclo-[6.2.1.0^{5,10}]undec-2-ene-7,8-dicarboxylic acid *N*-tribromophenylimide by acylation of 2,4,6-tribromoaniline with this acid anhydride. The structure of imide obtained was proved by IR spectrum, TLC method, and by independent synthesis.

DOI: 10.1134/S1070428007050077

Among the indispensable qualities of the modern polymer materials the low inflammability and self-extinguishing are known to be required [1, 2] that can be ensured by introducing various modifiers serving as fire-retardants. Nowadays widely spread fire-retardants are nitrogen and halogen containing compounds. An important representative among this type fire-retardants is 2,4,6-tribromoaniline and its derivatives [3].

No published data exist on the application of imides based on 2,4,6-tribromoaniline and on the possibility of its reaction with anhydrides of dicarboxylic acids save [4], where by melting tribromoaniline with maleic anhydride under very stringent conditions (10-fold excess of maleic anhydride, 210°C, catalyst ZnCl₂) has been prepared *N*-(2,4,6-tribromophenyl)maleimide in 20% yield.

The low reactivity of tribromoaniline in acylation [5] is due to its low basicity and to steric hindrances from the *O, O'*-bromine atoms.


We developed synthesis conditions for *N*-(2,4,6-tribromophenyl)imides of cyclic dicarboxylic acids of


tetrahydrophthalic and tricycloundecene series. Acylation of 2,4,6-tribromoaniline (**I**) with anhydrides of *cis*-4-cyclohexene-1,2-dicarboxylic acid (**II**) and *endo,exo*-1,2,3,4,11,11-hexachlorotricyclo[6.2.1.0^{5,10}]undec-2-ene-7,8-dicarboxylic acid (**III**) was performed at equimolar amounts of components, at 180±5°C for 36 h in sealed ampules [6, 7]. Compounds **IV** and **V** were obtained in high yields (~75%).

The increase in the temperature to 190°C at the reaction interval 25 h resulted in decrease in the yield of compounds **IV** and **V** to 65.9 and 60% respectively, and after 36 h the reaction products suffered tarring. At 170°C the yield of compounds **IV** and **V** also reduced to 53 and 50% respectively.

The structure of compounds **IV** and **V** was proved by IR spectroscopy. In the IR spectrum of compound **V** the absorption bands were observed in the region ν 1601, 1603 (C=O), 1778 and 1780 (C=C), 600–650 cm⁻¹ (C–Br).

To prove the *endo,exo*-configuration and to develop a more efficient procedure for preparation of fire-retardant modifier we performed an independent synthesis of

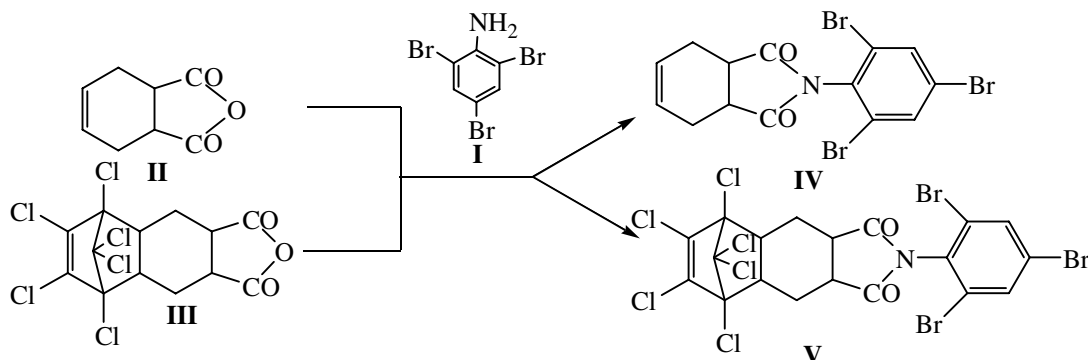

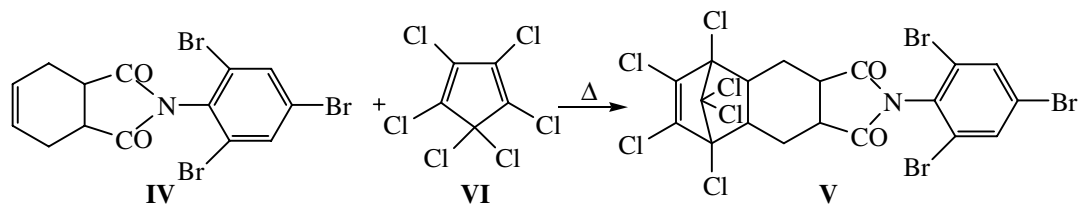

compound **V**. A reaction of *cis*-*N*-2,4,6-tribromophenylimide (**IV**) with hexachlorocyclopentadiene (**VI**) at a molar ratio 2:1 and 140°C resulted within 2 h in 99% yield of *endo,exo*-*N*-(2,4,6-tribromophenyl)imide (**V**).

EXPERIMENTAL

IR spectra of compounds **IV** and **V** were recorded on a spectrophotometer UR-20 from mulls in mineral oil [8].

The purity of compounds was checked by TLC on Silufol plates using as eluent a mixture benzene–dichloroethane–acetic acid, 4:1.5:1 by volume, development under UV irradiation [9]. Molecular weight was measured by cryoscopy in camphor [10]. Initial high-purity 2,4,6-tribromoaniline was prepared by procedure we previously developed, a liquid-phase oxibromination of aniline [11].

Anhydrides of *endo,exo*-1,2,3,4,11,11-hexachlorotricyclo[6.2.1.0^{5,10}]undec-2-ene-7,8-dicarboxylic acid (**III**) and *cis*-4-cyclohexene-1,2-dicarboxylic acid (**II**) were prepared by procedures [12, 13] respectively.

***cis*-4-Cyclohexene-1,2-dicarboxylic acid *N*-(2,4,6-tribromophenyl)imide (**IV**)**. Into an ampule was charged 10 g (0.066 mol) of 2,4,6-tribromoaniline and 22 g (0.06 mol) of anhydride **II**. The ampule was sealed and heated in a temperature-controlled device at 180°C for 36 h. Afterwards the ampule was cooled, opened, the reaction mixture was treated with ether to remove the unreacted 2,4,6-tribromoaniline. The precipitated crystals were filtered off and dried in air. Yield 20.9 g (75%), mp 168°C (from benzene), *R_f* 0.62. IR spectrum, ν , cm⁻¹: 1603 (C=O), 1780 (C=C), 600–650 (C–Br). Found, %: C 36.00; H 2.07; Br 51.2; N 3.0. *M* 462. C₁₄H₁₀Br₃NO₂. Calculated, %: C 36.00; H 2.17; Br 51.72; N 3.01. *M* 464.

***endo,exo*-1,2,3,4,11,11-Hexachlorotricyclo[6.2.1.0^{5,10}]undec-2-ene-7,8-dicarboxylic acid *N*-(2,4,6-tribromophenyl)imide (**V**)**. *a*. Into an ampule was charged 0.1 mol of compound **IV** and 0.2 mol of hexachlorocyclopentadiene (**VI**), and the mixture was heated for 12 h on an oil bath for 140°C. Then the content of the ampule was treated with hot pentane, the precipitated crystals were filtered off. Yield 14.51 g (99.8%), mp 298°C, *R_f* 0.74. Found *M* 735. Calculated *M* 737.

b. In 100 ml of DMF was dissolved 0.1 mol of *N*-2,4,6-tribromoaniline (**I**) and 0.1 mol of compound **III**, and the mixture was heated at reflux for 6 h. Then the mixture was poured at stirring into ice water, the precipitated crystals were filtered off, dried, and recrystallized from hot pentane. Yield 99.9%, mp 298°C. IR spectrum, ν , cm⁻¹: 1601 (C=C), 1778 (C=O), 600–650 (C–Br). Found, %: C 30.1; H 1.41; N 2.03; Hlg 63.80. C₁₉H₁₀Cl₆Br₃NO₂. Calculated, %: C 30.90; H 1.40; N 1.98; Hlg 64.46.

REFERENCES

1. Aseeva, R.M. and, Zaikov G.E., *Snizhenie goryuchesti polimernykh materialov* (Decrease in Burning Quality of Polymers), Moscow: Znaniye, 1981, 64, p.
2. Adrova, N.A., Bessonov, M.K., Laius, L.A., and Rudakov, A.P., *Poliimidy – novyi klass termostoikikh polimerov* (Polyimides: New Class of Heat-Resistant Polymers), Moscow: Nauka, 1968, 200 p.
3. Gaevskii, B.D., Dorofeev, V.T., Matveeva, A.P., and, Rilo, R.P., *Khimiya 2,4,6-tribromanilina* (Chemistry of 2,4,6-Tribromoanilines), VNII Iodobrom, dep. VINITI, no. 962_{khP}-D84.
4. Hrabak, F. and Bouchal, K., ChSSR Inventor's Certificate 171593; *Ref. Zh. Khim.*, 1979, 3N198.
5. Salakhov, M.S., Guseinov, M.M., Salakhova, R.S., and Treivus, E.M., *Azerb. Khim. Zh.*, 1971, no. 2, p. 97.
6. Salakhov, M.S., Mamedova, O.M., Umaeva, V.S., Nagiev, V.A., and Shabanova, D.A., USSR Inventor's Certificate 1218646; *SSSR Byull. Izobr.*, 1986, no. 10, p. 278.
7. Salakhov, M.S., Dzhafarov, A.S., Mamedova, O.M., Musaveva, N.F., Mamedov, N.T., Nagiev, V.A., USSR Inventor's Certificate 1311205; *SSSR Byull. Izobr.*, 1987, no. 18, p. 259.
8. Cross, A.D., *An Introduction to Practical Infra-red Spectroscopy*, London: Butterworths, 1960.
9. Akhrem, A.A. and Kuznetsova, A.I., *Tonkosloinaya khromatografiya* (Thin-Layer Chromatography), Moscow: Nauka, 1965, 75 p.
10. Nekrasov, V.V., *Rukovodstvo k malomu praktikumu po organicheskii khimii* (Handbook to Workshop on Organic Chemistry), Moscow: Khimiya, 1964, p. 66.
11. Salakhov, M.S., Nagiev, V.A., Mamedova, O.M., Umaeva, V.S., and Bagmanov, B.T., USSR Inventor's Certificate 1398346; *SSSR Byull. Izobr.*, 1986, no. 15.
12. Salakhov, M.S., Treivus, E.M., Umaeva, V.S., USSR Inventor's Certificate 722069, *SSSR Byull. Izobr.*, 1980, no. 10.
13. Nazarov, I.N. and Kucherov, V.F., *Izv. Akad. Nauk SSSR*, 1954, p. 329.