

## Crystalline structure and the superconducting properties of $\text{NbB}_{2+x}$

This article has been downloaded from IOPscience. Please scroll down to see the full text article.

2004 J. Phys.: Condens. Matter 16 5979

(<http://iopscience.iop.org/0953-8984/16/32/029>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 129.252.86.83

The article was downloaded on 27/05/2010 at 16:42

Please note that [terms and conditions apply](#).

# Crystalline structure and the superconducting properties of $\text{NbB}_{2+x}$

R Escamilla<sup>1</sup>, O Lovera<sup>1</sup>, T Akachi<sup>1</sup>, A Durán<sup>2</sup>, R Falconi<sup>1</sup>, F Morales<sup>1</sup>  
and R Escudero<sup>1</sup>

<sup>1</sup> Instituto de Investigaciones en Materiales, Universidad Nacional Autónoma de México,  
Apartado Postal 70-360, México DF, 04510, Mexico

<sup>2</sup> Centro de Ciencias de la Materia Condensada, Universidad Nacional Autónoma de México,  
Apartado Postal 2681, Ensenada BC, 22800, Mexico

Received 13 April 2004

Published 30 July 2004

Online at [stacks.iop.org/JPhysCM/16/5979](http://stacks.iop.org/JPhysCM/16/5979)

doi:10.1088/0953-8984/16/32/029

## Abstract

The effect of boron excess in the structure and superconducting properties of  $\text{NbB}_2$  is reported. Rietveld refinements of the x-ray diffraction patterns indicate that boron excess induces significant changes in the Nb–B bond length, increasing the *c*-axis. In contrast, the B–B bond length remains essentially constant. Magnetization behaviour was studied in the temperature range from 2 to 15 K. We found that for  $(\text{B/Nb})_{\text{exp}} \geq 2.20(2)$  of boron excess samples display superconductivity with a maximum  $T_C$  of about 9.8 K at  $(\text{B/Nb})_{\text{exp}} = 2.34(1)$ . High pressure measurements in samples with two different boron contents reveal that  $T_C$  decreases at different ratios,  $dT_C/dP$ . Superconducting parameters were determined, indicating that  $\text{NbB}_{2+x}$  is a type II superconductor. We correlated the change of  $T_C$  with the evolution of the structural parameters and found that it coincides with theoretical predictions of band structure.

(Some figures in this article are in colour only in the electronic version)

## 1. Introduction

The discovery of superconductivity in  $\text{MgB}_2$  at about 40 K by Nagamatsu *et al* [1] has generated a great deal of excitement, and many studies related to fundamental and practical aspects of the material have been performed. Much research has investigated other diborides expecting to find higher transition temperatures, but without success.  $\text{NbB}_2$  is a diboride which has been studied recently; this compound is interesting because of its similar behaviour to  $\text{MgB}_2$ . This fact has conduced us to study the superconducting and crystallographic characteristics when B excess is introduced; in this work we will analyse its general behaviour.

Before describing details of the compound under study, such as the crystalline and superconducting characteristics of  $\text{Nb}_{1+x}\text{B}_2$ , it will be necessary to introduce details of  $\text{MgB}_2$  related to defects in the structure, and their influence on the superconducting properties. Actually this is a matter of debate, due to the inherent difficulties in synthesis and to the exact details of the crystalline structure. The stoichiometry of this compound can slightly be modified [2], mainly due to the high ionicity of the Mg–B bond. Theoretical studies related to band structure [3] clearly reveal that while the B–B bond is covalent the Mg–B bond is highly ionic [4]. From the experimental and theoretical points of view, it is known that the high transition temperature in  $\text{MgB}_2$  is essentially related to the large value of the electron–phonon coupling constant,  $\lambda$ , and to the participation of the high phonon frequency: the  $E_{2g}$  vibrational mode.

Earlier experiments showed that for other  $\text{MB}_2$  diborides ( $M = \text{Ti, Zr, Hf, V, Nb, Ta, Cr, Mo}$ )  $T_C$  is below 0.4 K [5]. Nevertheless, only  $\text{NbB}_2$  has shown moderate superconducting transition temperature depending on the preparation route [6–12]. Studies for stoichiometric  $\text{NbB}_2$  reveal a  $T_C$  of about 5.2 K [13], whereas other studies reported the absence of superconductivity down to 2 K [5]. However, metal-deficient  $\text{Nb}_{1-x}\text{B}_2$  has shown a transition temperature at about 9.2 K when it was prepared under high pressure conditions [12]. Also it has been found by Schirber *et al* [10] that a  $\text{NbB}_x$  single crystal with  $x$  near 2 shows a maximum  $T_C = 9.4$  K, when measured under high pressure conditions of about 5 kbar.


Theoretical studies related to band structure of  $\text{NbB}_2$  by Shein and Ivanovskii [3] show an enhancement of the covalent interactions between boron and Nb planes (due to hybridization of the B  $2p$ –Nb  $d$  states), which in turn changes the density of states at the Fermi level  $N(E_F)$ ; this fact must also be valid for the non-stoichiometric  $\text{NbB}_{2+x}$  compound. Then,  $N(E_F)$  will change with the atomic ratio B/Nb, giving a peak in the density of states at the Fermi level,  $T_C$  thus reaching a maximum value [3]. In this context it will be interesting to probe theoretical predictions by performing systematic experimental studies in non-stoichiometric  $\text{NbB}_2$ , in order to understand the role of excess boron in structural and superconducting properties of the compound. In this work we will show the importance of defects in the electronic properties of  $\text{NbB}_2$ .

We report that in  $\text{NbB}_{2+x}$ , careful synthesizing procedures allow us to increase the transition temperature to about 9.8 K, for  $(\text{B/Nb})_{\text{exp}}$  in the range 2.32(1)–2.34(1). We analyse the changes of the lattice parameters due to boron excess, and the superconducting state. Additionally we compared this behaviour with our high pressure experiments performed using a diamond anvil cell.

## 2. Experimental details

$\text{NbB}_{2+x}$  samples were prepared at different boron contents, from  $\text{B/Nb} = 2.0$  to 2.6, by solid-state reaction ( $\text{B/Nb}$  means the starting B excess in the sintering reaction). Precursors from Aldrich were  $\text{NbB}_2$ , 325 mesh, and boron 99.5% < 60 mesh. Both were mixed and pressed into pellets with different compositions, placed in sealed stainless steel tubes under Ar atmosphere, and sintered in a tube furnace at 1000 °C; after 3 h they were quenched to room temperature. The process was repeated after grinding the sintered material. Phase identification was performed with an x-ray diffractometer (XRD) Siemens D5000 using  $\text{Cu K}\alpha$  radiation and a Ni filter. Intensities were measured in small steps of 0.02°, from 10° to 120° at room temperature. Crystallographic parameters were refined with the program Quanto (Rietveld program for quantitative phase analysis of polycrystalline samples) [14].

Magnetization measurements were performed in a SQUID based magnetometer (Quantum Design) at zero field cooling (ZFC) and field cooling (FC) conditions, under 5 Oe magnetic field. Resistance versus temperature ( $R$ – $T$ ) measurements were performed at different

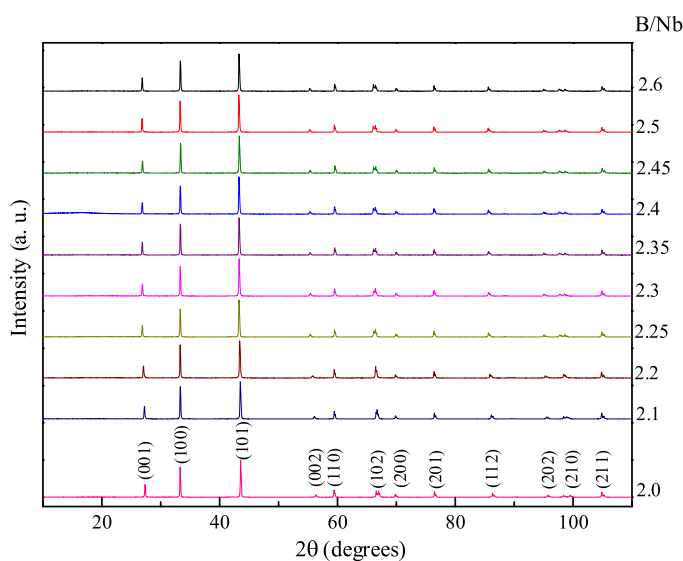


**Figure 1.** X-ray diffraction patterns of the NbB<sub>2+x</sub> for 2.0 ≤ B/Nb ≤ 2.6 of nominal composition.

pressures. Powder samples were mechanically compacted and shaped to appropriate sizes and mounted into a diamond anvil cell (DAC) with diamonds of 500  $\mu\text{m}$  culet size. Cu–Be gaskets were used to perform the quasi-hydrostatic measurements; they were filled with fine powder of MgO < 2  $\mu\text{m}$  size. Four gold wires of 10  $\mu\text{m}$  diameter were used for the  $R$ – $T$  measurements. The experiments were performed from room temperature to about 1.6 K. The pressure calibration was determined with the change of the superconducting temperature of Pb. Additional information about high pressure measurements and procedures can be found in Falconi *et al* [15].


### 3. Results and discussion

Figure 1 shows the powder x-ray diffraction patterns of NbB<sub>2+x</sub> samples with nominal compositions B/Nb from 2.0 to 2.6. These correspond to the NbB<sub>2</sub> common structure (No 75-1048 of the International Centre for Diffraction Data ICDD). The impurities observed are faint features of Nb<sub>5</sub>B<sub>6</sub> (ICDD No 42-1040), B<sub>2</sub>O<sub>3</sub> (ICDD No 76-1655) and Nb<sub>2</sub>O<sub>5</sub> (ICDD No 80-2493). Diffraction patterns were fitted using Rietveld analysis, with the hexagonal AlB<sub>2</sub> structure model and space group  $P6/mmm$  (No 191). The analysis shows that the majority phase is NbB<sub>2+x</sub> > 90%. Figure 2 shows an example of the Rietveld analysis for the composition with B/Nb = 2.0.

Structural analysis extracted from Rietveld refining considering NbB<sub>2+x</sub> structure, see figure 3, indicates the occupancy factor for niobium and boron as a function of boron excess. However, the real niobium occupation factor is included in table 1 using the Nb<sub>1-x</sub>B<sub>2</sub> stoichiometry. This must be compared to the boron nominal starting compositions, B/Nb. It seems that for compositions below B/Nb ≤ 2.3 both are similar. As the nominal composition increases from B/Nb = 2.35 to 2.6 Rietveld refining determines the real composition, given (B/Nb)<sub>exp</sub> = 2.30(1)–2.34(2) with respect to the B/Nb values. The structural parameter data are listed in table 1. Figure 4 shows the evolution of the lattice parameters and cell

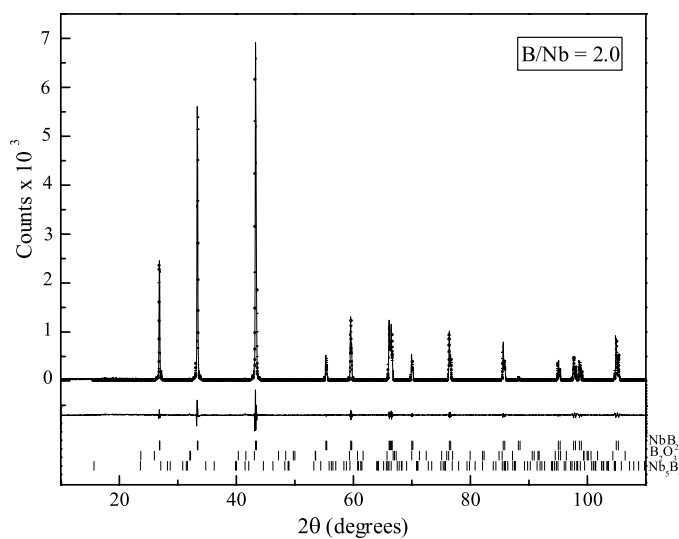

**Figure 2.** Example of Rietveld refinement for the  $\text{NbB}_2$  sample. X-ray experimental diagram (dots), and calculated pattern (continuous curve), difference (middle curve) and calculated peak positions (bottom).

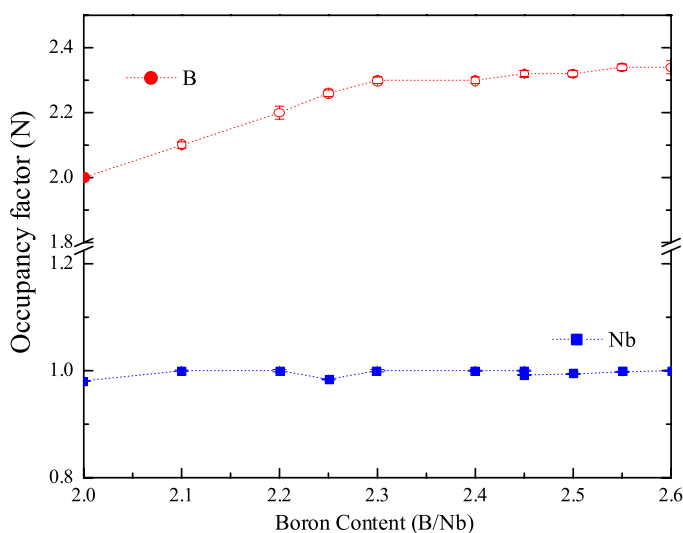


**Figure 3.** Occupancy factor for Nb and B metals in  $\text{NbB}_{2+x}$  as determined by Rietveld analysis.

volume as a function of boron content at room temperature. We observed that the  $a$ -axis decreases slightly as  $(\text{B/Nb})_{\text{exp}}$  increases, while the  $c$ -axis increases continuously in the interval  $2.00(1) \leq (\text{B/Nb})_{\text{exp}} \leq 2.26(1)$ , and remains almost constant from about  $\text{B/Nb} = 2.3$  to 2.6. As a consequence of these changes the unit cell volume increases in the composition interval  $2.00(1) \leq (\text{B/Nb})_{\text{exp}} \leq 2.26(1)$  and remains almost constant in the interval  $2.30(1) \leq (\text{B/Nb})_{\text{exp}} \leq 2.34(2)$ .

Similar results have been observed in other studies related to high pressure synthesis in the hole-doped  $\text{Nb}_x\text{B}_2$ , [12]. The authors observed that when  $x$  is increased, the  $a$ -axis decreases,

**Table 1.** Structural parameters for NbB<sub>2+x</sub> at 295 K. Space group: *P6/mmm* (No 191). Atomic positions: Nb, 1a (0, 0, 0); B, 2d (1/3, 2/3, 1/2). (Note: space group is *P6/mmm* (No 191) and the atomic positions are as follows: Nb, 1a (0, 0, 0); B, 2d(1/3, 2/3, 1/2), B/Nb—nominal boron to metal ratio; B/Nb<sub>exp</sub>—experimentally determined boron to metal ratio in sample. *B* in Å<sup>2</sup> and *N* are the isotropic thermal and occupancy parameters. Numbers in parentheses are the estimated standard deviation of the last significant digit.)

B/Nb	2.0	2.1	2.2	2.25	2.3	2.35	2.4	2.45	2.5	2.55	2.6
<i>a</i> (Å)	3.110(2)	3.110(2)	3.108(3)	3.104(2)	3.105(2)	3.104(2)	3.104(2)	3.104(2)	3.104(2)	3.104(2)	3.104(2)
<i>c</i> (Å)	3.267(2)	3.282(3)	3.296(3)	3.317(3)	3.316(3)	3.319(2)	3.319(3)	3.320(2)	3.319(3)	3.321(2)	3.320(3)
<i>V</i> (Å <sup>3</sup> )	27.369	27.488	27.578	27.677	27.683	27.696	27.695	27.704	27.690	27.699	27.701
<i>c/a</i>	1.050	1.055	1.060	1.068	1.068	1.069	1.070	1.070	1.069	1.070	1.070
B/Nb <sub>exp</sub>	2.00(1)	2.10(1)	2.20(2)	2.26(1)	2.30(1)	2.30(1)	2.32(1)	2.32(1)	2.34(1)	2.34(1)	2.34(2)
<i>N</i> <sub>(Nb)</sub>	0.986(1)	0.943(2)	0.909(1)	0.878(1)	0.869(1)	0.864(1)	0.857(1)	0.854(1)	0.848(1)	0.849(1)	0.848(1)
<i>B</i> (Å <sup>2</sup> ) <sub>(Nb)</sub>	0.37(1)	0.12(1)	0.15(1)	0.07(1)	0.13(1)	0.14(1)	0.07(1)	0.14(1)	0.16(1)	0.17(2)	0.13(1)
<i>B</i> (Å <sup>2</sup> ) <sub>(B)</sub>	0.8(1)	0.9(1)	0.9(2)	0.5(1)	1.4(1)	1.2(1)	1.0(1)	1.1(1)	1.6(1)	1.50(2)	1.38(1)
B–Nb bond length (Å)	2.426(3)	2.431(2)	2.435(3)	2.440(3)	2.441(2)	2.441(3)	2.441(3)	2.442(2)	2.441(3)	2.441(3)	2.441(2)
B–B bond length (Å)	1.794(2)	1.794(3)	1.793(2)	1.790(3)	1.791(2)	1.790(2)	1.790(3)	1.790(2)	1.790(3)	1.790(3)	1.790(2)
% NbB <sub>2+x</sub>	95.23(2)	95.02(2)	96.13(2)	97.220(9)	95.40(2)	98.118(6)	97.910(8)	94.55(2)	98.219(6)	93.08(2)	94.36(2)
% Nb <sub>5</sub> B <sub>6</sub>	0.8(1)	1.31(8)	0.92(7)	0.80(8)	1.7(1)	0.23(4)–	0.36(5)	0.56(6)	0.24(3)	0.22(4)	0.69(8)
% B <sub>2</sub> O <sub>3</sub>	4.0(6)	3.5(4)	2.8(5)	1.9(3)	2.9(4)	1.3(2)	1.7(4)	4.8(5)	1.5(2)	6.7(5)	4.9(4)
% Nb <sub>2</sub> O <sub>5</sub>	—	0.18(7)	0.19(7)	—	—	0.33(7)	—	0.03(3)	0.08(6)	—	—
<i>R</i> <sub><i>p</i></sub> (%)	12.1	11.5	13.4	11.7	12.2	11.2	10.0	10.6	11.4	9.8	10.9
<i>R</i> <sub><i>wp</i></sub> (%)	17.3	16.7	18.7	16.4	17.3	16.2	13.8	15.8	16.7	14.5	16.4
Re (%)	12.3	12.4	12.6	12.7	12.5	12.1	11.0	12.5	12.4	11.7	12.5
GoF (%)	1.4	1.3	1.5	1.3	1.4	1.3	1.3	1.3	1.3	1.2	1.3

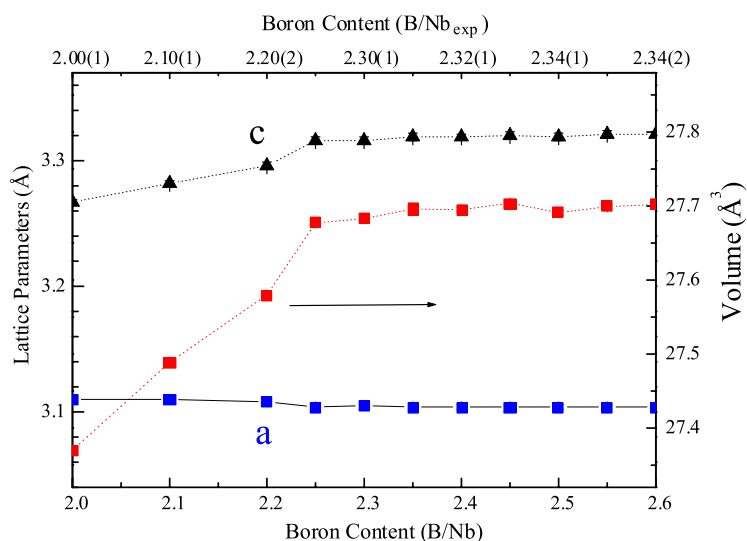

**Figure 4.** Crystal parameters and unit cell volume as a function of boron content ( $(B/Nb)_{\text{exp}}$  or  $B/Nb$ ).

whereas the  $c$ -axis is increased; this effect was attributed to Nb vacancies. Other studies with transition metal diborides show that boron excess is incorporated into the phase, creating vacancies in the metal site, rather than going into lattice interstitials [16]. The expectation that excess boron could be accommodated at interstitial sites comes from the closely related  $\text{Mo}_2\text{B}_{5-x}$  phase [17]. However, recent work [18] confirms the existence of a puckered plane, but does not locate the interstitial boron atoms. A subsequent study using neutron powder diffraction detected the interstitial boron sites, but with only a small occupancy [19]. So according to this evidence we are assuming in this study that the effect of boron excess is to create vacancies in Nb sites. Such a conclusion is in agreement with the fact that the honeycomb network of B is very rigid and therefore it will be very difficult to find interstitial spaces for additional B. Another indication related to structural characteristics is that when  $x$  is increased the B–B bond length associated to the basal plane decreases slightly, while the Nb–B bond length (along the  $c$ -axis) increases continuously in the  $2.00(1) \leq (B/Nb)_{\text{exp}} \leq 2.26(1)$  range, remaining almost constant for  $2.30(1) \leq (B/Nb)_{\text{exp}} \leq 2.34(2)$ ; this is shown in figure 5.

In order to corroborate the consequences of the increase of the  $c$ -axis length in the superconducting properties of this compound, it is worthwhile to study the effect of hydrostatic or quasi-hydrostatic high pressure (as also the equivalent effects) as well as the internal chemical pressure.

Slusky *et al* [20] investigated the substitution of Al on the Mg site, i.e.  $(\text{Mg}_{1-x}\text{Al}_x\text{B}_2)$ , and observed that  $T_C$  decreases smoothly with increasing  $x$  for  $0 < x < 0.1$ , accompanied by a slight decrease of the  $c$ -axis length. They concluded that the compound  $\text{MgB}_2$  is near to a structural instability that can destroy superconductivity. On the other hand, high pressure diffraction studies at room temperature at several pressures from about 6 to 30 GPa [21–24] have been performed. These show that the  $c$ -axis length decreases faster with pressure than the  $a$ -axis length, demonstrating that the out-of-plane Mg–B bond is much weaker than the in-plane Mg–Mg bond. Accordingly, clearly the Mg–B bond length has an important influence in the superconducting behaviour of  $\text{MgB}_2$ . Going back to the structural characteristics and superconducting behaviour of  $\text{NbB}_{2+x}$  phase, this work shows that  $T_C$  increases as

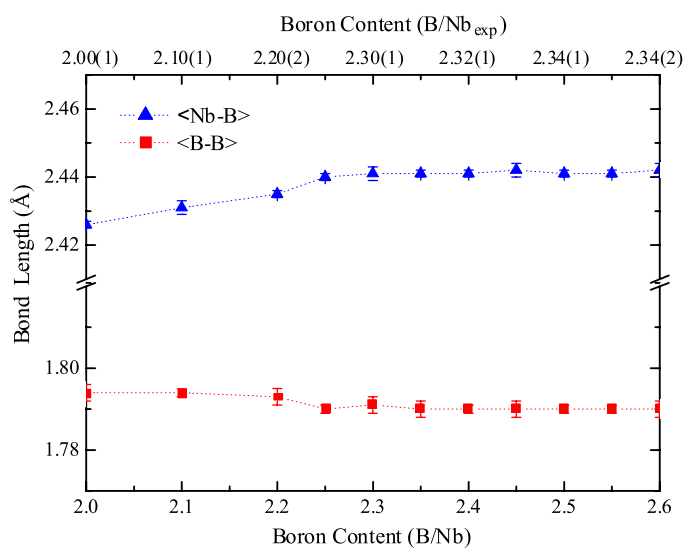


Figure 5.  $\langle \text{Nb-B} \rangle$  and  $\langle \text{B-B} \rangle$  bond lengths versus boron content.


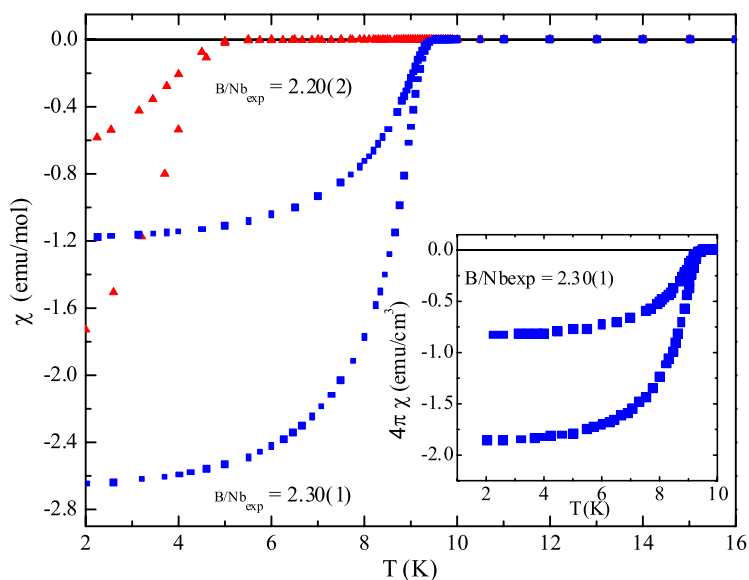


Figure 6. Susceptibility-temperature measurements showing the transition temperature (shielding and Meissner fraction) for two samples with different B concentrations. The inset shows the shielding and Meissner fractions in terms of  $1/4\pi$ .

boron excess is increased to the limit of about  $(\text{B}/\text{Nb})_{\text{exp}} = 2.34(1)$  where the transition temperature  $T_C = 9.8$  K reaches a maximum. Figures 6 and 7 show results of magnetic measurements. The superconducting transition temperature,  $T_C$ , was defined at the onset of the diamagnetic response in  $\chi(T)$ . It must be pointed out that we did not detect superconductivity in  $(\text{B}/\text{Nb})_{\text{exp}} = 2.00(1)\text{NbB}_2$  and  $(\text{B}/\text{Nb})_{\text{exp}} = 2.10(1)\text{NbB}_{2.1}$ . At compositions from  $2.26(1) < (\text{B}/\text{Nb})_{\text{exp}} < 2.34(2)$ , the transition temperature increases continuously from



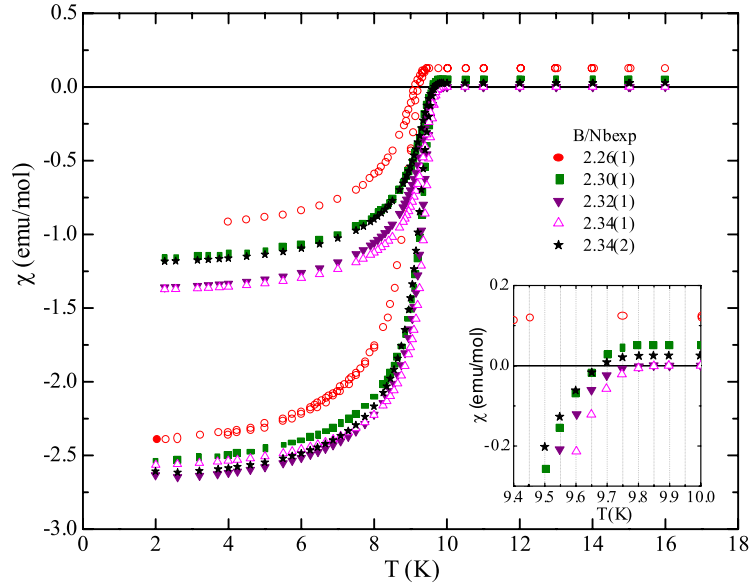


**Figure 7.** Temperature dependence of the susceptibility, from 2 to 15 K in applied magnetic field of 5 Oe for  $\text{NbB}_{2+x}$ , with different boron concentrations. The inset shows  $T_C$  decreasing for boron concentration higher than 2.32(1).

**Table 2.** Magnetic fields  $H_{C1}(0)$  and  $H_{C2}(0)$  estimated from experimental data at low temperature using a parabolic fit;  $H_C(T) = H_C(0)[1 - (T/T_C)^2]$ . Ginzburg–Landau parameters were determined from the GL equations.


$T_C$ (K)	$H_{C1}$ (Oe)	$H_{C2}$ (Oe)	$\xi_{GL}$ (nm)	$\kappa_{GL}$	$\lambda_{GL}$ (nm)
9.75	196	2226	40	2.49	87

5 K to a maximum of 9.8 K. In all these samples the Meissner fraction indicates bulk superconductivity. One example of the superconducting fraction can be seen in figure 6, where the Meissner and shielding fractions are plotted; the shielding fraction corresponds to about 190%. The estimated Meissner fraction was about 80%. Determination of the percentages used the theoretical density for  $(\text{B}/\text{Nb})_{\text{exp}} = 2.30(1)\text{NbB}_{2.3}$ ; see the inset of figure 6. In order to illustrate the  $T_C$  changes, the inset of figure 7 shows an amplification of the  $\chi(T)$  curves around  $T_C$  values. For instance the composition with  $(\text{B}/\text{Nb})_{\text{exp}} = 2.26(1)$  shows a transition temperature at  $T_C = 9.2$  K, and further increase of boron increases the transition temperature to 9.8 K. Above  $(\text{B}/\text{Nb})_{\text{exp}} = 2.34(1)$ ,  $T_C$  drops to about 9.4 K.

Following the characterization of the superconducting behaviour of this material, we used magnetization measurements as a function of applied magnetic field. We found that the compound behaves as a type II superconductor. Figure 8 shows the critical magnetic fields and table 2 shows the superconducting parameters.  $H_{C1}(0)$  and  $H_{C2}(0)$  were estimated from experimental data and a parabolic fit near zero temperature with the expression  $H_C(T) = H_C(0)[1 - (T/T_C)^2]$  below 5 K. Ginzburg–Landau (GL) parameters such as coherence length  $\xi_{GL}$ , penetration length  $\lambda_{GL}$ , and  $\kappa$  were determined from the equations;  $H_{C2}(0) = \Phi_0/2\pi\xi_{GL}^2$ ,  $H_{C2}(0)/H_{C1}(0) = 2\kappa^2 \ln \kappa$ , and  $\lambda_{GL}^2 = \Phi_0 \ln \kappa/4\pi H_{C1}(0)$ . In the equations  $\Phi_0 = hc/2e \approx 2.07 \times 10^{-7}$  G cm<sup>2</sup> is the flux quantum. Thus,  $\kappa = 2.49$  confirms that  $\text{NbB}_{2+x}$  is a type II superconductor.

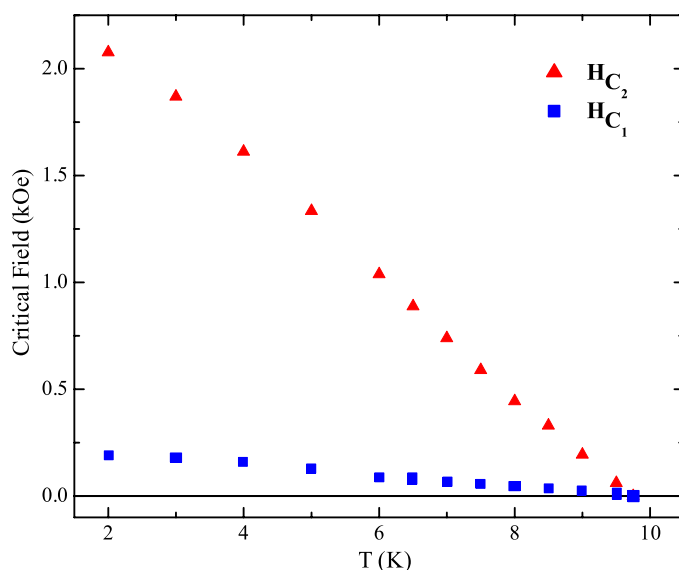


**Figure 8.** Critical fields  $H_{C1}$  and  $H_{C2}$  as functions of temperature for  $(B/Nb)_{\text{exp}} = 2.32(1)$  determined from magnetic measurements.

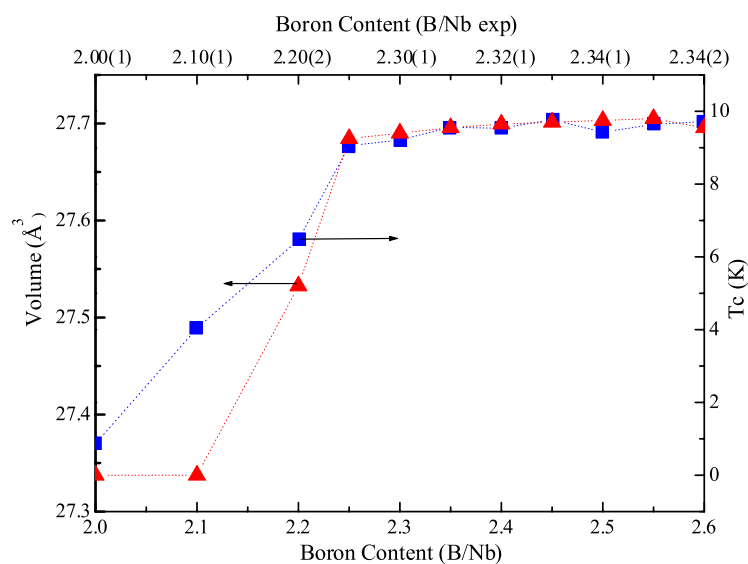

**Figure 9.** Cell volume and the superconducting transition  $T_C$  at different boron concentrations.


From the viewpoint of the chemical pressure effects, one important observation of this study is that  $T_C$  and cell volume increase in the same manner as boron content is increased. Figure 9 shows this behaviour. In order to see the external pressure effect on the superconducting characteristics we performed measurements at quasi-hydrostatic high pressure with diamond cells on two extreme compositions,  $(B/Nb)_{\text{exp}} = 2.26(1)$ , and  $2.32(1)$ . The corresponding  $R$  versus  $T$  curves at different pressures up to 5.9 GPa for the sample with composition  $(B/Nb)_{\text{exp}} = 2.26(1)$  are shown in figure 10. The inset of this figure reveals in

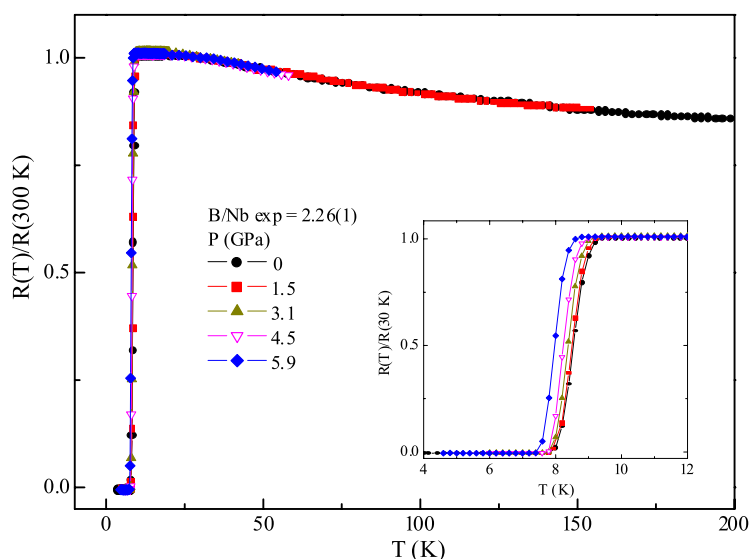

**Figure 10.**  $R$  versus  $T$  curves at different pressures up to 5.9 GPa for a sample with  $(\text{B/Nb})_{\text{exp}} = 2.26(1)$ . The inset reveals details at low temperature.

detail the low temperature behaviour of curves and changes of the superconducting transition. Variation of  $T_C$  as function of temperature for the two compositions  $(\text{B/Nb})_{\text{exp}} = 2.26(1)$  and  $(\text{B/Nb})_{\text{exp}} = 2.32(1)$  ( $T_C$  determined as the 50% value of the resistance drops at the transition temperature) is shown in figure 11. As a matter for comparison, the inset shows the pressure variation of normalized  $T_C/T_{C0}$  ( $T_{C0}$  is the room pressure superconducting transition temperature). From those measurements we determined the ratios  $dT_C/dP = -0.104$  and  $-0.054 \text{ K GPa}^{-1}$  for samples with composition 2.26(1), and 2.32(1) respectively. It seems that the ratio of decreasing temperature with pressure is quite different for the two samples. First of all, it seems that the sample with higher boron content requires more pressure to decrease  $T_C$ , which implies a strong Nb–B bond, perhaps very close to the limit of strength. Secondly, the sample with  $(\text{B/Nb})_{\text{exp}} = 2.26(1)$  shows a higher value for  $dT_C/dP$  than the 2.32(1) composition; this suggests that the Nb–B bond presents less stiffness than the other composition with 2.32(1). The implication of these high pressure experiments is that we corroborate the hypothesis that reducing the bond length in the crystalline direction  $c$  (mainly) reduces  $T_C$ , via displacing the Fermi level to a minimum in  $N(E)$ ; this in turn decreases the Coulombic repulsion and the alloy will be in a region with higher stability. Here we are invoking a mechanism of the Hume–Rothery type [25]. The reduction of  $T_C$  in our high pressure measurements is in clear contrast to the Schirber *et al* result, where they observe an increase of  $T_C$  under pressure to about 9.6 K, determined in a single crystal of  $\text{NbB}_x$ , with  $x$  close to 2.

Lastly, we explain the experimental results based on theoretical aspects. Band structure calculations [3] show that the band structure changes when boron content is increased; this in turn affects the density of states at the Fermi level, changing from a minimum to a maximum value. According to this,  $T_C$  must increase, following BCS theory. This fact was also explained for the decreasing  $T_C$  in the compound  $\text{TaB}_2$ , and the absence of superconductivity in  $\text{VB}_2$  in terms of the considerable decrease in the contributions of the B 2p states to the density of states at the Fermi level. Such a B 2p contribution to  $N(E_F)$  for the three compounds is

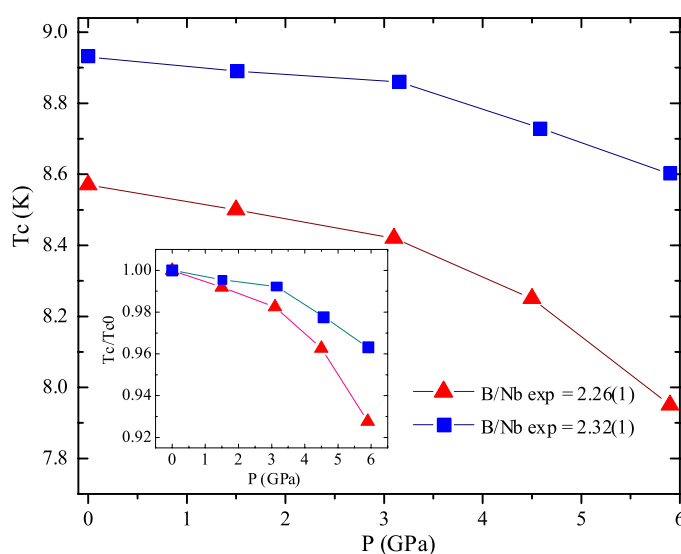

**Figure 11.** Pressure dependence of  $T_c$  for two compositions of NbB<sub>2+x</sub>, with  $(B/Nb)_{exp} = 2.26(1)$ , and  $2.32(1)$ . The inset shows the normalized variation,  $T_c/T_{c0}$ , where  $T_{c0}$  is the superconducting transition temperature at room pressure.

MgB<sub>2</sub>(0.448), TaB<sub>2</sub>(0.178), and VB<sub>2</sub>(0.085) states  $eV^{-1}$ . We may conclude that on the basis of the previous ideas, and band calculations we can certainly assume that the increase in the excess boron generates an increase in the number of niobium vacancies (see table 1 [14]) which increases the number of carriers [12] by positioning the Fermi level at a maximum in  $N(E)$ .

#### 4. Conclusions

In summary, we have reported studies on samples of NbB<sub>2+x</sub> prepared by solid-state reaction at ambient pressure. Samples are superconducting with a maximum transition temperature at 9.8 K. XRD and Rietveld refinements show that boron excess induces significant changes in the Nb–B bond length, giving rise to an increase in the  $c$ -axis. The superconducting fraction determined in the samples was about 80%. The maximum  $T_c$  was obtained at boron concentrations in the range from  $(B/Nb)_{exp} = 2.32(1)$  to  $2.34(1)$ . From structural and magnetization characterization we found that the increase of  $T_c$  is directly related to the Nb–B bond length. Studies at high quasi-hydrostatic pressure show that  $T_c$  decreases, by reducing  $N(E_F)$ ; we assume that the Fermi level is displaced to a minimum in  $N(E)$ , according to theoretical studies. Finally, the critical magnetic fields were determined at low temperature, showing values of about 200 and 2200 Oe for  $H_{C1}$  and  $H_{C2}$  respectively.

#### Acknowledgments

We thank DGAPA-UNAM for financial support, and F Silvar for technical support.

#### References

- [1] Nagamatsu J, Nakagawa N, Muranaka T, Zenitani Y and Akimitsu J 2001 *Nature* **410** 63
- [2] Indenbom M V, Uspenskaya L S, Kulakov M P, Bdikin I K and Zver'kov S A 2001 *Pis. Zh. Eksp. Teor. Fiz.* **74** 304

- [3] Shein I R and Ivanovskii A L 2002 *Phys. Solid State* **44** 1833  
Shein I R et al 2003 *Phys. Solid State* **45** 1617  
Ivanovskii A L 2003 *Phys. Solid State* **45** 1829
- [4] Kortus J, Mazin I I, Belashchenko K D, Antropov V P and Boyer L L 2001 *Phys. Rev. Lett.* **86** 4656
- [5] Gasparov V A, Sidorov N S, Zver'kova I L and Kulakov M P 2001 *JEPT Lett.* **73** 532  
Kaczorowski D, Zaleski A J, Zogal O J and Klamut J 2001 *Preprint cond-mat/0103571*
- [6] Ziegler W T and Young R A 1953 *Phys. Rev.* **90** 115
- [7] Hulm J K and Matthias B T 1951 *Phys. Rev.* **82** 273
- [8] Leyarovska L and Leyarovski E 1979 *J. Less-Common Met.* **67** 249
- [9] Cooper A S, Corenzwit E, Longinotti L D, Matthias B T and Zachariassen W H 1970 *Proc. Natl Acad. Sci.* **67** 313
- [10] Schirber J E, Overmyer D L, Morosin B, Venturini E L, Baughman R, Emin D, Klesnar H and Aselage T 1992 *Phys. Rev. B* **45** 10787
- [11] Kotegawa H, Ishida K, Kitaoka Y, Muranaka T, Nakagawa N, Takagiwa H and Akimitsu J 2002 *Physica C* **378-381** 25
- [12] Yamamoto A, Takao C, Masui T, Izumi M and Tajima S 2002 *Physica C* **383** 197
- [13] Akimitsu J 2001 *Annual Mtg of Physical Society of Japan* vol 3, p 533
- [14] Altomare A, Burla M C, Giacovazzo C, Guagliardi A, Moliterni A G G, Polidori G and Rizzi R 2001 *J. Appl. Crystallogr.* **34** 392
- [15] Falconi R, Durán A and Escudero R 2001 *Phys. Rev. B* **65** 024505
- [16] Muzzy L E, Avdeev M, Lawes G, Haas M K, Zandbergen H W, Ramirez A P, Jorgensen J D and Cava R J 2002 *Physica C* **382** 153
- [17] Kiessling R 1947 *Acta Chem. Scand.* **1** 893
- [18] Higashi I, Takahashi Y and Okada S 1986 *J. Less-Common Met.* **123** 277
- [19] Klesnar H, Aselage T L, Morosin B and Kwei G H 1996 *J. Alloys Compounds* **241** 180
- [20] Slusky J S, Rogado N, Regan K A, Hayward M A, Khalifah P, He T, Inumaru K, Loureiro S M, Haas M K, Zandbergen H W and Cava R J 2001 *Nature* **410** 343
- [21] Prassides K, Iwasa Y, Ito T, Chi D H, Uehara K, Nishibori E, Takata M, Sakata M, Ohishi Y, Shimomura O, Muranaka T and Akimitsu J 2001 *Phys. Rev. B* **64** 012509
- [22] Goncharov A F, Struzhkin V V, Gregoryanz E, Hu J, Hemley R J, Mao H K, Lapertot G, Bud'ko S L and Canfield P C 2001 *Phys. Rev. B* **64** 100509
- [23] Schlachter S I, Fietz W H, Grube K and Goldacker W 2002 *Advances in Cryogenic Engineering, ICMC'01: Proc. Int. Cryogenic Materials Conf. (Madison, July 2002)* p 809
- [24] Bordet P J, Mezouar M, Nuñez-Regueiro M, Monteverde M, Nuñez-Regueiro M D, Rogado N, Regan K A, Hayward M A, He T, Loureiro S M and Cava R J 2001 *Phys. Rev. B* **64** 172502
- [25] Friedel J and Dénoyer F 1987 *C. R. Acad. Sci. II* **305** 171