

Enhanced superconducting properties of bicrystalline $\text{YBa}_2\text{Cu}_3\text{O}_x$ and alkali metals under pressure

This article has been downloaded from IOPscience. Please scroll down to see the full text article.

2005 J. Phys.: Condens. Matter 17 S921

(<http://iopscience.iop.org/0953-8984/17/11/024>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 129.252.86.83

The article was downloaded on 27/05/2010 at 20:31

Please note that [terms and conditions apply](#).

Enhanced superconducting properties of bicrystalline $\text{YBa}_2\text{Cu}_3\text{O}_x$ and alkali metals under pressure

T Tomita¹, S Deemyad¹, J J Hamlin¹, J S Schilling¹, V G Tissen²,
B W Veal³, L Chen³ and H Claus³

¹ Department of Physics, Washington University, CB 1105, St Louis, MO 63130, USA

² Institute of Solid State Physics, Chernogolovka 142432, Moscow District, Russia

³ Materials Science Division, Argonne National Labs, 9700 S Cass Avenue, Argonne, IL 60439, USA

Received 5 January 2005

Published 4 March 2005

Online at stacks.iop.org/JPhysCM/17/S921

Abstract

Nearly hydrostatic pressures are found to enhance the critical current density J_c through single grain boundaries in $\text{YBa}_2\text{Cu}_3\text{O}_x$ rings and to induce superconductivity in Li. Whereas Li becomes superconducting above 20 GPa at temperatures as high as 15 K, no superconductivity was observed above 4 K in Na to 65 GPa nor in K above 4 K to 43.5 GPa or above 1.5 K to 35 GPa.

1. Introduction

The first high pressure experiments on a superconductor were carried out in 1925 by Sizoo and Onnes [1], 14 years after the discovery of the first superconductor [2]. Since then high pressure investigations have had an important impact on the field. Following the discovery of a new superconductor, one of the first experiments is to determine the pressure dependence of the superconducting transition temperature T_c . If the magnitude of dT_c/dP is large, one can have good hope that higher values of T_c at ambient pressure are possible. In addition, a comparison of the pressure dependences of T_c with those of selected normal state properties provides information regarding the mechanism(s) responsible for the superconductivity, as recently illustrated for MgB_2 , the high T_c oxides, and the alkali-doped fullerenes [3].

In this paper we give further examples to illustrate how the high pressure technique can provide vital information and uncover new physics for two completely different classes of superconductors: (1) the high pressure enhancement of the critical current density J_c across a single grain boundary (GB) in bicrystalline rings of the high T_c oxide $\text{YBa}_2\text{Cu}_3\text{O}_x$ (YBCO); and (2) pressure-induced superconductivity in the alkali metals. The observation of pressure-induced superconductivity in Li is at odds with the conventional wisdom that metals become more free-electron-like under pressure.

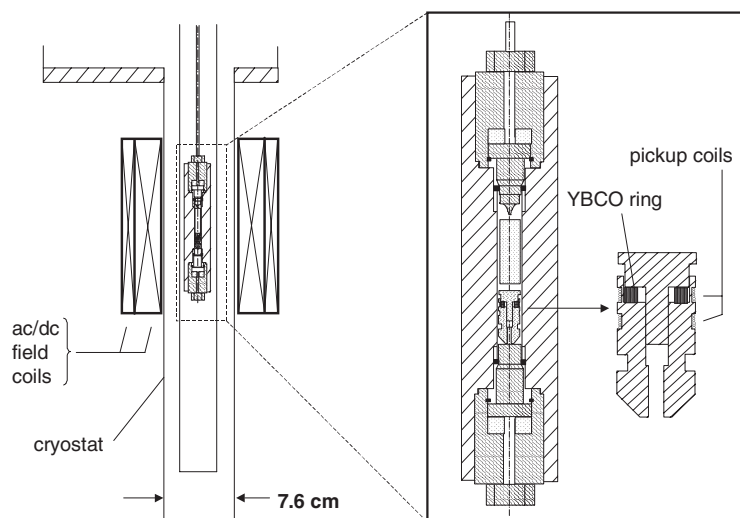


Figure 1. The sample holder on the right fits inside the 7 mm bore of the He gas pressure cell which is inserted in the closed-cycle refrigerator.

2. Results on YBCO grain boundaries

Shortly after the discovery of the high T_c oxides in 1986 it became clear that the J_c values for polycrystalline materials not only are vastly inferior to those obtained for single-crystalline samples, but also degrade sharply in a magnetic field [4]. Experiments on epitaxially grown YBCO thin films demonstrated that this strong degradation in J_c resulted from the presence of grain boundaries in the polycrystals [5]; for adjacent grains with parallel c -axes, J_c was found to decrease roughly exponentially with increasing misorientation angle θ [6]. Pinpointing the mechanisms behind this J_c degradation and developing strategies to enhance J_c to the values needed for many applications have been at the focus of intensive research for many years.

Possible candidates for causing the J_c degradation include various kinds of imperfections in or at the GB such as site disorder, lattice strains, and oxygen vacancies [4, 7, 8]. High pressure experiments may shed some light on these matters by modifying the conditions at the GB in several different ways: (1) reduction of tunnelling barrier width; (2) varying the degree of lattice strain; (3) enhancing the degree of oxygen ordering in the GB, in analogy with the well studied pressure-induced oxygen ordering effects in the bulk [9, 10]. The very existence of relaxation effects due to oxygen ordering in the GB would signal that the oxygen sublattice is only partially full and thus capable of accepting further oxygen doping.

Previous ac susceptibility studies on bulk polycrystalline samples of $\text{YBa}_2\text{Cu}_4\text{O}_8$ and $\text{Tl}_2\text{CaBa}_2\text{Cu}_2\text{O}_8$ indicated that the bulk J_c was enhanced through pressure, but it was not possible to extract detailed information [11]. Studies of pressure-dependent effects for a single grain boundary are clearly needed. Such experiments have recently become possible with the availability of bicrystalline rings of $\text{YBa}_2\text{Cu}_3\text{O}_x$ with varying misorientation angles θ and oxygen content x [12].

A He gas pressure cell (Unipress) suitable for hydrostatic pressure studies to 1.4 GPa is shown in figure 1. The YBCO bicrystalline ring with typical dimensions 5 mm O.D. \times 3 mm I.D. \times 1 mm is mounted in the sample holder made of Vespel which is placed in the 7 mm bore of the BeCu pressure cell. An alumina cylinder is positioned above the sample holder to reduce the volume of He in the cell.

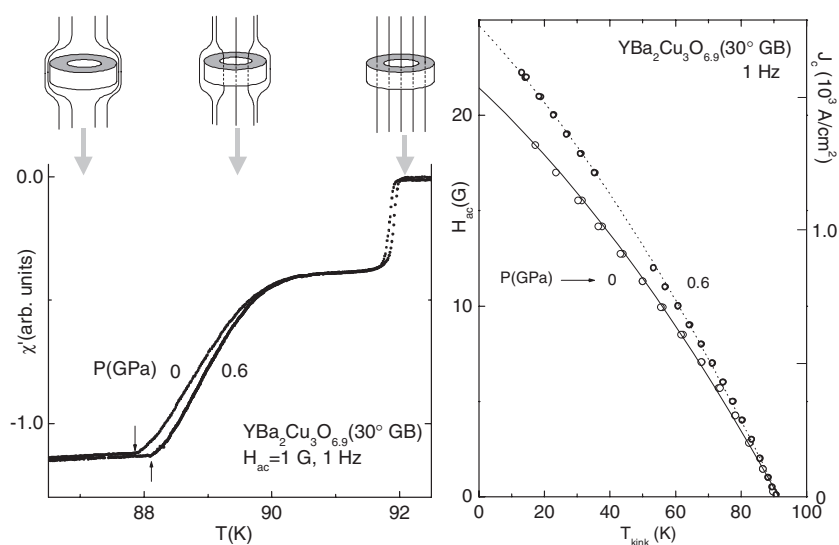


Figure 2. Left: the real part of the ac susceptibility versus temperature for the YBCO ring at two different pressures. Right: the ac field amplitude versus the kink temperature at two different pressures.

Two counterwound pickup coils are used in the ac susceptibility measurement, one positioned around the YBCO ring, the other 2.3 mm below. To vary the temperature over the range 6–300 K the pressure cell is placed in the sample tube of a closed-cycle refrigerator (Balzers) with the BeCu capillary tube (3 mm O.D. \times 0.3 mm I.D.) exiting out the top and connected to a three-stage He gas compressor system (Harwood) to 1.4 GPa with a digital manganin gauge. Since primary ac field amplitudes as high as 300 G are required, internal heating effects are avoided by removing the field coil from the pressure cell and placing it outside the tail piece of the cryostat. To ensure full field penetration to the sample, the frequency of the ac field was reduced to 1 Hz. Standard ac susceptibility techniques are used with an SR830 digital lock-in amplifier.

In figure 2 (left) the real part of the ac susceptibility χ_{ac} is plotted versus temperature for an ac field amplitude of 1 G at both ambient and 0.6 GPa hydrostatic pressure. The sample studied is a $\text{YBa}_2\text{Cu}_3\text{O}_{6.9}$ bicrystalline ring with misorientation angle $\theta = 30^\circ$. At temperatures below 88 K at ambient pressure, the applied flux is not able to penetrate into the ring since the induced current density through the two grain boundaries in the ring lies below the critical value J_c . Since $J_c(T)$ decreases monotonically with increasing temperature, as the temperature is raised, a value $T = 87.9$ K is reached where flux begins to penetrate through the weaker of the two grain boundaries into the interior of the ring; this leads to a sharp break in both the real and imaginary parts of χ_{ac} (see the vertical arrow in figure 2 (left)) at the kink temperature T_{kink} . As the temperature is increased further, additional flux penetrates into the centre of the ring, but not through the superconducting material of the ring itself, until a plateau is reached above 90 K. Above 91.7 K magnetic flux begins to penetrate into the ring material until above 92 K all superconductivity has been destroyed and the flux distribution is uniform. These results from ac susceptibility measurements are in excellent agreement with parallel dc susceptibility measurements using a SQUID magnetometer on the same YBCO ring.

The shielding current I around the ring is directly proportional to the field amplitude H , $I = DH$, where, to a good approximation, D is the outer diameter of the ring [12]. In

figure 2 (left) it is seen that under 0.6 GPa pressure T_{kink} shifts to higher temperatures, i.e. J_c at a given temperature increases. This means that under hydrostatic pressure the ability of the GB to carry current is enhanced. This result is confirmed by further studies at magnetic field amplitudes to ~ 23 G which suppress T_{kink} to temperatures below 20 K, as seen in figure 2 (right). In this figure the calculated values for J_c are given, where $J_c = I_c/A$ and A is the cross-sectional area of the ring. At all measured temperatures, J_c is seen to increase rapidly with hydrostatic pressure at the rate $+26\%$ GPa^{-1} which is much more rapid than that of T_c for the bulk material ($\sim 0.24\%$ GPa^{-1}).

We also find the change in J_c to be less if the pressure is varied at temperatures significantly below ambient; time dependences in J_c are also observed. Similar relaxation effects are well known in bulk YBCO where T_c is found to depend on the detailed pressure/temperature history of the sample [9, 10]. The extreme sensitivity of these relaxation effects on the oxygen content points to mobile oxygen ions in the basal plane, the ‘chain layer’, as being their source. The bulk relaxation effects are smallest when the chain layer is fully developed and essentially all chain sites are filled, i.e. at the stoichiometry $\text{YBa}_2\text{Cu}_3\text{O}_{7.0}$. In analogy, the relaxation effects observed in J_c for the GB give evidence that the GB contains a sizable number of oxygen vacancies, i.e. there is room for more oxygen! If a way can be found to further enhance the oxygen concentration in the GB region, it is likely that higher values of J_c can be attained.

Further research is under way to determine the dependence of J_c on pressure as a function of both temperature and dc magnetic field over a wide range of oxygen content and misorientation angle θ [13].

3. Results on alkali metals

The nearly free electron picture works best for simple s, p electron metals such as the alkali metals and noble metals. If a simple metal happens to be superconducting at ambient pressure (e.g. Pb, In, Sn, Al), T_c is invariably found to *decrease* under hydrostatic pressure. This result has a simple explanation [3]. According to the well known McMillan formula, T_c depends exponentially on the electron–phonon coupling parameter $\lambda = \eta/\kappa$, where η is a purely electronic term, the Hopfield parameter, and $\kappa \equiv M\langle\omega^2\rangle$ is a mean ‘spring constant’ for the lattice. If λ decreases, so does T_c . The reason for the universal decrease in T_c under pressure for simple metals is that κ increases much more rapidly than does η . Another way to express this is that T_c decreases under pressure due to lattice stiffening. In transition metals the increase of η with pressure is comparable to that of κ , so T_c may increase or decrease.

Since for simple-metal superconductors T_c always *decreases* under pressure, it would appear unlikely that a nonsuperconducting simple metal, such as any of the alkali metals, would ever become superconducting under pressure. Over 30 years ago, however, Wittig [14] demonstrated that at pressures above 7 GPa the alkali metal Cs becomes superconducting near 1.5 K. At first glance this result would appear to contradict our above conclusions, but it does not. At pressures above 7 GPa Cs is no longer a simple metal! Near these pressures s–d transfer occurs as the bottom of the 5d band drops below the top of the 6s band, thus turning Cs into a transition metal [15]. A similar scenario would be expected for the next lighter alkali metals Rb and K.

In this connection the alkali metal Li is of particular interest. Its unoccupied 3d band lies far above the Fermi energy; indeed, Li lies two rows up in the periodic table from the 3d transition metal series. In this picture, therefore, no pressure-induced superconductivity would be expected in Li, except at pressures well above the 100 GPa range. In 1986 Lin and Dunn [16] did report a possible phase transition in Li under quasihydrostatic pressures above 20 GPa, but the evidence for superconductivity was not unequivocal.

In 1998 Neaton and Ashcroft [17] made the alarming prediction that at sufficiently high pressures Li should cease to behave like a simple metal, but rather should show marked deviations from free-electron-like behaviour. Because of core overlap the bands near E_f actually become narrower and band gaps increase markedly, thus contradicting basic high pressure wisdom that under pressure bands broaden and band gaps decrease! This result was mentioned in an earlier paper by Boettger and Trickey [21]. At pressures sufficient to generate overlap of the Li ion cores, the requirements of orthogonality of the valence electrons to the core states lead to a marked enhancement in the pseudopotential and thus in the electron–lattice coupling. This in turn would be expected to generate structural phase transitions to lower symmetry structures and possible superconductivity. Extensive experimental [18, 19] and theoretical [20] investigations of structural phase changes in the alkali metals have confirmed these general expectations. In 2001 Christensen and Novikov [22] predicted from *ab initio* electronic structure calculations that for fcc Li T_c would increase rapidly with pressure to values approaching 80 K. These predictions prompted several experimental groups to search in earnest for superconductivity in Li under pressure.

The first group to confirm a superconducting transition in Li was that of Shimizu *et al* [23] in 2002 in a diamond anvil cell experiment to 50 GPa. In their electrical resistivity measurement superconductivity appeared at 7.5 K for 30 GPa pressure, rising rapidly to values approaching 20 K; the pressure dependence $T_c(P)$ was combined from four separate experiments and exhibited considerable scatter. A few months later Struzhkin *et al* [24] measured the ac susceptibility to 40 GPa and the resistivity to 82 GPa, reporting an onset of superconductivity at 10 K for 23 GPa with a rapid rise under pressure to ~ 16 K at 35 GPa.

In both of these studies no pressure medium was used, the diamond anvils being allowed to press directly onto the Li sample. This raises the question of whether shear stresses on the Li in such experiments may have played a role in the reported superconducting transition. Such effects have been well documented. In the first high pressure study ever carried out on a superconductor, Sizoo and Onnes [1] reported for both Sn and In that T_c decreased under hydrostatic pressure, but *increased* if uniaxial pressure was applied. If Li metal is cooled from ambient temperature, it undergoes a martensitic phase transformation at $T_{pt} \simeq 75$ K from the bcc to an Rh6 low temperature phase. Under hydrostatic pressure T_{pt} increases at the rate $+30$ K GPa $^{-1}$ [25], but under uniaxial pressure $dT_{pt}/dP \simeq +1250$ K GPa $^{-1}$ [26], a rate $40\times$ faster! In the present experiment, in fact, nonhydrostatic shear stresses on the Re gasket resulted in a sharp increase in Re's superconducting transition temperature to 3.5 K, thus preventing the detection of superconductivity from the Li sample at lower temperatures. Further examples of sharply differing hydrostatic versus uniaxial pressure effects on superconductivity are given in [27]. For this reason we set out to search for superconductivity in Li using the most hydrostatic pressure medium of all, dense He.

In figure 3 (left) we show the coil arrangement that we used for ac susceptibility measurements in our nonmagnetic BeCu diamond anvil cell. Two identical coils are shown wound with $60\ \mu\text{m}$ Cu wire consisting of an outer primary coil (130 turns) and an inner secondary coil (180 turns). One coil is placed around the lower diamond anvil (1/6 carat, 0.5 mm culet) with the compensating coil directly adjacent. Both coils and lead wires are thermally anchored to an insulating board with GE varnish. A preindented Re gasket is placed in both measuring and compensating coils to reduce the background signal in the ac susceptibility. Before applying pressure, liquid He is filled into the gasket hole to serve as a nearly hydrostatic pressure medium. Further experimental details are given in [27].

In figure 4 we show the superconducting phase diagram for Li metal under nearly hydrostatic pressures to 67 GPa [27]; this diagram differs significantly from the results of the previous studies [16, 23, 24], particularly above 30 GPa. In the first run 25 data points

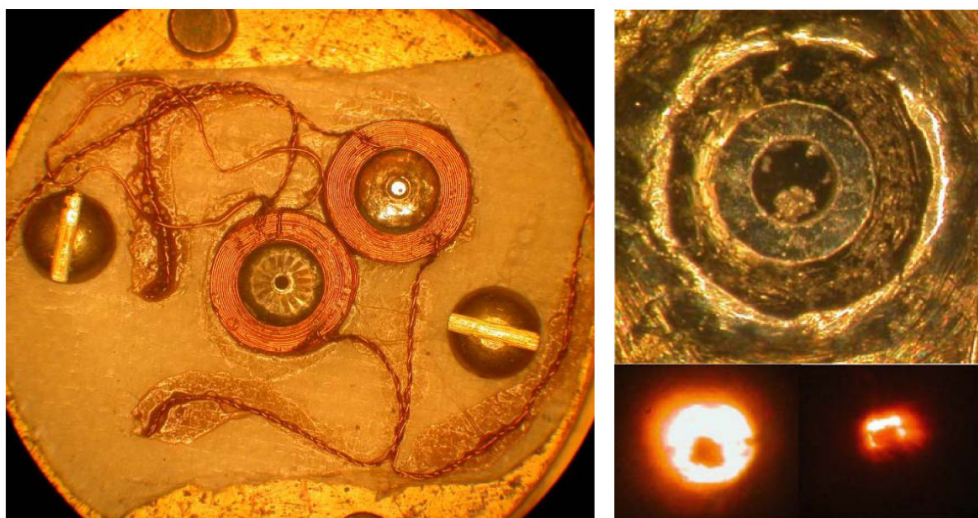


Figure 3. Left: the arrangement of measuring and compensating coils in the diamond anvil cell. Right, on the top: the Au-plated Re gasket with a 250 μm bore containing the Li sample and ruby spheres; at the bottom, on the left: a transmitted light photograph of cell at ambient pressure; and on the right: one at 30 GPa pressure.

(This figure is in colour only in the electronic version)

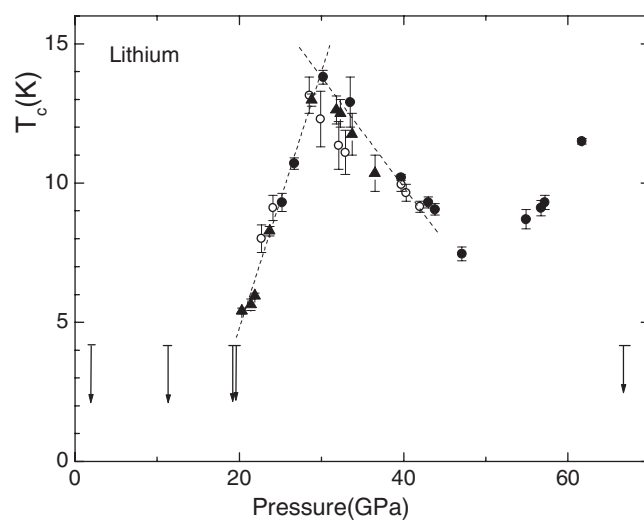


Figure 4. The superconducting phase diagram of Li metal under nearly hydrostatic pressure: run 1 with increasing pressure (\bullet), run 1 with decreasing pressure (\circ) and run 2 with increasing pressure (\blacktriangle).

were obtained as a function of both increasing and decreasing pressure. We find that under nearly hydrostatic pressure Li becomes superconducting at ~ 5 K for 20 GPa, T_c increasing initially rapidly with pressure to ~ 14 K at 30 GPa. At this pressure a structural phase transition appears to occur as evidenced by the sharp break in slope dT_c/dP . At higher pressures $T_c(P)$ passes through a minimum before dropping below 4 K at 67 GPa. Although it is possible that at

or above 67 GPa Li has transformed into the paired semiconducting/insulating state envisioned by Neaton and Ashcroft, we have no clear evidence for this. At 67 GPa our Li sample remains opaque to transmitted light in the visible region; from this one can infer that Li is either still a metal or a semiconductor with a band gap less than 1.7 eV. A more complete discussion of these results, including evidence that Li is a type I superconductor, is given in [27].

Following the experiments on Li metal, two further alkali metals, Na and K, were subjected to nearly hydrostatic dense He pressure in a search for superconductivity. Shi *et al* [28] have carried out an electronic structure calculation on K and Rb and predict an onset of superconductivity near 13 GPa for K and 8 GPa for Rb with a rapid rise in T_c with pressure, in analogy with the Li case. In our experiment on Na metal to 65 GPa, however, no superconducting transition could be detected above 4 K. K metal also failed to become superconducting above 4 K to 43.5 GPa pressure. In a second experiment on K a nonsuperconducting MoW gasket was used which permitted measurements to lower temperatures. In this experiment no superconductivity was detected in K above 1.5 K to 35 GPa pressure. In a quasihydrostatic experiment to 21 GPa by Ullrich *et al* [29], no superconductivity was found in Rb above 0.05 K.

It would seem almost certain that all alkali metals will become superconducting under sufficient pressure; after all, both the lightest (Li) and heaviest (Cs) alkali metals do become superconducting! Further experiments are under way over expanded temperature/pressure ranges to search for superconductivity in Na, K and Rb.

Acknowledgments

The authors are grateful to N W Ashcroft and J B Neaton for stimulating discussions. This research was supported by NSF Grant No DMR-0404505.

References

- [1] Sizoo G J and Onnes H K 1925 *Commun. Phys. Lab. Univ. Leiden* No. 180b
- [2] Onnes H K 1911 *Akad. van Wetenschappen* **14** 113
- [3] Schilling J S 2001 *Frontiers of High Pressure Research II: Application of High Pressure to Low-Dimensional Novel Electronic Materials* ed H D Hochheimer *et al* (The Netherlands: Kluwer–Academic) pp 345–60
- [4] Mannhart J and Chaudhari P 2001 *Phys. Today* (November) 48
Hilgenkamp H and Mannhart J 2002 *Rev. Mod. Phys.* **74** 485
- [5] Chaudhari P *et al* 1988 *Phys. Rev. Lett.* **60** 1653
- [6] Dimos D *et al* 1988 *Phys. Rev. Lett.* **61** 219
- [7] Caldwell W A, Celestre R S, MacDowell A A, Padmore H A, Geballe T H, Koster G, Batterman B W and Patel J R 2004 *Phys. Rev. Lett.* **92** 216105
- [8] Chisholm M F and Pennycook S J 1991 *Nature* **351** 47
- [9] Fietz W H, Quenzel R, Ludwig H A, Grube K, Schlachter S I, Hornung F W, Wolf T, Erb A, Kläser M and Müller-Vogt G 1996 *Physica C* **270** 258
- [10] Sadewasser S, Schilling J S, Paulikas A P and Veal B W 2000 *Phys. Rev. B* **61** 741
- [11] Diederichs J, Reith W, Sundqvist B, Niska J, Easterling K A and Schilling J S 1991 *Supercond. Sci. Technol.* **4** S97
- [12] Claus H, Welp U, Zheng H, Chen L, Paulikas A P, Veal B W, Gray K E and Crabtree G W 2001 *Phys. Rev. B* **64** 144507
- [13] Tomita T, Schilling J S, Veal B W, Chen L and Claus H 2005 unpublished
- [14] Wittig J 1970 *Phys. Rev. Lett.* **24** 812
- [15] Ross M and McMahan A K 1982 *Phys. Rev. B* **26** 4088
- [16] Lin T H and Dunn K J 1986 *Phys. Rev. B* **33** 807
- [17] Neaton J B and Ashcroft N W 1999 *Nature* **400** 141
- [18] For a review, see Syassen K 2002 *Proc. Int. School of Physics Enrico Fermi Course CXLVII* ed R J Hemley *et al* (Amsterdam: IOS Press) pp 251–73

-
- [19] Hanfland M 2005 *J. Phys.: Condens. Matter* **17**
 - [20] Ackland G J, Macleod I R and Degtyareva O 2003 *Preprint cond-mat/0310380*
 - [21] Boettger J C and Trickey S B 1985 *Phys. Rev. B* **32** 3391
 - [22] Christensen N E and Novikov D L 2001 *Phys. Rev. Lett.* **86** 1861
 - [23] Shimizu K, Ishikawa H, Takao D, Yagi T and Amaya K 2002 *Nature* **419** 597
 - [24] Struzhkin V V, Erements M I, Gan W, Mao H K and Hemley R J 2002 *Science* **298** 1213
 - [25] Smith H G, Berlinger R, Jorgensen J D, Nielsen M and Trivisonno J 1990 *Phys. Rev. B* **41** 1231
 - [26] Maier Ch, Blaschko O and Pichl W 1995 *Phys. Rev. B* **52** 9283
 - [27] Deemyad S and Schilling J S 2003 *Phys. Rev. Lett.* **91** 167001
 - [28] Shi L, Papaconstantopoulos D A and Mehl M J 2003 *Solid State Commun.* **127** 13
 - [29] Ullrich K, Probst C and Wittig J 1978 *J. Physique Coll.* **1** 6 463
Ullrich K, Probst C and Wittig J 1980 *Bericht Kernforschungsanlage Jülich (Juel-1634)*