

Identifying valence structure in LiFeAs and NaFeAs with core-level spectroscopy

This article has been downloaded from IOPscience. Please scroll down to see the full text article.

2009 J. Phys.: Condens. Matter 21 345701

(<http://iopscience.iop.org/0953-8984/21/34/345701>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 129.252.86.83

The article was downloaded on 29/05/2010 at 20:47

Please note that [terms and conditions apply](#).

Identifying valence structure in LiFeAs and NaFeAs with core-level spectroscopy

E Z Kurmaev¹, J A McLeod², N A Skorikov¹, L D Finkelstein¹,
A Moewes², Yu A Izyumov¹ and S Clarke³

¹ Institute of Metal Physics, Russian Academy of Sciences—Ural Division,
620219 Yekaterinburg, Russia

² Department of Physics and Engineering Physics, University of Saskatchewan,
116 Science Place, Saskatoon, SK, S7N 5E2, Canada

³ Inorganic Chemistry Laboratory, Department of Chemistry, University of Oxford,
South Parks Road, Oxford OX1 3QR, UK

E-mail: john.mcleod@usask.ca

Received 6 May 2009, in final form 2 July 2009

Published 6 August 2009

Online at stacks.iop.org/JPhysCM/21/345701

Abstract

Resonant x-ray emission spectroscopy (XES) measurements at Fe L_{2,3} edges and electronic structure calculations for LiFeAs and NaFeAs are presented. Experiment and theory show that in the vicinity of the Fermi energy, the density of states is dominated by contributions from Fe 3d states. The comparison of Fe L_{2,3} XES with spectra of related FeAs compounds reveals similar trends in energy and the ratio of intensities of the L₂ and L₃ peaks ($I(L_2)/I(L_3)$ ratio). The $I(L_2)/I(L_3)$ ratio for all FeAs-based superconductors is found to be closer to that of metallic Fe than that of the strongly correlated FeO. We conclude that iron-based superconductors are weakly or, at most, moderately correlated systems.

1. Introduction

Recently, a new class of iron-based superconductors was discovered. LiFeAs and NaFeAs were found to be superconducting with $T_c = 18$ K and 9 K, respectively [1–4]. These compounds have an unexpected lack in magnetic order at all temperatures whereas in REOFeAs (where RE is a rare earth element) and AEF₂As₂ (where AE is an alkaline earth element) the Fe magnetic moments adopt a collinear antiferromagnetic (c-AFM) order at low temperatures [2]. In contrast with other iron-based compounds, no further doping is necessary to induce superconductivity and the spin-density wave (SDW) state appears to be notably absent from these new systems [5]. This suggests LiFeAs and NaFeAs can offer important insights to understanding the mechanism of superconductivity in iron-based superconductors. The absence of SDW transitions and the relatively low T_c in comparison with REOFeAs and AEF₂As₂ iron-based superconductors make these two compounds possible candidates for conventional BCS superconductors [6]. However the estimation of the electron–phonon coupling parameter λ from band structure calculations [6] gives low values of $\lambda = 0.29$ and 0.27

for LiFeAs and NaFeAs respectively, which are too weak to account for conventional BCS superconductivity in this class of superconductors. Experimental studies of electronic structure of LiFeAs and NaFeAs superconductors and their comparison with that of REOFeAs and AEF₂As₂ iron-based superconductors are important in resolving this puzzle. In this manuscript we present and analyse x-ray emission spectroscopy (XES) measurements at the Fe L_{2,3} edge of LiFeAs and NaFeAs. These measurements probe the occupied Fe 3d density of states (DOS). We compare the measured spectra with our electronic structure calculations of the valence structure. We contrast our findings with our previous studies of REOFeAs (RE = La, Sm) [7] and CaFe₂As₂ [8].

2. Experimental and calculation details

LiFeAs and NaFeAs were synthesized by the reaction of stoichiometric quantities of elemental Li (or Na), Fe and As. Fe and As powders were ground together and added to pieces of Li (or Na) in a tantalum tube, which was then sealed by welding under 1 atm argon gas; the mixture was heated to 800 °C for two days. Preliminary characterization of the resulting product

Table 1. Structural parameters for various Fe compounds. Here ‘Fe–Fe’ refers to the distance between iron atoms, ‘Fe–R’ refers to the distance between the iron atom and the anion, both in Å. NN(*n*) refers to the number of nearest neighbours of the specified type. The final column, ‘Pt. Grp.’ refers to the point group around the Fe atom.

Compound	Fe–Fe	NN(Fe)	Fe–R	NN(R)	Pt. Grp.
LaOFeAs [12]	2.85	4	2.41	4	$-42m$
CaFe ₂ As ₂ [13]	2.74	4	2.32	4	$-42m$
NaFeAs	2.79	4	2.44	4	$-42m$
LiFeAs	2.67	4	2.41	4	$-42m$
Fe (bcc) [14]	2.54	8	—	—	$m3m$
FeO [15]	3.06	12	2.16	6	$m3m$

by powder x-ray diffraction revealed pure LiFeAs and NaFeAs phases. For details of sample preparation see [1] and [4].

The x-ray emission measurements of LiFeAs and NaFeAs were performed at the soft x-ray fluorescence endstation at Beamline 8.0.1 of the Advanced Light Source at Lawrence Berkeley National Laboratory [9]. The endstation uses a Rowland circle geometry x-ray spectrometer with spherical gratings and an area sensitive multichannel detector. We have measured resonant and non-resonant Fe L_{2,3} (3d4s → 2p transition) x-ray emission spectra (XES). The instrumental resolving power ($E/\Delta E$) for Fe L_{2,3} spectra was 10³. All spectra were normalized to the incident photon current using a highly transparent gold mesh in front of the sample to correct for intensity fluctuations in the photon beam. The excitations for the XES measurements were determined from Fe 2p x-ray absorption spectroscopy (XAS) measurements (using total electron yield mode); the chosen energies corresponded to the location of the L₂ and L₃ thresholds, an energy between them, and an energy well above the L₂ threshold.

All density of states calculations were performed within the full-potential linear augmented plane-wave method as implemented in WIEN2k code [10]. For the exchange–correlation potential we used the generalized gradient approximation in the Perdew–Burke–Ernzerhof variant [11]. The Brillouin zone integrations were performed with a 12 × 12 × 7 special *k*-point grid for LiFeAs and a 12 × 12 × 6 special *k*-point grid for NaFeAs and $R_{MT}^{min} K_{max} = 7$ (the product of the smallest of the atomic sphere radii R_{MT} and the plane-wave cutoff parameter K_{max}) was used for the expansion of the basis set. The experimental values of the high-temperature lattice constants and atomic positions are used [1, 4]. Both compounds have a tetragonal crystal lattice in the $P4/nmm$ space group. In NaFeAs, the lattice constants are $a = 3.9494$ Å and $c = 7.0396$ Å, whereas in LiFeAs, $a = 3.7754$ Å and $c = 6.3534$ Å (for a summary of structural parameters see table 1). The atomic sphere radii were chosen as $R_{Na} = 2.5$, $R_{Fe} = 2.3$, $R_{As} = 2.04$ au and $R_{Li} = 2.36$, $R_{Fe} = 2.28$, $R_{As} = 2.02$ au for NaFeAs and LiFeAs respectively. The sphere radii were chosen in such a way that the spheres were nearly touching.

3. Results and discussion

The measured XES and XAS spectra are shown in figure 1. The LiFeAs and NaFeAs Fe L_{2,3} XES (figure 1, bottom panels)

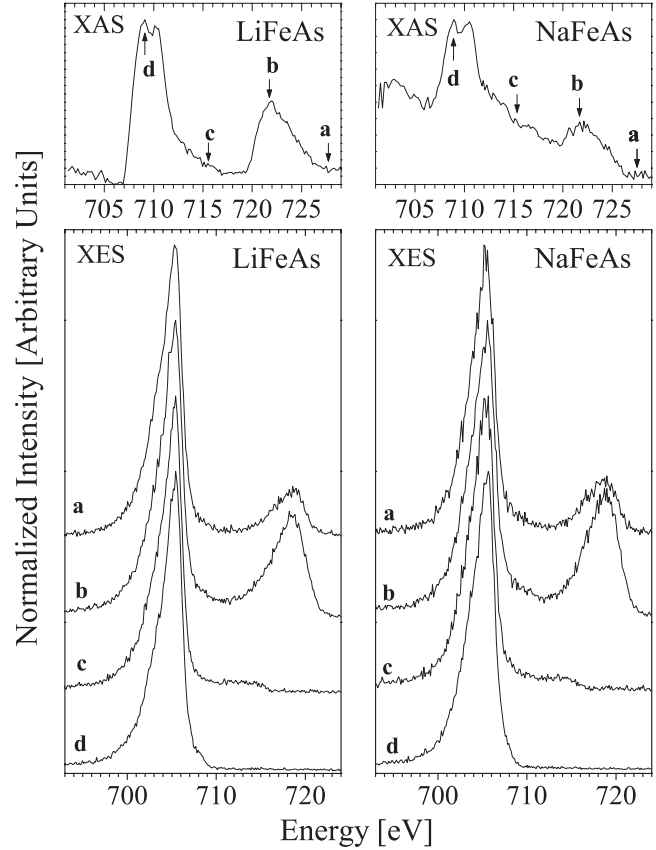


Figure 1. Summary of spectra for LiFeAs (left side) and NaFeAs (right side). The excitation energies for resonant Fe L_{2,3} XES are indicated by arrows in the XAS spectra in the left panels.

indicate two main bands located around 705 and 718 eV, these correspond to the Fe L₃ (3d4s → 2p_{3/2} transitions) and Fe L₂ (3d4s → 2p_{1/2} transitions) normal emission lines separated by the spin–orbital splitting of Fe 2p states. The non-resonant Fe L_{2,3} XES (XES curve a) for both materials lacks the low energy satellite structure typical for correlated systems (for instance for FeO [16]) and the main peak is sharp and similar to metallic iron [17]. The resonant XES spectra (XES curves b–d in the bottom panels of figure 1) show no energy-loss features; this indicates that even resonant Fe L_{2,3} XES probes mainly the partial DOS in these materials. The XAS spectra (top panels of figure 1) indicate the absorption thresholds for Fe 2p_{1/2} and 2p_{3/2} electrons, and are used to determine the appropriate excitation energies for resonant XES. The detailed features in XAS spectra reveal information about the Fe 3d unoccupied states (the conduction band), however due to the greater effective atomic potential when a 2p core electron is removed the states in a XAS spectra are greatly distorted from those in the unperturbed crystal; this is referred to as the ‘core-hole effect’.

The integral of the L₂ and L₃ peaks in a non-resonant XES measurement are related to the population of the 2p_{1/2} and 2p_{3/2} states respectively. For free atoms the ratio of the integrals of the L₂ and L₃ XES peaks (the $I(L_2)/I(L_3)$ ratio) should be equal to $\frac{1}{2}$. In metals the radiationless L₂L₃M_{4,5} Coster–Kronig (CK) transitions strongly reduce

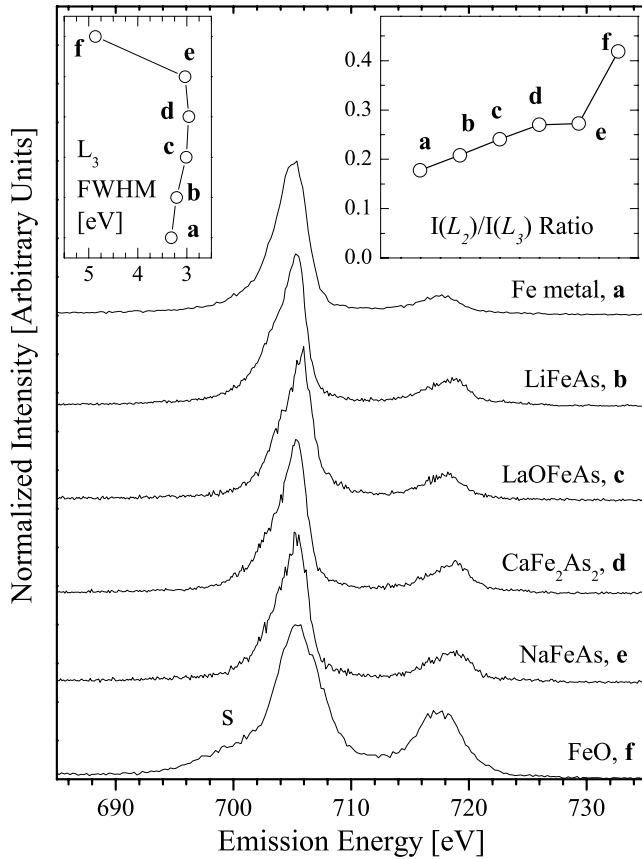


Figure 2. Comparison of the $L_{2,3}$ XES spectra for metallic Fe, LiFeAs, LaOFeAs [7], CaFe_2As_2 [8], NaFeAs, and FeO. Note the low energy shoulder *s* appears in FeO but not in any of the other spectra. The left inset shows the full width at half maximum (FWHM) of the Fe L_3 peak. The right inset shows the $I(L_2)/I(L_3)$ ratios for metallic Fe, LaOFeAs, CaFe_2As_2 , and correlated FeO. The $I(L_2)/I(L_3)$ ratio was calculated from the ratios of the integral under the L_2 and L_3 peaks, respectively.

the $I(L_2)/I(L_3)$ ratio [18]. Figure 2 illustrates that the $I(L_2)/I(L_3)$ ratio is almost identical for all previously mentioned FeAs compounds. This ratio is closer to that of metallic Fe than to that of FeO, and indicates that the Fe 3d states in FeAs compounds are much less correlated than those in FeO. Further, the low energy edge of the L_3 peaks in the FeAs compounds and metallic Fe lack the prominent satellite that is present in FeO. As previously mentioned this also supports the conclusion that the Fe 3d electrons in FeAs compounds are largely itinerant. For metallic compounds, the Fe 3d bandwidth should decrease with increasing Fe–Fe distance and decreasing number of Fe–Fe neighbours (see table 1), and this is somewhat demonstrated in the full width at half maximum (FWHM) of the Fe L_3 peak (figure 2, top left inset), which reduces from ~ 3.3 eV for Fe metal to ~ 3.0 eV for NaFeAs. Except for LaOFeAs, which we would expect to have a smaller FWHM than NaFeAs, the trend in decreasing FWHM qualitatively matches the trend in increasing Fe–Fe distance in table 1 for the metallic compounds. It should be noted that these changes in FWHM are less than the instrumental resolution by roughly a factor of two and that core-level spectroscopy is not an appropriate

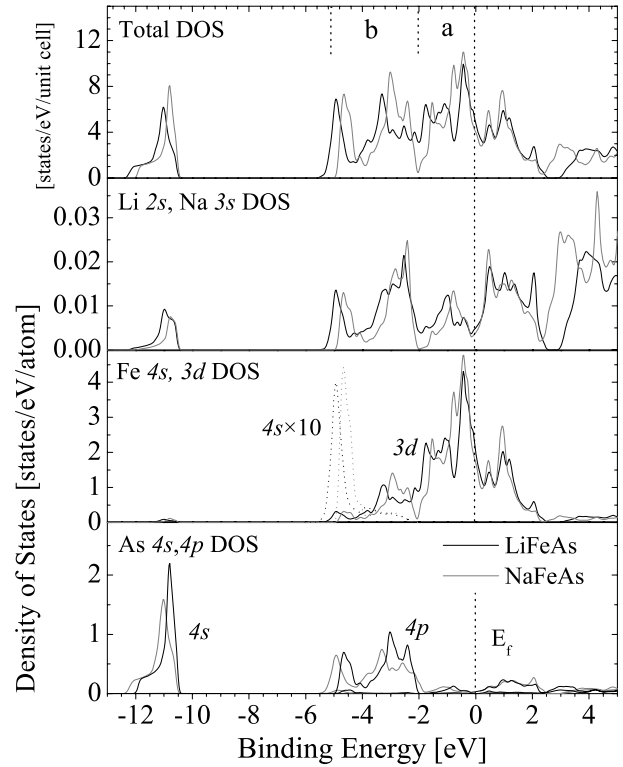


Figure 3. Calculated DOS for LiFeAs and NaFeAs. The dotted lines in the Fe 3s, 3p DOS plot refer to the 3s states increased by a factor of 10. The As 4s states are separated from the 4p states so they are plotted with the same line style. The y-axis in the total DOS plot is in units of (states/eV/unitcell). Two regions, a and b are identified in the total DOS plot. Fe 3d states dominate in region a. Roughly even contribution from Fe 3d states and As 4p states occurs in region b.

technique to probe this effect—so we do not attempt to draw any conclusions from this trend. There is, however, a clear difference in the FWHM between the FeAs compounds and FeO.

The calculated electronic structure of LiFeAs and NaFeAs are presented in figure 3. Our calculations match those performed in [6]. The calculated partial density of states (DOS) distribution is quite similar for both compounds. In particular, the density of states in the vicinity of the Fermi level (0 to -2 eV) is dominated by contributions from Fe 3d states (region a) and As 4p states mixed with Fe 3d, 4s states (region b) are located at the bottom of the valence band (-2 to -5.5 eV). The alkali earth 2s, 3s states (for Li and Na, respectively) provide a minimal but consistent contribution from 0 to -5.5 eV, these states hybridize with the Fe 3d states.

To compare the XES spectra with the calculated DOS in a meaningful way, we separated the L_3 band in the XES spectra into pseudo-Voigt components (of the form given in (1)). As discussed, XES probes the partial occupied density of states; however the DOS features are broadened by both the instrumental resolution (Gaussian in nature) and the core-hole lifetime [19] (Lorentzian in nature). We only fit the L_3 band since the L_2 band is basically the same partial occupied density of states with poorer statistics. The position μ_i , amplitude A_i , and Lorentz broadening Γ_i for each component are determined

by least-squares fitting. Here we set the Gaussian σ parameter to the position μ_i divided by the instrumental resolving power ($E/\Delta E$), and kept a consistent mixing factor η for all component peaks. We calculated best-fit curves with one to six pseudo-Voigt components and the quality of fit parameter $F'' = \sqrt{\sum_x (f_{\text{data}}(x) - f_{\text{fit}}(x))^2}$ was examined to determine the ‘simplest best fit’. Since least-squares fitting requires initial estimates for the fitted parameters, fitting was conducted several times for a given number of pseudo-Voigt components with range of different initial positions μ_i ; this quantity is the hardest to fit accurately and is also the one we are most interested in. The initial estimates for A_i , Γ_i , and η were set to 1.0, 1.0, and 0.5 respectively in all cases, these quantities are fitted quite well regardless of the initial estimate. We obtained consistent fits for several different initial estimates for μ_i , indicating that the fit is unbiased by our choice for initial conditions.

$$\begin{aligned}
 f_V &= A(\eta f_G + (1 - \eta) f_L) \\
 f_G &= \frac{1}{\sqrt{2\pi}\sigma} \exp\left(-\frac{(x - \mu)^2}{2\sigma^2}\right) \\
 f_L &= \frac{1}{\pi} \left(\frac{\frac{\Gamma}{2}}{(x - \mu)^2 + (\frac{\Gamma}{2})^2} \right).
 \end{aligned} \tag{1}$$

For LiFeAs four or more pseudo-Voigt components produced fits with F'' values within 10% of each other while the F'' for the best fit with three components was $\sim 25\%$ greater than the four component fit (see figure 4, top panel, inset). Likewise, three or more pseudo-Voigt components produced a consistently good fit for NaFeAs, whereas the F'' for the best two component fit was $\sim 50\%$ greater than that of the three component fit. The fit for NaFeAs was not as good as for LiFeAs because the NaFeAs data had more noise. The fitted curve for LiFeAs matches the measured Fe L_3 spectrum, and the components are located around the main features in the Fe 3d DOS calculation (figure 4, top panel). Only the main Fe 3d DOS feature at 705.5 eV is sharp and isolated enough to potentially provide a pure pseudo-Voigt spectrum, so we expect the fitted components at lower energies to have higher amplitudes relative to the pseudo-Voigt at 705.5 eV than a comparison of the representative heights of the Fe 3d DOS features at the Fermi energy and elsewhere in the valence band would indicate. For example, the ratio between the heights of the Fe 3d DOS feature plotted at 705.5 eV and the feature plotted at 702.8 eV in the top panel of figure 4 is much greater than the ratio between heights of the pseudo-Voigt component at 705.5 eV and the pseudo-Voigt component at 703.1 eV (see table 2), which is not unexpected since there are many other Fe 3d DOS features at ~ 703 eV within the instrumental resolution of each other, and all of them would contribute to the spectrum, but would not be independently resolvable.

The fitted curve for NaFeAs matches the measured Fe L_3 spectrum, but only one of the pseudo-Voigt components is in good agreement with a Fe 3d DOS feature (see figure 4, centre panel). It is likely that the poorer quality of the NaFeAs XES spectrum compared to the LiFeAs XES spectrum is to blame here; it is possible to obtain a good fit using four pseudo-Voigt

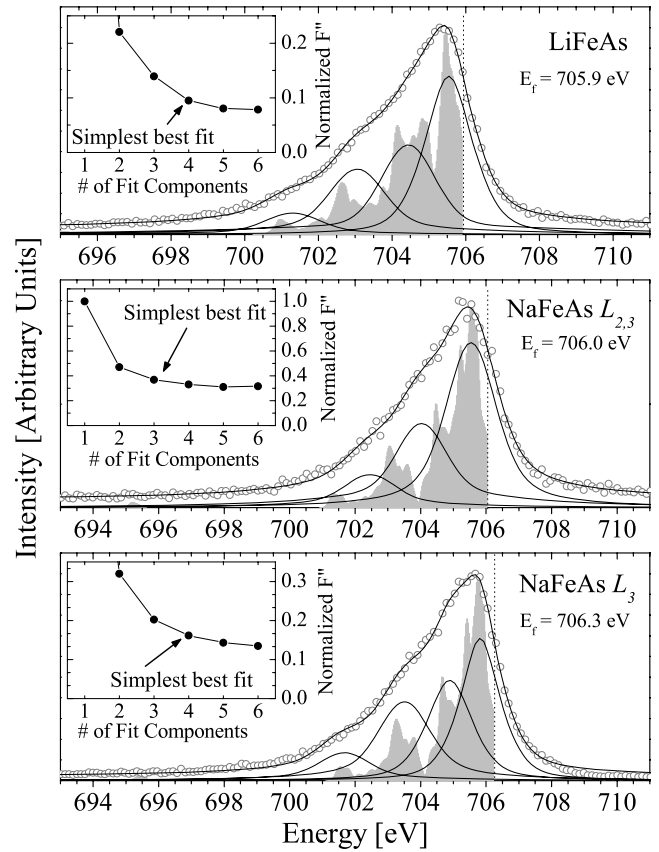


Figure 4. Comparison of calculated DOS and measured spectra. The top panel shows the L_3 peak of the Fe $L_{2,3}$ spectrum, the Fe 3d DOS, best-fit curve, and the 4 pseudo-Voigt components contributing to the best-fit curve for LiFeAs. The centre panel shows the L_3 peak of the Fe $L_{2,3}$ spectrum, the Fe 3d DOS, best-fit curve, and the 3 pseudo-Voigt components contributing to the best-fit curve for NaFeAs. The bottom panel shows the resonantly excited Fe L_3 spectrum, the Fe 3d DOS, best-fit curve, and the 3 pseudo-Voigt components contributing to the best-fit curve for NaFeAs. The insets show the normalized fit parameter F'' for fits with different numbers of pseudo-Voigt components for each material. Note that the maximum F'' has been scaled to 1.0 in each case—for example in LiFeAs the worst fit (with 1 pseudo-Voigt function) falls far outside the range of the plot. The estimated Fermi level is indicated in each plot.

components fixed at 705.5, 704.8, 703.0 and 701.2 eV as the features in the Fe 3d DOS suggest, however our aim was to identify features in the DOS from the XES spectra without requiring input from calculations.

Resonant XES spectra usually have better signal-to-noise ratio, and since these materials do not show significant energy-loss features in the resonantly excited spectra, we can attempt to fit the resonantly excited Fe L_3 spectrum by the method outlined above. In this case, four pseudo-Voigt components provide the optimal fit (figure 4, inset in bottom panel) and these components give a much better agreement to the Fe 3d DOS than the three component non-resonant XES fitting did (see figure 4, bottom panel). The fitted curve matches the measured spectrum except at the edge above 708 eV. This is not unexpected, since 708 eV is the excitation energy for this spectrum (see figure 1, top right panel) and the elastically

Table 2. Fit results for the 4 pseudo-Voigt peaks for fitting the Fe L_3 XES of LiFeAs and the 3 and 4 pseudo-Voigt peaks for fitting the non-resonant and resonant Fe L_3 XES of NaFeAs (NaFeAs_{*i*}^N and NaFeAs_{*i*}^R respectively). Note there is only one mixing factor η for all components in the same spectrum.

	η_i	A_i	μ_i (eV)	Γ_i (eV)
LiFeAs ₁	0.47	1.48	705.5	1.34
LiFeAs ₂		1.44	704.4	9.12
LiFeAs ₃		0.96	703.1	5.24
LiFeAs ₄		0.29	701.3	4.15
NaFeAs ₁ ^N	0.37	2.07	705.5	2.27
NaFeAs ₂ ^N		1.46	704.0	5.77
NaFeAs ₃ ^N		0.53	702.5	4.19
NaFeAs ₁ ^R	0.39	1.28	705.8	1.25
NaFeAs ₂ ^R		1.05	704.9	1.61
NaFeAs ₃ ^R		1.12	703.5	3.31
NaFeAs ₄ ^R		0.43	701.7	4.62

scattered x-ray peak will distort the spectrum near 708 eV—in particular by increasing the amplitude of the feature with less broadening (the elastic scatter has a purely Gaussian profile) then a pseudo-Voigt with parameters consistent with the remainder of the spectrum will be able to satisfy. The Fe L_3 XES band from the other measured spectra (curves b and c in figure 1 for both LiFeAs and NaFeAs) produced results consistent with those discussed above. In general, non-resonant XES should provide the best results if the signal-to-noise ratio is high enough, XES resonant with the L_3 feature may be used if there are no energy-loss features or prominent scattering features.

The Fermi levels in figure 4 were estimated by aligning the calculated DOS with the fitted pseudo-Voigt components, so the agreement between DOS and the first pseudo-Voigt component is manufactured. One method of estimating the Fermi level from emission spectra is to use the peak of the second derivative [20]. We have estimated Fermi levels of 705.9 eV, 706.0 eV, and 706.3 eV from aligning DOS and fit components and 706.5 eV, 706.8 eV, and 706.7 eV from the peak in the second derivative of the appropriate Fe L_3 XES for LiFeAs, non-resonant NaFeAs, and resonant NaFeAs, respectively. Since the main peak at 705.5 eV is so close to the Fermi level, the Fe 3d occupied states suffer an abrupt cutoff rather than a gradual decline at the Fermi level, and the L_3 XES portions at higher energies than that are due only to spectral broadening. It is therefore not unexpected that the XES second-derivative estimates of the Fermi level are greater than the curve-fit alignment Fermi level estimate by a shift of roughly the instrumental energy resolution.

To summarize, we have studied the electronic structure of LiFeAs and NaFeAs via resonant and non-resonant XES spectra and DFT calculations using the generalized gradient approximation. We demonstrate that pseudo-Voigt curve fitting of XES measurements without knowledge of the electronic structure can give good agreement with prominent features in the calculated valence band. The results from DFT calculations and the comparison of Fe L_3 FWHM and $I(L_2)/I(L_3)$ ratio with standard reference compounds suggests the Fe 3d states

are mostly itinerant in nature. The comparison of our results with previous studies on LaOFeAs and CaFe₂As₂ show that the main features of electronic structure found here are general for all studied FeAs-systems: Fe 3d states dominate near the Fermi level and As 4p states are concentrated at the bottom of the valence band. We conclude that all FeAs-systems studied herein are weakly or moderately correlated systems.

Acknowledgments

We acknowledge support of the Research Council of the President of the Russian Federation (Grants NSH-1929.2008.2 and NSH-1941.2008.2), the Russian Science Foundation for Basic Research (Project 08-02-00148), the Natural Sciences and Engineering Research Council of Canada (NSERC), the Canada Research Chair program and the United Kingdom Engineering and Physical Sciences Research Council (EPSRC) for funding under grant EP/E025447.

References

- [1] Pitcher M J, Parker D R, Adamson P, Herkelrath S J C, Boothroyd A T and Clarke S J 2008 *Chem. Commun.* **45** 5918
- [2] Tapp J H, Tang Z, Lv B, Sasmal K, Lorenz B, Chu P C W and Guloy A M 2008 *Phys. Rev. B* **78** 060505(R)
- [3] Wang X C, Liu Q Q, Lv Y X, Gao W B, Yang L X, Yu R C, Li F Y and Jin C Q 2008 arXiv:0806.4688 [cond-mat]
- [4] Parker D R, Pitcher M J and Clarke S J 2008 arXiv:0810.3214 [cond-mat]
- [5] Chu C W, Chen F, Gooch M, Guloy A M, Lorenz B, Lv B, Sasmal K, Tang Z J, Tapp J H and Xue Y Y 2009 *Physica C* at press (Chu C W, Chen F, Gooch M, Guloy A M, Lorenz B, Lv B, Sasmal K, Tang Z J, Tapp J H and Xue Y Y 2009 arXiv:0902.0806 [cond-mat])
- [6] Jishi R A and Alyahyaie H M 2008 arXiv:0812.1215v1 [cond-mat]
- [7] Kurmaev E Z, Wilks R G, Moewes A, Skorikov N A, Izyumov Yu A, Finkelstein L D, Li R H and Chen X H 2008 *Phys. Rev. B* **78** 220503(R)
- [8] Kurmaev E Z, McLeod J A, Buling A, Skorikov N A, Moewes A, Neumann M, Korotin M A, Izyumov Yu A, Ni N and Canfield P C 2009 arXiv:0902.1141 [cond-mat]
- [9] Jia J J, Callcott T A, Yurkas J, Ellis A W, Himpfel F J, Samant M G, Stöhr J, Ederer D L, Carlisle J A, Hudson E A, Terminello L J, Shuh D K and Perera R C C 1995 *Rev. Sci. Instrum.* **66** 1394
- [10] Blaha P, Schwarz K, Madsen G K H, Kvasnicka D and Luitz J 2001 *WIEN2k, An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties* ed K Schwarz, Techn. Universität Wien, Austria, ISBN 3-9501031-1-2
- [11] Perdew J P, Burke K and Ernzerhof M 1996 *Phys. Rev. Lett.* **77** 3865
- [12] Chen G F, Li Z, Wu D, Li G, Hu W Z, Dong J, Zheng P, Luo J L and Wang N L 2008 *Phys. Rev. Lett.* **100** 247002
- [13] Ronning F, Klimczuk T, Bauer E D, Volz H and Thompson J D 2008 *J. Phys.: Condens. Matter* **20** 322201
- [14] Basinski Z S, Hume-Rothery W and Sutton A L 1955 *Proc. R. Soc.* **229** 459

- [15] Fjellvag H, Gronvold F, Stolen S and Hauback B C 1996 *J. Solid State Chem.* **124** 52
- [16] Galakhov V R, Poteryaev A I, Kurmaev E Z, Anisimov V I, Bartkowski St, Neumann M, Lu Z W, Klein B M and Zhao T-R 1997 *Phys. Rev. B* **56** 4584
- [17] Gao X, Qi D, Tan S C, Wee A T S, Yu X and Moser H O 2006 *J. Electron. Spectrosc. Relat. Phenom.* **151** 199
- [18] Kurmaev E Z, Ankudinov A L, Rehr J J, Finkelstein L D, Karimov P F and Moewes A 2005 *J. Electron. Spectrosc. Relat. Phenom.* **148** 1
- [19] Goodings D A and Harris R 1969 *J. Phys. C: Solid State Phys.* **2** 1808
- [20] Kurmaev E Z, Wilks R G, Moewes A, Finkelstein L D, Shamin S N and Kuneš J 2008 *Phys. Rev. B* **77** 165127