

Organosulfur polymer batteries with high energy density

Noboru Oyama^{a,*}, Tetsu Tatsuma^a, Tadashi Sotomura^b

^a Department of Applied Chemistry, Faculty of Technology, Tokyo University of Agriculture and Technology, Naka-cho, Koganei, Tokyo 184, Japan

^b Corporate Research Division, Matsushita Electric Industries Co., Ltd., 3-1 Yagumo-nakamachi, Moriguchi, Osaka 570, Japan

Accepted 14 October 1996

Abstract

The redox reaction of 2,5-dimercapto-1,3,4-thiadiazole (DMcT) at the electrode surfaces is slow at room temperature and influenced strongly by the acidity of the solutions. However, this reaction can be accelerated when the electron-transfer reaction is coupled with that of polyaniline (PAN). PAN can be used as a molecular current collector for the insulating organosulfur compounds which are promising high capacity energy storage materials. The charge/discharge capability of a polymer composite cathode prepared from DMcT, PAN, 3-alkylcarboxylate-4-methylpyrrole and acetylene black has been investigated on different types of current collector, such as copper and porous carbon film, in a lithium-cell system with a gel-like polymer electrolyte. A battery assembled from the polymer composite cathode with a copper current collector provides a flat discharge potential difference from 3.4 to 2.8 V and high current capability (137–194 A/kg-cathode) without undue deterioration of the energy density. The battery can be charged up to 550 Wh/kg-cathode within 1.25 h and reversibly discharged within 1.25 h. © 1997 Elsevier Science S.A.

Keywords: Cathode materials; Polymer batteries; Organosulfur compounds

1. Introduction

The increasing popularity of portable electronics has created a strong, unfulfilled demand for rechargeable batteries which possess high gravimetric energy density. The most likely products to meet this demand are those based on lithium-ion (or 'rocking-chair') technology. Recent advances in developing lithium-intercalated anodic materials to replace the traditional highly reactive lithium metal anodes in these batteries are quite promising. However, the development of active cathode materials to increase the overall storage capacity of the cell has been slow and mainly centered on materials based on metal salts of lithium, although some works have been done on cathode materials based on conducting polymers, with limited success.

We have developed an active cathode material based on the combination of a conducting polymer such as polyaniline (PAN) and an organosulfur compound such as 2,5-dimercapto-1,3,4-thiadiazole (DMcT) as shown in Fig. 1. Cathodes made using composites of these materials exhibit extremely high energy capacities (about 185 Ah/kg) and reasonable discharge voltages (average 3.4 V) versus a lithium metal anode to give a gravimetric energy density of > 600 Wh/kg-cathode [1]. Further improvements in our

system have shown the promise of this type of chemistry to provide reliable, non-toxic, extremely high energy density batteries. These improvements also included the use of a polypyrrole dopant to increase the charging rate of the cell, the use of a copper current collector to increase substantially the cycling stability of the cell, and our recent elucidation of the proton-transfer processes which may be responsible for the electrochemical behavior of the composite. These advances in the technology and its understanding taken together with the fact that organosulfur compounds similar to DMcT, for example *N,N,N,N*-tetramercapto-ethylenediamine, possess theoretical energy capacities of up to 582 Ah/kg-cathode indicate that the study of this general system has a great promise.

In this contribution, we report some details of our recent advances regarding the chemistry of the PAN/DMcT cathode material, emphasizing the improvements in cycling stability due to the use of a copper current collector and the conceptual breakthrough in the understanding of the proton coupled redox processes in the cathode.

2. Experimental

2.1. Materials

Chemically polymerized PAN in powder form (undoped, reduced form) was obtained from Nitto Denko, Japan.

* Corresponding author.

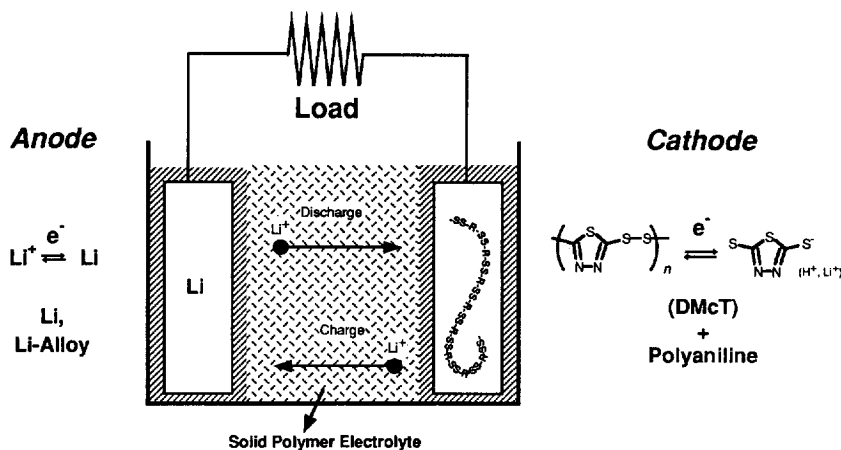


Fig. 1. Configuration of lithium secondary battery which includes a PAN/DMcT cathode.

PAMPy (reduced form) was purchased from Nippon Soda, Japan. Battery-grade lithium foil of 300 μm thick was obtained from Kyokuto Metal, Japan. A porous carbon film of 85 μm thick consisting of fluoropolymer and carbon black powder (density: 0.95 g/cm^3 , volume resistivity: 0.46 Ωcm) was obtained from Japan Goretex. It was laminated with a 30 μm thick titanium foil. Copper, nickel, aluminum and titanium foil of 30 μm thick were obtained from Takeuchi Metal, Japan. Gold (400 nm thick)-plated titanium foil was prepared by a vacuum deposition method. All other chemicals were purchased from Kanto Chemical and used after proper purification treatments.

2.2. Preparation of gel-like polymer electrolyte

A gel-like polymer electrolyte was prepared under a dry argon atmosphere by dissolving 2.3 g LiBF_4 in a mixture of 7.9 g ethylene carbonate (EC) and 10.5 g propylene carbonate (PC); dispersing 2.5 g acrylonitrile–methylacrylate copolymer powder in the resulting electrolyte solution, heating the dispersion at 120 to 150 $^\circ\text{C}$ in a sealed Teflon container until a viscous transparent liquid was obtained. The liquid was cast on a stainless-steel pad (120 mm \times 95 mm), sealed with an aluminum laminated bag, and cooled at -20 $^\circ\text{C}$ overnight.

2.3. Cell testing

A test cell was charged and discharged at a constant current for a given time. The charging/discharging current and time were defined on the basis of the theoretical capacity (for further details see Section 3). The upper potential difference of charging was limited to 4.65 V. If the potential difference of 4.65 V was reached in the course of charging, the charging was continued at a constant potential difference of 4.65 V until a given charging time fully elapsed. The discharging was cut off when the potential difference of 2.0 or 2.85 V was reached. The cell was allowed to stand for 0.5 h before discharging. All the charge/discharge experiments were car-

ried out at 20 $^\circ\text{C}$ using a computer-controlled automatic battery charging/discharging instrument.

3. Results and discussions

3.1. Reactivity of organosulfur compounds

The reversible conversion of DMcT between polymerized and depolymerized forms corresponds to the formation and cleavage processes of the disulfide bond (Fig. 1), which accompanies the electron-transfer processes. The theoretical capacity of poly(DMcT) is 362 Ah/kg-cathode. However, since the redox reaction of a disulfide is very slow at room temperature, the performance of a battery which consists of an organosulfur cathode is reasonable only at higher temperatures [2]. The redox reaction processes of DMcT can be accelerated in a PAN matrix and, thus, even at room temperature the DMcT–PAN composite film can act as a cathodic material in a secondary battery [1,3,4].

In the redox reaction processes of the DMcT–PAN film, it has been shown that a proton-transfer reaction between DMcT and PAN plays an important role in the reaction activity [4–7]. Therefore, it is of interest to examine how the protonation and deprotonation processes of the mercapto-thiadiazole influence the activity of the redox reaction processes. The effects of the addition of acid and base on the redox reaction of thiadiazoles were examined via electrochemistry and semi-empirical molecular orbital calculations [6]. It was found that the electrochemical oxidation from thiol to disulfide was promoted by the deprotonation at the thiol group. Changes of the electronic state of the thiadiazole ring due to the protonation at two nitrogen atoms in the ring or of the substituent thiolate group affect the reduction processes of the disulfide bond, whereby, the protonation of the thiadiazole ring or substituents facilitates cleavage of the disulfide bond. In addition, it was found that the reduction current of the oxidized DMcT is enhanced by the addition of pyridine [7]. The results described above predict that this acceleration will depend strongly upon the acidity within the polymer matrix.

3.2. Polydisulfide–polyaniline composite cathode

Conducting polymers such as a PAN, which possess electronic conductivity as well as capability of storing charges, have attracted attention as the electrode materials for rechargeable batteries. However, conducting polymers are not very stable in general because stored charges exist as radicals on conducting polymers. Since PAN is a relatively stable conducting polymer, it has been commercialized as a cathode of rechargeable batteries [8]. PAN can store one positive charge per monomer unit theoretically, so that it can potentially attain an energy density of 450 Wh/kg-cathode. However, PAN stores only 0.5 positive charges per monomer unit in non-acidic media, otherwise it loses protons on its nitrogen atoms. Therefore, stored energy of PAN has never exceeded metal oxides as a cathode.

Reversible electron transfer was observed between PAN and thiol/disulfide couples of DMcT, 2-mercapto-5-methyl-1,3,4-thiadiazole, 2-mercaptopyridine and thiophenol [4]. Thus, PAN can be used as a molecular current collector for those insulating organosulfur compounds at room temperature, probably because of the chemical interaction between organosulfur and PAN. Among those couples, DMcT exhibited the fastest reversible electron transfer. Electron transfer from other aromatic and aliphatic thiols to oxidized PAN is also observed. The reactions and reaction kinetics were affected by protons.

Then, we composed cathodes from DMcT and PAN [1]. The composite cathodes were prepared by casting *N*-methyl-2-pyrrolidone (NMP) solution containing both DMcT and PAN. Preparation of the cathodic materials in this way allows intimate molecular-level mixing between DMcT and PAN, both of which are redox active at the cathode. Further, rechargeable batteries were fabricated by coupling the composite cathode with a lithium anode and a polymer electrolyte.

When the battery was charged at 4.75 V, the cathode exhibited a discharge capacity of over 185 Ah/kg-cathode and gravimetric energy density of over 600 Wh/kg-cathode. The theoretically expected maximum discharge capacity of PAN in the composite cathode is 65 Ah/kg-cathode (one electron is assumed to be consumed per one aniline monomer unit). That of DMcT in the cathode is 159 Ah/kg-cathode (a two-electron reaction is assumed). The experimentally evaluated discharge capacity of 185 Ah/kg-cathode is thus more than 80% of the overall theoretical capacity of 224 Ah/kg-cathode.

A polymer composite cathode prepared from DMcT and PAN shows high gravimetric energy density when it is coupled with a lithium anode. However, charging and discharging currents should be 35 A/kg-cathode or less, otherwise the cycle life is shortened. This value is not enough for practical use. Then, we added a polypyrrole derivative to the DMcT–PAN composite to make it more conductive [9]. The addition of the polypyrrole derivative enabled the rapid charging at 87 A/kg-cathode without undue deterioration of

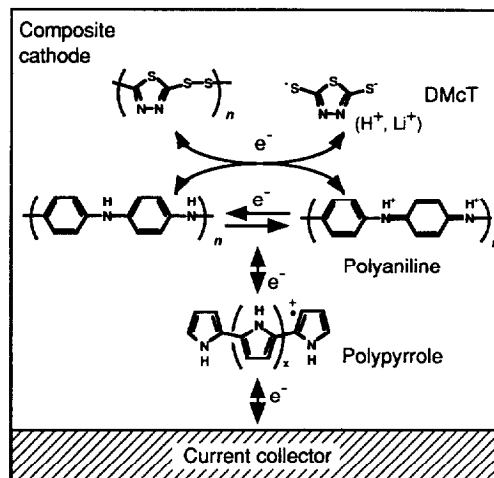


Fig. 2. Modeling of charge-transfer reactions in the composite cathode film.

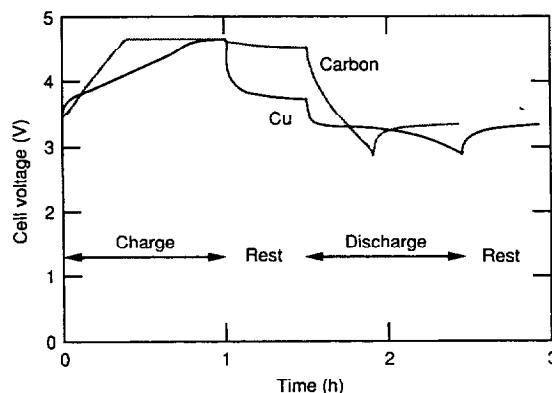


Fig. 3. Charge/discharge curves of the 15th cycle of lithium cells with copper and carbon cathode current collectors: the cells are charged and discharged at a rate of 0.83 C at 20 °C.

energy density. That is, the polypyrrole derivative functions as subsidiary molecular current collector (Fig. 2).

3.3. High rate capabilities of the composite cathode with a copper current collector

The cells with carbon and copper current collectors exhibited better cycle performances than those with nickel, aluminum and titanium foil. We compare cells with carbon and copper current collectors under the same conditions, at higher charge/discharge rates [10].

Fig. 3 shows the results of charge/discharge testing of the cells with copper and carbon cathode current collectors at 0.83 C, where 1 C defined the charge/discharge current of the (cathode theoretical capacity (Ah/kg)) × (cathode weight (kg)). The cells with a copper current collector gave a quite stable cell performance. Discharge capacities of the cells were around 150 Ah/kg-cathode. On the other hand, although the cell with a carbon current collector exhibited stable cycle abilities at a charging current of 0.095 C (not shown here), a greater charging current lowered the stability. That is, the cycle performance of the cells with the copper

current collector were much better than those of cells with the carbon current collector.

Cells with a copper current collector exhibited a stable cycle performance over 250 cycles (at 0.5 C, 220 ± 10 A h/kg-cathode). This capacity exceeded the theoretical capacity (186 Ah/kg) calculated from the amount of PAn and DMcT contained in the cathode. This indicates that not only DMcT and PAn but also copper ion dissolving from the current collector function as a cathode-active material in the present cell. Actually, we observed the dissolution of a slight amount of copper in the first charging process. In addition, the discharge curves of DMcT-conducting polymer cathodes were flattened by using the copper current collector, retaining high energy-storage capability with low weight and good mechanical strength. Work is currently in progress toward preparing and characterizing Cu–DMcT complexes and fabricating a cathode by coupling them with electrochemically inert current collectors.

Acknowledgements

The authors are grateful to A. Kaminaga, T. Sato, H. Matsui, Y. Yokoyama, Dr E. Shouji, Dr J.M. Pope and Professor

D.A. Buttry for their help. This work was supported in a part by a Grant-in-Aid for Scientific Research (No. 09232214) on Priority Areas (No. 277) from the Ministry of Education, Science, Sports and Culture of Japan.

References

- [1] N. Oyama, T. Tatsuma, T. Sato and T. Sotomura, *Nature*, **373** (1995) 598.
- [2] M. Liu, S.J. Visco and L.C. De Jonghe, *J. Electrochem. Soc.*, **138** (1991) 1891.
- [3] A. Kaminaga, T. Tatsuma, T. Sotomura and N. Oyama, *J. Electrochem. Soc.*, **142** (1995) L47.
- [4] T. Tatsuma, H. Matsui, E. Shouji and N. Oyama, *J. Phys. Chem.*, **100** (1996) 14016.
- [5] E. Shouji, Y. Yokoyama, J.M. Pope, N. Oyama and D.A. Buttry, *J. Phys. Chem.*, in press.
- [6] E. Shouji, H. Matsui and N. Oyama, *J. Electroanal. Chem.*, **417** (1996) 17.
- [7] J.M. Pope, E. Shouji and N. Oyama, submitted for publication.
- [8] E. Daifuku, T. Kawagoe and T. Matsunaga, *Denki Kagaku*, **57** (1989) 557.
- [9] T. Tatsuma, T. Sotomura, T. Sato, D.A. Buttry and N. Oyama, *J. Electrochem. Soc.*, **142** (1995) L182.
- [10] T. Sotomura, T. Tatsuma and N. Oyama, *J. Electrochem. Soc.*, **143** (1996) 3152.