

Short communication

LiMn₂O₄ electrode prepared by gold–titanium codeposition with improved cyclability

Ali Eftekhari*

Electrochemical Research Center, P.O. Box 19395-5139 Tehran, Iran

Received 9 February 2003; received in revised form 28 August 2003; accepted 24 November 2003

Abstract

An LiMn₂O₄ electrode was prepared based on mixed-metals (gold–titanium) codeposition method. By this method, titanium oxide is also incorporated into the electroactive film formed on substrate electrode. Formation of titanium oxide on the spinel surface avoids dissolution of Mn from the spinel at elevated temperatures. TiO₂ can act as a bridge between the spinel particles to reduce the interparticle resistance and as a good material for the Li intercalation/deintercalation. Thus, electrochemical performance of the LiMn₂O₄ spinel can be improved by the surface modification with TiO₂. This action improves cyclability for lithium battery performance and reduces capacity fades of LiMn₂O₄ at elevated temperatures.

© 2004 Elsevier B.V. All rights reserved.

Keywords: LiMn₂O₄; Cyclability; Capacity fade; Surface modification; Au-codeposition; TiO₂

1. Introduction

LiMn₂O₄ is a promising candidate cathode material for lithium secondary battery applications due to its noticeable advantages such as nontoxicity, inexpensivity, etc. However, its significant capacity fade at elevated temperatures is the greatest obstacle in the commercialization of this valuable cathode material. This phenomenon can be attributed to different reasons such as manganese dissolution [1,2], formation of oxygen deficiencies [3], electrolyte decomposition [4], Jahn-Teller distortion [5], cation mixing between lithium and manganese [6] and loss of crystallinity during cycling [7]. This disadvantage can be reduced by surface modification of LiMn₂O₄ with LiCoO₂ to avoid Mn dissolution and other responsible phenomena [8,9]. More recently, Kannan and Manthiram [10] have reported that metal oxides can also be used for the surface modification of LiMn₂O₄ as well as LiCoO₂ and other modifiers. The surface modification can be carried out by mixing the modifier with LiMn₂O₄ spinel before the deposition process.

Another important subject of research in studies of LiMn₂O₄ as cathode material is the investigation of different deposition methods. Various methods such as electron-beam evaporation [11], RF magnetron sputtering [12], pulsed

laser deposition [13], chemical vapor deposition [14], etc. have been proposed for the deposition of thin films of LiMn₂O₄ suitable for the practical use. The main advantage of these methods is the ability to add doping cations which modifies the capacity fading of LiMn₂O₄. A low capacity fade is, in fact, the most important requirement for commercial applications. As the above-mentioned methods are based on high-technology, high-energy techniques, proposing simple methods for the deposition of cathode materials is very interesting for the development of lithium secondary batteries. In previous works [15,16], we have successfully used gold-codeposition method [17] for the fabrication of LiMn₂O₄ cathodes. The simplicity of this method is the interesting advantage in comparison with available high-technology methods. In this work, we show that the unique advantage of the high technology methods, i.e. the addition of the modifiers to LiMn₂O₄ films, is also achieved by the simple gold-codeposition method. In addition, a new modifier to improve the cyclability of LiMn₂O₄ particularly at elevated temperature is introduced.

2. Experimental

Nanostructured LiMn₂O₄ spinel was synthesized similar to the previous work [18]. Detailed characterization of the synthesized LiMn₂O₄ spinel has been reported in the literature [19]. Small particles (smaller than 100 nm)

* Tel.: +98-21-204-2549; fax: +98-21-205-7621.

E-mail address: eftekhari@elchem.org (A. Eftekhari).

have been used for the present study, as large particles are not suitable for codeposition method. The deposition of LiMn_2O_4 was carried out during deposition of gold and codeposition of gold–titanium on a Pt substrate. The electroactive material (LiMn_2O_4) is deposited onto the substrate surface as the result of occlusion between the gold particles deposited. The presence of gold in the deposit does not cause any problem in the electrode performance, since gold does not provide any electrochemical reaction in the potential range of our experiments.

The deposition process was performed using a solution containing 15 g/l of potassium gold cyanide, 80 g/l of monopotassium phosphate, 70 g/l of potassium citrate and 1.5 g/l of titanium chloride with near-neutral pH, as the deposition electrolyte. The solution contains Ti hydroxide as a result of the hydrolysis of titanium chloride in water [20].

Due to the small amount of the titanium oxide modifier incorporated into the LiMn_2O_4 film, the exact form (whether crystalline or composition) of the electroactive material cannot be determined by XRD to understand if the modification of the LiMn_2O_4 spinel was physical (surface covering of the spinel particles) or chemical (e.g. formation of $\text{LiTi}_x\text{Mn}_{2-x}\text{O}_4$). As the electroactive material is incorporated within the gold film deposited, it is difficult to inspect the presence of TiO_2 on the spinel particles. Even sequential Ar^+ -ion sputtering and XPS analysis, which is a common way for depth analysis of electroactive materials to inspect the distribution of the modifier, was not successful for the present case. Nevertheless, we have found that the dissolution of the deposit in acidic medium for elemental analysis is a reliable way to estimate the Ti content. The results obtained from the elemental analysis of Ti showed that the amount of titanium oxide (or hydroxide) in the electroactive material deposited is about 4 wt.%. The amount of gold deposited is about 50–60 wt.% of the total deposit.

A small amount of LiMn_2O_4 (ca. 40 μg) was also added to the deposition electrolyte solution (plating bath). The electrolyte solution was stirred for a few minutes before the deposition process to reach a well-conditioned suspension. The deposition process was carried out by applying a cathodic current of 4.0 mA in a warm bath (50 °C). The electrode was washed thoroughly to remove any potassium ion from its surface, and heated at 200 °C for 1 h to remove water.

The amount of the deposit was determined by weighing the electrode before and after the deposition process. This is related to the overall mass of the deposit including the Au and also the titanium oxide codeposited. The amount of LiMn_2O_4 deposited onto the substrate surface was also checked by weighing the insoluble LiMn_2O_4 added to the plating bath before and after the deposition process. Indeed, weighing the amount of spinel in the plating bath before and after the deposition process is for one experience the best approach. However, the use of both approaches is desirable to obtain a reliable value for the amount of electroactive material used for the preparation of the cathode and to know the Au/spinel ratio of the deposit.

As the amount of titanium ions in the plating bath (and consequently the amount of titanium oxide incorporated into the deposits) is very small, there is no significant difference in the mass and thickness of the films deposited by gold-codeposition and mixed-metals (gold–titanium) codeposition methods. Indeed, the amount of LiMn_2O_4 attached to the substrate surface was $13 \mu\text{g} \pm 0.2$ and the film thickness estimated by S.E.M. was about 2.2 μm for the cathodes prepared with and without titanium oxide modifier. However, the presence of Ti hydroxide should not make any problem in our investigation, as metal hydroxides are also responsible for the surface modification of LiMn_2O_4 [10].

The LiMn_2O_4 electrodes prepared using gold-codeposition method are referred to as unmodified electrodes, as LiMn_2O_4 was simply attached to the substrate surface. The electrodes prepared using the mixed-metals (gold–titanium) codeposition approach are referred to as modified electrodes, as titanium oxide generated during the Ti electrodeposition can act as a surface modifier of the LiMn_2O_4 spinel. The two different types of electrodes were investigated and compared to understand the advantages of the modifier material and the deposition approach proposed. The reproducibility of the results obtained was verified by fabricating several similar electrodes (by gold-codeposition or mixed-metals (gold–titanium) codeposition methods). The electrochemical measurements were performed in a conventional cell containing a lithium metal anode and the prepared cathodes of LiMn_2O_4 electrodes as cathodes. The electrolyte solution was 1 M LiPF_6 in ethylene carbonate (EC) and diethyl carbonate (DEC).

3. Results and discussion

Addition of a small amount of titanium oxide does not make significant change in the electrochemical behavior and the spectroscopic characteristics of LiMn_2O_4 , which were approximately similar to those reported for the LiMn_2O_4 prepared by the gold-codeposition [16,17].

Fig. 1 shows the discharge characteristics of both unmodified and modified LiMn_2O_4 electrodes. While the discharge profiles are similar, it is evident that the modification of LiMn_2O_4 by the incorporation of titanium oxide greatly enhances the electrode capacity, as shown by the higher capacity delivered in the first cycle by the modified LiMn_2O_4 electrode in comparison with the unmodified LiMn_2O_4 electrode. It should be taken into account that the specific capacity is calculated in accordance with the net weight of LiMn_2O_4 spinel included into the deposits.

This can be due to the fact that metal oxides can act as Li intercalating materials and most of them have higher theoretical capacity for this process in comparison with LiMn_2O_4 . For example, LiCoO_2 -modified LiMn_2O_4 has higher capacity than unmodified LiMn_2O_4 . Of course, intercalation of Li into TiO_2 is not the only possible reason for

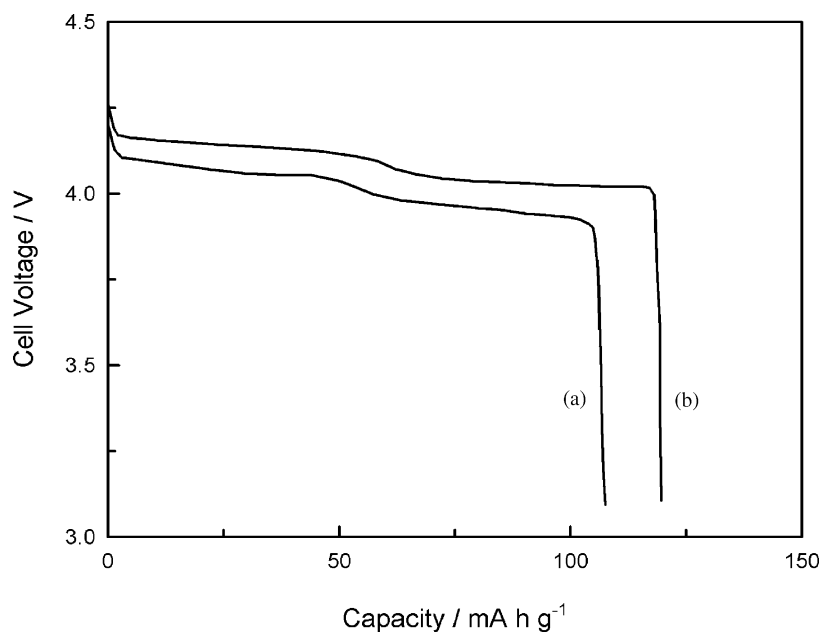


Fig. 1. Discharge characteristic of (a) the unmodified LiMn_2O_4 electrode and (b) the modified LiMn_2O_4 electrode prepared by the incorporation of titanium oxide recorded at the rate of $C/5$.

the enhanced capacity of the cathode, as the dispersed particles may provide easier diffusion of Li ions to reach or leave the spinel particles upon insertion and extraction. Also, the TiO_2 particles may act as contact bridges between the spinel particles reducing the interparticle resistance, thus facilitating the insertion–extraction process across the electroactive material mass. Of course, the specific capacity of the modified electrode is still lower than the theoretical capacity of LiMn_2O_4 .

From Fig. 1, it is obvious that the cell voltage of the TiO_2 -modified LiMn_2O_4 cathode is higher than the TiO_2 -free cathode. This behavior cannot be attributed to the presence of TiO_2 , which is known to intercalate Li at significantly lower voltages in comparison with LiMn_2O_4 [21–24]. Also, it should not be related to the modification method employed, since it has been reported that the modification of LiMn_2O_4 with similar metal oxide (cobalt oxide) by using mixed-metals codeposition had no effect on the cell voltage [16]. Such increase in the intercalating voltage of LiMn_2O_4 may be due to the chemical modification of the spinel to form $\text{LiTi}_x\text{Mn}_{2-x}\text{O}_4$, though, it is not very probable, since chemical modification of LiMn_2O_4 usually occurs at high temperature (e.g. 600°C) which were not used here. The exact reaction for the observed increased cell voltage of TiO_2 -included LiMn_2O_4 cathode is not still clear.

The evolution of capacity during cycling in the potential range of 3.0–4.3 V at $C/5$ rate and room temperature of the modified and unmodified LiMn_2O_4 electrodes is compared in Fig. 2. The results indicate that the incorporation of titanium oxide within the LiMn_2O_4 film deposited, significantly reduces the capacity fade of LiMn_2O_4 .

As the main problem for the use of LiMn_2O_4 is the capacity fade at elevated temperatures, the experiments were also

carried out at 60°C . Fig. 3 clearly shows that the capacity fade of LiMn_2O_4 at elevated temperatures can be significantly reduced by the incorporation of titanium oxide into the LiMn_2O_4 film. Although the influence of temperature to increase the initial capacity is stronger for unmodified LiMn_2O_4 [10], the initial capacity of the modified LiMn_2O_4 electrode is still higher than that of the unmodified LiMn_2O_4 electrode. The XRD pattern in the discharged state after cycling at 60°C for over 100 cycles displays significant peak broadening, which indicates structural degradation and a decrease of crystallinity of the LiMn_2O_4 electrode prepared by the gold codeposition method. Whereas, such behavior is not shown in the LiMn_2O_4 electrode prepared by the mixed-metals (gold–titanium) codeposition method.

Similar results were also obtained for storage at elevated temperatures. Table 1 shows the capacity loss of both electrodes stored at 70°C for 48 h. The values of capacity fading percentage (CFP) of the electrodes indicate the ratio of the difference in discharge capacity before and after the storage divided by the discharge capacity before the storage. The amount of Mn dissolved during the storage was estimated by the measurement of the amount of Mn dissolved in 10 ml of the supporting electrolyte used for the storage. The results obviously suggest that the approach proposed for the surface modification of LiMn_2O_4 spinel with TiO_2 is useful to reduce capacity fading of LiMn_2O_4 stored at elevated temperatures.

For further investigation of the improvement achieved by the modification approach proposed, effects of both storage temperature and time on the capacity fading and the Mn dissolution at fully charged state were examined in detail. As expected, Mn dissolution and consequently the capacity loss of the cathode material increase by increasing storage

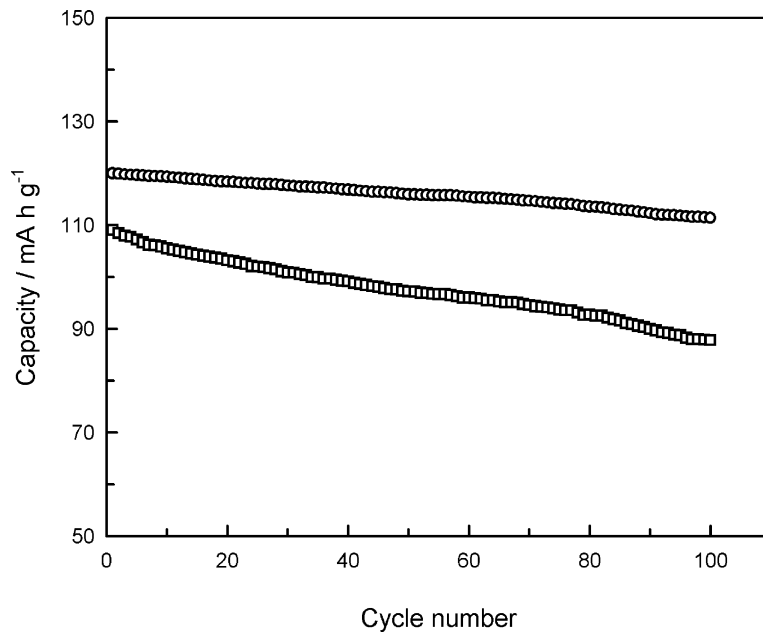


Fig. 2. The variations of the capacity for the cells with the modified LiMn₂O₄ (□) and the unmodified LiMn₂O₄ cathodes (○) during charge–discharge cycling at room temperature (25 °C).

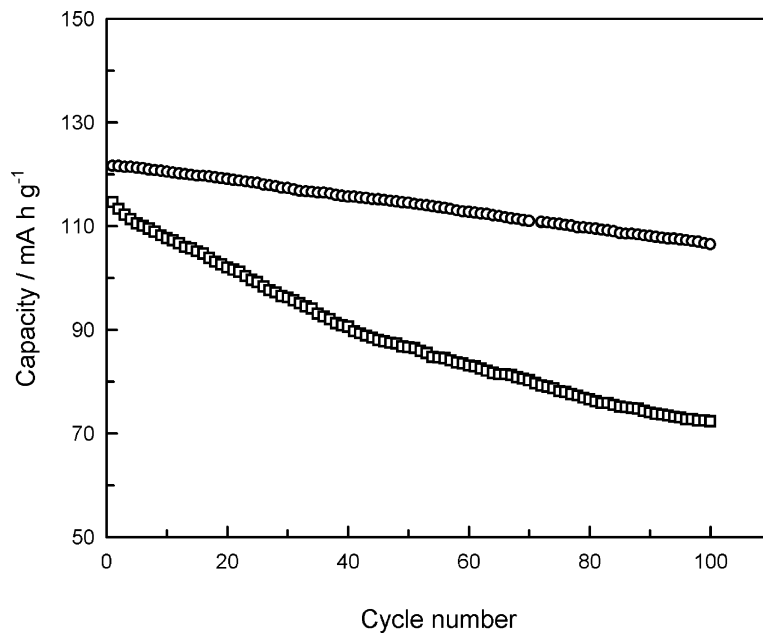


Fig. 3. The variations of the capacity for the cells with the unmodified LiMn₂O₄ (□) and the modified LiMn₂O₄ (○) cathodes during the charge–discharge cycling at the elevated temperature of 60 °C.

Table 1

Specific capacity and capacity fading of both unmodified LiMn₂O₄ electrode and TiO₂-modified LiMn₂O₄ electrodes after storage at 70 °C for 48 h

| Electrode | Concentration of dissolved Mn (μg) | Specific discharge capacity (mA h/g) | | CFP ^a (%) |
|---|------------------------------------|--------------------------------------|---------------|----------------------|
| | | Before storage | After storage | |
| Unmodified LiMn ₂ O ₄ | 2.55 | 115.3 | 65.7 | 43 |
| Modified LiMn ₂ O ₄ | 0.51 | 121.9 | 104.8 | 14 |

^a CFP = [(discharge capacity before storage – discharge capacity after storage)/discharge capacity before storage] × 100.

Table 2
Specific discharge capacity performances of the TiO₂-modified LiMn₂O₄ electrode after storage at different temperatures for 48 h

| Storage temperature (°C) | Concentration of dissolved Mn (μg) | Specific discharge capacity (mA h/g) | | CFP ^a (%) |
|--------------------------|------------------------------------|--------------------------------------|---------------|----------------------|
| | | Before storage | After storage | |
| 25 | 0.19 | 119.6 | 110.4 | 7.7 |
| 40 | 0.32 | 120.1 | 109.0 | 9.2 |
| 50 | 0.40 | 121.0 | 108.1 | 10.6 |
| 60 | 0.44 | 121.6 | 105.6 | 13.1 |
| 70 | 0.51 | 121.9 | 104.8 | 14.0 |
| 80 | 0.56 | 122.5 | 102.2 | 16.6 |

$$^a \text{CFP} = [(\text{discharge capacity before storage} - \text{discharge capacity after storage}) / \text{discharge capacity before storage}] \times 100.$$


Table 3
Specific discharge capacity performance of the TiO₂-modified LiMn₂O₄ electrode stored at 70 °C for different storage times

| Storage time (h) | Concentration of dissolved Mn (μg) | Specific discharge capacity (mA h/g) | | CFP ^a (%) |
|------------------|------------------------------------|--------------------------------------|---------------|----------------------|
| | | Before storage | After storage | |
| 6 | 0.31 | 121.9 | 119.0 | 2.4 |
| 12 | 0.37 | 121.9 | 116.2 | 4.7 |
| 24 | 0.39 | 121.9 | 113.5 | 6.9 |
| 36 | 0.45 | 121.9 | 109.8 | 9.9 |
| 48 | 0.51 | 121.9 | 104.8 | 14.0 |

$$^a \text{CFP} = [(\text{discharge capacity before storage} - \text{discharge capacity after storage}) / \text{discharge capacity before storage}] \times 100.$$

temperature or time (Tables 2 and 3). The results are indicative of the fact that capacity fading of the LiMn₂O₄ cathode is negligible for the TiO₂-modified LiMn₂O₄ electrode fabricated with the mixed-metal codeposition method. This suggests that the cathode proposed is suitable for the practical application, as it overcomes the problem of capacity fading of LiMn₂O₄. The surface modification of LiMn₂O₄ with titanium oxide proposed here can reduce the capacity fade of LiMn₂O₄ during both cycling and storage at elevated temperatures. This is also accompanied by the better battery performance at room temperature. The improvement of the LiMn₂O₄ cyclability achieved here is comparable with those reported in the literature [8–10]. Furthermore, the present material has another interesting feature due to the simplicity of the fabrication method employed.

To induce the chemically modification of LiMn₂O₄, the modifier material is forced to diffuse into the spinel by heating [10], which is not appropriate for the procedure reported here. The metal oxide (TiO₂ is just formed on the surface of the depositing LiMn₂O₄ particles, and the present process can be described as surface modification (even rather than physical modification). The surface modification of the spinel can significantly avoid Mn dissolution, which is the main reason for capacity fading of LiMn₂O₄. It is described that the instability of spinel in electrolyte solution at elevated temperatures is due to the formation of Mn²⁺ as the result of the following disproportionation reaction [25]:



According to the values reported in Table 1 for the amount of Mn dissolved for the unmodified and modified LiMn₂O₄

electrodes, it is obvious that the surface modification of the spinel with TiO₂ significantly protects the Mn dissolution as a result of reaction (1). In addition, the data presented in Tables 2 and 3 suggest that although the capacity fading of the LiMn₂O₄ spinel (as a result of Mn dissolution) is significantly reduced by the approach employed (surface modification), however, Mn dissolution is still responsible for the (slight) capacity fading of the TiO₂-modified LiMn₂O₄.

4. Conclusion

The results are indicative of the fact that the incorporation of titanium oxide into the LiMn₂O₄ film deposited based on the gold–titanium codeposition method can be applied to improve capacity fade of LiMn₂O₄, which is an important need for the practical performances of LiMn₂O₄-based lithium battery cathodes. In addition, the simple and efficient approach employed for the LiMn₂O₄ deposition can be successfully used for the fabrication of LiMn₂O₄ cathodes. Indeed, the advantage of the ability to induce surface modification of LiMn₂O₄ makes the method useful as well as usual high-technological methods. Further investigations of different cases may lead to new opportunity for the fabrication of LiMn₂O₄ cathodes with improved properties based on the simple method of gold-codeposition.

References

- [1] A. Blyr, C. Sigala, G.G. Amatucci, D. Guyomard, Y. Chabre, J.M. Tarascon, *J. Electrochem. Soc.* 145 (1998) 194.
- [2] X. Sun, H.S. Lee, X.Q. Yang, J. McBreen, *Electrochem. Solid-State Lett.* 4 (2001) A184.

- [3] Y. Xia, T. Sakai, T. Fujieda, X.Q. Yang, X. Sun, Z.F. Ma, J. McBreen, J. Electrochem. Soc. 148 (2001) A723.
- [4] G.G. Amatucci, C.N. Schmutz, A. Blyr, C. Sigala, A.S. Gozdz, D. Larcher, J.M. Tarascon, J. Power Sources 69 (1997) 11.
- [5] M.M. Thackeray, Y. Shao-Horn, A.J. Kahaian, K.D. Kepler, E. Skinner, J.T. Vaughey, S.J. Hackney, Electrochem. Solid-State Lett. 1 (1998) 7.
- [6] J.M. Tarascon, F. Coowar, G. Amatucci, F.K. Shokoohi, D. Guyomard, J. Electrochem. Soc. 141 (1994) 1421.
- [7] H. Huang, C.A. Vincent, P.G. Bruce, J. Electrochem. Soc. 146 (1999) 3649.
- [8] S. Park, Y. Han, Y. Kang, P.S. Lee, S. Ahn, H. Lee, J. Lee, J. Electrochem. Soc. 148 (2001) A680.
- [9] Z. Li, H. Wang, L. Fang, J.Y. Lee, L.M. Gan, J. Power Sources 104 (2002) 101.
- [10] A.M. Kannan, A. Manthiram, Electrochem. Solid-State Lett. 5 (2002) A167.
- [11] F.K. Shokoohi, J.M. Tarascon, B.J. Wakens, D. Guyomard, C.C. Chang, J. Electrochem. Soc. 139 (1992) 1845.
- [12] K.-H. Hwang, S.-H. Lee, S.-K. Joo, J. Electrochem. Soc. 141 (1994) 3296.
- [13] A. Rougier, K.A. Striebel, S.J. Wen, E.J. Cairns, J. Electrochem. Soc. 145 (1998) 2975.
- [14] P. Fragnaud, R. Nagarajan, D.M. Schleich, D. Vujic, J. Power Sources 54 (1995) 362.
- [15] A. Eftekhari, Electrochim. Acta, 47 (2002) 4347; Erratum 48 (2002) 290.
- [16] A. Eftekhari, J. Electrochem. Soc. 150 (2002) A966.
- [17] M.-R. Lim, W.-I. Cho, K.-B. Kim, J. Power Sources 92 (2001) 168.
- [18] A. Eftekhari, Electrochim. Acta 47 (2001) 495.
- [19] D.S. Ahn, M.Y. Song, J. Electrochem. Soc. 147 (2000) 874.
- [20] L. Kavan, B. O'Regan, A. Kay, M. Gratzel, J. Electroanal. Chem. 346 (1993) 291.
- [21] W.J. Macklin, R.J. Neat, Solid State Ionics 53–56 (1992) 694.
- [22] B. Zachau-Christiansen, K. West, T. Jacobsen, S. Atlung, Solid State Ionics 28–30 (1988) 1176.
- [23] R. van de Krol, A. Goossens, E.A. Meulenkaamp, J. Electrochem. Soc. 146 (1999) 3150.
- [24] R. van de Krol, A. Goossens, J. Schoonman, J. Phys. Chem. 103 (1999) 7151.
- [25] M.M. Thackeray, P.J. Johnson, L.A. De Picciotto, P.G. Bruce, J.B. Goodenough, Mater. Res. Bull. 19 (1984) 179.