

## Solid-State Synthesis and X-ray Diffraction Studies of Na<sub>2</sub>S

M. KIZILYALLI\* AND M. BİLGİN

*Middle East Technical University, Department of Chemistry,  
Ankara, 06531 Turkey*

AND H. M. KIZILYALLI

*Ankara University, Department of Physics, Ankara 06100 Turkey*

Received April 12, 1988; in revised form November 20, 1989

Na<sub>2</sub>S was synthesized by a new solid–gas reaction of Na<sub>2</sub>CO<sub>3</sub> with a sulfidizing gas mixture and a solid–solid reaction of carbon with Na<sub>2</sub>SO<sub>4</sub>. The reaction products were analyzed by X-ray powder diffraction and IR methods. Two new crystal modifications of Na<sub>2</sub>S were identified in addition to the previously reported antiferite structure. They were designated as cubic Form II and orthorhombic Form III. The approximate unit cell dimensions were found to be  $a = 11.29 \text{ \AA}$  for the cubic form and  $a = 15.94$ ,  $b = 16.00$ , and  $c = 16.18 \text{ \AA}$  for the orthorhombic form. © 1990 Academic Press, Inc.

### Introduction

Almost all of the metals in the periodic table react with sulfur in various proportions forming sulfides and polysulfides. Although some crystallographic data can be found in Wyckoff's compilation (1), sulfides are still being intensively studied because of their outstanding electrical properties, such as fast ion conduction (2) in antiferite-type structures or superconducting properties shown by Chevrel-type phases which are the ternary metal molybdenum sulfides (3, 4). In our energy-conscious world impetus for further research related to binary sulfides comes from the possibility of developing new solid-state batteries.

In sulfide formation, the preferred coordination of the cation depends on the size,

charge, and electron configuration of the ions. The similarities of monosulfides and monoxides of alkali metals (lithium to rubidium) are also seen in their crystal structures which are antiferite type.

Alkali metal sulfides are soluble in water and almost completely hydrolyzed in solution. However, hydrates of Na<sub>2</sub>S can be crystallized from aqueous solutions. Na<sub>2</sub>S forms two hydrates: Na<sub>2</sub>S · 5H<sub>2</sub>O (5) and Na<sub>2</sub>S · 9H<sub>2</sub>O (6).

Anhydrous Na<sub>2</sub>S usually has been obtained by the reduction of Na<sub>2</sub>SO<sub>4</sub> at 600–1100°C with various methods. Asphaltite, a waste from oil refineries (7), natural gas (8), solid carbon (9), natural gas in fluidized bed (10), and coke in air (11, 12) have been used as reductants.

Another recently reported way of obtaining Na<sub>2</sub>S (13) was from waste gas containing SO<sub>2</sub> that was scrubbed at 70–90°C with a saturated solution of Na<sub>2</sub>CO<sub>3</sub>. The solu-

\* To whom correspondence should be addressed.

tion was filtered and the filtrate treated with methane, CH<sub>4</sub>, at 300–400°C for the reduction of sulfite to sulfide. The mixture of sulfite and sulfide was heated in a rotary furnace at 500–900°C to complete the reaction.

Steck *et al.* (14) prepared Na<sub>2</sub>S from Na<sub>2</sub>S · 9H<sub>2</sub>O in a vacuum desiccator at 150°C with P<sub>2</sub>O<sub>5</sub> desiccant. Anhydrous Na<sub>2</sub>S was prepared recently by Chiotti and Markuszewskii (15) by heating Na<sub>2</sub>S · 9H<sub>2</sub>O in vacuum at 650–700°C for 4 hr, then cooling overnight. None of these techniques lead to sufficiently pure material. Brauer (16) lists two possible methods of preparation:




- (a) 2Na(s) + S(s) → Na<sub>2</sub>S(s) in liquid ammonia  
 (b) Na<sub>2</sub>S · 9H<sub>2</sub>O(s) → Na<sub>2</sub>S(s) + 9H<sub>2</sub>O.

Both of these methods were investigated by Walker (17) to prepare Na<sub>2</sub>S of single crystal growing quality.

Preparation and handling of Na<sub>2</sub>S must be carried out extremely carefully to avoid contamination and all operations should be done in an inert atmosphere. Considerable difficulty has been experienced in X-ray Laue photography. The samples deteriorated very rapidly. Laue photographs and X-ray powder diffraction data were not presented by Walker.


In this paper preparation of Na<sub>2</sub>S by the interaction of Na<sub>2</sub>CO<sub>3</sub> with a sulfidizing gas mixture containing CS<sub>2</sub>, COS, and CO and small amounts of CO<sub>2</sub> and S<sub>2</sub> vapor are discussed.

This gas mixture was obtained by Owen *et al.* (18) when SO<sub>2</sub> was passed through activated charcoal at 1000, 1200, and 1400 K. The equilibrium constants of the following equations and the partial pressures of the gases were calculated with respect to the reaction temperature by the method of successive approximations:



The change in partial pressures with respect to temperature was reported in a previous publication (19).

Welch proposed that this reducing and sulfidizing gas mixture could be used to prepare metal sulfides (20). The sulfides of iron and copper, namely, bornite, cubanite, stoichiometric and nonstoichiometric chalcopyrite (19), and CdS (21, 22) were prepared previously in our laboratory by this method. If unreduced sulfur dioxide is present in the gaseous mixture the following side reaction may occur:



In this work we also tried to synthesize Na<sub>2</sub>S by the reaction of Na<sub>2</sub>SO<sub>4</sub> with carbon in the solid state or by the dehydration of Na<sub>2</sub>S · 5H<sub>2</sub>O and determined X-ray powder patterns of the products for comparison.

#### *Structure of Na<sub>2</sub>S · 5H<sub>2</sub>O and Anhydrous Na<sub>2</sub>S*

The X-ray powder diffraction data of Na<sub>2</sub>S · 5H<sub>2</sub>O were published by Bedlivy and Preisinger (5). The structure is orthorhombic (space group: *CmCm*) with the unit cell parameters, *a* = 6.479, *b* = 12.55, and *c* = 8.655 Å (JCPDS Card No. 18-1249). Sodium ions are coordinated by six and four H<sub>2</sub>O molecules and form layers. These layers are linked to each other by hydrogen bonding.

The X-ray powder diffraction data of anhydrous Na<sub>2</sub>S were reported by Zintl and Harder (23) and indexed with an fcc structure (space group: *Fm3m* JCPDS Card No. 23-441) with *a* = 6.539 Å (24). Although numerous workers have investigated and synthesized Na<sub>2</sub>S, the X-ray powder diffraction data have received little attention due to peculiarities of sulfide crystal structures. Sulfide structures are considered as comprising two substructures, one com-

posed of the large sulfur anions and the other composed of the small metallic cations (25). The former substructure is based on a fcc lattice. In the sulfide structures which have been studied by Morimoto *et al.* (25), the sulfur atoms remain at the fcc positions and the symmetry of the sulfur substructure is truly cubic. The cation substructure is based on a larger cell.

The metal ions are quite mobile and migrate through the structure as the temperature changes. They can settle along the body diagonal of the cube at  $\frac{1}{4}, \frac{1}{4}, \frac{1}{4}$  positions with tetrahedral or  $\frac{1}{2}, \frac{1}{2}, \frac{1}{2}$  with octahedral sulfur coordination. On cooling from the high temperature form the cations are ordered such that the unit cell changes. The size of the cell and the crystal structure depend on both composition and cooling rate. In some cases metastable forms are also obtained.

## Experimental

### *Materials and Instrumentation*

The starting materials were reagent grade Na<sub>2</sub>CO<sub>3</sub>, Na<sub>2</sub>SO<sub>4</sub>, Na<sub>2</sub>S · 5H<sub>2</sub>O, and carbon powder (Merck or Riedel). Na<sub>2</sub>CO<sub>3</sub> and Na<sub>2</sub>SO<sub>4</sub> were dried at 100°C before use. Nitrogen, technical grade sulfur dioxide, coke, and activated charcoal were obtained locally.


Spectroscopic grade KBr was used as a pellet material and a Perkin Elmer 1430 ratio recording IR spectrophotometer was employed for taking IR spectra.

Either an Enraf nonius Diffractis 582 type of diffraction generator and Guinier de Wolff Camera No. II or a Philips diffractometer and PW 1050/25 goniometer were employed with CuK $\alpha$  radiation for X-ray diffraction studies.

### *Heat Treatments of Na<sub>2</sub>SO<sub>4</sub> and Na<sub>2</sub>S · 5H<sub>2</sub>O*

To facilitate comparison of X-ray and IR data of the products obtained in solid-state

reactions, these chemicals were heat treated under the same conditions as those of the reaction products and X-ray and IR data were recorded.




### *Reactions*

The reaction of Na<sub>2</sub>CO<sub>3</sub> and SO<sub>2</sub> to check the formation of Na<sub>2</sub>SO<sub>4</sub> and to determine its diffraction data was attempted at 750°C.

### *Preparation of Na<sub>2</sub>S by*

#### *Solid-State Reactions*

Appropriate quantities of Na<sub>2</sub>SO<sub>4</sub> and C to obtain the stoichiometric formula, Na<sub>2</sub>S, were crushed and thoroughly mixed in an agate mortar. The mixture was then put into a porcelain boat and placed in the middle of a horizontal tubular furnace. Reactions were carried out at 350 to 800°C for about 2 hr in a dry N<sub>2</sub> atmosphere. N<sub>2</sub> gas was used to remove O<sub>2</sub> from the system and to avoid the side reaction:



### *Reaction of Na<sub>2</sub>CO<sub>3</sub> with the Sulfidizing Gas Mixture*

The methods and apparatus used in obtaining data herein reported were given in detail in a previous publication and need only be summarized briefly (19, 22).

A horizontal tubular furnace and a silica tube of 2.5 cm inside diameter and 60 cm length were used as a reaction chamber. A silica tube of the same size filled with coke or activated charcoal and inserted vertically in a tubular furnace comprised the reduction chamber. SO<sub>2</sub> gas was bubbled through the vertical furnace at the rate of two bubbles per second. A weighed amount of Na<sub>2</sub>CO<sub>3</sub> in a porcelain boat was inserted into the horizontal furnace. The system was flushed with N<sub>2</sub> to remove O<sub>2</sub>, then the sulfidizing gas mixture was introduced into the reaction chamber and the furnace heated to the desired temperature. After the reaction

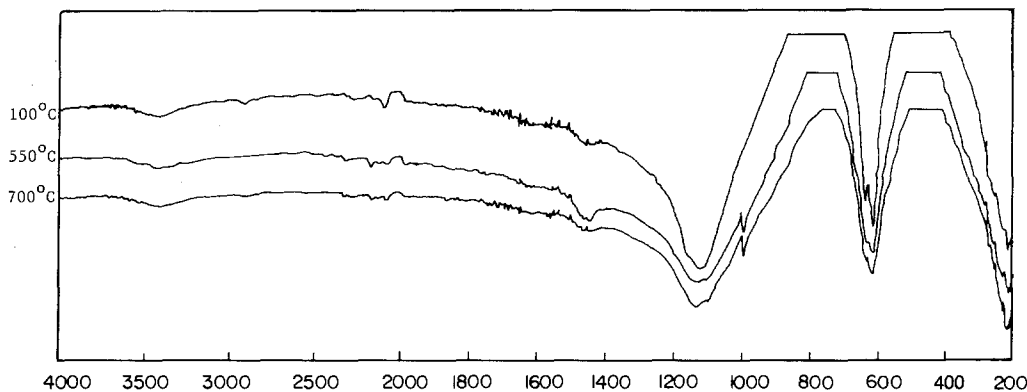


FIG. 1. IR spectra of sodium sulfate treated at different temperatures.

was complete the samples could be either quenched by withdrawal of the porcelain boat from the furnace into a region at ambient temperature while remaining in the sulfidizing gas or  $N_2$  atmosphere, or cooled slowly in the furnace.

### Results and Discussion

#### *X-ray and IR Results of $Na_2SO_4$ and Heat Treated Forms*

X-ray diffraction data of  $Na_2SO_4$  obtained by reaction of  $Na_2CO_3$  with  $SO_2$  agreed very well with the data of reagent grade  $Na_2SO_4$ . The 550° and 750°C forms gave the same diffraction patterns. The experimental orthorhombic lattice parameters  $a = 5.59$ ,  $b = 8.92$ , and  $c = 6.95$  Å (space group:  $CmCm$ ) are in good agreement with those reported by Frevel (26) and Fischmeister (27). The infrared spectrum of  $Na_2SO_4$  and heated forms is shown in Fig. 1. The IR spectrum of sulfate ion was reported by Ross and Nakamoto (28, 29). The following frequencies (in  $cm^{-1}$ ) were given:

$\nu_1$	$\nu_2$	$\nu_3$	$\nu_4$
983	450	1105	611

where  $\nu_1$  and  $\nu_2$  are only Raman active. It is clear from Fig. 1 that  $\nu_3$  and  $\nu_4$  are IR active

and appear strongly in the spectra. On heating, Raman active  $\nu_1$  also appears since the symmetry of the  $SO_4^{2-}$  ion was lowered from  $T_d$  to  $C_{3v}$  or  $C_{2v}$  (30). Ions of the formula  $XO_4^{2-}$  are tetrahedral but distort upon heating in such a way that there are two long and two short  $X-O$  bonds so the symmetry turns out to be  $C_{2v}$ . On the other hand the IR spectra of sodium sulfate are given by Gadsden (31) with the following frequencies ( $cm^{-1}$ ): 1135–1130 (vs), 1116–1095 (vs), 991 (vw, sharp), 725 (w), 640–635 (s), 620–615 (s). These agreed quite well with Fig. 1.

#### *X-ray Powder Diffraction and IR Results of $Na_2S \cdot 5H_2O$ and Heat Treated Forms*

The X-ray powder diffraction data of  $Na_2S \cdot 5H_2O$  (Riedel) were obtained and compared with the literature data (JCPDS Card No. 18-1249). The spacings observed in this work agreed quite well with the data of Bedlivy and Preisinger (5), but it was observed that the data also contain some lines due to  $NaHS$  (JCPDS Card No. 3-645) and  $Na_2SO_3$  (JCPDS Card 37-1488). The pattern was indexed in the orthorhombic system and the unit cell parameters were calculated to be  $a = 6.48$ ,  $b = 12.54$ , and  $c = 8.66$  Å.

Figure 2 shows the previously unre-

ported IR spectrum of Na<sub>2</sub>S · 5H<sub>2</sub>O. The IR spectrum of metal sulfides depends on S–S stretching or metal–S stretching vibrations (32) due to the covalent nature of the bonds. Any sulfide absorption bands that arise usually occur below 400 cm<sup>-1</sup> in the low frequency region, but there is no simple correlation (31). However, the frequency of the vibration decreases with increasing atomic weight of the cation. In hydrated inorganic salts, the presence of lattice or coordinated water gives rise to lattice vibrations in the low frequency region in addition to 3550–3200 cm<sup>-1</sup> antisymmetric and symmetric OH<sup>-</sup> stretching and 1630–1600 H–O–H bending modes. Librational modes occur between 300–600 cm<sup>-1</sup>. Coordinated water is also expected to show other modes. Rocking, wagging, and the metal–oxygen stretching vibrations appear at 900, 768, and 673 cm<sup>-1</sup>, respectively (33). The water twisting vibration is only Raman active. These frequencies depend on coordination as well as hydrogen bonds in the crystal, so these two effects must be carefully differentiated, since there is no definite borderline between the lattice and the coordinated water.

The following probable modes were assigned to the bands observed in Fig. 2.

(cm <sup>-1</sup> )	Remarks
270	Sulfide lattice vibration
550	Librational mode of water
626	SO <sub>3</sub> <sup>2-</sup> (ν <sub>2</sub> ) (29–34)

670	Na–O stretching vibration
870	δ-S–H (35) or rocking mode of coordinated water
892	SO <sub>3</sub> <sup>2-</sup> (ν <sub>3</sub> )
900	NaHS · xH <sub>2</sub> O (36)
1000–1138	SO <sub>3</sub> <sup>2-</sup> (ν <sub>1</sub> )
1450	NaHS · xH <sub>2</sub> O

These observations together with the X-ray data showed that the commercial Na<sub>2</sub>S · 5H<sub>2</sub>O oxidized partially to Na<sub>2</sub>SO<sub>3</sub>.

The X-ray and IR data of Na<sub>2</sub>S · 5H<sub>2</sub>O dried in vacuum (1 mbar) at room temperature are given in Table I and Fig. 3, respectively. The formula of the vacuum dried product was found to be Na<sub>2</sub>S · 1.17H<sub>2</sub>O by mass loss. Comparison of the two samples revealed that as the water content decreased, the X-ray and IR data changed considerably. Examination of the X-ray data showed that the product is a mixture of the pentahydrate (JCPDS Card No. 18-1249) and antifluorite-type Na<sub>2</sub>S (JCPDS card No. 23-441), but the intensities and the *d* spacings of Na<sub>2</sub>S lines do not fit properly to the reported data. The pattern may also contain some NaHS and Na<sub>2</sub>SO<sub>3</sub> reflections.

The vacuum dried product was then heated very slowly at 50°, 75°, and 100°C to avoid melting. The low temperature removal of water was quite difficult, so the specimens were heated again to constant weight in the temperature range 500–800°C. The IR data proved that water was still present at 500°C and was practically re-

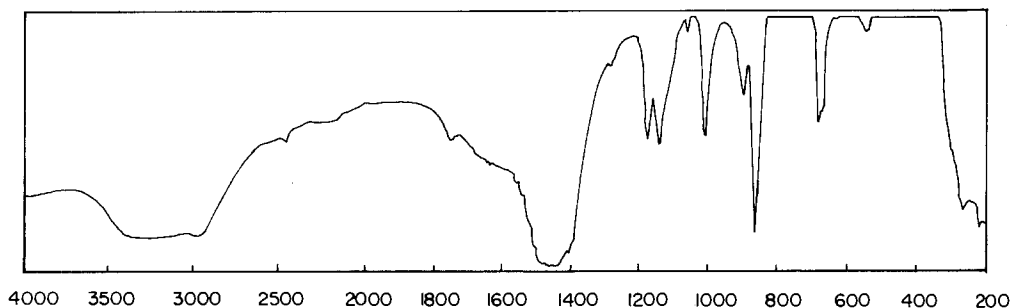


FIG. 2. IR spectrum of Na<sub>2</sub>S · 5H<sub>2</sub>O.

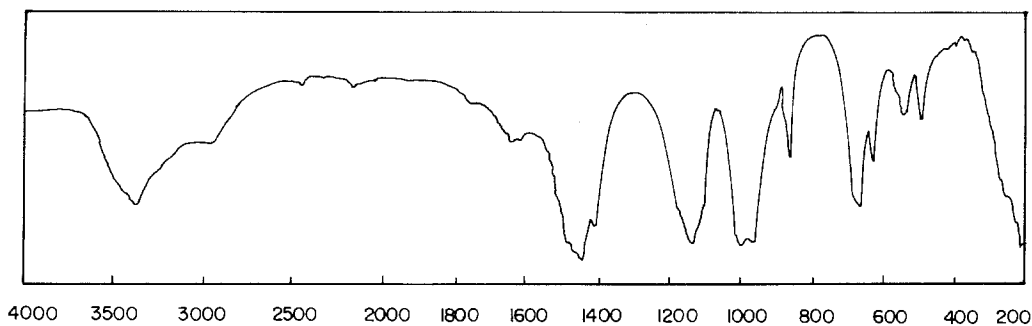
FIG. 3. IR spectrum of vacuum dried  $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$ .

TABLE I  
X-RAY DIFFRACTION DATA OF VACUUM DRIED  
 $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$

$I/I_0$	$d(\text{Å})$	$I/I_0$	$d(\text{Å})$
5	5.29	40	2.045
5	3.99	40	2.006
20	3.70- $\text{Na}_2\text{S}$	40	1.9649- $\text{Na}_2\text{S}$
5	3.65	40	1.9375
5	3.51	15	1.9084
10	3.25- $\text{Na}_2\text{S}$	80	1.8766- $\text{Na}_2\text{S}$
35	3.196	50	1.8625
5	3.079	15	1.8039
10	2.940	10	1.7874
20	2.829	10	1.7664
35	2.746	5	1.7374
100	2.694	5	1.7250
50	2.659	20	1.6894
75	2.611	20	1.6509
5	2.501	25	1.6474
40	2.478	10	1.6313- $\text{Na}_2\text{S}$
40	2.453	20	1.6045
5	2.429	10	1.5901
35	2.371	25	1.5583
45	2.311- $\text{Na}_2\text{S}$	25	1.5436
20	2.284	10	1.5245
25	2.241	20	1.4974- $\text{Na}_2\text{S}$
25	2.182	10	1.4629
10	2.144	5	1.4508
40	2.114	15	1.4447
		15	1.3894
		15	1.3474
		25	1.3187- $\text{Na}_2\text{S}$

Note. Formula calculated as  $\text{Na}_2\text{S} \cdot 1.17\text{H}_2\text{O}$  Rad.  $\text{CuK}\alpha$  ( $\lambda = 1.54178 \text{ Å}$ ).

moved at 700–800°C (Fig. 4). Theoretical and calculated weight loss agreed quite well at this stage.

The IR spectra of  $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$  dried in vacuum (Fig. 3) have frequencies common with  $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$  except for the split bands at 540 and 1000  $\text{cm}^{-1}$ . The IR spectra of the compound heated at 500°, 700°, 750°, and 800°C are given in Figs. 4a,b,c,d. It was observed that the band at 1450  $\text{cm}^{-1}$  progressively disappears as the temperature increases. This band was attributed to NaHS (36) and we assumed that H-S was destroyed upon heating. The bands due to  $\text{SO}_3^{2-}$  also disappeared after 500°C, and strong bands of  $\text{SO}_4^{2-}$  were observed in spectra 4b, c, and d.

The X-ray powder patterns of  $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$  heated at 300°, 400°, 500°C were very complicated and contained a number of phases including  $\text{Na}_2\text{S}$  (Form I), NaHS, and  $\text{Na}_2\text{SO}_3$ . The product heated at 550°C does not contain NaHS and  $\text{Na}_2\text{SO}_3$ . A new phase which we assumed to be a different cubic crystal modification of  $\text{Na}_2\text{S}$  (Form II,  $a = 11.29 \text{ Å}$ ) was observed together with strong  $\text{Na}_2\text{SO}_4$  lines.

Since the sample heated at 800–850°C gave a very complicated pattern with strong  $\text{Na}_2\text{SO}_4$  reflections, it was assumed that anhydrous  $\text{Na}_2\text{S}$  cannot be easily obtained through heating the pentahydrate. Utmost

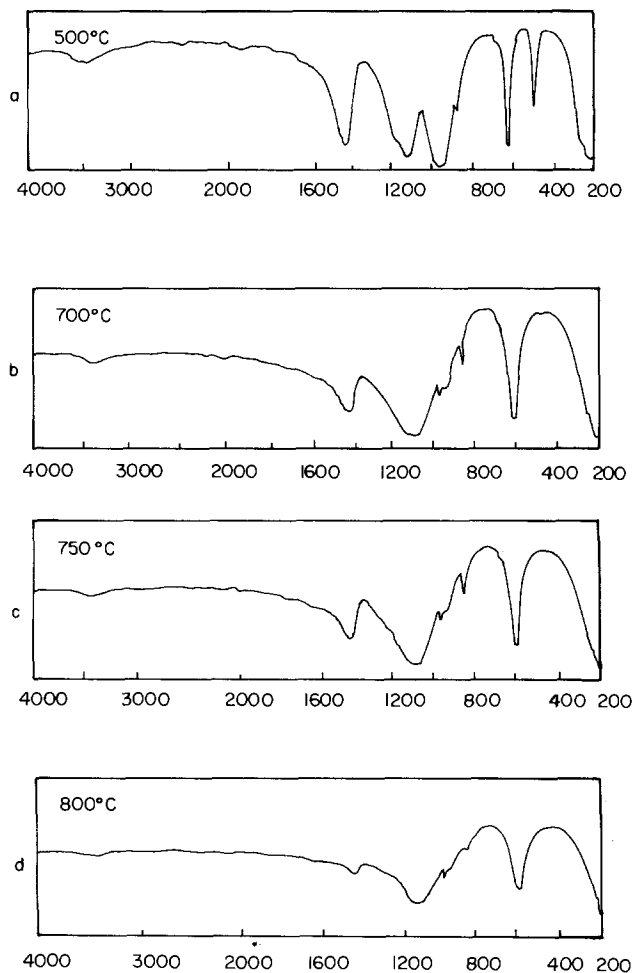


FIG. 4. IR spectra of  $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$  heated at different temperatures.

care should be taken to avoid contamination.

#### *X-ray and IR Results of $\text{Na}_2\text{S}$ Obtained from $\text{Na}_2\text{SO}_4 + \text{C}$ Solid-State Reactions*

The experiments were performed at 350, 450, 500, 550, and 800°C for 2 hr and at 900°C for 1 hr. The X-ray powder patterns of the products proved that the optimum condition for preparing  $\text{Na}_2\text{S}$  was 2 hr heating time at 800°C. A new type of structure was observed together with weak  $\text{Na}_2\text{SO}_4$  lines (see the following paragraph and Ta-

ble II). The IR spectra of this product were about the same as that of  $\text{Na}_2\text{S} \cdot 5\text{H}_2\text{O}$  heated at 800°C (Fig. 4d) showing the presence of  $\text{Na}_2\text{SO}_4$  bands.

#### *X-ray and IR Results of the Reaction $\text{Na}_2\text{CO}_3 + \text{Sulfidizing Gas Mixture}$*

Several different sets of experiments were performed at 700°, 750°, and 800°C for 1,2,3,4,5, and 12 hr heating periods with cooling under a dry nitrogen or sulfidizing gas atmosphere. Of the experimental conditions studied to prepare  $\text{Na}_2\text{S}$ , the optimum

TABLE II

X-RAY DIFFRACTION DATA OF Na<sub>2</sub>S AT 800–850°C  
(FORM III)

$I/I_0$	$d(\text{Å})$	Remarks
50	11.276	
5	8.154	
10	6.549	
5	5.626	
10	5.366	
5	5.111	
5	5.039	
10	4.635	+Na <sub>2</sub> SO <sub>4</sub>
10	4.250	
10	3.969	
3	3.890	Na <sub>2</sub> SO <sub>4</sub>
5	3.746	+Na <sub>2</sub> SO <sub>4</sub>
5	3.655	
5	3.583	+Na <sub>2</sub> SO <sub>4</sub>
5	3.499	+Na <sub>2</sub> SO <sub>4</sub>
15	3.421	
15	3.402	
10	3.190	Na <sub>2</sub> SO <sub>4</sub>
40	3.074	+Na <sub>2</sub> SO <sub>4</sub>
10	2.910	
60	2.831	
3	2.797	Na <sub>2</sub> SO <sub>4</sub>
1	2.733	
5	2.694	
25	2.660	
100	2.584	
5	2.521	
10	2.495	
90	2.442	
90	2.432	
70	2.382	+Na <sub>2</sub> SO <sub>4</sub>
25	2.211	
5	2.194	
5	2.153	
5	2.144	+Na <sub>2</sub> SO <sub>4</sub>
5	2.114	
30	2.076	
15	1.9930	
15	1.9649	+Na <sub>2</sub> SO <sub>4</sub>
10	1.8934	
5	1.8711	
5	1.7906	
5	1.7841	
5	1.7554	
10	1.7292	
15	1.7202	
10	1.7077	
5	1.6260	+Na <sub>2</sub> SO <sub>4</sub>
5	1.6090	

TABLE II—Continued

$I/I_0$	$d(\text{Å})$	Remarks
5	1.6104	
5	1.5801	+Na <sub>2</sub> SO <sub>4</sub>
5	1.5453	
5	1.4764	
5	1.4588	+Na <sub>2</sub> SO <sub>4</sub>
5	1.3481	
5	1.3109	

Note. Rad. CuK $\alpha$  orthorhombic,  $a = 15.94$ ,  $b = 16.00$ ,  $c = 16.18$  Å.

was 12 hr heating time at 700°C and slow cooling in the sulfidizing gas atmosphere. Activated charcoal (6–12 mesh) instead of coke in the reduction chamber increased the Na<sub>2</sub>S yield. The X-ray powder diffraction data were about the same as those obtained from the Na<sub>2</sub>SO<sub>4</sub> + C reactions. At 700°C the product was found to be a mixture of two phases (Forms II and III) but at 800°C only Form III was observed. The intensities of Na<sub>2</sub>SO<sub>4</sub> lines are very weak and are not consistent with Na<sub>2</sub>SO<sub>4</sub> data, but the IR spectra are the same as that of Fig. 4d showing the presence of SO<sub>4</sub><sup>2-</sup> ions.

The powder pattern of Form III is recorded in Table II. The whole system could be indexed on a large pseudocubic (orthorhombic) unit cell with approximate unit cell parameters  $a = 15.94$ ,  $b = 16.00$ , and  $c = 16.18$  Å. The sulfur content of the compound was 39.9% compared with the theoretical value of 41.08% (37). These results, together with X-ray and IR data, proved the presence of SO<sub>4</sub><sup>2-</sup> impurity in the Na<sub>2</sub>S product.

In conclusion we have shown that Na<sub>2</sub>S can be prepared through solid–gas reactions which have not been reported before. In these reactions care should be taken to avoid diffusion of oxygen into the system and formation of Na<sub>2</sub>SO<sub>4</sub> (38).

A new orthorhombic crystal modification of Na<sub>2</sub>S was observed (Form III) and a cu-



bic modification of it with an approximate 11.29 Å unit cell parameter was predicted (Form II) in this work. The cell parameter relations between the antiferroite type of Na<sub>2</sub>S (Form I), Form II, and Form III are found to be:

$$(i) a_{\text{Form I}} \cdot \sqrt{2} \sim a_{\text{Form II}}$$

$$(ii) a_{\text{Form II}} \cdot \sqrt{3} \sim a_{\text{Form III}} \text{ (pseudocubic) } \cdot$$

Further research is going on in our laboratories to clarify these difficult sets of phase relationships in sodium sulfide structures and to refine the unit cell parameters.

### Acknowledgments

The authors dedicate this paper to the memory of the late Dr. A. J. E. Welch, who initiated a sulfide project at Imperial College of Science and Technology, Chemistry Department. We thank the University Grant Commission for partial support of this project through METU Research Fund 87-01-03-07.

### References

1. R. W. G. WYCKOFF, "Crystal Structures," 2nd ed., Vol. 1 (1963), Vol. 2 (1964), Vol. 3 (1965), Interscience, New York.
2. N. AGNIHOTRI, R. K. SINGH, AND S. P. SANYAL, *Phys. Status Solidi B* **125**, 113 (1984).
3. O. PENA, R. HORYN, M. MOTEL, J. PADIOU, AND M. SERGENT, *J. Less-Common Met.* **105**, 105 (1985).
4. K. S. NANJUNDASWAMY, N. Y. VASANTHACHARYA, J. GOPALAKRISHMAN, AND C. N. R. RAO, *Inorg. Chem.* **26**, 4286 (1987).
5. D. BEDLIVY AND A. PREISINGER, *Z. Kristallogr.* **121**(2-4), 131 (1965).
6. D. BEDLIVY AND A. PREISINGER, *Z. Kristallogr.*, 114 (1965).
7. A. G. PROKHOROV AND G. A. GANICHEVA, *Tr. Ural. Nauchno-Issled. Khim. Inst.* **24**, 49-52, 91-93 (1973).
8. H. HUA AND P. TUNG, *R. China* **5**, 278 (1976).
9. M. F. VOLKOVA AND A. G. PROKHOROV, *Otkrytiya Izobret. Prom. Obraztsy Tavarnye Znaki* **54**(31), 56 (1977).
10. V. T. KUNIN, *Izv. Vyssh. Uchebn. Zaved. Khim. Khim. Tekhnol.* **21**(6), 873 (1978).
11. A. G. PROKHOROV, V. N. BABKOV, V. YA. NECHEPURENKO, G. A. GANICHEVA, V. N. KESHETNIKOV, AND V. N. BRUNOV, *Otkrytiya Izobret. Prom. Obraztsy, Tavarnye Znaki* **6**, 92 (1980).
12. V. G. GORSHKOV, A. V. POPOV, G. V. PRYAKHIN, B. I. PSAKHIS, AND V. N. SENICK, *Khim Prom-St.* **9**, 563 (1983).
13. C. VOLCOVINSCHI, "Intreprinderca Metalurgica de Metale Neferoase, Bia Mare," *Rom.* **67**, 221 (Cl. C01B17/22), 30 Nov. (1978), *App.* **78**, 875, 21 May (1974).
14. L. STECK, M. SLAVIN, AND O. J. RALSTON., *J. Amer. Chem. Soc.* **51**, 1241 (1929).
15. P. CHIOTTI AND R. MARKUSZEWSKII, *J. Chem. Eng. Data* **30** (2), 197 (1985).
16. G. BRAUER, "Handbook of Preparative Inorganic Chemistry," Vol. 1, p. 980, 2nd ed., Academic Press, New York (1963).
17. P. J. WALKER, *J. Cryst. Growth* **47**, 598 (1979).
18. A. J. OWEN, K. W. SYKES, AND D. J. D. THOMAS, *Trans. Faraday Soc.* **47**, 419 (1951).
19. M. KIZILYALLI AND H. M. KIZILYALLI, "Transport in Nonstoichiometric Compounds" (G. Simkovich, Ed.), Physics Ser. B, p. 441, Plenum, New York (1985).
20. A. J. E. WELCH, Interim Report, Imperial College, London (1971).
21. M. ÇETİN, "Solid State Synthesis and X-ray Diffraction Studies of CdS, Na<sub>2</sub>S, and Na<sub>2</sub>SO<sub>4</sub>," M.Sc. thesis, Middle East Tech. Univ. Ankara (1986).
22. M. KIZILYALLI, M. BİLGIN, AND A. USANMAZ, *J. Solid State Chem.* **80**, 75 (1989).
23. E. ZINTL, A. HARDER, AND B. DAUTH, *Z. Electrochem.* **40**, 988 (1934).
24. National Bureau of Standards, Monograph 25, Sect. 10 (1972).
25. N. MORITOMOTO, G. DONNAY, AND G. KULLERUD, "Carnegie Institute of Washington Year Book," No. 59, p. 169 (1959-1960).
26. L. K. FRELVE, *J. Chem. Phys.* **8**, 290 (1940).
27. H. FISCHMEISTER, *Acta Crystallogr.* **7**, 776 (1954).
28. S. D. ROSS, "Inorganic Infrared and Raman Spectra," McGraw-Hill, UK (1972).
29. K. NAKAMATO, "Inf. Spectra of Inorg. and Coord. Comp." Wiley, New York (1963).
30. R. J. FERRARO, "Low Frequency Vibrations of Inorg. and Coord. Comp." Plenum, New York (1971).
31. J. A. GADSDEN, "Inf. Spect. of Minerals and Related Inorg. Comp.," Butterworths, London (1975).
32. W. B. WHITE AND R. ROY, *Amer. Mineral.* **49**, 1670 (1964).

33. G. SARTORI, C. FURLANI, AND A. DAMIANI, *J. Inorg. Nucl. Chem.* **8**, 119 (1958).
34. D. DOLPHIN AND A. WICK, "Tabulation of IR Spectral Data," Wiley, New York (1977).
35. IRSCOT "Infrared Structural Correlation Tables," Hyden, London (1966).
36. C. G. POUCHERT, The Aldridge Library of Inf. Spect., Ed. III, Wisconsin (1981).
37. H. I. VOGEL, "Textbook of Quantitative Inorg. Analysis," p. 467, Longmans, London (1961).
38. M. FREDRIKSSON AND E. ROSEN, *Chem. Sci.* **18**(3), 139 (1981).