

# Tetrahedral-Network Organo-zincophosphates: Syntheses and Structures of $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ , $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ , and $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$

Alejandra V. Chavez,\* Tina M. Nenoff,\* Lakshitha Hannooman,† and William T. A. Harrison‡,<sup>1</sup>

\*Catalysis and Chemical Technologies Department, Sandia National Laboratories, Albuquerque, New Mexico 87185-0710;

†Department of Chemistry, University of Western Australia, Nedlands, Western Australia 6907, Australia; and ‡Department of Chemistry, University of Aberdeen, Aberdeen AB24 3UE, United Kingdom

Received March 12, 1999; in revised form May 25, 1999; accepted May 27, 1999

The solution-mediated syntheses and single crystal structures of  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$  (I),  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  (II), and  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$  (III) are described. These phases contain vertex-sharing  $\text{ZnO}_4$  and  $\text{HPO}_4$  tetrahedra, accompanied by doubly protonated organic cations. Despite their formal chemical relationship, as members of the series of  $t \cdot \text{Zn}_n(\text{HPO}_4)_{n+1}$  ( $t = \text{template}$ ,  $n = 1-3$ ), these phases adopt fundamentally different crystal structures, as one-dimensional, two-dimensional, and three-dimensional  $\text{ZnO}_4/\text{HPO}_4$  networks, for I, II, and III, respectively. Similarities and differences to some other zinc phosphates are briefly discussed. Crystal data:  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ ,  $M_r = 389.54$ , monoclinic, space group  $P2_1/n$  (No. 14),  $a = 9.864(4) \text{ \AA}$ ,  $b = 8.679(4) \text{ \AA}$ ,  $c = 15.780(3) \text{ \AA}$ ,  $\beta = 106.86(2)^\circ$ ,  $V = 1294.2(8) \text{ \AA}^3$ ,  $Z = 4$ ,  $R(F) = 4.58\%$ ,  $R_w(F) = 5.28\%$  [1055 reflections with  $I > 3\sigma(I)$ ].  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ ,  $M_r = 494.84$ , monoclinic, space group  $P2_1/c$  (No. 14),  $a = 8.593(2) \text{ \AA}$ ,  $b = 9.602(2) \text{ \AA}$ ,  $c = 17.001(3) \text{ \AA}$ ,  $\beta = 93.571(8)^\circ$ ,  $V = 1400.0(5) \text{ \AA}^3$ ,  $Z = 4$ ,  $R(F) = 4.09\%$ ,  $R_w(F) = 4.81\%$  [2794 reflections with  $I > 3\sigma(I)$ ].  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ ,  $M_r = 694.25$ , monoclinic, space group  $P2_1/n$  (No. 14),  $a = 9.535(2) \text{ \AA}$ ,  $b = 23.246(4) \text{ \AA}$ ,  $c = 9.587(2) \text{ \AA}$ ,  $\beta = 117.74(2)^\circ$ ,  $V = 1880.8(8) \text{ \AA}^3$ ,  $Z = 4$ ,  $R(F) = 3.23\%$ ,  $R_w(F) = 3.89\%$  [4255 reflections with  $I > 3\sigma(I)$ ]. © 1999 Academic Press

## INTRODUCTION

Many tetrahedral-network zincophosphates ( $\text{ZnPOs}$ ) templated by organic cations have been described (1). Although the fundamental building units— $\text{ZnO}_4$  and  $\text{PO}_4$  tetrahedra—are common to all these phases, their crystal structures are strongly but unpredictably dependent on the identity of the structure-directing organic species. The pres-

ence of “dangling”  $\text{Zn}-\text{OH}_2$ ,  $\text{P}-\text{O}$ , and  $\text{P}-\text{OH}$  bonds (2) and three-coordinated framework O atoms, invariably to 2 Zn + 1 P (3), complicate the picture further, in terms of rationalizing and predicting  $\text{ZnPO}$  crystal structures. Thus, exploratory synthesis continues to play a vital role in mapping out this phase space and seeking further correlations between preparations and crystal structures.

In this paper we report the solution-mediated syntheses and single-crystal structures of  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ ,  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ , and  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ , three new zinc hydrogen phosphate phases templated by the doubly protonated, “bifunctional” organic cations 1,4-diazabicyclo[2.2.2]octane (dabco),  $\text{N}_2\text{C}_6\text{H}_{14}$ , and 1,3-diammonium propane,  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3$ . These phases may be regarded as members of the series of  $t \cdot \text{Zn}_n(\text{HPO}_4)_{n+1}$  ( $t = [\text{template}]^{2+}$ ,  $n = 1-3$ ). Despite their formal chemical relationship, these phases adopt fundamentally different crystal structures, as one-dimensional, two-dimensional, and three-dimensional  $\text{ZnO}_4/\text{PO}_4$  networks for  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ ,  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ , and  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ , respectively. These phases are briefly compared and contrasted to known zinc phosphates.

## EXPERIMENTAL

### Syntheses

$(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ : 10.08 g (90 mmol) dabco, 0.81 g (10 mmol)  $\text{ZnO}$ , and 6.91 g (216 mmol) of  $\text{H}_2\text{O}$  were added to a Teflon bottle. Then 10.35 g (90 mmol) of 85%  $\text{H}_3\text{PO}_4$  was added. A thixotropic mixture formed, resulting in a milky white solution upon shaking. The solution was heated in a sealed bottle at  $70^\circ\text{C}$  for 14 days. The product was recovered by vacuum filtration and washing with deionized  $\text{H}_2\text{O}$ , resulting in a few clear needle- and rod-shaped crystals.

<sup>1</sup>To whom correspondence should be addressed. E-mail: [w.harrison@abdn.ac.uk](mailto:w.harrison@abdn.ac.uk).

$\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ :  $\text{ZnO}$ ,  $\text{TiO}_2$ , 85%  $\text{H}_3\text{PO}_4$ , and 1,3-diaminopropane were mixed in a 2:1:10:2 ratio in 10 cc of water. This mixture was enclosed in a Teflon-lined 23-ml hydrothermal bomb and heated to 150°C for 3 days. The product was vacuum filtered and washed with deionized  $\text{H}_2\text{O}$ , resulting in block-like crystals to 1 mm. Preparations omitting the  $\text{TiO}_2$  powder led to other, unidentified products.

$(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ :  $\text{ZnO}$ ,  $\text{TiO}_2$ , 85%  $\text{H}_3\text{PO}_4$ , and 1,4-diazabicyclo[2.2.2]octane (dabco) were mixed in a 4:1:4:2 ratio in 10 cc of water. This mixture was enclosed in a Teflon-lined 23-ml hydrothermal bomb and heated to 150°C for 3 days. The product was vacuum filtered and washed with deionized  $\text{H}_2\text{O}$ , resulting in clear, chunky crystals.

### Structure Determinations

Suitable single crystals [ $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ , translucent lump,  $\sim 0.1 \times 0.3 \times 0.4$  mm;  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ , clear block,  $\sim 0.3 \times 0.3 \times 0.4$  mm;  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ , clear chunk,  $\sim 0.4 \times 0.5 \times 0.5$  mm] were mounted on thin glass fibers with cyanoacrylate adhesive, and room-temperature [25(2)°C] intensity data were collected on a Siemens P4 automated four-circle diffractometer (graphite-monochromated  $\text{MoK}\alpha$  radiation,  $\lambda = 0.71073$  Å), as summarized in Table 1. The application of

TABLE 1  
Crystallographic/Data Collection Parameters

	$(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$	$\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$	$(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$
Emp. formula	$\text{ZnP}_2\text{O}_9\text{N}_2\text{C}_6\text{H}_{18}$	$\text{Zn}_2\text{P}_3\text{O}_{12}\text{N}_2\text{C}_3\text{H}_{15}$	$\text{Zn}_3\text{P}_4\text{O}_{16}\text{N}_2\text{C}_6\text{H}_{18}$
Formula wt.	389.54	494.84	694.25
Crystal system	Monoclinic	Monoclinic	Monoclinic
<i>a</i> (Å)	9.864 (4)	8.593 (2)	9.535 (2)
<i>b</i> (Å)	8.679 (4)	9.602 (2)	23.246 (4)
<i>c</i> (Å)	15.780 (3)	17.001 (3)	9.587 (2)
$\beta$ (°)	106.86 (2)	93.571 (8)	117.74 (2)
<i>V</i> (Å <sup>3</sup> )	1294.2 (8)	1400.0 (5)	1880.8 (8)
<i>Z</i>	4	4	4
Space group	$P2_1/n$ (No. 14)	$P2_1/c$ (No. 14)	$P2_1/n$ (No. 14)
<i>T</i> (°C)	25 (2)	25 (2)	25 (2)
$\lambda$ (MoK $\alpha$ ) (Å)	0.71073	0.71073	0.71073
$\rho_{\text{calc}}$ (g/cm <sup>3</sup> )	2.00	2.35	2.45
$\mu$ (cm <sup>-1</sup> )	22.3	39.1	43.1
Total data	2528	4827	6342
Observed data <sup>a</sup>	1055	2794	4255
Parameters	183	201	282
<i>R</i> ( <i>F</i> ) <sup>b</sup>	4.58	4.09	3.23
<i>R</i> <sub>w</sub> ( <i>F</i> ) <sup>c</sup>	5.28	4.81	3.89

<sup>a</sup> $I > 3\sigma(I)$  after data merging.

<sup>b</sup> $R = 100 \times \sum |F_o| - |F_c| / \sum |F_o|$ .

<sup>c</sup> $R_w = 100 \times [\sum w(|F_o| - |F_c|)^2 / \sum w|F_o|^2]^{1/2}$ .

peak-search, centering, indexing and least-squares refinement routines led to a primitive monoclinic unit cell in each case. Intensity data [for the weakly scattering  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ ,  $2^\circ < 2\theta < 45^\circ$ ; for  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  and  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ ,  $2^\circ < 2\theta < 60^\circ$ ] were collected using the  $\theta/2\theta$  scan mode. Three check reflections, remeasured every 100 observations, showed no significant variation in intensity over the course of each data collection. Empirical corrections for crystal absorption [for  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ , range of equivalent transmission factors = 0.490–0.759;  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  0.517–0.818;  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$  0.676–0.839] were applied on the basis of  $\psi$  scans.

Data merging for  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$  resulted in 1696 reflections ( $R_{\text{int}} = 0.026$ ), with 1162 of these observed according to the criterion  $I > 3\sigma(I)$ . The systematic absences ( $h0l$ ,  $h + l \neq 2n$ ;  $0k0$ ,  $k \neq 2n$ ) indicated space group  $P2_1/n$  (nonstandard setting of  $P2_1/c$ , No. 14). For  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  [3936 merged data; 2794 observed;  $R_{\text{int}} = 0.047$ ], the systematic absences ( $h0l$ ,  $l \neq 2n$ ;  $0k0$ ,  $k \neq 2n$ ) indicated space group  $P2_1/c$ . For  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ , there were 5110 merged data, of which 4255 were observed ( $R_{\text{int}} = 0.025$ ) with the systematic absences indicating space group  $P2_1/n$ .

Direct methods (4) established enough of each structure (Zn, P, some O atoms) to enable the remaining nonhydrogen atoms to be located from difference maps without difficulty. Hydrogen atoms associated with the doubly protonated template molecules were located geometrically [ $d(\text{N-H}) = 0.95$  Å,  $d(\text{C-H}) = 0.95$  Å] and refined by riding on their N and C atoms. Some H atoms associated with P–O bonds were located from Fourier syntheses and refined by riding on their O atoms. The final cycles of full-matrix least-squares refinement [program CRYSTALS (5)], using complex, neutral-atom scattering factors (6), minimized the function  $\sum w_i(F_o - F_c)^2$ , with  $w_i$  described by a three-term Chebychev polynomial (7), and included anisotropic temperature factors for all the nonhydrogen atoms and a Larson-type secondary extinction correction (8). Refinement details are summarized in Table 1. Supplementary data (hydrogen atom coordinates, anisotropic thermal factors, and observed and calculated structure factors) are available from the authors.

## RESULTS

### Crystal Structure of $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$

Final atomic positional and thermal parameters are listed in Table 2, with selected bond distance/angle data in Table 3.  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$  is a new dabco-zinc hydrogen phosphate hydrate with strong one-dimensional character based on chains of  $\text{ZnO}_4$  and  $\text{HPO}_4$  tetrahedra, fused together via Zn–O–P bonds. An ORTEP-3 (9) view of

TABLE 2  
Atomic Coordinates/Thermal Factors for  
(N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn(HPO<sub>4</sub>)<sub>2</sub> · H<sub>2</sub>O

Atom	x	y	z	U <sub>eq</sub> <sup>a</sup>
Zn1	0.44346(9)	0.2480(1)	0.00314(5)	0.0183
P1	0.2622(2)	0.5427(2)	-0.07694(12)	0.0162
P2	0.4067(2)	-0.0575(2)	0.11522(12)	0.0162
O1	0.2805(6)	0.3840(6)	-0.0331(3)	0.0252
O2	0.6010(6)	0.3746(6)	0.0643(3)	0.0264
O3	0.4721(6)	0.1458(7)	-0.0981(3)	0.0272
O4	0.4065(7)	0.1099(6)	0.0884(4)	0.0379
O5	0.4295(6)	-0.0614(7)	0.2189(3)	0.0274
O6	0.2638(6)	-0.1327(6)	0.0762(3)	0.0262
O7	0.1647(6)	0.6383(7)	-0.0320(4)	0.0274
O8	0.1838(6)	0.5316(6)	-0.1758(3)	0.0265
O10	-0.1365(8)	0.679(1)	-0.0958(5)	0.0637
N1	0.1130(7)	0.0359(7)	-0.2399(4)	0.0208
N2	-0.0719(7)	0.0739(8)	-0.1613(4)	0.0245
C1	0.1608(9)	-0.043(1)	-0.1514(5)	0.0311
C2	0.0571(9)	0.0073(11)	-0.0996(5)	0.0315
C3	0.095(1)	0.2046(9)	-0.2259(6)	0.0271
C4	-0.036(1)	0.226(1)	-0.1957(6)	0.0320
C5	-0.0247(9)	-0.030(1)	-0.2939(5)	0.0292
C6	-0.1268(9)	-0.0343(11)	-0.2392(5)	0.0308

$$^a U_{eq} (\text{\AA}^2) = 1/3[U_1 + U_2 + U_3].$$

the asymmetric unit of (N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn(HPO<sub>4</sub>)<sub>2</sub> · H<sub>2</sub>O is shown in Fig. 1, and the complete crystal structure in Fig. 2.

Zn1 makes four Zn–O–P linkages to nearby phosphorus atoms, with typical (1) geometrical parameters [ $d_{av}(\text{Zn–O}) = 1.924(4) \text{\AA}$ ]. Both P atoms form the centers of hydrogen phosphate groups with  $d_{av}(\text{P1–O}) = 1.534(5) \text{\AA}$  and  $d_{av}(\text{P2–O}) = 1.531(5) \text{\AA}$ . Each of these entities participates in two P–O–Zn links, and has two terminal P–O bonds. Assuming that the organic species is doubly protonated, then two “framework” protons are required for

TABLE 3  
Selected Bond Distances (Å) and Angles (°) for  
(N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn(HPO<sub>4</sub>)<sub>2</sub> · H<sub>2</sub>O

Zn1–O1	1.943(5)	Zn1–O2	1.920(5)
Zn1–O3	1.919(5)	Zn1–O4	1.914(5)
P1–O1	1.530(5)	P1–O2	1.490(6)
P1–O7	1.585(6)	P1–O8	1.531(6)
P2–O3	1.510(6)	P2–O4	1.515(6)
P2–O5	1.585(5)	P2–O6	1.513(6)
N1–C1	1.51(1)	N1–C3	1.50(1)
N1–C5	1.492(11)	N2–C2	1.478(11)
N2–C4	1.51(1)	N2–C6	1.52(1)
C1–C2	1.546(12)	C3–C4	1.509(12)
C5–C6	1.505(12)		
Zn1–O1–P1	131.3(3)	Zn1–O2–P1	155.9(4)
Zn1–O3–P2	134.4(3)	Zn1–O4–P2	144.4(4)

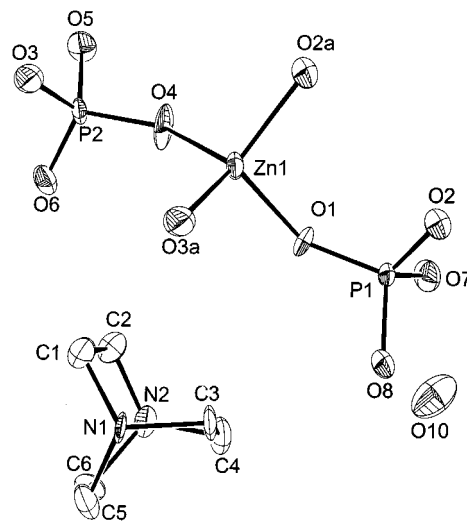


FIG. 1. Fragment of the (N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn(HPO<sub>4</sub>)<sub>2</sub> · H<sub>2</sub>O structure (50% thermal ellipsoids) showing the atom labeling scheme. Symmetry-related atoms are indicated by, e.g., O2a.

charge-balancing purposes. Variations in terminal P–O bond lengths and individual P–O bond valences (10) suggest that the P1–O7 and P2–O5 bonds are protonated, *i.e.*, there are two HPO<sub>4</sub> groups in this phase. The eight distinct framework oxygen atoms thus divide into four Zn–O–P bridges [ $\theta_{av} = 141.5^\circ$ ] and four terminal P–O vertices. The N–C and C–C geometrical parameters for the dabco cation

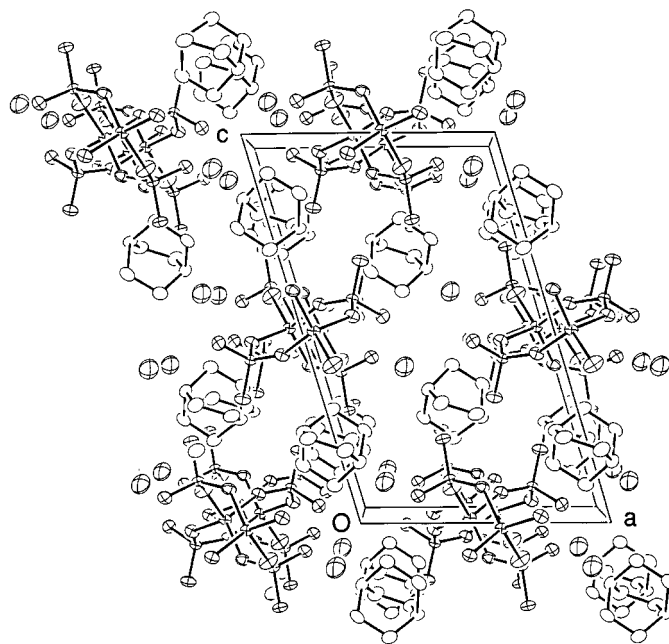


FIG. 2. View down [010] of the (N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn(HPO<sub>4</sub>)<sub>2</sub> · H<sub>2</sub>O crystal structure with H atoms omitted for clarity.

are typical (2). A water molecule of hydration (oxygen atom O10) is present. H atoms associated with this O atom were not located, but hydrogen bonding may well be present, based on the presence of short O10...O1 and O10...O7 contacts of 2.851(9) and 2.87(1) Å, respectively, and an O1...O10...O7 bond angle of 113.9(3)°. If this is the case, then the water molecule serves to crosslink adjacent  $[\text{Zn}(\text{HPO}_4)_2]^{2-}$  chains.

The polyhedral connectivity in  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ , results in corner sharing, anionic four-ring (four nodal tetrahedral atoms) chains of stoichiometry  $[\text{Zn}(\text{HPO}_4)_2]^{2-}$ , which propagate along [010]. The doubly protonated dabco cations occupy interchain sites and bond to the zincophosphate chains through N-H...O hydrogen bonds. Based on the geometrical placement of the hydrogen atoms, both N-H protons are involved in such linkages, as N1-H1...O8 [ $d(\text{H}\cdots\text{O}) = 1.77$  Å,  $d(\text{N}\cdots\text{O}) = 2.706(9)$  Å] and N2-H2...O6 [1.72 Å, 2.668(9) Å], thus the dabco cation bridges adjacent [010]  $[\text{Zn}(\text{HPO}_4)_2]^{2-}$  chains.

#### Crystal Structure of $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$

Final atomic positional and thermal parameters and selected geometrical data are listed in Tables 4 and 5, respectively.  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  is a new 1,3-diammonium propane zinc hydrogen phosphate with

**TABLE 4**  
Atomic Coordinates/Thermal Factors for  
 $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$

Atom	x	y	z	$U_{\text{eq}}^a$
Zn1	0.75902(5)	0.51877(5)	0.47819(3)	0.0132
Zn2	0.67667(5)	0.13227(5)	0.52116(3)	0.0132
P1	0.99029(11)	0.25402(11)	0.48902(6)	0.0131
P2	0.55594(11)	0.40868(11)	0.60954(6)	0.0117
P3	0.54496(11)	-0.10326(11)	0.62802(6)	0.0128
O1	1.1323(4)	0.3077(3)	0.53784(19)	0.0206
O2	0.8922(4)	0.3686(4)	0.44933(19)	0.0215
O3	0.8966(4)	0.1599(4)	0.5391(2)	0.0277
O4	1.0479(4)	0.1707(4)	0.4169(2)	0.0286
O5	0.6702(4)	0.5151(4)	0.57929(18)	0.0207
O6	0.3934(3)	0.4722(3)	0.61202(17)	0.0185
O7	0.5515(4)	0.2755(4)	0.5633(2)	0.0280
O8	0.6104(4)	0.3751(4)	0.69667(18)	0.0230
O9	0.6599(4)	-0.0496(3)	0.5707(2)	0.0203
O10	0.3829(4)	-0.1232(4)	0.59012(19)	0.0269
O11	0.5392(4)	-0.0120(4)	0.70074(18)	0.0237
O12	0.6098(4)	-0.2476(3)	0.66138(19)	0.0241
N1	-0.2408(4)	0.1643(4)	0.7917(2)	0.0201
N2	0.2714(5)	0.1779(5)	0.6731(3)	0.0265
C1	-0.1140(6)	0.0845(6)	0.7585(3)	0.0289
C2	0.0139(5)	0.1799(5)	0.7307(3)	0.0223
C3	0.1414(6)	0.0910(5)	0.7004(3)	0.0265

$$^a U_{\text{eq}} (\text{Å}^2) = 1/3[U_1 + U_2 + U_3]$$


**TABLE 5**  
Selected Bond Distances (Å)<sup>a</sup> and Angles (°) for  
 $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$

Zn1-O1	1.937(3)	Zn1-O2	1.924(3)
Zn1-O5	1.924(3)	Zn1-O6	1.955(3)
Zn2-O3	1.914(3)	Zn2-O7	1.912(3)
Zn2-O9	1.948(3)	Zn2-O10	1.931(3)
P1-O1	1.522(3)	P1-O2	1.518(3)
P1-O3	1.509(3)	P1-O4	1.569(3)
P2-O5	1.528(3)	P2-O6	1.527(3)
P2-O7	1.500(3)	P2-O8	1.559(3)
P3-O9	1.520(3)	P3-O10	1.510(3)
P3-O11	1.518(3)	P3-O12	1.585(3)
N1-C1	1.473(6)	N2-C3	1.492(6)
C1-C2	1.528(7)	C2-C3	1.505(6)
N1-H1...O6	1.98, 2.840(5)	N1-H2...O2	2.20, 2.864(5)
N1-H3...O8	1.91, 2.844(5)	N2-H4...O11	2.17, 2.951(5)
N2-H5...O12	2.15, 3.019(6)	N2-H6...O1	1.89, 2.816(5)
O4-H101...O9	1.87, 2.763(5)	O8-H102...O11	1.67, 2.479(4)
O12-H103...O5	1.84, 2.738(5)		
Zn1-O1-P1	126.28(19)	Zn1-O2-P1	138.8(2)
Zn2-O3-P1	123.3(2)	Zn1-O5-P2	127.7(2)
Zn1-O6-P2	124.40(18)	Zn2-O7-P2	144.4(2)
Zn2-O9-P3	130.53(19)	Zn2-O10-P3	127.2(2)

<sup>a</sup>For the hydrogen bonds, the two distances correspond to the H...O and X...O separations, respectively, for an X-H...O bond.

strong two-dimensional character consisting of infinite, anionic  $[\text{Zn}_2(\text{HPO}_4)_3]^{2-}$  sheets sandwiching 1,3-diammonium-propane cations. The bonding unit and atom labeling scheme for  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  is shown in Fig. 3, and the complete crystal structure in Fig. 4.

The tetrahedral zinc and phosphorus atoms in this phase have typical geometrical parameters (1):  $d_{\text{av}}(\text{Zn1-O}) = 1.935(2)$  Å;  $d_{\text{av}}(\text{Zn2-O}) = 1.926(2)$  Å;  $d_{\text{av}}(\text{P1-O}) = 1.530(2)$  Å;  $d_{\text{av}}(\text{P2-O}) = 1.528(2)$  Å;  $d_{\text{av}}(\text{P3-O}) = 1.533(2)$  Å. Each Zn

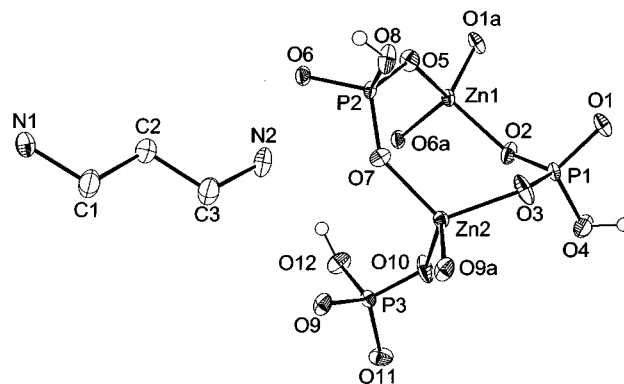

**FIG. 3.** Fragment of the  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  structure showing the atom labeling scheme (50% thermal ellipsoids). Symmetry-related atoms are indicated by, e.g., O1a.

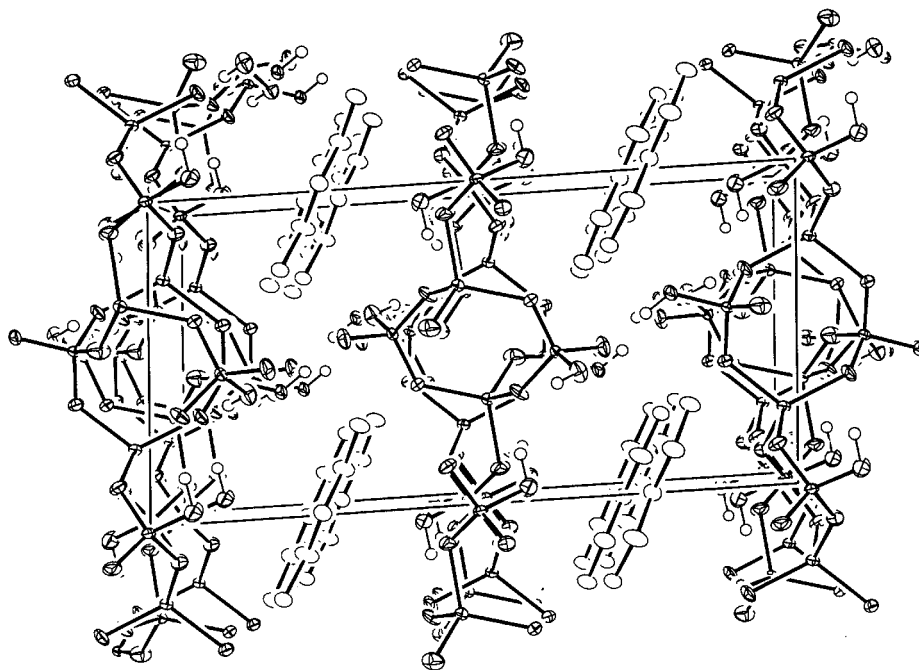


FIG. 4. View down [100] of the  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  structure (H atoms omitted for clarity).

center makes four Zn–O–P bonds. P1 and P2 make three P–O–Zn links and one terminal P–OH bond, whereas P3 makes two links to Zn and has two terminal P–O bonds. The P1–O4H, P2–O8H, and P3–O12H entities were located from Fourier maps. The presence of three  $\text{HPO}_4$  groups is consistent with the charge balancing criterion, which requires three framework H atoms. The average Zn–O–P bond angle (eight contributors) is  $130.3^\circ$ . N–C and C–C bond lengths for the template are unexceptional (1). Torsion angles of  $177.9^\circ$  for the N1–C1–C2–C3 and  $179.3^\circ$  for the C1–C2–C3–N2 groupings of the 1,3-diammonium-propane chain result.

The  $\text{ZnO}_4$  and  $\text{HPO}_4$  groups in  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  fuse together to result in infinite sheets which propagate normal to [001] (Fig. 5). Four-rings and 12-rings are apparent in these sheets.

Template-to-framework hydrogen bonding interactions appear to be significant in stabilizing the layered nature of the  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  structure. All six N–H vertices make H bonds to zincophosphate chain oxygen atoms (Table 5) which variously form parts of Zn–O–P and P–OH groups. Because of the canted arrangement of the  $[\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3]^{2+}$  species (Fig. 4), both N1 and N2 are involved in  $\text{O} \cdots \text{H}-\text{N}-\text{H} \cdots \text{O}$  interlayer interactions. Thus, we might visualize that each end of the  $[\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3]^{2+}$  cation is serving to pillar the anionic zincophosphate layers by “typical” hydrogen bonding interactions (1). The three zincophosphate layer P–OH bonds also serve as H bond donors; two of these bonds are *intralayer*, and one [O8–H102  $\cdots$  O11] is *interlayer*.

#### Crystal Structure of $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$

Final atomic positional and thermal parameters are listed in Table 6, with selected bond distance/angle data in Table 7.  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$  is a new phase based on a three-dimensional network of vertex-sharing  $\text{ZnO}_4$  and  $\text{HPO}_4$  tetrahedra, accompanied by doubly protonated

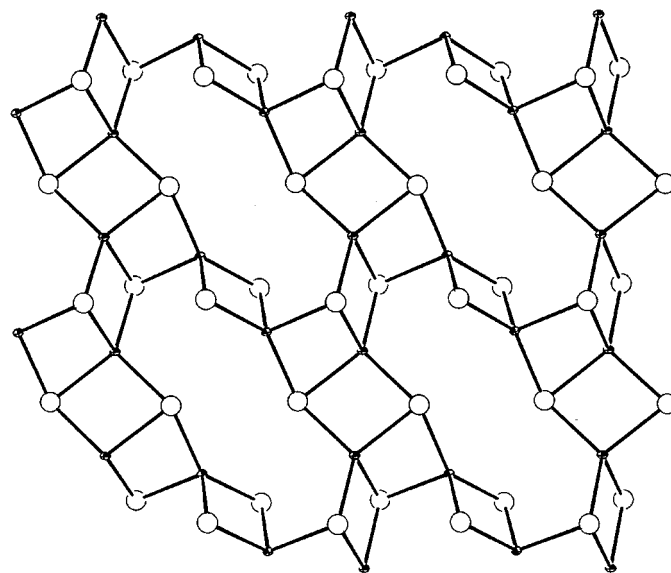


FIG. 5. Topological [Zn (small filled circle) to P (larger open circle)] connectivity of a  $[\text{Zn}_2(\text{HPO}_4)_3]^{2-}$  layer in  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ , showing the presence of 4-rings and 12-rings.

TABLE 6  
Atomic Coordinates/Thermal Factors for  
(N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn<sub>3</sub>(HPO<sub>4</sub>)<sub>4</sub>

Atom	x	y	z	U <sub>eq</sub> <sup>a</sup>
Zn1	0.53789(4)	0.062059(16)	0.66432(4)	0.0146
Zn2	0.77144(4)	0.132774(16)	0.37704(4)	0.0148
Zn3	0.87360(4)	0.226624(16)	1.09671(4)	0.0154
P1	0.54094(9)	0.17871(4)	0.50164(9)	0.0148
P2	0.75547(9)	0.09971(3)	1.03238(9)	0.0133
P3	0.23179(9)	-0.01297(4)	0.46630(9)	0.0153
P4	1.07834(9)	0.20413(4)	0.44911(9)	0.0152
O1	0.4507(3)	0.13111(11)	0.5367(3)	0.0267
O2	0.5803(3)	0.16138(12)	0.3727(3)	0.0244
O3	0.4459(3)	0.23393(11)	0.4614(3)	0.0222
O4	0.7058(3)	0.18723(13)	0.6538(3)	0.0290
O5	0.6061(3)	0.08387(11)	0.8840(3)	0.0202
O6	0.8464(3)	0.14937(11)	1.0084(3)	0.0254
O7	0.7139(3)	0.11151(12)	1.1627(3)	0.0264
O8	0.8658(3)	0.04463(11)	1.0723(3)	0.0265
O9	0.3528(3)	0.01534(11)	0.6163(3)	0.0238
O10	0.2918(3)	-0.02470(15)	0.3488(3)	0.0357
O11	0.1542(4)	-0.06433(13)	0.4982(3)	0.0379
O12	0.0881(3)	0.03080(11)	0.3753(3)	0.0255
O13	0.9257(3)	0.19271(12)	0.4548(3)	0.0294
O14	1.0548(3)	0.23493(13)	0.3006(3)	0.0319
O15	1.1937(3)	0.23645(12)	0.5938(3)	0.0255
O16	1.1505(4)	0.14264(12)	0.4509(4)	0.0366
N1	0.6539(3)	-0.10396(13)	0.0616(3)	0.0216
N2	0.8735(4)	-0.1400(2)	0.0187(5)	0.0526
C1	0.6377(5)	-0.16734(17)	0.0390(6)	0.0357
C2	0.6464(5)	-0.0757(2)	-0.0795(5)	0.0361
C3	0.8090(5)	-0.0899(2)	0.2027(4)	0.0321
C4	0.7727(8)	-0.1883(3)	0.0123(11)	0.0877
C5	0.7790(7)	-0.0977(4)	-0.1069(7)	0.0838
C6	0.9412(5)	-0.1119(3)	0.1744(5)	0.0473

$$^a U_{eq} (\text{\AA}^2) = 1/3[U_1 + U_2 + U_3].$$

dabco cations. The bonding unit of (N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn<sub>3</sub>(HPO<sub>4</sub>)<sub>4</sub> is shown in Fig. 6, and the complete crystal structure in Fig. 7.

The tetrahedral ZnO<sub>4</sub> and HPO<sub>4</sub> moieties in (N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn<sub>3</sub>(HPO<sub>4</sub>)<sub>4</sub> have typical geometrical parameters, with average bond lengths as follows: Zn1 1.937(1) Å, Zn2 1.919(1) Å, Zn3 1.935(1) Å, P1 1.533(2) Å, P2 1.532(2) Å, P3 1.532(2) Å, P4 1.528(2) Å. Each of the Zn centers makes four Zn–O–P bonds. All the P atoms make three P–O–Zn bonds and one terminal P–OH bond, as required by the charge balancing criterion, which requires four framework H atoms. Three of these H atoms were located from difference maps, and the fourth was implied by the long P3–O12 bond. The average Zn–O–P bond angle, based on 12 contributors, is 132.6°. N–C and C–C bond lengths for the dabco template are typical (2).

The ZnO<sub>4</sub> and HPO<sub>4</sub> groups in H<sub>3</sub>N(CH<sub>2</sub>)<sub>3</sub>NH<sub>3</sub> · Zn<sub>2</sub>(HPO<sub>4</sub>)<sub>3</sub> fuse together to result in a three-dimensional framework which contains 12-rings propagating along

TABLE 7  
Selected Bond Distances (Å) and Angles (°) for  
(N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn<sub>3</sub>(HPO<sub>4</sub>)<sub>4</sub>

Zn1–O1	1.954(2)	Zn1–O5	1.960(2)
Zn1–O9	1.936(2)	Zn1–O10	1.897(3)
Zn2–O2	1.923(2)	Zn2–O7	1.928(2)
Zn2–O11	1.917(3)	Zn2–O13	1.908(2)
Zn3–O3	1.958(2)	Zn3–O6	1.951(2)
Zn3–O14	1.923(3)	Zn3–O15	1.907(2)
P1–O1	1.532(3)	P1–O2	1.504(2)
P1–O3	1.514(2)	P1–O4	1.582(3)
P2–O5	1.517(2)	P2–O6	1.524(3)
P2–O7	1.501(2)	P2–O8	1.586(3)
P3–O9	1.513(2)	P3–O10	1.507(3)
P3–O11	1.509(3)	P3–O12	1.600(2)
P4–O13	1.505(2)	P4–O14	1.514(3)
P4–O15	1.509(2)	P4–O16	1.583(3)
N1–C1	1.487(5)	N1–C2	1.475(5)
N1–C3	1.504(5)	N2–C4	1.461(9)
N2–C5	1.489(9)	N2–C6	1.474(5)
C1–C4	1.505(7)	C2–C5	1.496(8)
C3–C6	1.498(5)		
Zn1–O1–P1	127.75(15)	Zn2–O2–P1	132.17(15)
Zn3–O3–P1	125.56(15)	Zn1–O5–P2	140.15(14)
Zn3–O6–P2	127.00(15)	Zn2–O7–P2	151.54(17)
Zn1–O9–P3	132.64(15)	Zn1–O10–P3	140.09(18)
Zn2–O11–P3	135.18(19)	Zn2–O13–P4	134.23(17)
Zn3–O14–P4	125.31(16)	Zn3–O15–P4	120.21(15)

[001]. Based on atom-to-atom measurements, these highly-squashed rings are ~4.0 × 17.5 Å in size. Four-rings, and 8-rings are also present in this topology. A notable feature of the structure is the grouping of three edge-sharing 4-rings (Fig. 8).

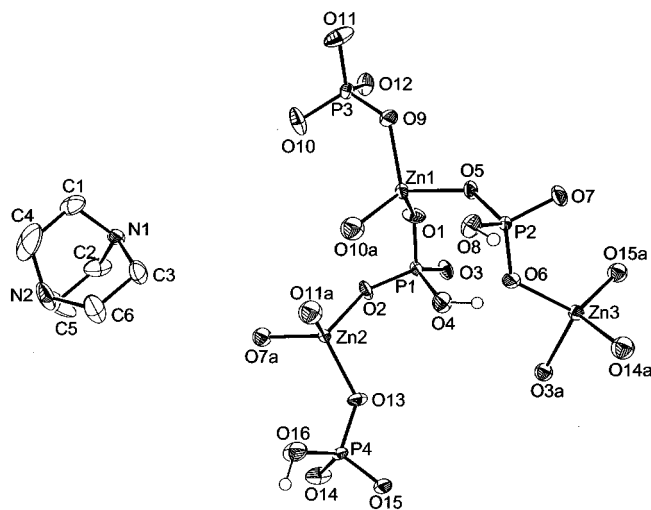


FIG. 6. Fragment of the (N<sub>2</sub>C<sub>6</sub>H<sub>14</sub>) · Zn<sub>3</sub>(HPO<sub>4</sub>)<sub>4</sub> structure (50% thermal ellipsoids) showing the atom labeling scheme. Symmetry-related atoms are indicated by, e.g., O3a.

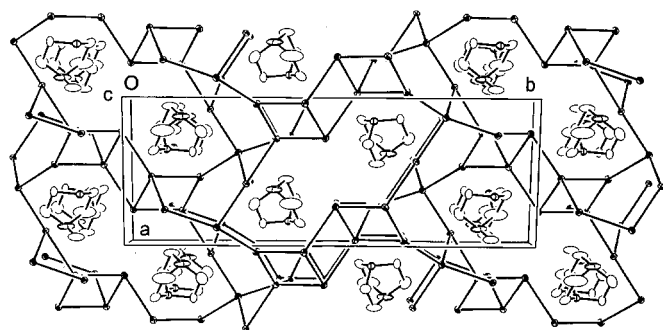


FIG. 7. View down [001] of the  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$  crystal structure with the  $\text{Zn}_3(\text{HPO}_4)_4$  framework represented in skeletal form, showing only the Zn to P connectivity. Pairs of dabco cations occupy the 12-ring windows.

The doubly protonated dabco cations bond to the zincophosphate network through N–H...O hydrogen bonds, as N1–H1...O5 [ $d(\text{H} \cdots \text{O}) = 1.87 \text{ \AA}$ ,  $d(\text{N} \cdots \text{O}) = 2.801(3) \text{ \AA}$ ] and N2–H2...O6 [ $1.92 \text{ \AA}$ ,  $2.809(4) \text{ \AA}$ ], based on the geometrical placement of the hydrogen atoms. In this structure, the dabco cation occupies and bridges across an [001] 12-ring. Two P–OH...O bonds are also involved in stabilizing the 12-ring channels, as O8–H16...O12 [ $1.85 \text{ \AA}$ ,  $2.702(4) \text{ \AA}$ ] and O16–H18...O1 [ $1.66 \text{ \AA}$ ,  $2.599(4) \text{ \AA}$ ]. The third definitely located P–OH...O bond in this structure weakly bonds across a 6-ring, as O4–H15...O14 [ $2.26 \text{ \AA}$ ,  $3.035(4) \text{ \AA}$ ].

## DISCUSSION

Three new organically templated zincophosphates,  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ ,  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ ,

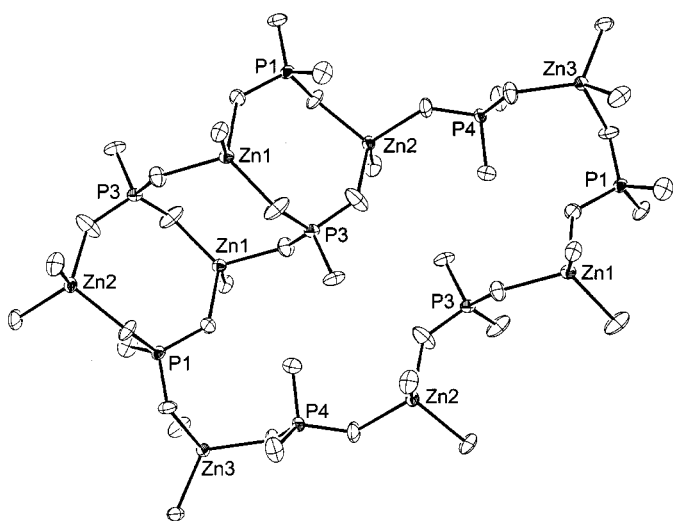


FIG. 8. Detail of the zincophosphate framework of  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$  showing a triplet of edge-sharing 4-rings and a 12-ring window.

and  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$ , have been prepared as single crystals from solution mediated reactions and structurally characterized by X-ray methods. They consist of the typical polyhedral units of  $\text{ZnO}_4$  and  $\text{HPO}_4$  tetrahedra, sharing vertices (1). Only Zn–O–P bonds occur as intertetrahedral linkages in these phases, despite the less-than-unity Zn:P atomic ratio found in each phase. Some terminal P–O and P–OH vertices occur, as previously observed in related compounds (1). Based on chemical composition, they form a family of phases  $t \cdot \text{Zn}_n(\text{HPO}_4)_{n+1}$  ( $t = [\text{template}]^{2+}$ ,  $n = 1-3$ ). However, their structures are completely different and the chain, layer, and network structures described above result. Similar results have been achieved for vanadium phosphates, where the dimensionality of the vanadophosphate network can be controlled by choice of template (11).

$(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$  is closely related to  $\text{RbZn}(\text{HPO}_4)(\text{H}_2\text{PO}_4) \cdot \text{H}_2\text{O}$  (12) and  $\text{NH}_4\text{Zn}(\text{HPO}_4)(\text{H}_2\text{PO}_4) \cdot \text{H}_2\text{O}$  (13), with all three phases showing the same corner-sharing 4-ring ZnPO chain architecture. The rubidium and ammonium phases achieve charge balance with an additional framework proton, as an  $\text{H}_2\text{PO}_4$  group. In  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$ ,  $\text{RbZn}(\text{HPO}_4)(\text{H}_2\text{PO}_4) \cdot \text{H}_2\text{O}$ , and  $\text{NH}_4\text{Zn}(\text{HPO}_4)(\text{H}_2\text{PO}_4) \cdot \text{H}_2\text{O}$ , the ZnPO chains all propagate in the same direction. Conversely, in  $(\text{NC}_2\text{H}_8) \cdot \text{Zn}(\text{HPO}_4)(\text{H}_2\text{PO}_4) \cdot 1/2\text{H}_2\text{O}$  (14), similar ZnPO chains adopt a criss-cross *motif* between layers.  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}(\text{HPO}_4)_2$  (1) adopts a distinctly different structure, based on *edge*-shared tetrahedral 4-rings. This topology is also adopted by the one-dimensional organoaluminophosphate  $\text{C}_{10}\text{N}_2\text{H}_9 \cdot \text{Al}(\text{PO}_4)(\text{H}_2\text{PO}_4)$  (15). Both the corner shared and edge-shared 4-ring *motifs* are well known as subunits in three-dimensional aluminosilicate structures (16). Other phases with a 1:2 Zn:P ratio, such as  $\text{N}(\text{CH}_3)_4 \cdot \text{Zn}(\text{HPO}_4)(\text{H}_2\text{PO}_4)$  (17) and  $(\text{CN}_3\text{H}_6)_2 \cdot \text{Zn}(\text{HPO}_4)_2$  (18), form a radically different type of three-dimensional structure in which the  $\text{H}_2/\text{HPO}_4$  groups serve as “spacers” between tetrahedral  $\text{ZnO}_4$  nodes, leading to fragile, but exceptionally low-density structures based on tetrahedral 12-rings.

The layered  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  complements the one-dimensional  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}(\text{HPO}_4)_2$  and the two-dimensional  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_2(\text{H}_2\text{PO}_4)_2$  templated by the same cation (1). A notable difference between these three phases is in the geometry of the 1,3-diammonium propane template cation. In  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}(\text{HPO}_4)_2$  and  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_2(\text{H}_2\text{PO}_4)_2$ , the organic species is highly contorted, whereas in  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$  it is in the almost ideal, “straight” configuration as quantified in terms of torsion angles which are near  $180^\circ$ . The same molecule adopts an essentially identical conformation in  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot (\text{H}_2\text{PO}_4)_2$  with similar N–H...O hydrogen bonding linkages (19). Although the  $[\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3]^{2+}$  cation has

a quite different conformation, there appears to be a rather similar templating effect for the layered  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_2(\text{H}_2\text{PO}_4)_2$  and  $\text{H}_3\text{N}(\text{CH}_2)_3\text{NH}_3 \cdot \text{Zn}_2(\text{HPO}_4)_3$ . For the former (1), a strong correlation between N–H...O bonds and 12-ring holes in adjacent zincophosphate layers is apparent; for the latter, the situation is described above.

$(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_3(\text{HPO}_4)_4$  complements other complex three-dimensional dabco–zinc phosphates including  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_2(\text{HPO}_4)_3$  (2),  $(\text{N}_2\text{C}_6\text{H}_{14}) \cdot \text{Zn}_4(\text{PO}_4)_2(\text{HPO}_4)_2 \cdot 3\text{H}_2\text{O}$  (2),  $(\text{N}_2\text{C}_2\text{H}_{14})_2 \cdot \text{Zn}_5(\text{PO}_4)_2(\text{HPO}_4)_4 \cdot \text{H}_2\text{O}$  (20), and  $(\text{N}_2\text{C}_2\text{H}_{13}) \cdot \text{Zn}_3(\text{PO}_4)(\text{HPO}_4)_2$  (20). One point of commonality may be identified in terms of the presence of the ubiquitous 4-ring subunit (21). However, these five structures have little further similarity in terms of their overall architectures.  $(\text{N}_2\text{C}_2\text{H}_{13}) \cdot \text{Zn}_3(\text{PO}_4)(\text{HPO}_4)_2$  contains Zn–N(template) bonds, which are so far unique in open-framework zincophosphates.

Overall, it would be optimistic to claim any clear structure-directing effect for these cations at this stage. Clearly, template-to-framework hydrogen bonding is important, but there are many other structural variables involved, including the Zn:P ratio, presence of “dangling,” terminal P–O, P–OH, Zn–OH<sub>2</sub> bonds, and framework charge. Indeed, the variety of structures obtainable in this area of chemistry is one of its most striking features. We are continuing to explore these materials, with one goal being the synthesis of more “zeolite-like” [materials containing a 1:1 Zn:P ratio with Zn–O–P bridges linking *all* the ZnO<sub>4</sub> and PO<sub>4</sub> groups and no dangling bonds] organically templated zincophosphates (22).

#### ACKNOWLEDGMENTS

W.T.A.H. thanks the Australian Research Council for partial funding. T.M.N. and A.V.C. thank the U.S. DOE/OIT/Advanced Industrial Materials (AIM) for financial support. This work is partially supported by the U.S. DOE under Contract DE-AC04-94AL85000.

#### REFERENCES

1. W. T. A. Harrison, Z. Bircsak, L. Hannooman, and Z. Zhang, *J. Solid State Chem.* **136**, 93 (1998), and included references.
2. W. T. A. Harrison, T. E. Gier, T. E. Martin, and G. D. Stucky, *J. Mater. Chem.* **2**, 175 (1992).
3. T. Song, M. B. Hursthouse, J. Chen, J. Xu, K. M. A. Malik, R. H. Jones, R. Xu, and J. M. Thomas, *Adv. Mater.* **6**, 679 (1994).
4. G. M. Sheldrick, SHELXS User Guide, University of Göttingen, Germany.
5. D. J. Watkin, J. R. Carruthers, and P. W. Betteridge, CRYSTALS User Guide, Chemical Crystallography Laboratory, Univ. of Oxford.
6. “International Tables for Crystallography,” Vol. IV. Kynoch Press, Birmingham, UK.
7. J. R. Carruthers and D. J. Watkin, *Acta Crystallogr.* **A35**, 698 (1979).
8. A. C. Larson, *Acta Crystallogr.* **23**, 664 (1967).
9. L. J. Farrugia, *J. Appl. Crystallogr.* **30**, 565 (1997).
10. P. Lightfoot and D. Masson, *Acta Crystallogr.* **C52**, 1077 (1996).
11. V. Sogomonian, Q. Chen, R. C. Haushalter, and J. Zubietta, *Angew. Chem. Int. Ed. Engl.* **34**, 223 (1995).
12. W. T. A. Harrison, Z. Bircsak, and L. Hannooman, *J. Solid State Chem.* **134**, 148 (1997).
13. A. Boudjada, D. Tranqui, and J. C. Guitel, *Acta Crystallogr.* **B36**, 1176 (1980).
14. P. Reinert, N. Z. Logar, J. Patarin, and V. Kaucic, *Eur. J. Solid State Inorg. Chem.* **35**, 373 (1998).
15. A. M. Chippindale and C. Turner, *J. Solid State Chem.* **128**, 318 (1997).
16. M. Schindler and W. H. Baur, *Angew. Chem.* **109**, 88 (1997).
17. (a) W. T. A. Harrison and L. Hannooman, *Angew. Chem. Int. Ed. Engl.* **36**, 640 (1997); (b) W. T. A. Harrison and L. Hannooman, *J. Solid State Chem.* **131**, 363 (1997).
18. W. T. A. Harrison and M. L. F. Phillips, *Chem. Mater.* **9**, 1837 (1997).
19. S. Kamoun, A. Jouini, A. Daoud, A. Durif, and J.-C. Guitel, *Acta Crystallogr.* **C48**, 133 (1992).
20. W. T. A. Harrison, T. M. Nenoff, M. M. Eddy, T. E. Martin, and G. D. Stucky, *J. Mater. Chem.* **2**, 1127 (1992).
21. D. Chidambaram, S. Neeraj, S. Natarajan, and C. N. R. Rao, *J. Solid State Chem.* **147**, 154–169 (1999).
22. (a) R. H. Jones, J. Chen, G. Sankar, and J. M. Thomas, “Zeolites and Microporous Materials: State of the Art 1994,” p. 2229. Elsevier, New York, 1994, (b) S. B. Harmon and S. C. Sevov, *Chem. Mater.* **10**, 3020 (1998).