

Synthesis, crystal structure and magnetic property of a new nickel selenite chloride: $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$

Yue-Ling Shen, Jiang-Gao Mao*, Hai-Long Jiang

State Key Laboratory of Structural Chemistry, Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences, and the Graduate School of the Chinese Academy of Sciences, Fuzhou 350002, PR China

Received 3 May 2005; received in revised form 25 June 2005; accepted 7 July 2005

Abstract

The new nickel selenite chloride, $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$, was obtained by high-temperature solid state reaction of NiCl_2 , Ni_2O_3 and SeO_2 in a 1:2:4 molar ratio at 700 °C in an evacuated quartz tube. Its structure was established by single-crystal X-ray diffraction. $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ crystallizes in the triclinic system, space group $P-1$ (No. 2) with cell parameters of $a = 8.076(2)$, $b = 9.288(2)$, $c = 9.376(2)$ Å, $\alpha = 101.97(3)$, $\beta = 105.60(3)$, $\gamma = 91.83(3)^\circ$ and $Z = 2$. All nickel(II) ions in $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ are octahedrally coordinated by selenite oxygens or/and chloride anions ($[\text{Ni}(1)\text{O}_5\text{Cl}]$, $[\text{Ni}(2)\text{O}_4\text{Cl}_2]$, $[\text{Ni}(3)\text{O}_5\text{Cl}]$, $[\text{Ni}(4)\text{O}_6]$ and $[\text{Ni}(5)\text{O}_4\text{Cl}]$). The structure of the title compound features a condensed three-dimensional (3D) network built by Ni(II) ions interconnected by SeO_3^{2-} anions as well as Cl^- anions. Magnetic property measurements show strong antiferromagnetic interaction between nickel(II) ions. © 2005 Elsevier Inc. All rights reserved.

Keywords: Nickel selenite chloride; Crystal structure; Solid state reaction; Open framework; Magnetic property

1. Introduction

During the past two decades, metal selenites and tellurites have been of research interest to scientists in chemistry and materials [1]. The asymmetric coordination polyhedron adopted by Se(IV) or Te(IV) atom may result in noncentrosymmetric structures with consequent interesting physical properties, such as nonlinear optical second harmonic generation (SHG) [2–5]. Furthermore, lone-pair elements such as Se(IV) and Te(IV), when mixed with a transition metal in the presence of halogen ions, can be regarded as “chemical scissors” [6–9]. Transition metal Te(IV) or Se(IV) oxo-halogenides have also been proved to be promising new low-dimensional magnets [6–9]. A number of transition metal oxo-halogenides containing lone-pair elements have been reported [6–20], some of which are similar to natural minerals [21–24].

As far as the $\text{NiO-NiX}_2\text{-QO}_2$ ($X = \text{Cl, Br, I; Q} = \text{Se, Te}$) system is concerned, several nickel tellurite halides have been reported [9–10]. For example, $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ with a layered structure has been found to be a new two-dimensional (2D) $S = 1$ quantum spin system with antiferromagnetic super-exchange interaction. To the best of knowledge, there are no structural reports on nickel selenite halides. Our exploration of compounds in $\text{Ni-SeO}_2\text{-Cl}$ system lead to a new nickel(II) selenite chloride, $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$, whose structure differs significantly from the layered $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ with a comparable formula [9]. Herein we report its synthesis, crystal structure and magnetic property.

2. Experimental

2.1. Synthesis

All chemicals were obtained from commercial sources and used without further purification. $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$

*Corresponding author. Fax: +86 591 371 4946.
E-mail address: mjg@ms.fjirsm.ac.cn (J.-G. Mao).

was prepared by solid state reaction of 0.4 mmol of NiCl_2 , 0.8 mmol of Ni_2O_3 and 1.6 mmol of SeO_2 . The reaction mixture was thoroughly ground and pressed into a pellet, which was subsequently put into a quartz tube, evacuated and sealed. The quartz tube was heated at 700°C for 6 days and then cooled to 350°C at 4°C h^{-1} before switching off the furnace. Two major phases were observed, namely, $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ (brick, orange) and NiSeO_3 (plate, red). Efforts to make a single-phase product were tried but unsuccessful. The sample used for magnetic measurements is composed of single crystals of $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ selected based on its unique color and shape.

2.2. Single-crystal structure determination

An orange brick-shaped single crystal with dimension of $0.30 \times 0.20 \times 0.16$ mm was mounted on Rigaku Mercury CCD using $\text{MoK}\alpha$ radiation ($\lambda = 0.71073 \text{ \AA}$), and a graphite monochromator at room temperature. The data were corrected for Lorentz factor, polarization, air absorption and absorption due to variations in the path length through the detector faceplate. Absorption correction based on Multi-scan technique was also applied [25]. The space group was determined to be $P-1$ (No. 2). The structure was solved by direct methods (SHELXTL) and refined by least-square methods with atomic coordinates and anisotropic thermal parameters [25]. O(10) atom was refined with isothermal parameters. Final difference Fourier maps were essentially featureless with residual peaks of 1.967 and $-1.792 \text{ e \AA}^{-3}$, which are less than 0.9 \AA from Se(4) and Se(2), respectively. The crystallographic data collection and refinement parameters are summarized in Table 1. Selected bond lengths are listed in Table 2.

2.3. Magnetic susceptibility measurements

Magnetic susceptibility measurements for $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ (0.0231 g, single crystals) were performed with a PPMS-9T magnetometer at 200 Oe and 1.0 T in the range of 2.0–300 K, respectively. Zero-field-cooling (ZFC) measurements were also performed. The raw data were corrected for the susceptibility of the container and the diamagnetic contributions of the sample using Pascal's constants.

3. Results and discussion

$\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ exhibits a different structure from $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ with a similar formula [9]. $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ (monoclinic $C2/c$) is layered while $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ (triclinic, $P-1$) has a 3D structure.

There are five independent nickel atoms in $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$. As shown in Fig. 1, all five nickel(II) ions are six-

Table 1
Crystal data and structure refinement for $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$

Empirical formula	$\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$
Formula weight	872.29
T (K)	293
Crystal system	Triclinic
Space group	$P-1$ (No. 2)
a (\AA)	8.076(2)
b (\AA)	9.288(2)
c (\AA)	9.376(2)
α ($^\circ$)	101.97(3)
β ($^\circ$)	105.60(3)
γ ($^\circ$)	91.83(3)
V (\AA^3)	659.8(2)
Z	2
D_c (g cm^{-3})	2.195
μ ($\text{MoK}\alpha$) (mm^{-1})	9.251
$F(000)$	406
Colour, habit	Orange, brick
Crystal size (mm)	$0.30 \times 0.20 \times 0.16$
Data collected	5409
Independent data	3225 ($R_{\text{int}} = 0.0296$)
Observed data [$I > 2\sigma(I)$]	2830
Data/restraints/parameters	3225/0/209
Goodness-of-fit on F^2	1.035
R_1, wR_2 [$I > 2\sigma(I)$] ^a	0.0324, 0.0759
R_1, wR_2 (all data)	0.0364, 0.0774
Largest diff. peak and hole (e \AA^{-3})	1.967 and -1.792

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|, wR_2 = \{ \sum w[(F_o)^2 - (F_c)^2]^2 / \sum w[(F_o)^2]^2 \}^{1/2}.$$

Table 2
Selected bond lengths (\AA) for $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$

Ni(1)–O(9)#1	2.001(4)	Ni(1)–O(6)#2	2.074(4)
Ni(1)–O(6)	2.084(4)	Ni(1)–O(3)	2.117(4)
Ni(1)–O(2)	2.149(4)	Ni(1)–Cl(1)	2.356(2)
Ni(2)–O(12)#3	2.022(4)	Ni(2)–O(10)#4	2.052(3)
Ni(2)–O(8)#4	2.072(3)	Ni(2)–O(1)	2.080(3)
Ni(2)–Cl(1)	2.329(2)	Ni(2)–Cl(2)	2.493(2)
Ni(3)–O(3)#3	2.020(4)	Ni(3)–O(12)	2.035(3)
Ni(3)–O(7)#5	2.060(4)	Ni(3)–O(5)#6	2.177(4)
Ni(3)–O(11)	2.294(4)	Ni(3)–Cl(2)	2.353(2)
Ni(4)–O(7)	2.039(4)	Ni(4)–O(11)	2.045(4)
Ni(4)–O(9)	2.051(4)	Ni(4)–O(5)#1	2.054(3)
Ni(4)–O(5)#6	2.095(3)	Ni(4)–O(10)	2.117(3)
Ni(5)–O(4)#1	1.997(4)	Ni(5)–O(11)	1.999(4)
Ni(5)–O(8)#4	2.001(4)	Ni(5)–O(2)#1	2.026(3)
Ni(5)–O(1)	2.111(4)	Ni(5)–Cl(2)	2.783(2)
Ni(1)–Ni(1)#2	3.215(2)	Ni(2)–Ni(5)	2.940(1)
Ni(3)–Ni(4)#5	3.086(1)	Ni(3)–Ni(4)	3.211(1)
Ni(3)–Ni(5)	3.444(1)	Ni(4)–Ni(4)#5	3.094(2)

Symmetry transformations used to generate equivalent atoms: #1 $-x+1, -y, -z+1$; #2 $-x, -y, -z$; #3 $-x+1, -y+1, -z+1$; #4 $x-1, y, z$; #5 $-x+2, -y+1, -z+2$; #6 $x+1, y+1, z+1$.

coordinated by selenite oxygen or/and chlorine atoms in a distorted octahedral geometry. Ni(1) and Ni(3) are octahedrally coordinated by one chlorine and five oxygen atoms from four selenite anions, and Ni(2) is coordinated by two chlorine and four oxygen atoms from four selenite anions. Ni(4) is octahedrally coordinated by six oxygen atoms from four selenite anions,

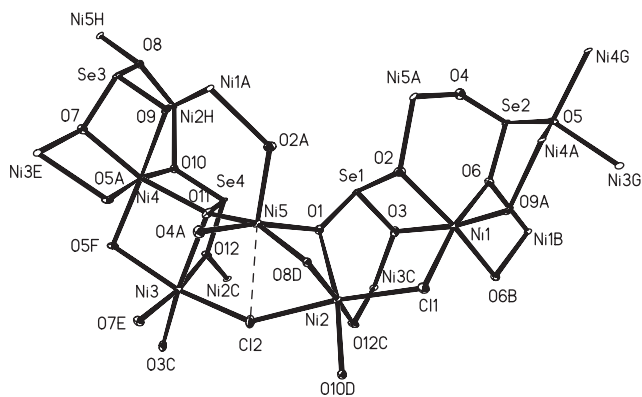


Fig. 1. ORTEP representation of the selected unit of $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ showing the coordination geometries around the Ni(II) and Se(IV) ions. The thermal ellipsoids are drawn at 50% probability. Symmetry codes for the generated atoms: (a) $-x+1, -y, -z+1$; (b) $-x, -y, -z$; (c) $-x+1, -y+1, -z+1$; (d) $x-1, y, z$; (e) $-x+2, -y+1, -z+2$; (f) $x+1, y+1, z+1$; (g) $x-1, y-1, z-1$; (h) $x+1, y, z$.

Ni(5) is octahedrally coordinated by one chlorine and five oxygen atoms from five selenite anions. The Ni–O distances are in the range of 1.997(4)–2.294(4) Å and the Ni–Cl ones ranges from 2.329(2) to 2.783(2) Å, which are similar to those reported in the literatures [9]. The Ni(2) octahedron with Ni(2)–Cl(1) bond length of 2.783(2) Å has the largest distortion (Table 2). There are only NiO_6 and NiO_5Cl octahedra in the layered $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ [9]. All four selenium(IV) atoms are three-coordinated by three oxygen atoms in a distorted ψ - SeO_3 tetrahedral geometry with the fourth site occupied by the lone-pair electrons, which are similar to those of the tellurium(IV) atoms in $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ [9]. The Se–O distances range between 1.657(4) and 1.782(4) Å, which are comparable to those reported in other metal selenites [1]. Results of the bond valence calculations indicate that all selenium atoms are in +4 oxidation state [26]. The calculated total bond valences are 4.04, 3.93, 3.98 and 3.91, respectively, for Se(1), Se(2), Se(3) and Se(4). Cl(1) and Cl(2) anions in $\text{Ni}_5(\text{SeO}_3)_4\text{Cl}_2$ bridge to two and three nickel(II) ions, respectively, whereas the chloride anions in $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$ are unidentate and are orientated toward the interlayer space [9].

The Se(1) O_3 group is hexadentate, chelating bidentately with a Ni(1) (O(2) and O(3)) and also bridging with 1 Ni(2), 1 Ni(3), and 2 Ni(5). The Se(2) O_3 group is hexadentate and bridges with 2 Ni(1), 2 Ni(4), 1 Ni(3) and 1 Ni(5). O(5) is a tridentate metal linker. The Se(3) O_3 group is hexadentate, chelating bidentately with a Ni(4) (O(7) and O(9)) and also bridging to four other Ni(II) ions (Ni(1), Ni(2), Ni(3) and Ni(5)). The Se(4) O_3 group is heptadentate, chelating bidentately with a Ni(3) (O(11) and O(12)) and chelating bidentately with a Ni(4) (O(10) and O(11)), as well as bridging to 1 Ni(5) and 2 Ni(2) atoms (Fig. 1), O(10) is tridentate metal linker and

other two oxygen atoms are bidentate. These coordination modes are different from those of tellurite anion in $\text{Ni}_5(\text{TeO}_3)_4\text{Cl}_2$, in which all tellurite anions are heptadentate, two of which each chelates bidentately with a nickel(II) ion and bridges to five other nickel(II) ions whereas the remaining two each bridges to seven nickel(II) ions [9].

It is worthy to mention the particular connectivity between different nickel(II) octahedra (Fig. 2). The Ni(1) O_6 octahedron is edge-sharing (O6–O6) with a neighbouring Ni(1) O_6 octahedron, and is also corner-sharing with Ni(2), Ni(3), Ni(4) and Ni(5) octahedra (Fig. 2a). Ni(3) O_5Cl octahedron is edge-sharing with one Ni(4) (O5–O7) and one Ni(5) (O11–Cl2) octahedron, corner-sharing with one Ni(1) (O3) and two Ni(2) (Cl2 and O12) octahedra. The Ni(5) ClO_5 octahedron connects by face-sharing with a Ni(2) (O1–Cl2–O8) octahedron and edge-sharing with a Ni(3) (Cl2–O11) octahedron, and corner-sharing with Ni(3) and Ni(4) octahedra. The Ni(2) O_5Cl octahedra is face-sharing with a Ni(5) octahedron and corner-sharing with Ni(1), Ni(3)

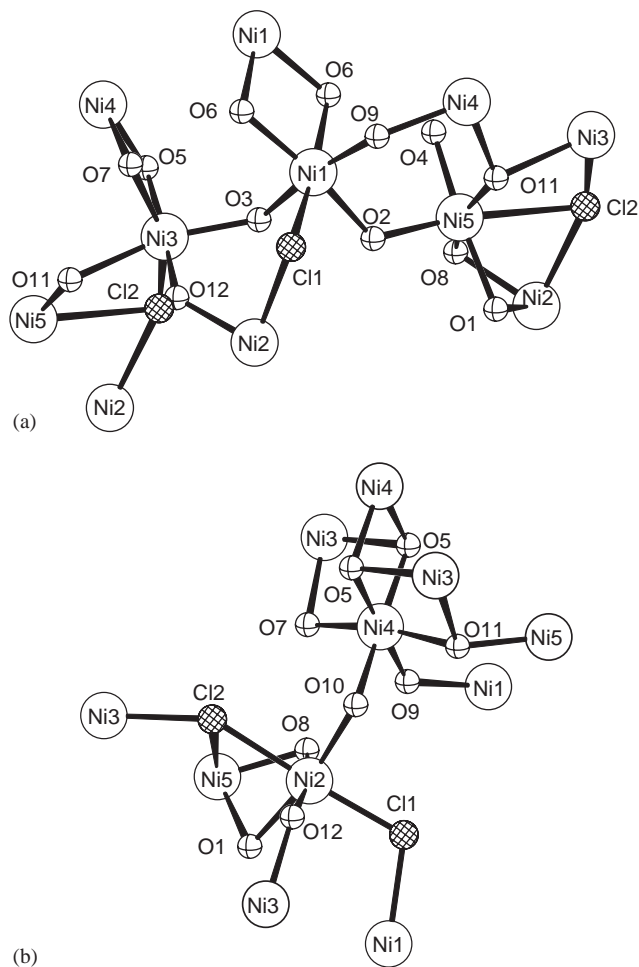


Fig. 2. (a) The connectivity scheme of Ni(1), Ni(3) and Ni(5) with their neighbouring Ni(II) ions; (b) The connectivity scheme of Ni(2) and Ni(4) with their neighbouring Ni(II) ions.

and Ni(4) octahedra (Fig. 2b). The Ni(4)O₅Cl octahedron is edge-sharing with two Ni(3) (O5–O11 and O5–O7) octahedra and one Ni(4) (O5–O5) octahedron, in addition to corner-sharing with the Ni(1), Ni(2) and Ni(5) octahedra (Fig. 2b). The two nickel octahedra interconnected via face-sharing have the shortest Ni...Ni separation (2.934(2) Å), followed by those via O–O edge-sharing (in the range of 3.086(1)–3.215(1) Å) and via O–Cl edge-sharing (3.444(1) Å) (Table 2). The Ni...Ni distances between nickel(II) centres bridged by a selenite oxygen are at least 3.657(1) Å.

The interconnection of the Ni(II) ions by SeO₃²⁻ anions as well as Cl⁻ anions results in a 3D network with cavities occupied by the lone-pair electrons of the Se⁴⁺ ions (Fig. 3). The 3D network can also be viewed as formed by the interconnection of nickel(II) octahedra via corner-, edge- and face-sharing with Se⁴⁺ ions capping on the cavities (Fig. 3).

Magnetic property of Ni₅(SeO₃)₄Cl₂ has also been studied. The μ_{eff} of 6.1 μ_{B} at room temperature measured at 1 T is slightly smaller than 6.33 μ_{B} expected for five spin-only Ni²⁺ ions (Ni²⁺, $S = 1$, $\mu_{\text{eff}} = 2.83 \mu_{\text{B}}$). It is decreased with cooling and reaches 1.7 μ_{B} at 2.5 K, indicating antiferromagnetic interaction between nickel(II) centres. Plot of the inverse of molar susceptibility (χ^{-1}) versus temperature shows that it obeys the Curie–Weiss law above 50 K, but it deviates significantly from the Curie–Weiss law below 50 K (Fig. 4). Nonlinear fitting of the susceptibility data above 50 K according to $\chi = C/(T - \theta) + \chi_0$ gave a Weiss constant of $-143(2)$ K, indicating very strong

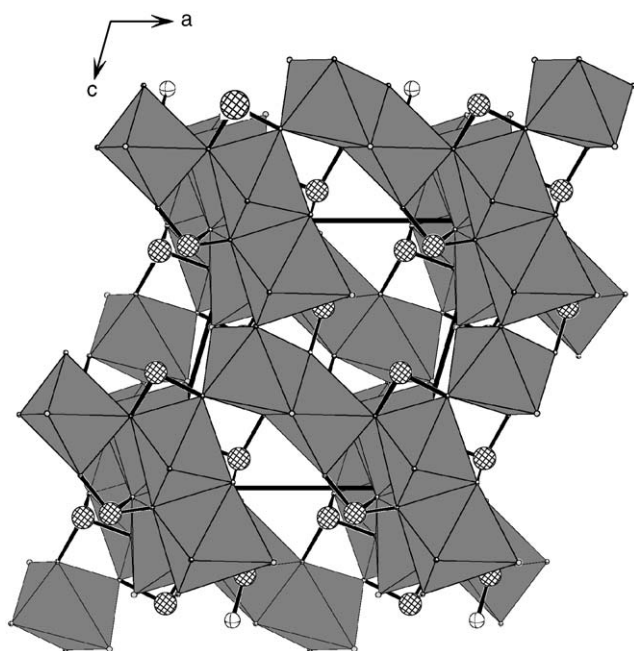


Fig. 3. View of the structure of Ni₅(SeO₃)₄Cl₂ down the *b*-axis. The nickel(II) octahedra are shaded in grey. The Se and O atoms are represented by hatched and crossed circles, respectively.

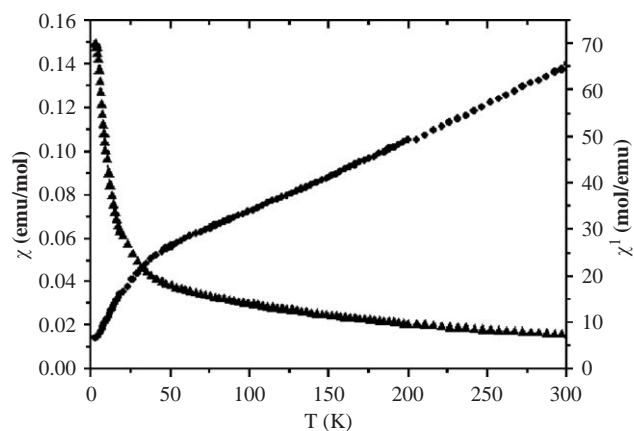


Fig. 4. Plot of χ and χ^{-1} versus temperature (10,000 Oe).

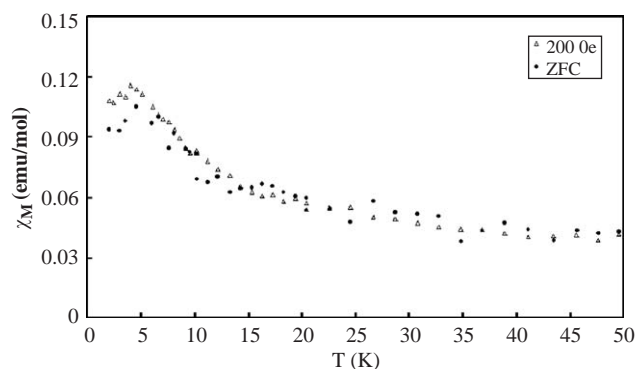


Fig. 5. Plot of χ_{M} versus temperature under ZFC and FC (200 Oe).

antiferromagnetic interactions between nickel ions. Such strong antiferromagnetic interactions are expected since the Ni...Ni separation between face-sharing or edge-sharing nickel octahedra are very short (ranging from 2.940(1) to 3.444(1) Å, Table 2) and the structure of Ni₅(SeO₃)₄Cl₂ is a very condensed 3D network. ZFC measurements and low field-cooling (FC) measurements at 200 Oe have also been performed to detect the possible existence of a weak ferromagnetic contribution. As shown in Fig. 5, the ZFC and FC (200 Oe) $\chi - T$ curves are almost identical, both show a maximum of molar susceptibility at around 4.5 K (T_{N}), which provides further evidence of antiferromagnetic interactions between magnetic centres. Based on these results we think that a weak ferromagnetic contribution is unlikely. Further detailed magnetic studies are still needed to establish the magnetostructural correlations.

4. Conclusions

In summary, a novel nickel(II) selenite chloride Ni₅(SeO₃)₄Cl₂ has been synthesized successfully by solid state reaction. Its structure features a complex con-

densed 3D network. Future efforts will be devoted to syntheses and magnetic studies of other compounds in similar systems.

Acknowledgments

The authors gratefully acknowledge the support from the National Natural Science Foundation of China (No. 20371047), NSF of Fujian Province (No. E0420003), and the Scientific Research Foundation for the Returned Overseas Chinese Scholars, State Education Ministry.

References

- [1] M.S. Wickleder, *Chem. Rev.* 102 (2002) 2011 (and references therein); V.P. Verma, *Thermochim. Acta* 327 (1999) 63 (and references therein).
- [2] H.-S. Ra, K.-M. Ok, P.S. Halasyamani, *J. Am. Chem. Soc.* 125 (2003) 7764; K.-M. Ok, P.S. Halasyamani, *Inorg. Chem.* 43 (2004) 4248; K.-M. Ok, J. Orzechowski, P.S. Halasyamani, *Inorg. Chem.* 43 (2004) 964; J. Goodey, K.-M. Ok, J. Broussard, C. Hofmann, F.V. Escobedo, P.S. Halasyamani, *J. Solid State Chem.* 175 (2003) 3.
- [3] R.T. Hart, K.-M. Ok, P.S. Halasyamani, J.W. Zwanziger, *Appl. Phys. Lett.* 85 (2004) 938; Y. Porter, P.S. Halasyamani, *J. Solid State Chem.* 174 (2003) 441; J. Goodey, J. Broussard, P.S. Halasyamani, *Chem. Mater.* 14 (2002) 3174; K.-M. Ok, P.S. Halasyamani, *Chem. Mater.* 13 (2001) 4278; P.S. Halasyamani, *Chem. Mater.* 16 (2004) 3586.
- [4] W.T.A. Harrison, L.L. Dussack, A.J. Jacobson, *J. Solid State Chem.* 125 (1996) 234; M.G. Johnston, W.T.A. Harrison, *Inorg. Chem.* 40 (2001) 6518; V. Balraj, K. Vidyasagar, *Inorg. Chem.* 38 (1999) 5809; V. Balraj, K. Vidyasagar, *Inorg. Chem.* 38 (1999) 3458; M.G. Johnston, W.T.A. Harrison, *J. Solid State Chem.* 177 (2004) 4680.
- [5] M.A. Cooper, F.C. Hawthorne, *Can. Miner.* 39 (2001) 797; G. Giester, *Z. Kristallogr.* 214 (1999) 305; H. Effenberger, *J. Alloy Compd.* 281 (1998) 152; G. Giester, *Acta Chem. Scand.* 51 (1997) 501.
- [6] R. Becker, M. Johnsson, R. Kremer, P. Lemmens, *Solid State Sci.* 5 (2003) 1411.
- [7] M. Johnsson, K.W. Törnroos, F. Mila, P. Millet, *Chem. Mater.* 12 (2000) 2853.
- [8] P. Millet, B. Bastide, V. Pashchenko, S. Gnatchenko, V. Gapon, Y. Ksari, A. Stepanov, *J. Mater. Chem.* 11 (2001) 1152.
- [9] M. Johnsson, K.W. Törnroos, P. Lemmens, P. Millet, *Chem. Mater.* 15 (2003) 68.
- [10] M. Johnsson, S. Lidin, K.W. Törnroos, H.-B. Bürgi, P. Millet, *Angew. Chem. Int. Ed.* 43 (2004) 4292.
- [11] M. Johnsson, K.W. Törnroos, *Solid State Sci.* 5 (2003) 263.
- [12] P.C. Burns, S.V. Krivovichev, S.K. Filatov, *Can. Miner.* 40 (2002) 1587.
- [13] W.T.A. Harrison, M.G. Johnston, *Z. Anorg. Allg. Chem.* 626 (2000) 2487.
- [14] M.S. Wickleder, M. Ben Hamida, *Z. Anorg. Allg. Chem.* 629 (2003) 556.
- [15] R. Berrigan, B.M. Gatehouse, *Acta Crystallogr. C* 52 (1996) 496.
- [16] C.R. Feger, J.W. Kolis, *Inorg. Chem.* 37 (1998) 4046.
- [17] J. Wontcheu, T. Schleid, *J. Solid State Chem.* 171 (2003) 429.
- [18] J. Galy, J.J. Bonnet, S. Andersson, *Acta Chem. Scand. A* 33 (1979) 383; P. Millet, B. Bastide, M. Johnsson, *Solid State Commun.* 113 (2000) 719; B. Bastide, P. Millet, M. Johnsson, J. Galy, *Mater. Res. Bull.* 35 (2000) 847.
- [19] M. Johnsson, K.W. Törnroos, *Acta Crystallogr. C* 59 (2003) i53.
- [20] R. Becker, M. Johnsson, *Solid State Sci.* 6 (2004) 519.
- [21] S.V. Krivovichev, R.R. Shuvalov, T.F. Semenova, S.K. Filatov, *Z. Kristallogr.* 214 (1999) 135.
- [22] S.V. Krivovichev, S.K. Filatov, T.F. Semenova, I.V. Rozhdestvenskaya, *Z. Kristallogr.* 213 (1998) 645.
- [23] A. Pring, B.M. Gatehouse, W.D. Birch, *Am. Miner.* 75 (1990) 1421.
- [24] T.F. Semenova, I.V. Rozhdestvenskaya, S.K. Filatov, L.P. Vergasov, *Miner. Mag.* 56 (1992) 241.
- [25] CrystalClear version 1.3.5, Rigaku Corp.: Woodlands, TX, 1999; G.M. Sheldrick, SHELXTL, Crystallographic Software Package, version 5.1, Bruker Analytical X-ray Instruments, Madison, WI, 1998.
- [26] I.D. Brown, D. Altermat, *Acta Crystallogr. B* 41 (1985) 244.