

The catalyzed reduction of the simple methylene derivative **11** afforded after deacetylation (*S*)-salsolidine (**15**) in 96% ee. Thus the present catalytic method is chirally flexible and allows synthesis of both antipodal products in high enantiomeric excesses with equal ease by choosing the handedness of the BINAP-Ru catalysts. Most of the tetrahydroisoquinoline products are crystalline and the homochiral materials are readily accessible by single recrystallization.

Acknowledgment. We are grateful to Tanabe Pharmaceutical Co. for a generous gift of the commercial (*S*)-tetroquinol sample. We thank Dr. K. Mashima, Institute for Molecular Science, for valuable contribution in the X-ray crystallographic analyses.

Supplementary Material Available: Descriptions of the determination of crystal structures including complete listings of atomic parameters, anisotropic temperature factors, bond distances, and bond angles for (*Z*)-**2c** and (*Z*)-**2e**, preparation of Δ -(*R*)-**1** and Δ -(*S*)-**1**, and physical properties of the new compounds (37 pages). Ordering information is given on any current masthead page.

Phosphine Oxides as NMR Probes for Adsorption Sites on Surfaces

Laima Baltusis, James S. Frye, and Gary E. Maciel*

Department of Chemistry, Colorado State University
 Fort Collins, Colorado 80523

Received March 3, 1986

Studies of small basic probe molecules by NMR to identify surface acidic sites on oxides of aluminum and silicon have yielded information on the types of surface acid sites, on the numbers of these sites, and about the molecular dynamics of the adsorbed probe molecules. Initial work in this area employed amines as probes via ^{13}C and ^{15}N magic-angle spinning (MAS) NMR.¹⁻⁷

- (1) Gay, I. D.; Liang, S. *J. Catal.* **1976**, *44*, 306.
- (2) Dawson, W. H.; Kaiser, S. W.; Ellis, P. D.; Inners, R. R. *J. Am. Chem. Soc.* **1981**, *103*, 6780.
- (3) Michel, D.; Germanus, A.; Pfeifer, H. *J. Chem. Soc., Faraday Trans. 1* **1982**, *79*, 237.
- (4) Dawson, W. H.; Kaiser, S. W.; Ellis, P. D.; Inners, R. R. *J. Phys. Chem.* **1982**, *86*, 867.
- (5) Ripmeester, J. A. *J. Am. Chem. Soc.* **1983**, *105*, 2925.
- (6) Maciel, G. E.; Haw, J. F.; Chuang, I.-S.; Hawkins, B. L.; Early T. E.; McKay, D. R.; Petrakis, L. *J. Am. Chem. Soc.* **1983**, *125*, 5529.
- (7) Haw, J. F.; Chuang, I.-S.; Hawkins, B. L.; Maciel, G. E. *J. Am. Chem. Soc.* **1983**, *105*, 7206.

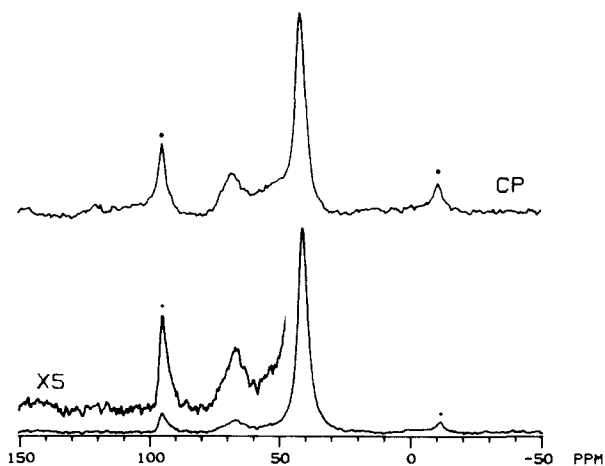


Figure 1. ^{31}P MAS spectra of $(CH_3)_3PO$ on silica-alumina (2.8×10^{-3} mol/g of silica-alumina). Upper, cross polarization. Lower, single pulse. Asterisks designate spinning sidebands.

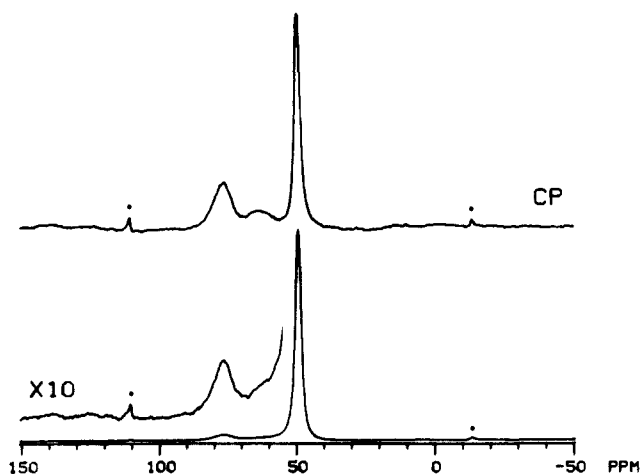


Figure 2. ^{31}P MAS spectra of $(C_2H_5)_3PO$ on silica-alumina (3.0×10^{-3} mol/g of silica-alumina). Upper, cross polarization. Lower, single pulse. Asterisks designate spinning sidebands.

More recent work has focused on the study of phosphines via ^{31}P NMR.⁸⁻¹⁰ ^{31}P has the advantage over ^{15}N of greater NMR sensitivity due to a higher magnetogyric ratio and 100% natural abundance of the spin- $1/2$ isotope, therefore permitting extensive sets of experiments over a wide range of surface coverage of phosphines. Although studies of silica-alumina with trialkylphosphines have been successful in the quantitative analysis of surface Brønsted sites,¹⁰ the quantitative analysis of surface Lewis sites has been hampered not only by small chemical shift differences between Lewis-bound and physisorbed phosphines but also by the similarity of surface binding equilibrium constants for these two types of sites; these factors result in the absence of a break point in the "titration" curves for Lewis-bound phosphines from which the concentration of Lewis sites could otherwise be calculated.

In an effort to find a probe molecule that would give a good distinction between the Lewis-bound and physisorbed molecules on surfaces, we have investigated the use of trialkylphosphine oxides as probe molecules for surface acid sites of amorphous materials. In the present paper we report promising ^{31}P NMR results obtained on $(CH_3)_3PO$ and $(C_2H_5)_3PO$ on silica-alumina.

Figure 1 shows ^{31}P MAS NMR spectra of high-surface-loading $(CH_3)_3PO$ on amorphous silica-alumina (75%/25% by weight)

- (8) Rothwell, W. P.; Shen, W. X.; Lunsford, J. H. *J. Am. Chem. Soc.* **1983**, *106*, 2452.
- (9) Lunsford, J. H.; Rothwell, W. P.; Shen, W. *J. Am. Chem. Soc.* **1985**, *107*, 1540.
- (10) Baltusis, L.; Frye, J. S.; Maciel, G. E., submitted for publication in *J. Am. Chem. Soc.*

taken in the single-pulse and cross-polarization (CP) modes, both with proton decoupling during data acquisition.^{11,12} On the basis of model compound studies, we have assigned the highest shielding resonance (40 ppm) to physisorbed $(\text{CH}_3)_3\text{PO}$, the shoulder at 53 ppm (which is more visible in the CP spectrum) to Lewis-bound $(\text{CH}_3)_3\text{PO}$ and the lower shielding resonance at 65 ppm to $(\text{CH}_3)_3\text{POH}^+$ bound to surface Brønsted sites. The spinning side bands (marked by asterisks), which are more pronounced in the CP spectra, are due to excess crystalline $(\text{CH}_3)_3\text{PO}$, which has the same ^{31}P chemical shift as physisorbed material but can be differentiated by a 3-s T_1 value, which contrasts with the much shorter T_1 (0.15 s) for the surface-physisorbed species.

Figure 2 displays CP and single-pulse ^{31}P MAS spectra of a high-loading sample of $(\text{C}_2\text{H}_5)_3\text{PO}$ on silica-alumina. In contrast to trialkylphosphines, for which the greatest chemical difference between species occurs for the smallest phosphine, $(\text{C}_2\text{H}_5)_3\text{PO}$ shows better chemical shift differentiation among the various surface species than does $(\text{CH}_3)_3\text{PO}$. The highest shielding resonance at 49.5 ppm has been assigned to surface-physisorbed $(\text{C}_2\text{H}_5)_3\text{PO}$ species, the central resonance at 63 ppm to Lewis-bound species, and the lowest shielding resonance at 76 ppm to $(\text{C}_2\text{H}_5)_3\text{POH}^+$ bound to surface Brønsted sites. As can be clearly seen in Figure 2, the CP spectrum enhances the signals due to molecules bound to the Brønsted sites and Lewis sites, presumably because these molecules are more rigidly bound to the surface than are the physisorbed species. As in the case of Figure 1, the spinning side bands, due to crystalline phosphine oxide, are enhanced in the CP spectra.

The 13-ppm decrease in ^{31}P shielding upon complexation to Al is larger than that seen for the analogous system of trialkylphosphines on silica-alumina.¹⁰ We have not been able to prepare a satisfactory model compound with $\text{R}_3\text{P}\cdot\text{OAl}(-\text{O})_3$ coordination, but 1:1 mixtures of $(\text{CH}_3)_3\text{PO}$ and AlCl_3 and of $(\text{C}_2\text{H}_5)_3\text{PO}$ and AlCl_3 in CH_2Cl_2 give ^{31}P shifts of 58 and 64 ppm at -60°C , respectively, corroborating the above assignments and illustrating that Lewis complex formation can cause a substantial decrease of ^{31}P shielding in phosphine oxides. The chemical shifts assigned here for the Brønsted complex, Lewis complex, and physisorbed molecules agree with our interpretation of corresponding peaks in the ^{31}P NMR spectra (not shown here) of $(\text{C}_2\text{H}_5)_3\text{PO}$ adsorbed on γ -alumina and give the same order as observed previously for phosphines.¹⁰

It should be noted that, although hydrogen-bonding ^{31}P shifts of several ppm have been reported for phosphine oxides,¹³ we have not distinguished hydrogen-bonded phosphine oxides in the present work. To the extent that hydrogen-bonded species are present in these systems, their resonances are presumably contained in the region we have identified with physisorption.

With the much larger dispersion found in the ^{31}P chemical shifts among the surface-bound species of trialkylphosphine oxides, it now appears practical to quantitate not only the number of Brønsted sites but also the number of Lewis sites on an amorphous surface. Also, by making use of the appearance of signals due to crystalline trialkylphosphine oxide, one can obtain an estimate of the total number of physisorption "sites" for a specific probe molecule on a surface. In addition, through a surface concentration study one can estimate the relevant surface binding constants and compare them to those of other probe molecules investigated. Detailed studies of this type are currently in progress.

Acknowledgment. NMR spectra were obtained at the Colorado State University Regional NMR Facility, supported by the National Science Foundation Grant CHE-8208821. Project support was provided by NSF Grant CHE-8306518.

(11) The ^{31}P NMR spectra were obtained at 60.745 MHz on a modified NT-150 spectrometer, using MAS speeds of 3.0-3.5 KHz.

(12) The silica-alumina (from American Cyanamid) was formally 75% $\text{SiO}_2/25\%$ Al_2O_3 by weight, with a surface area of 485 m^2/g , as determined by the nitrogen BET method. The silica-alumina was dried for 12-16 h at 10^{-4} torr and 160-170 $^\circ\text{C}$ prior to treatment with the phosphine oxides (Strem), adsorbed onto the silica-alumina from CH_2Cl_2 solution.

(13) Maciel, G. E.; James, R. V. *Inorg. Chem.* 1964, 3, 1560.

Concave Functionality: Design of a Phenol Sticky Host

R. E. Sheridan and H. W. Whitlock, Jr.*

Samuel McElvain Laboratories of Organic Chemistry
Department of Chemistry
University of Wisconsin—Madison
Madison, Wisconsin 53706

Received June 9, 1986

There is considerable current interest in the design of host molecules possessing rigidly defined vacancies capable of accommodating guests with a high degree of selectivity and binding.¹⁻⁴ We report here construction of a host molecule (**1**) possessing a phenol sticky^{2b} cavity. Host **1** was designed to test the idea that an inwardly pointing (concave) functionality, e.g., a 4-(dimethylamino)pyridine, would exhibit guest stickiness in *non-aqueous media*.

Cyclization of **2**⁵ afforded a 2:1 mixture of *dl*-**1** and its meso isomer. The structure of **1** was confirmed by a single-crystal X-ray structure of its ethylene dichloride (EDC) incavitated complex **1**-EDC (Figure 1a). The EDC is in van der Waals contact with the sides and surfaces of the cyclophane box but not with the pyridine. The latter is rotated approximately 90° from the desired concave arrangement.⁶

Host *dl*-**1** binds certain phenols *very tightly*, thus confirming the above hypothesis. Titration of *dl*-**1** in CHCl_3 ⁷ with *p*-nitrophenol (PN), with nonlinear least-squares treatment of δ_{obsd} vs. PN/**1** ratio, leads to chemical shifts of the **1**/PN complex and association constants for the 1:1 complex formed.⁸ Both the PN protons and H1 or **1** show pronounced upfield shifts (ca. 1 ppm) in the complex. K_{assoc} for **1**/PN is $3000 \pm 300 \text{ M}^{-1}$; it is $1100 \pm 300 \text{ M}^{-1}$ for **1**/*p*-cyanophenol, 500 M^{-1} for (*p*-nitrophenyl)-azophenol,⁹ $\sim 50 \text{ M}^{-1}$ for **1**/*p*-carboethoxyphenol, and $\sim 20 \text{ M}^{-1}$ for phenol. A ρ of ~ 6 may be calculated from these data. The **1**/PN complex was isolated. Its X-ray structure (Figure 1b) fully confirms the conclusions from the above NMR experiments. The pyridine now projects into the cavity, hydrogen bonding with the phenolic OH. The PN aromatic ring just fits the cavity, being in van der Waals contact with the surrounding carbon net.

We have been singularly unsuccessful in factoring out the forces involved in formation of these remarkably stable and guest-selective complexes. The following observations are salient with respect to this.

1. Prehost **2** exhibits *no* complexation behavior as described above for **1**. The three-dimensional cavity of **1** is thus required.
2. Non-phenolic isosteres, *p*-nitroanisole and *p*-nitrochlorobenzene, do *not* compete with PN for occupancy of the cavity. Acid-base interaction (hydrogen bonding) is thus required.
3. More acidic guests, benzoic acids and 2,4-dinitrophenol, do *not* form cavity complexes. Rather simple proton transfer occurs,

(1) (a) Moran, J. R.; Karbach, S.; Cram, D. J. *J. Am. Chem. Soc.* 1982, 104, 5826-5828. (b) Cram, D. J.; Kaneda, T.; Helgeson, R. C.; Brown, S. B.; Knobler, C. B.; Maverick, E.; Trueblood, K. N. *Ibid.* 1985, 107, 3645-3657.

(2) (a) Whitlock, B. J.; Whitlock, H. W. *J. Am. Chem. Soc.* 1985, 107m, 1325-1329. (b) Miller, S. P.; Whitlock, H. W. *Ibid.* 1984, 106, 1492-1494. (c) Jarvi, E. T.; Whitlock, H. W. *Ibid.* 1982, 104, 7196-7201.

(3) O'Krongly, D.; Denmeade, S. R.; Chiang, M. Y.; Breslow, R. *J. Am. Chem. Soc.* 1985, 107, 5544-5545.

(4) (a) Canceill, J.; Lacombe, L.; Collet, A. *J. Am. Chem. Soc.* 1985, 107m, 6993-6996. (b) Rebeck, J., Jr.; Askew, B.; Islam, N.; Killoran, M.; Nemeth, D.; Wolak, R. *Ibid.* 1985, 108, 6736-6738. (c) Diederich, F.; Dick, K.; Griebel, D. *Ibid.* 1986, 108, 2273-2286. (d) Bauer, L. J.; Gutsche, C. D. *Ibid.* 1985, 107, 6063-6069.

(5) $\text{Cu}(\text{OAc})_2$, pyridine, 40°C : **2** was prepared from 3,7-bis(propargyloxy)-2-naphthoic acid^{2c} and 4-(dimethylamino)-2,6-bis(hydroxymethyl)pyridine by standard procedures.

(6) MM2 calculations suggest that the desired concave arrangement of the pyridine is the minimum-energy conformation: the depth of this minimum appears not to be overwhelming.

(7) A "big" solvent, one incapable of fitting into the cavity.

(8) The nonlinear LS PC program SIMPLEX is available on request from the authors.

(9) The *p*-nitrophenyl group apparently protrudes from the cavity like a tongue, as only the phenol-ring protons move upfield.