

An Electron-Conducting Cross-Linked Polyaniline-Based Redox Hydrogel, Formed in One Step at pH 7.2, Wires Glucose Oxidase

Nicolas Mano,^{*,†} Joung Eun Yoo,[‡] Jacob Tarver,[‡] Yueh-Lin Loo,[‡] and Adam Heller^{*,‡}

Université Bordeaux I, CNRS, Centre de Recherche Paul Pascal (CRPP), UPR 8641, Avenue Albert Schweitzer, 33600 Pessac, France, and Department of Chemical Engineering, The University of Texas at Austin, Austin, Texas 78712

Received March 20, 2007; E-mail: heller@che.utexas.edu; mano@crpp-bordeaux.cnrs.fr

Depending on its hydration, polyaniline (PANI) conducts charge carriers by two different mechanisms. When not hydrated, it conducts through one-dimensional (1D) bands. Such conduction requires at least 1D semicrystalline PANI.^{1,2} Hydration disrupts the parallel alignment of the chains and lowers the conduction. When dissolved, PANI behaves as a polymeric redox couple,^{3,4} and if cross-linked and hydrated, it can form an electron-conducting redox hydrogel.⁵ In redox hydrogels, electrons diffuse through electron-transferring collisions between hydrated reducible and oxidizable polymer segments.⁶ Hydration lowers the local viscosity and reduces attractive Coulombic interactions, thereby increasing segmental mobility and electron diffusion. It also increases the permeability of water-soluble ions and molecules.

Here we show that an electrostatic adduct of emeraldine-polyaniline and a polymer acid, which exhibits small band gap semiconductor-kind conductivity in the solid state, forms an electron-conducting redox hydrogel when cross-linked with a water-soluble diepoxide at neutral pH and hydrated. The cross-linked polymer triples its weight upon hydration, and the absorbed water makes it permeable to glucose. When glucose oxidase (GOx) is co-cross-linked within the hydrogel, its reaction centers are electrically wired. As a result, the PANI-GOx hydrogel catalyzes the electrooxidation of glucose at +0.3 V vs Ag/AgCl and at a current density of 225 $\mu\text{A}\cdot\text{cm}^{-2}$.

The PANI-GOx bioelectrocatalyst was prepared at neutral pH in one pot in a single step. Methods reported by other groups were more difficult to practice. For example, a recently described high-rate electrocatalytic glucose oxidation method⁷ utilized special polyaniline-containing microrods with dissolved, rather than immobilized, GOx. The preparation of the microrods required pyrene sulfonic acid functionalization of single-walled carbon nanotubes, their embedding in aniline and polystyrene sulfonic acid, electropolymerization of the aniline in porous alumina membranes coated with a conductive gold support, and dissolving the alumina membrane. Although the steady-state glucose electrooxidation current densities were not reported for these microrods, voltammetric wave heights of 500 $\mu\text{A}\cdot\text{cm}^{-2}$ at 5 $\text{mV}\cdot\text{s}^{-1}$ scan rate were observed.⁷

Glucose-permeable poly(ethylene glycol) diglycidyl ether (PEGDGE) cross-linked electron-conducting redox hydrogels of $\text{Os}^{2+/3+}$ complex, comprising polymers with poly(*N*-vinylimidazole) and partially *N*-alkylated poly(4-vinylpyridine) backbones, have been studied extensively.⁶ PEGDGE cross-links primary, secondary, and tertiary amines, as well as heterocyclic nitrogens, including those of polyanilines.⁸ When GOx is coimmobilized in the $\text{Os}^{2+/3+}$ complex-comprising hydrogels, it is electrically wired, and 3D glucose electrooxidation catalysts, operating at -0.1 V vs Ag/AgCl

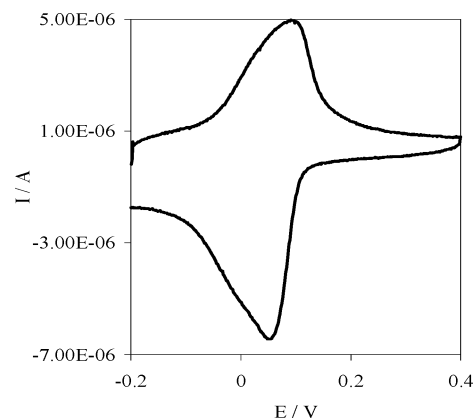


Figure 1. Cyclic voltammogram of PANI/PAAMPSA at 60 $\mu\text{g}\cdot\text{cm}^{-2}$ dry-weight loading; 50 mV/s scan rate; pH 7.2, 20 mM PBS.

and at $>1 \text{ mA}\cdot\text{cm}^{-2}$, are formed.^{9,10} In contrast, when GOx is physically adsorbed on,¹¹ entrapped in,¹² or electrodeposited on¹³ films of metallic or semiconducting PANI or otherwise integrated on or in PANI films,^{14–17} the glucose electrooxidation current densities are lower. Such is even the case when PANI is covalently bound to a gold substrate through a flavoenzyme thiol,¹⁸ or through nucleophilic thiol attack at ortho positions of PANI quinoimine mers.¹⁹

The emeraldine PANI was made by oxidative template polymerization of aniline on water-dissolved poly(2-acrylamido-2-methyl-1-propane sulfonic acid) (PAAMPSA) with ammonium persulfate.^{20,21} The conductivity of the PANI/PAAMPSA salt was $0.430 \pm 0.019 \text{ S/cm}$ after the purified aqueous polymer/salt dispersion was spin- or drop-cast and dehydrated.²⁰ The molecular mass of the PAAMPSA was 724 kDa, and solid-state NMR showed that the PANI segments were 8–20 repeat units long. The shorter units were removed by added non-solvent (acetone) precipitation and by filtration and repeated washings. Elemental analysis and X-ray photoelectron spectroscopy of the purified PANI/PAAMPSA indicated an aniline/sulfonic acid molar ratio of about 1:0.9. To show that uncross-linked PANI/PAAMPSA is a typical, diffusionally mobile redox couple, glassy carbon electrodes were coated with 10 μL of a 0.042 wt % aqueous solution of the polymer (60 $\mu\text{g}\cdot\text{cm}^{-2}$ initial dry-weight-based loading) and allowed to dry. Figure 1 shows the initial cyclic voltammograms of the PANI/PAAMPSA-modified electrode under argon in a 20 mM, pH 7.2 phosphate buffer (PBS) at 37.5 °C. The voltammogram is characteristic of the doped PANI emeraldine redox couple, peaking at +0.1 V vs Ag/AgCl. Although the film slowly dissolved in the absence of a cross-linker, the voltammetric wave was stable at pH 7.2, and the anodic peak current increased linearly with scan rates up to 400 $\text{mV}\cdot\text{s}^{-1}$, as expected for a weakly surface-bound redox couple.

[†] Université Bordeaux.

[‡] The University of Texas at Austin.

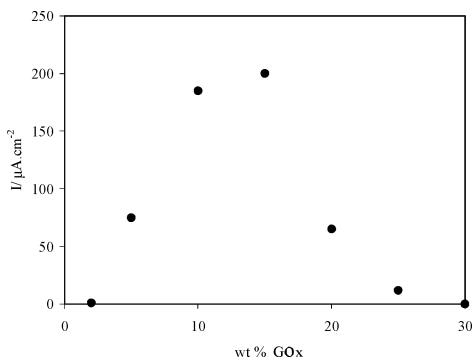


Figure 2. Dependence of the current density on the glucose oxidase weight percentage. The glucose concentration was maintained at 32 mM.

To show that a hydrogel is formed upon cross-linking the PANI/PAAMPSA with a 400 Da PEGDGE, through reaction with PANI nitrogens,⁸ we measured the water uptake at 0.1 g·cm⁻² dry-weight loading of the films (cast from a 5 wt % PANI/PAAMPSA dispersion) in multiple hydration–dehydration cycles. To form the films, aqueous polymer solutions were mixed at 1:0.07 w/w PANI/PAAMPSA solution/PEGDGE ratio, deposited on microscope slides, and cured in ambient air for 48 h. The increases–decreases in mass in cycles of (a) immersion in deionized water for 1 min, (b) tilting to drain the water, (c) contacting the surface with absorbent paper tissue (KimWipe) to remove surface water not bound in the hydrogel, (d) air-drying, and (e) repeat rehydration were measured. In three sets of measurements on different samples, the mass of the water added on swelling and lost upon drying was 2 ± 0.2 times the weight of the dry PANI/PAAMPSA/PEGDGE. To show that the hydrogel is permeable to glucose and is electrically wired to GOx, films were made by mixing droplets of known volume and concentration of aqueous solutions of PANI/PAAMPSA (in pH 7.4, 0.1 M phosphate buffer), GOx (in pH 7.2, 0.1 M phosphate buffer), and PEGDGE (in deionized water) on glassy carbon electrodes. The films were made as earlier described for an Os^{2+/3+} complex comprising redox polymer-wired GOx electrocatalyst,¹⁰ except that the Os^{2+/3+} complex-based polymer was replaced by PANI/PAAMSA, the solution of which was now diluted 10-fold with pH 7.4, 0.1 M phosphate buffer. The films were cured for > 18 h at ambient temperature.

Figure 2 shows the dependence of the glucose electrooxidation current density on the GOx weight percentage in the dry films in pH 7.2, 32 mM glucose, 20 mM phosphate buffer at 37 °C at a fixed loading of 0.8 mg·cm⁻² ($\rho = 1.39$ g·cm⁻³). In the 2–15 wt % GOx range, the current density increased with the weight percentage of GOx, reaching 200 $\mu\text{A}\cdot\text{cm}^{-2}$ at 15 wt %. At higher GOx content the current density declined. The decline is attributed to deswelling when the polyanionic GOx neutralizes the residual net positive charge of PANI/PAAMSA. To confirm that deswelling is caused by charge neutralization, GOx with a high negative surface charge was prepared by periodate oxidation of surface oligosaccharides of GOx.¹⁰ The glucose electrooxidation current density now declined when the oxidized GOx content reached 2 wt %. Figure 3 shows the dependence of the current density on glucose concentration under argon for an electrode that was poised at +0.3 V vs Ag/AgCl in a PBS buffer. The current density was 225 $\mu\text{A}\cdot\text{cm}^{-2}$ at 40 mM glucose. The apparent Michaelis constant, K'_M , obtained from an Edie–Hofstee plot was 16.8 mM glucose.

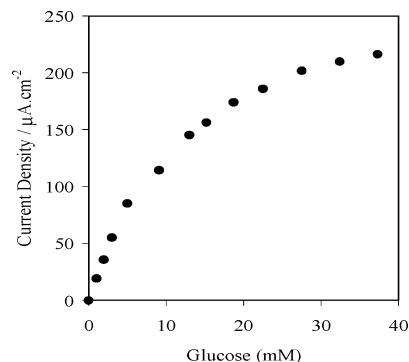


Figure 3. Dependence of the steady-state current density on glucose concentration for an electrode poised at +0.3 V vs Ag/AgCl, rotating at 500 rpm under argon.

In summary a polyaniline-based, electron-conducting, glucose-permeable redox hydrogel was formed in one step at pH 7.2 by cross-linking a polymer acid-templated PANI with water-soluble PEGDGE. Incorporation of glucose oxidase in the hydrogel by co-cross-linking in the same step led to electrical wiring of the enzyme and formation of a glucose electrooxidation catalyst, allowing the electrooxidation of glucose at a current density of 225 $\mu\text{A}\cdot\text{cm}^{-2}$ at 0.3 V vs Ag/AgCl.

Acknowledgment. Y.L.L. acknowledges funding from a Beckman Young Investigator Award and a DuPont Young Professor Grant and support from the Keck Foundation. A.H. thanks the Welch Foundation and the Office of Naval Research for financial support. N.M. acknowledges funding from a European Young Investigator Award (EURYI).

References

- (1) Epstein, A. J.; MacDiarmid, A. G. *J. Mol. Electron.* **1988**, *4*, 161–165.
- (2) Lee, K.; Cho, S.; Park, S. H.; Heeger, A. J.; Lee, C.-W.; Lee, S.-H. *Nature (London)* **2006**, *441*, 65–68.
- (3) Inzelt, G. *J. Electroanal. Chem. Interfacial Electrochem.* **1990**, *279*, 169–178.
- (4) Horanyi, G.; Inzelt, G. *Electrochim. Acta* **1988**, *33*, 947–952.
- (5) Brahim, S.; Wilson, A. M.; Narinesingh, D.; Iwuoha, E.; Guiseppi-Elie, A. *Microchim. Acta* **2003**, *143*, 123–137.
- (6) Heller, A. *Curr. Opin. Chem. Biol.* **2006**, *10*, 664–672.
- (7) Granot, E.; Basnar, B.; Cheglakov, Z.; Katz, E.; Willner, I. *Electroanalysis* **2006**, *18*, 26–34.
- (8) Hua, F.; Ruckenstein, E. *Macromolecules* **2003**, *36*, 9971–9978.
- (9) Mano, N.; Mao, F.; Heller, A. *J. Electroanal. Chem.* **2005**, *574*, 347–357.
- (10) Mao, F.; Mano, N.; Heller, A. *J. Am. Chem. Soc.* **2003**, *125*, 4951–4957.
- (11) Chaubey, A.; Pande, K. K.; Singh, V. S.; Malhotra, B. C. *Anal. Chim. Acta* **2000**, *407*, 907–913.
- (12) Borole, D. D.; Kapadi, U. R.; Mahulikar, P. P.; Hundiwale, D. G. *Polym. Adv. Technol.* **2004**, *15*, 306–312.
- (13) Garjonyte, R.; Malinauskas, A. *Biosens. Bioelectron.* **2000**, *15*, 445–451.
- (14) Parente, A. H.; Marques, E. T. A., Jr.; Azevedo, W. M.; Diniz, F. B.; Melo, E. H. M.; Lima Filho, J. L. *Appl. Biochem. Biotechnol.* **1992**, *37*, 267–273.
- (15) Cooper, J. C.; Hall, E. A. H. *Electroanalysis* **1993**, *5*, 385–397.
- (16) Hall, E. A. H.; Skinner, N. G.; Jung, C.; Szunerits, S. *Electroanalysis* **1995**, *7*, 830–837.
- (17) Pan, X.; Kan, J.; Yuan, L. *Sens. Actuators, B* **2004**, *B102*, 325–330.
- (18) Han, C.-C.; Heish, W. D.; Yeh, J. Y.; Hong, S.-P. *Chem. Mater.* **1999**, *11*, 480–486.
- (19) Simon, E.; Halliwell, C. M.; Toh, C. S.; Cass, A. E. G.; Bartlett, P. N. *J. Electroanal. Chem.* **2002**, *538–539*, 253–259.
- (20) Yoo, J. E.; Cross, J. L.; Buchholz, T. L.; Lee, K. S.; Espe, M. P.; Loo, Y.-L. *J. Mater. Chem.* **2007**, *17*, 1268–1275.
- (21) Lee, K. S.; Smith, T. J.; Dickey, K. C.; Stevenson, K. J.; Loo, Y.-L. *Adv. Funct. Mater.* **2006**, *16*, 2409–2409.

JA071946C