


Interchromophoric Interactions in Chiral X-type π -Conjugated Oligomers: A Linear and Nonlinear Optical Study

David Cornelis,[†] Edith Franz,[‡] Inge Asselberghs,[‡] Koen Clays,[‡] Thierry Verbiest,[‡] and Guy Koeckelberghs^{*,†}

Laboratory for Molecular Electronics and Photonics, Katholieke Universiteit Leuven, Celestijnenlaan [†]200F, [‡]200D, B-3001 Leuven, Belgium

S Supporting Information

ABSTRACT: A concept of chiral, X-type organized π -conjugated oligomers, linked by means of a binaphthalene pincer, is presented. NMR spectroscopy and cyclic and differential pulse voltammetry indicate that these oligomers are in close proximity and influence each other in a through-space manner in their neutral as well as in their oxidized states. The interaction between the oligomers was also confirmed by UV-vis, CD, and emission spectroscopy. The synthetic versatility of this design also enables the development of heterocoupled binaphthalene derivatives BN1-2 and BN1-3, consisting of an electron-neutral oligothiophene or electron-rich oligomer and an electron-poor oligothiazole. Hyper-Rayleigh scattering data show a significant enhancement of the second-order nonlinear hyperpolarizability β for BN1-3 and BN1-2, in contrast with the homocoupled binaphthalene derivatives (BN1-1, BN2-2, and BN3-3). This enhancement provides direct proof for the through-space charge-transfer interaction between the p-type and the n-type oligomers within BN1-3 and BN1-2.

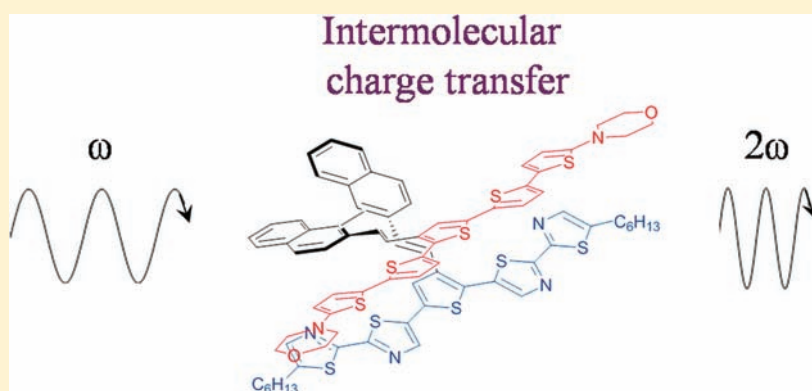

INTRODUCTION

During the past decade, the fundamental and applied research of π -conjugated systems has focused on the interplay between the intrinsic molecular features of the individual π -conjugated chains and their interchain interactions.¹ Some of these intermolecular couplings occur in the ground state, for example, π -stacking;² others, such as exciton coupling,³ arise in the excited state; in the oxidized state, the interchain hopping mechanisms contribute extensively to the electrical properties of these materials.⁴

To gain more fundamental insight into the origin and the strength of these interchain interactions, several oligomeric double-decker structures, constituted of two (stacked) oligothiophenes, have extensively been investigated.^{5–7} Unambiguously, they gave evidence for the existence of interchain radical cation π -dimers. We recently implemented chirality by covalently linking two π -conjugated oligomers to a chiral binaphthalene unit in an overall X-type geometry.⁸ This chiral X-type geometry was preferred, because it better ensures chiral exciton coupling between the two oligothiophene moieties, as previously demonstrated by CD experiments.⁸ By further exploiting the chirality of the binaphthalene unit, we could qualitatively monitor the strength of any type of (induced) interchain interaction through chiroptical evaluation of the dihedral angle of the binaphthalene hinge.⁹

Perhaps the most compelling feature of π -conjugated systems as active elements in new generations of organic light-emitting diodes (oLEDs) and organic photovoltaic devices (oPVDs) comprises the charge-transfer interaction between a p-type and an n-type π -conjugated system. Wang et al. studied the intermolecular charge-transfer interaction by mixing an excess of *N,N*-dimethylaniline (p-type) with a series of distyrylbenzene derivatives (n-type) to invoke exciplex formation.¹⁰ Alternatively, they extensively investigated [2.2]paracyclophane-bridged distyrylbenzene systems containing donor and acceptor groups and studied the impact of substitution patterns on their through-space interaction.¹¹

We present a chirally linked p-type and n-type complex to model the charge-transfer interaction of π -conjugated materials. This model compound (BN1-3) is constructed from an electron-rich morpholine-substituted oligothiophene and an electron-poor oligothiazole, which are covalently anchored by a chiral binaphthalene pincer (Figure 1). If through-space charge transfer occurs, this directly takes place between the two coupled oligomers, without any tunneling effects along a molecular bridge.

This Article first investigates the homocoupled chiral X-type binaphthalene derivatives (BN1-1, BN2-2, and BN3-3, Figure 1). NMR spectroscopy and cyclic and differential pulse voltammetry

Received: June 8, 2010

Published: January 6, 2011

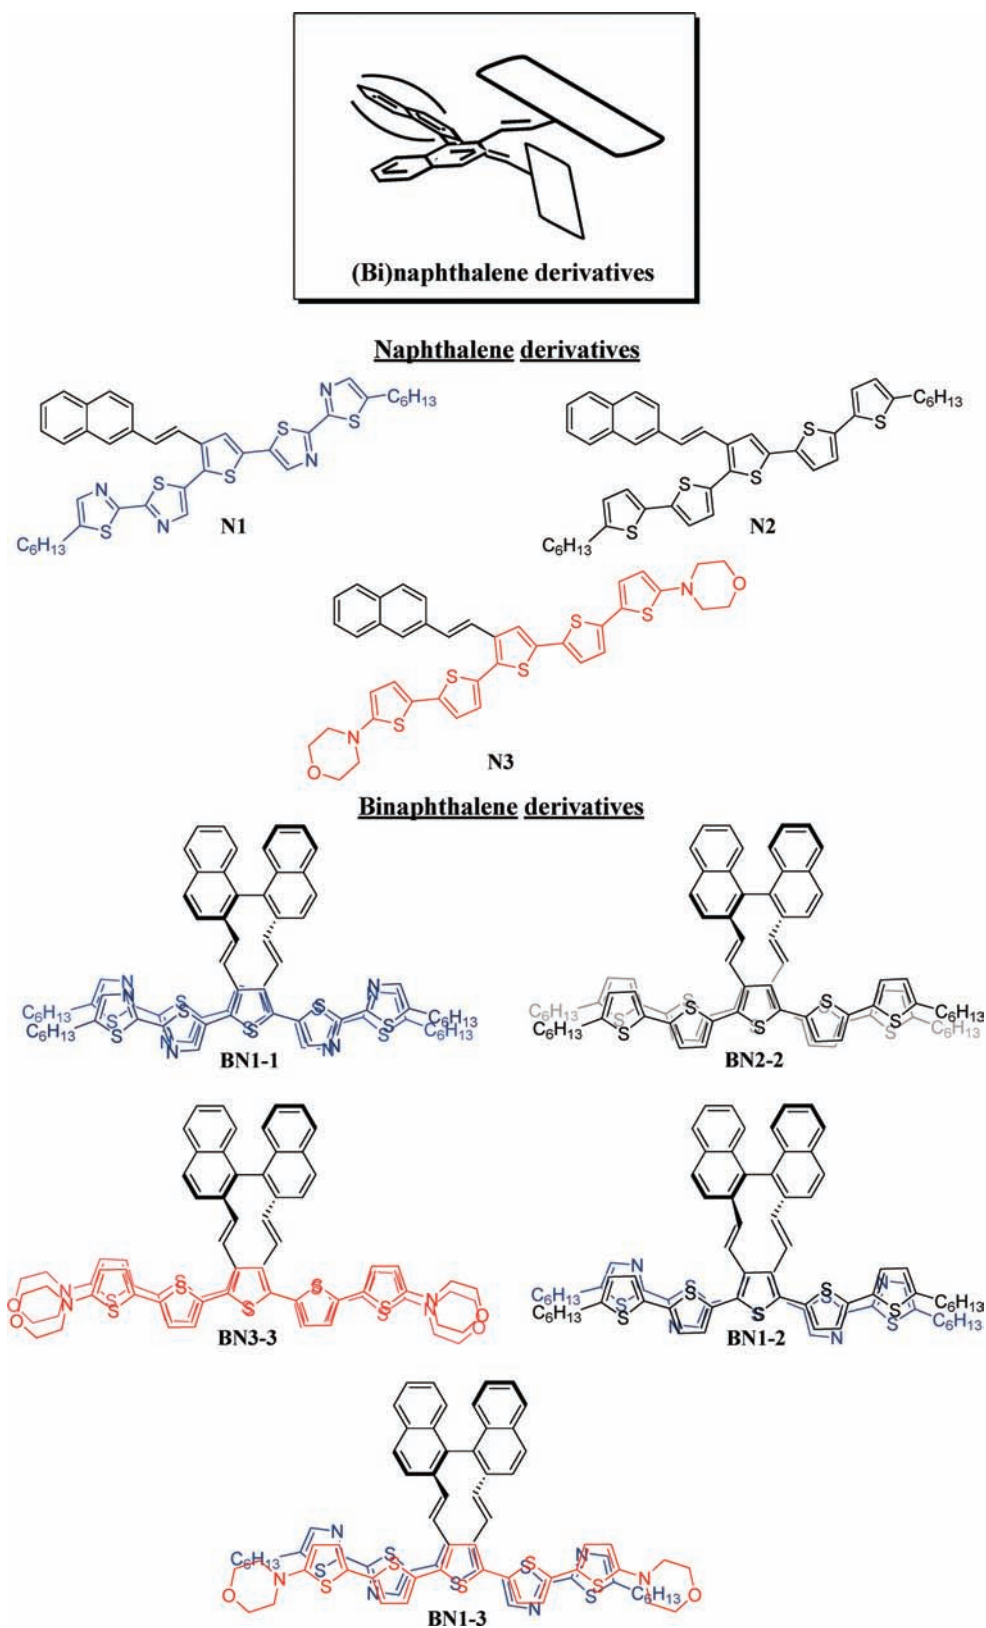


Figure 1. Overview of the synthesized (bi)naphthalene derivatives (N1, N2, N3 and BN1-1, BN2-2, BN3-3, BN1-2, and BN1-3).

are used to study the through-space π -electronic interactions between the oligomers in their neutral as well as in their oxidized states. Second, the BNs are evaluated by UV-vis, CD, and emission spectroscopy to find linear optical evidence for a charge-transfer

interaction. On the basis of computational calculations on intermolecular electron donor-acceptor (EDA) complexes as potential high-efficiency second-order nonlinear optical materials,¹² all naphthalene derivatives are finally analyzed by means of hyper-Rayleigh

scattering to obtain additional nonlinear optical evidence for a through-space charge-transfer process within BN1-3 and BN1-2.

EXPERIMENTAL SECTION

Reagents and Instrumentation. All reagents were purchased from Aldrich Chemical Co. and Acros Organics and were used as received. Tetrahydrofuran (THF) was dried over a Na/K alloy. Dichloromethane, dimethylformamide (DMF), and hexane were freshly distilled and further dried on molecular sieve (4 Å).

^1H and ^{13}C nuclear magnetic resonance (NMR) measurements were carried out with a Bruker Avance 300, 400, or 600 MHz apparatus. UV-vis and emission spectra were recorded with a Varian Cary 400 and a PTI Photon Technology International apparatus, respectively. The DSC measurements were performed on a Perkin-Elmer DSC 7 apparatus at the second heating (heating rate = 40 °C/min). Cyclic and differential pulse voltammetry were performed on a Princeton Applied Research PARSTAT 2273, equipped with a standard three-electrode configuration. A Ag/AgCl (3 M NaCl) electrode served as a reference electrode, and a Pt wire and disk served as the counter- and working electrode. The measurements were done in homogeneous solutions of $\pm 10^{-4}$ M binaphthalene derivative, 10^{-4} M ferrocene (internal standard), and 0.1 M Bu₄NBF₄ (supporting electrolyte) in dry dichloromethane under an argon atmosphere. The cyclic and differential pulse voltammograms were calibrated toward the Fe(II/III) couple at 0.60 V versus a standard calomel electrode.¹³

All samples are measured using the frequency resolved hyper-Rayleigh scattering technique as described before¹⁴ with a Ti-sapphire laser (Spectra Physics). Crystal violet (CV) dissolved in methanol was used as an octopolar external reference ($\beta_{\text{xxx}} = 338 \times 10^{-30}$ esu). All the samples were dissolved in chloroform. For each sample, a concentration series is measured and compared to the reference series. Except for BN1-2, none of the samples showed interfering multiphoton fluorescence at the second-harmonic wavelength. **1**,⁹ **2**,⁹ (**S**)-**5**,¹⁵ **6**,¹⁶ **11**,¹⁷ **BN2-2**,⁹ **BN1-2**,⁹ **13**,⁹ and **14**⁹ were synthesized according to literature procedures.

Synthesis of 2-Morpholine-5-tributyltinthiophene 7. A solution of **6** (1.05 mmol, 178 mg) in dry THF (4 mL) was purged with argon and cooled to -78 °C. Slowly, a solution of *t*-BuLi (1.11 mmol, 737 μL , 1.5 M in pentane) was added, and the mixture was stirred for 20 min at -60 °C. Subsequently, a solution of tributyltin chloride (1.16 mmol, 377 mg) in dry THF (2 mL) was added, and the reaction was allowed to reach room temperature. After 2 h of stirring at room temperature, the solvent was removed under reduced pressure, and the product was redissolved in dry hexane. LiCl was filtered off, and, after removal of the solvent, a brown oil was obtained, which was used in the next step without any further purification. Yield: 430 mg (89%). ^1H NMR (CDCl₃; 300 MHz): δ = 6.85 (d, *J* = 3.7 Hz, 1H), 6.27 (d, *J* = 3.7 Hz, 1H), 3.84 (t, 4H), 3.15 (t, 4H), 1.55 (m, 6H), 1.32 (m, 6H), 1.05 (t, 6H), 0.89 (t, 9H).

Synthesis of 5-Morpholine-[2,2'-bithiophene] 9. A solution of **7** (10.4 mmol, 4.74 g), **8** (15.5 mmol, 2.53 g), and Pd(PPh₃)₄ (260 μmol , 300 mg) in dry DMF (20 mL) was purged with argon and heated at 80 °C for 24 h. After reaction, the solvent was removed under reduced pressure, and the product was extracted with chloroform. The combined organic layers were washed with a saturated KCl solution and dried over MgSO₄. The solvents were removed under reduced pressure, and recrystallization of the crude compound from hexane afforded pure, pale yellow crystals. Yield: 1.90 g (73%). mp: 125.9–126.2 °C. ^1H NMR (CDCl₃; 300 MHz): δ = 7.10 (d, *J* = 4.8 Hz, 1H), 6.98 (dd, *J* = 4.8 Hz, *J* = 3.7 Hz, 1H), 6.95 (d, *J* = 3.7 Hz, 1H), 6.88 (d, *J* = 3.7 Hz, 1H), 6.05 (d, *J* = 3.7 Hz, 1H), 3.85 (t, 4H), 3.14 (t, 4H). ^{13}C NMR (CDCl₃; 300 MHz): δ = 158.2, 138.3, 127.8, 124.5, 123.1, 123.0, 122.0, 106.0, 66.4, 51.5. MS: *m/z* = 251 (M⁺), 194 (M⁺-C₄H₉) (calc.: 251.4).

Synthesis of 5-Morpholine-5'-tributyltin-[2,2'-bithiophene] 10. The same procedure as described for the preparation of **7** was followed, starting from **9** (1.00 mmol, 251 mg). The crude oil was used in the next step without any purification. Yield: 520 mg (96%). ^1H NMR (CD₂Cl₂; 300 MHz): δ = 7.09 (d, *J* = 3.7 Hz, 1H), 7.01 (d, *J* = 3.7 Hz, 1H), 6.86 (d, *J* = 4.0 Hz, 1H), 6.02 (d, *J* = 4.0 Hz, 1H), 3.80 (t, 4H), 3.11 (t, 4H), 1.56 (m, 6H), 1.34 (m, 6H), 1.10 (t, 6H), 0.90 (t, 9H). ^{13}C NMR (CD₂Cl₂; 300 MHz): δ = 158.5, 143.8, 136.3, 135.0, 124.5, 123.2, 122.9, 105.7, 66.5, 51.6, 29.2, 27.6, 13.7, 11.1. MS: *m/z* = 541 (M⁺), 484 (M⁺-C₄H₉) (calc.: 540.5).

Synthesis of 3. The same procedure as described for the preparation of **9** was followed, starting from **11** (260 μmol , 102 mg), **10** (911 μmol , 493 mg), and Pd(PPh₃)₄ (13.0 μmol , 15.0 mg) in dry DMF (3 mL). Recrystallization of the crude compound from isopropanol afforded a red solid. Yield: 109 mg (57%). mp: 103.0–104.0 °C. ^1H NMR (CD₂Cl₂; 300 MHz): δ = 7.19 (d, *J* = 3.7 Hz, 1H), 7.14 (s, 1H), 7.04 (d, *J* = 3.7 Hz, 1H), 6.95 (d, *J* = 3.7 Hz, 1H), 6.91 (d, *J* = 3.7 Hz, 1H), 6.90 (d, *J* = 3.7 Hz, 1H), 6.87 (d, *J* = 3.7 Hz, 1H), 6.04 (d, *J* = 3.7 Hz, 2H), 4.05 (qu, 4H), 3.80 (t, 8H), 3.27 (d, *J* = 21.9 Hz, 2H), 3.14 (t, 8H), 1.27 (t, 6H). ^{13}C NMR (CD₂Cl₂; 300 MHz): δ = 159.1, 159.0, 139.3, 137.9, 135.6, 133.7, 131.9, 128.8, 128.7, 127.8, 126.8, 124.7, 123.7, 123.6, 123.3, 123.2, 122.3, 105.5, 66.4, 62.6, 51.4, 27.8, 16.5. MS: *m/z* = 732 (M⁺) (calc.: 733.0).

Synthesis of N1. A suspension of NaH (200 μmol , 4.80 mg), **4** (220 μmol , 34.4 mg), and **1** (200 μmol , 147 mg) in dry THF (5 mL) was purged with argon and vigorously stirred for 20 h at reflux temperature. After reaction, the mixture was poured into a HCl solution (1 M) and extracted with dichloromethane. The combined organic layers were washed with a saturated NaCl solution and dried over MgSO₄. The solvents were removed under reduced pressure, and the crude compound was further purified by column chromatography (silica gel, eluent: chloroform:hexane (5:5 v/v)). After cold trituration in methanol, a pure orange solid was isolated. Yield: 147 mg (99%). mp: 182.8–183.5 °C. ^1H NMR (CDCl₃; 400 MHz): δ = 7.94 (s, 2H), 7.78–7.88 (m, 4H), 7.70 (d, *J* = 8.6 Hz, 1H), 7.59 (s, 1H), 7.58 (s, 1H), 7.54 (s, 1H), 7.43–7.51 (m, 2H), 7.38 (d, *J* = 16.1 Hz, 1H), 7.24 (d, *J* = 16.1 Hz, 1H), 2.89 (t, 2H), 2.88 (t, 2H), 1.72 (m, 4H), 1.20–1.50 (m, 12H), 0.90 (t, 6H). ^{13}C NMR (CDCl₃; 400 MHz): δ = 162.2, 161.0, 159.1, 143.4, 143.3, 142.4, 141.2, 140.2, 138.7, 134.2, 133.7, 133.4, 133.0, 132.6, 131.5, 128.7, 128.3, 127.9, 127.5, 126.6, 126.4, 124.9, 123.4, 120.5, 31.6, 28.8, 27.3, 22.7, 14.2. MS (APCI): *m/z* = 737 (M⁺) (calc.: 737.1).

Synthesis of N2. The same procedure as described for the preparation of **N1** was followed, starting from a suspension of NaH (141 μmol , 3.40 mg), **4** (141 μmol , 22.0 mg), and **2** (141 μmol , 103 mg) in dry THF (4 mL). The crude compound was further purified by column chromatography (silica gel, eluent: dichloromethane:ethylacetate (6:4 v/v)). After cold trituration in methanol, a pure orange solid was isolated. Yield: 87.2 mg (84%). mp: 140.0–141.0 °C. ^1H NMR (CD₂Cl₂; 400 MHz): δ = 7.78–7.88 (m, 4H), 7.71 (d, *J* = 8.6 Hz, 1H), 7.50 (d, *J* = 16.1 Hz, 1H), 7.46 (m, 2H), 7.44 (s, 1H), 7.19 (d, *J* = 16.1 Hz, 1H), 7.10 (s, 2H), 7.09 (d, *J* = 3.7 Hz, 1H), 7.04 (d, *J* = 3.7 Hz, 1H), 7.01 (d, *J* = 3.7 Hz, 2H), 6.71 (d, *J* = 3.7 Hz, 2H), 2.80 (t, 4H), 1.69 (qu, 4H), 1.20–1.50 (m, 12H), 0.91 (t, 6H). ^{13}C NMR (CD₂Cl₂; 400 MHz): δ = 146.5, 146.4, 139.2, 137.7, 136.8, 135.9, 135.1, 134.9, 134.5, 134.4, 134.0, 133.6, 133.4, 131.8, 131.0, 128.6, 128.3, 127.9, 127.8, 127.0, 126.7, 126.3, 125.3, 125.2, 125.1, 124.0, 123.9, 123.7, 122.4, 122.1, 31.9, 30.5, 29.1, 22.9, 14.2. MS (APCI): *m/z* = 733 (M⁺) (calc.: 733.2).

Synthesis of N3. The same procedure as described for the preparation of **N1** was followed, starting from a suspension of NaH (139 μmol , 3.30 mg), **4** (153 μmol , 23.9 mg), and **3** (139 μmol , 102 mg) in dry THF (4 mL). The crude compound was further purified by column chromatography (silica gel, eluent: dichloromethane:ethylacetate (7:3 v/v)). After cold trituration in methanol, a pure red solid was isolated. Yield: 93.5 mg (91%). mp: 220.0–221.0 °C. ^1H NMR (THF-*d*₈; 400 MHz): δ = 7.90 (s, 1H), 7.77–7.86 (m, 3H), 7.75 (d, *J* = 8.8 Hz,

1H), 7.57 (s, 1H), 7.55 (d, $J = 16.1$ Hz, 1H), 7.37–7.47 (m, 2H), 7.34 (d, $J = 16.1$ Hz, 1H), 7.14 (d, $J = 3.8$ Hz, 1H), 7.12 (d, $J = 3.8$ Hz, 1H), 7.01 (d, $J = 3.8$ Hz, 1H), 6.97 (d, $J = 3.8$ Hz, 1H), 6.93 (d, $J = 3.8$ Hz, 1H), 6.92 (d, $J = 3.8$ Hz, 1H), 6.08 (d, $J = 3.8$ Hz, 2H), 3.75 (t, 8H), 3.11 (t, 8H). ^{13}C NMR (THF- d_6 ; 400 MHz): $\delta = 159.9, 159.8, 140.4, 138.8, 137.3, 136.3, 135.9, 134.7, 134.1, 134.0, 132.6, 131.9, 131.6, 128.9, 128.6, 128.3, 128.2, 127.4, 126.8, 126.4, 125.5, 124.3, 124.1, 123.7, 123.5, 122.6, 122.5, 122.4, 105.9, 66.7, 51.9$. MS (APCI): $m/z =$ no fragments observed.

Synthesis of 12 and BN1-1. The same procedure as described for the preparation of **N1** was followed, starting from a suspension of NaH (250 μmol , 6.00 mg), (**S**)-**5** (250 μmol , 77.6 mg), and **1** (250 μmol , 184 mg) in dry THF (5 mL). The mixture of mono- and disubstituted product (**12**, respectively, **BN1-1**) was separated and purified by column chromatography (silica gel, eluent: dichloromethane:ethylacetate (95:5 v/v)). Both derivatives were isolated as an orange solid. Yield (**12**): 114 mg (51%). No melting point was detected by optical microscopy or DSC below 250 °C. T_g : 63.0 °C (determined by DSC at second heating with a heating rate = 40 °C/min). ^1H NMR (CD_2Cl_2 ; 300 MHz): $\delta = 9.59$ (s, 1H), 8.17 (d, $J = 9.1$ Hz, 1H), 8.12 (d, $J = 9.1$ Hz, 1H), 7.90–8.09 (m, 4H), 7.79 (s, 1H), 7.71 (s, 1H), 7.61 (t, $J = 8.6$ Hz, 1H), 7.58 (s, 1H), 7.53 (s, 1H), 7.47 (t, $J = 8.6$ Hz, 1H), 7.20–7.40 (m, 4H), 7.00 (d, $J = 8.6$ Hz, 1H), 6.76 (s, 1H), 6.61 (d, $J = 16.1$ Hz, 1H), 2.87 (m, 4H), 1.69 (m, 4H), 1.20–1.50 (m, 12H), 0.89 (m, 6H). ^{13}C NMR (CD_2Cl_2 ; 400 MHz): $\delta = 191.9, 162.4, 161.1, 159.2, 159.1, 143.7, 143.1, 142.7, 141.4, 141.3, 140.5, 138.5, 136.7, 135.0, 134.3, 133.3, 133.2, 133.0, 132.7, 131.8, 131.2, 130.1, 129.6, 129.5, 129.4, 128.9, 128.5, 127.7, 127.6, 127.5, 126.9, 126.8, 124.9, 123.2, 123.1, 122.5, 31.8, 29.0, 27.4, 22.9, 14.1$. MS (ESI): $m/z = 1805$ ($2\text{M}^+ + \text{Na}$) (calc.: 891.3). Yield (**BN1-1**): 73.2 mg (20%). No melting point detected by optical microscopy or DSC below 250 °C. T_g : 167.6 °C (determined by DSC at second heating with a heating rate = 40 °C/min). ^1H NMR (CD_2Cl_2 ; 600 MHz): $\delta = 8.05$ (d, $J = 8.6$ Hz, 2H), 7.98 (d, $J = 8.6$ Hz, 2H), 7.96 (d, $J = 8.6$ Hz, 2H), 7.68 (s, 2H), 7.66 (s, 2H), 7.50 (s, 2H), 7.45 (t, $J = 8.6$ Hz, 2H), 7.41 (s, 2H), 7.25 (t, $J = 8.6$ Hz, 2H), 7.19 (d, $J = 16.0$ Hz, 2H), 7.10 (d, $J = 8.6$ Hz, 2H), 6.86 (s, 2H), 6.70 (d, $J = 16.0$ Hz, 2H), 2.84 (t, 4H), 2.79 (t, 4H), 1.69 (m, 8H), 1.20–1.50 (m, 24H), 0.90 (m, 12H). ^{13}C NMR (CDCl_3 ; 300 MHz): $\delta = 162.0, 160.7, 159.2, 143.2, 143.0, 142.2, 141.1, 140.1, 138.8, 134.6, 134.0, 133.4, 133.3, 132.9, 132.6, 131.3, 131.1, 129.1, 128.3, 128.2, 127.1, 126.5, 125.0, 123.2, 122.3, 31.6, 28.8, 27.3, 22.7, 14.2$. MS (APCI): $m/z = 1472$ (M^+) (calc.: 1472.3).

Synthesis of BN1-3. The same procedure as described for the preparation of **N1** was followed, starting from a suspension of NaH (89.3 μmol , 2.10 mg), **12** (74.5 μmol , 66.4 mg), and **3** (89.3 μmol , 65.5 mg) in dry THF (4 mL). The crude compound was further purified by column chromatography (silica gel, eluent: dichloromethane:ethylacetate (9:1 v/v)). After cold trituration in methanol, a pure red solid was isolated. Yield: 69.2 mg (63%). mp: 172.1 °C. T_g : 112.0 °C (determined by DSC at second heating with a heating rate = 40 °C/min). ^1H NMR (THF- d_6 ; 600 MHz): $\delta = 8.00$ –8.10 (m, 4H), 7.95 (d, $J = 8.6$ Hz, 1H), 7.94 (d, $J = 8.6$ Hz, 1H), 7.83 (s, 1H), 7.76 (s, 1H), 7.57 (s, 1H), 7.51 (s, 1H), 7.43 (t, $J = 8.6$ Hz, 1H), 7.39 (t, $J = 8.6$ Hz, 1H), 7.35 (d, $J = 16.1$ Hz, 1H), 7.26 (d, $J = 16.1$ Hz, 1H), 7.18–7.26 (m, 2H), 7.13 (d, $J = 8.6$ Hz, 1H), 7.09 (d, $J = 8.6$ Hz, 1H), 7.02 (s, 1H), 6.75–6.90 (m, 7H), 6.74 (s, 1H), 6.69 (d, $J = 16.1$ Hz, 1H), 6.03 (d, $J = 3.7$ Hz, 1H), 5.98 (d, $J = 3.7$ Hz, 1H), 3.73 (m, 8H), 3.08 (m, 8H), 2.88 (t, 2H), 2.87 (t, 2H), 1.69 (m, 4H), 1.20–1.50 (m, 12H), 0.90 (m, 6H). ^{13}C NMR (CDCl_3 ; 600 MHz): $\delta = 161.9, 160.6, 159.3, 159.2, 158.6, 158.5, 143.1, 142.2, 141.1, 141.0, 140.1, 139.2, 138.8, 137.6, 136.4, 135.3, 134.9, 134.0, 133.9, 133.7, 133.6, 133.5, 133.4, 133.1, 133.0, 132.5, 131.8, 131.4, 131.3, 129.2, 129.0, 128.3, 127.4, 127.2, 127.0, 126.9, 126.4, 126.1, 125.0, 124.6, 124.0, 123.9, 123.7, 123.5, 123.4, 123.3, 122.3, 122.2, 122.1, 105.7, 100.1, 66.4, 51.3, 31.6, 28.8, 27.3, 22.7, 14.2$. MS (APCI): $m/z =$ no fragments observed.

Synthesis of BN3-3. The same procedure as described for the preparation of **N1** was followed, starting from a suspension of NaH (136 μmol ,

3.30 mg), (**S**)-**5** (63.5 μmol , 19.7 mg), and **3** (136 μmol , 100 mg) in dry THF (4 mL). The crude compound was further purified by cold trituration in methanol and isolated as a pure red solid. Yield: 70.0 mg (75%). No melting point was detected by optical microscopy or DSC below 250 °C. T_g : 159.5 °C (determined by DSC at second heating with a heating rate = 40 °C/min). ^1H NMR (THF- d_6 ; 600 MHz): $\delta = 8.03$ (s, 4H), 7.93 (d, $J = 8.6$ Hz, 2H), 7.40 (t, $J = 8.6$ Hz, 2H), 7.34 (d, $J = 16.2$ Hz, 2H), 7.21 (t, $J = 8.6$ Hz, 2H), 7.11 (d, $J = 8.6$ Hz, 2H), 6.88 (d, $J = 3.7$ Hz, 2H), 6.80–6.86 (m, 6H), 6.79 (d, $J = 3.7$ Hz, 2H), 6.77 (d, $J = 3.7$ Hz, 2H), 6.74 (s, 2H), 6.70 (d, $J = 16.2$ Hz, 2H), 6.02 (d, $J = 3.7$ Hz, 2H), 5.98 (d, $J = 3.7$ Hz, 2H), 3.72 (m, 16H), 3.07 (m, 16H). ^{13}C NMR (THF- d_6 ; 400 MHz): $\delta = 159.9, 159.8, 140.2, 138.7, 137.3, 136.0, 135.6, 134.9, 134.3, 134.0, 133.8, 132.4, 132.2, 130.0, 129.3, 128.8, 128.3, 127.5, 127.2, 126.6, 125.3, 124.4, 124.2, 124.1, 124.0, 123.7, 123.6, 122.7, 122.5, 122.4, 105.9, 66.7, 51.8$. MS (APCI): $m/z =$ no fragments observed.

RESULTS AND DISCUSSION

Synthesis. The (bi)naphthalene derivatives **N1**, **N2**, and **N3** (**BN1-1**, **BN2-2**, **BN3-3**, **BN1-2**, and **BN1-3**) are built up from the corresponding phosphonate-functionalized π -conjugated oligomers **1**, **2**, or **3** and 2-naphthaldehyde **4** (respectively, (**S**)-2,2'-diformyl-1,1'-binaphthalene (**S**)-**5**), as depicted in Scheme 1.

The syntheses of the electron-poor and the electron-neutral phosphonate **1** and **2** have already been reported.⁹ The synthesis of the p-type phosphonate **3** is depicted in Scheme 2 and starts with the selective deprotonation and a subsequent stannylation of 2-morpholinethiophene (**6**) in the 5-position. It is worth noting that *t*-BuLi had to be used instead of *n*-BuLi to obtain a quantitative conversion and that the tributyltin functional group assured a better stability than the trimethyltin analogue. In this way, the stannylated product **7** was used without any purification in a Stille coupling with 2-bromothiophene (**8**) to expand the conjugated segment with an extra thiophene ring. For the stannylation of this morpholine-substituted bithiophene **9**, the same procedure was followed as for compound **7**. A final Stille coupling of the stannylated bithiophene **10** with the dibromo-functionalized phosphonate **11** afforded the p-type phosphonate **3**.



All three naphthalene derivatives **N1**, **N2**, and **N3** were synthesized by means of a Wittig–Horner reaction of 2-naphthaldehyde (**4**) with the corresponding phosphonate (**1**, **2**, or **3**) (Scheme 3). ^1H NMR spectra unambiguously revealed an exclusive *trans*-configuration of the implemented double bond (see the Supporting Information).

The homocoupled binaphthalene derivatives **BN1-1** and **BN3-3** were also prepared in a *trans*-selective configuration according to the same Wittig–Horner procedure (Scheme 4) as described for the naphthalene derivatives and similar to **BN2-2** and **BN1-2**.⁹ The preparation of the heterocoupled binaphthalene derivative **BN1-3** required the monosubstituted product **12**, which could be separated from **BN1-1** by means of column chromatography. A final Wittig–Horner reaction with phosphonate **3** afforded **BN1-3** in good yield.


NMR Analysis. By comparing the ^1H NMR spectrum of **BN2-2** with those of two reference systems **13** and **14**, as depicted in Figure 2, possible interchain interactions between the two quinquethiophenes within **BN2-2** can elegantly be monitored. **13** consists of a single quinquethiophene, linked to a *t*-butyl group via a *trans*-ethylene linker, and **14** is the monosubstituted product in the Wittig–Horner reaction of (**S**)-**5** with **2**.

The aromatic region of the ^1H spectrum of **BN2-2** (Figure 2C) clearly shows that the spectrum is a superposition of two identical coupled “naphthalene arms”, which experience the same chemical

Scheme 1. Retrosynthesis of the (Bi)naphthalene Derivatives

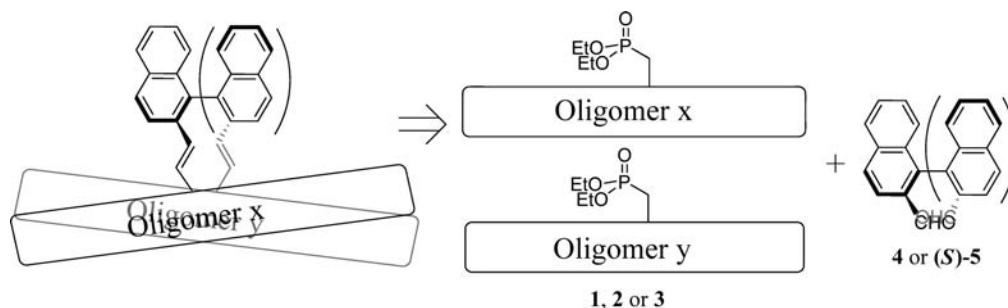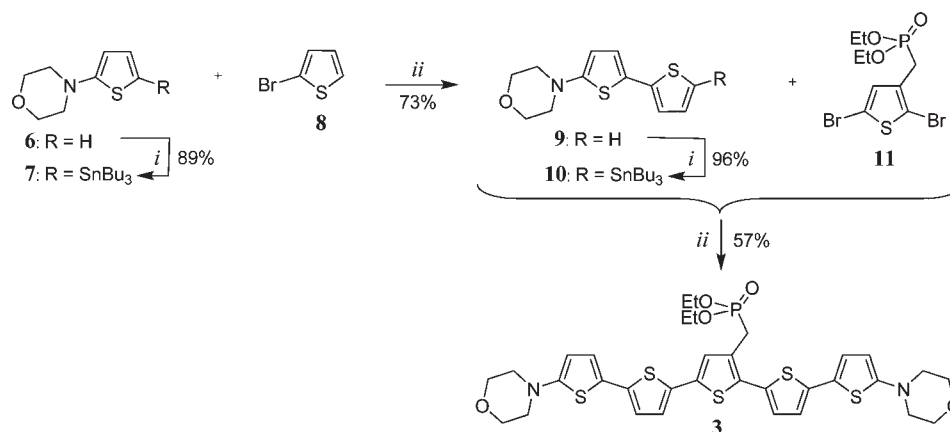Scheme 2. Synthesis of the Electron-Rich Phosphonate 3^a


^a Conditions: (i) (1) *t*-BuLi, THF, (2) Bu₃SnCl; (ii) Pd(PPh₃)₄, DMF.

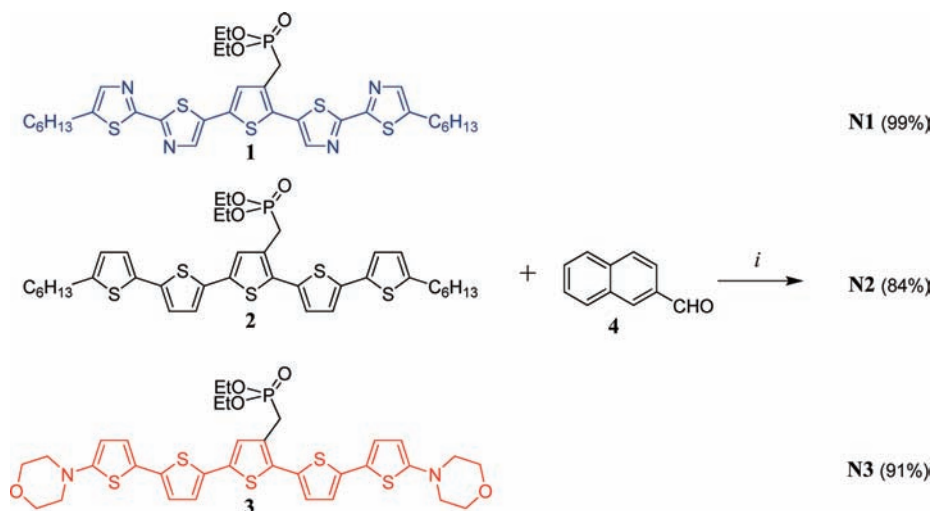Scheme 3. Synthesis of the Naphthalene Derivatives (N1–N3)^a

^a Conditions: (i) NaH, THF.

environment as a result of a single conformation. Indeed, if both naphthalene arms would exhibit a different conformation, additional peaks would be expected in this region. A NOESY spectrum of BN2-2 (Supporting Information) further reveals that this single conformation is characterized as drawn in Figure 2C; that is, the double bond proton **a** is oriented in such a way that it couples through space

with the α -thiophene proton, and the double bond proton **b** is in close proximity to the H3-proton of the naphthalene unit. Analogous ¹H NMR patterns are found for BN1-1 and BN3-3. However, the ¹H spectrum of BN1-1 shows a small percentage ($\pm 5\%$) of an additional set of peaks due to an alternative, single conformation, which could not be unraveled in more detail.

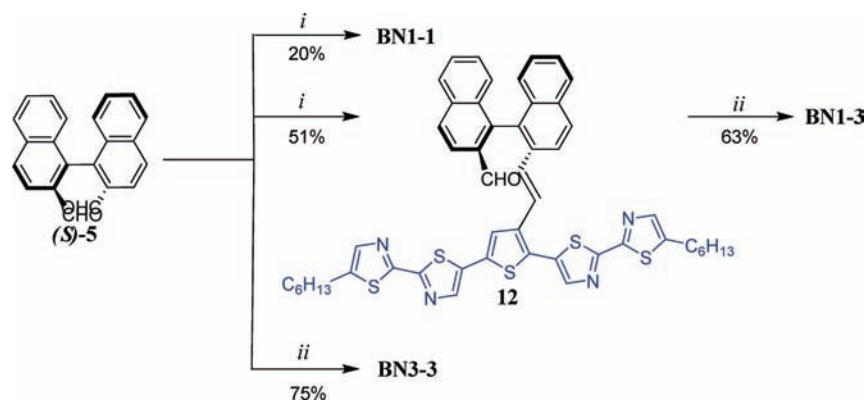Scheme 4. Synthesis of the Homo- and Hetero-coupled Binaphthalene Derivatives BN1-1, BN3-3, and BN1-3^a

^a Conditions: (i) 1, NaH, THF; (ii) 3, NaH, THF.

Focusing on the oligomer protons of **13** and **14** learns that the outermost thiophene protons $\beta^{(i)}$, $\gamma^{(i)}$, $\delta^{(i)}$, and $\epsilon^{(i)}$ (indicated in blue) resonate at more or less the same frequency. Only the innermost α -proton significantly differs due to the ring current effect of the adjacent naphthalene unit in **14**, which is absent in **13**. In comparison with the ¹H spectrum of the homocoupled **BN2-2**, a significant upfield shift can be observed for the outermost thiophene protons (marked in blue). This NMR shift gives evidence for a conformation in which both quinquethiophenes are in close proximity and influence each other through their individual aromatic ring current effect. Similar upfield shifts, also present when comparing the ¹H NMR spectra of **N3** with **BN1-3** (Supporting Information), have been observed for stacked quinquethiophenophanes⁵ and terthiophene-fused ketals.⁶ The α -thiophene proton, on the other hand, undergoes a clear downfield shift with respect to **14**. The NMR signal is highly dependent on the ring current effect of the adjacent naphthalene ring. Because of the stacked conformation of **BN2-2**, the dihedral angle between the naphthalene moieties will be smaller in comparison with **14**,⁹ and thus also the ring current effect will change and give rise to a clear (downfield) NMR shift. Another proof of this difference in dihedral angle between **BN2-2** and **14** can be visualized by the NMR shift of the H8-proton of the binaphthalene unit. All naphthalene protons H1–7 of **14** and **BN2-2** (marked in red) resonate more or less at the same frequency. Only the H8-naphthalene proton of **BN2-2** exhibits a significant downfield shift with respect to **14**. The NMR signal for the H8-proton of **BN2-2** is also highly sensitive to the ring current effect of the adjacent naphthalene ring and alters with respect to **14** as a result of the attractive stacking interaction.⁹

In conclusion, the NMR analysis of **BN2-2** clearly demonstrates the potential of the binaphthalene unit as a suitable molecular pincer to interconnect two π -conjugated oligomers of similar bulkiness in a direct through-space manner.

Electrochemical Analysis. In addition to the NMR analysis, the interchromophoric interactions within **BN2-2** can also be verified in the oxidized state. Therefore, the cyclic and differential pulse voltammograms of all compounds studied are compared and depicted in Figure 3 (differential pulse voltammetry) and the Supporting Information (cyclic voltammetry). **N2** and **BN2-2** show two quasi-reversible oxidations. For **N2**, this is consistent with a first one-electron oxidation, generating a radical-cation $[\text{N2}]^{+\cdot}$ and a second one-electron oxidation affording the dication $[\text{N2}]^{2+}$. In the case of **BN2-2**, no splitting of the first

and second one-electron oxidation (generating $[\text{BN2-2}]^{+\cdot}$ and $[\text{BN2-2}]^{2+}$) can be observed, and both oxidations occur at a lower potential than the unstacked analogue, as clearly shown in the differential pulse voltammogram in Figure 3a. This nonsplitting and lowering of the oxidation potential is also found for Otsubo's quinquethiophenophanes,⁵ but contrasts with Collard's observation that the first oxidation peak of their stacked quinquethiophenes is split.⁶ The fact that the first two one-electron oxidations of the stacked analogue take place at lower potentials than the one-electron oxidation of the linear analogue suggests that both $[\text{BN2-2}]^{+\cdot}$ and $[\text{BN2-2}]^{2+}$ are stabilized by an interaction between the oligothiophenes. The decrease of the potential of the first oxidation can be attributed to the stabilization of the radical cation by the stacked, second oligothiophene, which already points to an interaction between the oligothiophenes. The nonsplitting and the lowering of the second one-electron oxidation potential, generating $[\text{BN2-2}]^{2+}$, shows that the stacked dication is stabilized in such a way that it overcomes the destabilization that might be expected from Coulombic repulsion. To unravel this stabilizing interaction in more detail, **BN2-2** was chemically oxidized in dichloromethane solution by means of a selective oxidant, $\text{Et}_3\text{OSbCl}_6$.^{7,18} The gradual oxidation process was monitored with UV–vis and CD spectroscopy (see the Supporting Information). These spectra readily revealed the formation of radical-cation π -dimers at higher oxidation level, visualized by the appearance of blue-shifted oxidation bands. Therefore, this additional stabilization of $[\text{BN2-2}]^{2+}$ can clearly be attributed to π -dimerization.

At higher potential, the stacked analogue also undergoes subsequent oxidation, generating $[\text{BN2-2}]^{3+}$ and possibly $[\text{BN2-2}]^{4+}$. This latter process takes place without splitting and at higher potential than for the linear analogue, which may be ascribed to additional destabilization of the tricationic $[\text{BN2-2}]^{3+}$ and the tetracationic $[\text{BN2-2}]^{4+}$ through Coulombic repulsion.

An analogous behavior can be found for **N3** and **BN3-3** (although the oxidations occur at lower potentials), except that for **BN3-3**, the first (generating $[\text{BN3-3}]^{+\cdot}$) and second oxidation (to $[\text{BN3-3}]^{2+}$) are split. This can be explained by the fact that the π -dimerization in $[\text{BN3-3}]^{2+}$ cannot compensate for the strong stabilization of $[\text{BN3-3}]^{+\cdot}$ by the very electron-rich oligothiophenes.

For **N1** and **BN1-1**, finally, only an irreversible oxidation at much higher potentials is observed, which is in agreement with its electron-poverty. No reduction could be observed.

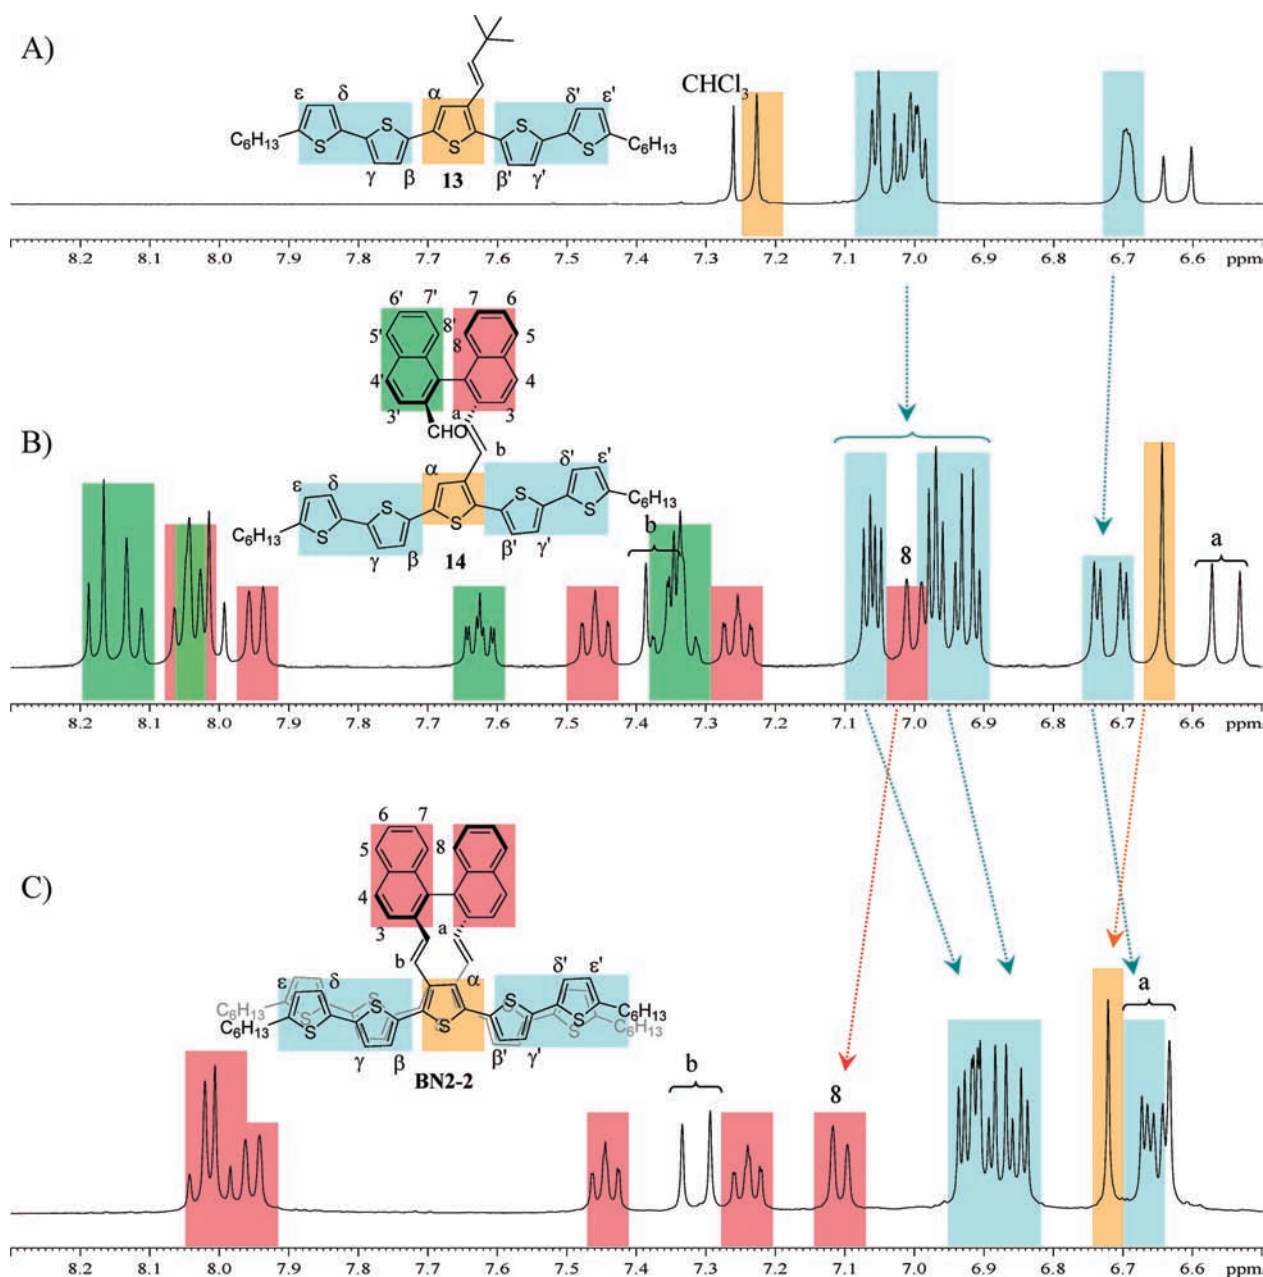


Figure 2. ^1H NMR spectra of the aromatic region of (A) **13** in CDCl_3 , (B) **14**, and (C) **BN2-2** in CD_2Cl_2 .

The voltammograms of the heterocoupled **BN1-2** and **BN1-3** are composed of an oxidation of the quinquethiophene or morpholine-substituted oligomer, an irreversible oxidation of the oligothiazole, and possibly further oxidations to tricationic species. As compared to their homocoupled counterparts (**BN2-2** and **BN3-3**), the first oxidation of **BN1-2** and **BN1-3** occurs at a higher potential, showing that the oxidized quinquethiophene/morpholine-substituted oligomer is more stabilized by a quinquethiophene/morpholine-substituted oligomer than by the electron-poor oligothiazole.

In conclusion, this electrochemical study provides insight into the oxidation-induced interchain interactions between the coupled oligomers and reveals their interactions not only in the neutral but also in the oxidized states.

Linear Optical Properties. Our concept of (chirally) organizing two π -conjugated oligomers by means of a binaphthalene

pincer to evoke interchain interaction in their neutral as well as in their oxidized states can also adequately be applied to study an interchromophoric charge-transfer process. Therefore, heterocoupled binaphthalene derivatives were developed (**BN1-3** and **BN1-2**). **BN1-3** is particularly interesting, because it is constituted of an electron-rich morpholine-substituted oligothiothiophene (p-type) and an electron-poor oligothiazole (n-type).

To provide a baseline measure of the optical properties of the BN compounds, the absorption and emission spectra of both the BNs and the uncoupled naphthalene derivatives **N1-3** were considered (Figure 4). By focusing on the UV-vis spectrum of **BN1-3**, no significant characteristic (red-shifted) charge-transfer absorption band can be observed. Further, the π - π^* transition of **BN1-3** (around 418 nm) can almost fully be explained as a superposition of the spectra of **N1** and **N3** (see the Supporting Information). These linear optical absorption spectra therefore

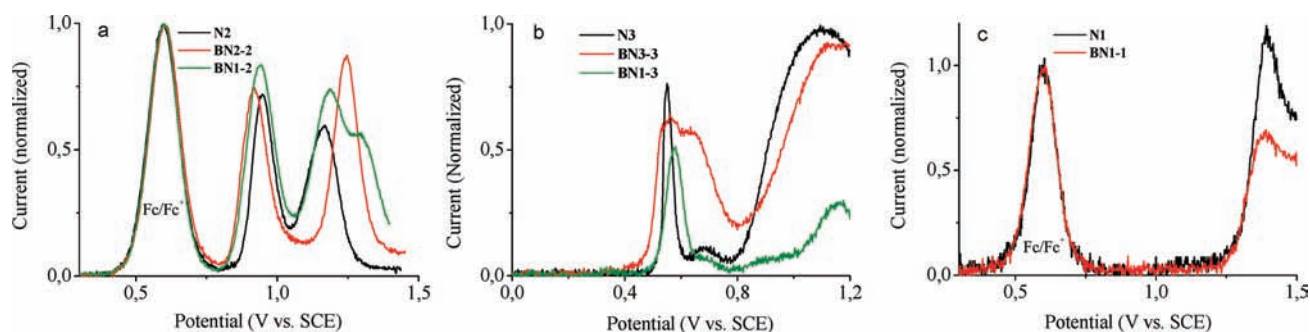


Figure 3. Normalized differential pulse voltammograms in dichloromethane with a pulse amplitude of 75 mV (50 ms) and a scan rate of 20 mV/s. Ferrocene was used as internal standard versus a standard calomel electrode.¹³ In case a morpholine-substituted oligomer is present in the molecular structure, ferrocene was added after the measurement to avoid overlapping of the ferrocene signal.

show no direct proof for an intermolecular charge-transfer complexation in the ground state. However, these data do not exclude the presence of a charge-transfer band, but they reveal that this band, if present, must be very weak.

The CD spectrum of BN1-3 (Figure 4b) is a superposition of Cotton effects arising from the binaphthalene part and the two oligomers. However, while at $\lambda < 380$ nm the CD spectrum of such oligothiophene-substituted binaphthalene is constituted of Cotton effects arising from transitions located on the binaphthalene pincer and the oligomers, the CD spectrum $\lambda > 380$ nm solely originates from the oligomer's $\pi-\pi^*$ transition.⁹ It is clear that in this region a bisignate Cotton effect is observed, which is fully in agreement with the theory of chiral exciton coupling. Therefore, this observation unambiguously demonstrates the chiral arrangement of the p-type and n-type oligomer.

All naphthalene compounds show a strong emission. The emission spectra of the homocoupled BNs (Figure 4c) show a shape similar to that of the constituting oligomers, demonstrating that the emission occurs from the oligomers. In the BN compounds, exciton coupling between the oligomers is present (see also the CD spectra). In such systems, the intensity of the fluorescence depends on the orientation of the chromophores. In a cofacial arrangement, for instance, the fluorescence is quenched. Therefore, the somewhat lower intensity can be attributed to the exciton coupling, but due to the twisted orientation of the oligomers in the BNs, emission is still possible.

By comparing the emission spectrum of BN1-3 with respect to N1 and N3 under the same conditions (chloroform, excitation at 375 nm), a total quenching of the fluorescence is observed for BN1-3 in contrast to the uncoupled systems N1 and N3. To account for the spectroscopic behavior of BN1-3 and BN1-2, an excitation and emission process is outlined in Scheme 5. As already mentioned, the oscillator strength for the lower-lying intermolecular charge-transfer excitation (process B) is considerably smaller than the A counterpart.^{11b} Likewise, the radiative emission (the inverse process of B) has a low probability. After excitation, a rapid electron transfer occurs. Subsequent nonradiative relaxation (process C) to the ground state results then in a full quenching of the fluorescence. This quenching of emission has also been observed by Bazan for the [2.2]paracyclophane derivative that consists of a cyclophane bridged donor- π -donor system with an acceptor- π -acceptor system.^{11b} In BN1-2, finally, the emission is strongly reduced and originates from the N2-oligomer. This is perfectly in line with a slower electron transfer from N2 to N1 due to a smaller difference in electron-poverty, allowing the radiative emission from N2 (the inverse process of A) to be competitive. It should, finally, be noted that energy and

electron transfer between orthogonal π -systems has been reported, leaving the possibility that energy is also transferred via the binaphthalene linker.¹⁹

Nonlinear Optical Properties. A charge-transfer interaction can also clearly be expressed by second-order nonlinear optical phenomena. Indeed, theoretical calculations have predicted a great enhancement of the second-order nonlinear hyperpolarizability β in intermolecular electron donor-acceptor complexes as a result of the large change in dipole moment that accompanies the charge transfer and the relatively low-lying charge-transfer excitation energies.¹² As a consequence, the interaction between the electron-rich morpholine-substituted oligothiophene (p-type) and the electron-poor oligothiazole (n-type) in BN1-3 should give rise to a significant enhanced second-order NLO response, which is not the case for the symmetrically substituted BN1-1, BN2-2, and BN3-3. The same holds for BN1-2. Nevertheless, polar sandwich complexes have been studied, and, although the presence of a through-space interaction was confirmed by cyclic voltammetry, no second harmonic generation could be observed.²⁰

The hyperpolarizabilities of BN1-1, BN2-2, BN3-3, BN1-2, and BN1-3 were determined by hyper-Rayleigh scattering (HRS). In classical 90° angle HRS geometry, the relation between β_{HRS} and the individual molecular tensor elements β_{ijk} is expressed as follows:²¹

$$\langle \beta_{zzz}^2 \rangle = \frac{1}{7} \sum_i \beta_{iii}^2 + \frac{6}{35} \sum_{i \neq j} \beta_{iii} \beta_{ijj} + \frac{9}{35} \sum_{i \neq j} \beta_{ijj}^2 + \frac{6}{35} \sum_{ijk, \text{cyclic}} \beta_{ijj} \beta_{jkk} + \frac{12}{35} \beta_{ijk}^2 \quad (1)$$

$$\langle \beta_{xzz}^2 \rangle = \frac{1}{35} \sum_i \beta_{iii}^2 - \frac{2}{105} \sum_{i \neq j} \beta_{iii} \beta_{ijj} + \frac{11}{105} \sum_{i \neq j} \beta_{ijj}^2 - \frac{2}{105} \sum_{ijk, \text{cyclic}} \beta_{ijj} \beta_{jkk} + \frac{8}{35} \beta_{ijk}^2 \quad (2)$$

where the β_{IZZ} ($I = \text{horizontal (X) or vertical (Z) polarized second-harmonic light}$) is expressed at the macroscopic level and β_{ijk} at the molecular level. The overall measured hyperpolarizability β_{HRS} equals:

$$\beta_{\text{HRS}} = \sqrt{\langle \beta_{zzz}^2 \rangle + \langle \beta_{xzz}^2 \rangle} \quad (3)$$

In general, the HRS response (β_{HRS}) of a molecule depends on both the electronic features and its symmetry. While the first parameter governs the magnitude of the individual tensor components β_{ijk} , the symmetry determines the relative contribution of the

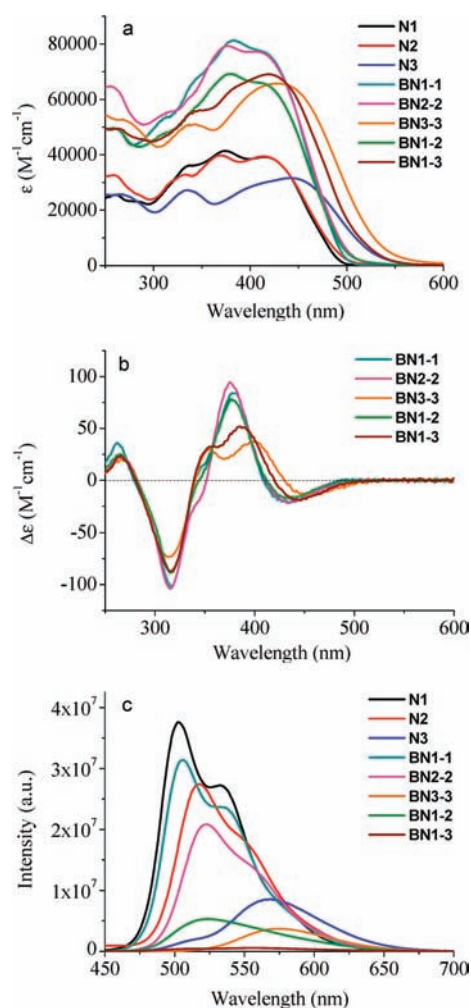


Figure 4. (a) UV-vis spectra of N1 (2.61×10^{-5} M), N2 (2.67×10^{-5} M), N3 (2.76×10^{-5} M), BN1-1 (1.42×10^{-5} M), BN2-2 (1.37×10^{-5} M), BN3-3 (1.37×10^{-5} M), BN1-2 (1.33×10^{-5} M), and BN1-3 (1.34×10^{-5} M) in chloroform. (b) CD spectra of BN1-1 (1.42×10^{-5} M), BN2-2 (1.37×10^{-5} M), BN3-3 (1.37×10^{-5} M), BN1-2 (1.33×10^{-5} M), and BN1-3 (1.34×10^{-5} M) in chloroform. (c) Absorption corrected emission spectra (excitation at 375 nm) of N1 (1.31×10^{-6} M), N2 (1.33×10^{-6} M), N3 (1.38×10^{-6} M), BN1-1 (7.09×10^{-7} M), BN2-2 (6.86×10^{-7} M), BN3-3 (6.83×10^{-7} M), BN1-2 (6.66×10^{-7} M), and BN1-3 (6.72×10^{-7} M) in chloroform.

individual tensor components to the overall signal. Because the binaphthalene compounds are characterized by several transitions and because the symmetry clearly differs from the geometry typically found in π -systems end-capped with an electron-donating and -accepting group (D π A structures), the relative contribution of each individual tensor component cannot be derived from the HRS results only in a straightforward manner. However, because all four binaphthalene derivatives have the same shape, a comparison of the β_{HRS} values does reveal possible electronic differences. The fact that the shape of each molecule is similar, the only difference is the heterocoupling instead of the homocoupling, is also in line with the fact that all compounds show similar depolarization ratios (ρ , expressed as $\rho = \langle \beta_{zzz}^2 \rangle / \langle \beta_{xxx}^2 \rangle$) (Figure 5). It must be mentioned that the experimental observation of statistically identical depolarization ratios for all BNs does not rule out a


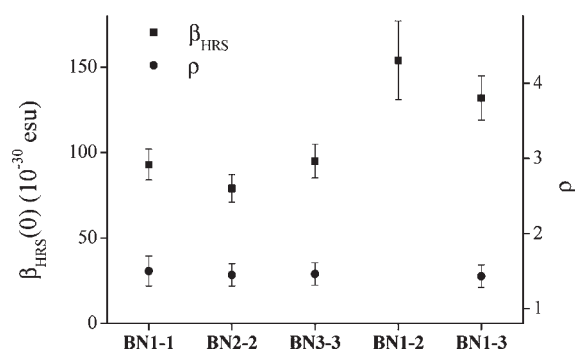


Figure 5. Static β_{HRS} values of the homocoupled BN1-1, BN2-2, and BN3-3 and the heterocoupled BN1-3 and BN1-2 in chloroform solution and the depolarization ratios (excited at 880 nm). Because the HRS signal of BN1-2 was contaminated with fluorescence, the high-frequency demodulation technique was applied to obtain a fluorescence free hyperpolarizability. Unfortunately, in these conditions, the fluorescence free depolarization ratio could not be calculated. This also explains the higher experimental error of $\beta_{\text{HRS}}(0)$.

Scheme 5. Possible Excitation and Emission Pathways, Accounting for the Spectroscopic Behavior of BN1-3 and BN1-2, Shown for Absorption of N2/N3^{11b}

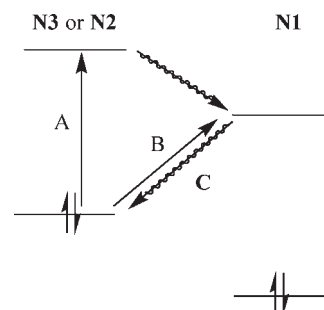

dipolar symmetry in the heterocoupled BN1-3 and BN1-2. Indeed, octopoles show the specific value of around 1.5, which can however also be found in dipoles for a particular hyperpolarizability tensor element combination, for example, $\beta_{xxx} = -\beta_{zzz}$, all other tensor elements being zero. In general, a value for the depolarization ratio close to 1.5 makes it very difficult to correlate it with a particular symmetry. In principle, one expects an octopolar symmetry (T_d , D_{3h} , ...), but a dipolar contribution can give values close to 1.5 as well.²²

The static $\beta_{\text{HRS}}(0)$ values of the binaphthalene compounds, calculated using the two-level model including damping,²³ are displayed in Figure 5, from which two conclusions can be drawn: (i) within the experimental error, the homocoupled BN1-1, BN2-2, and BN3-3 all exhibit a similar, nonvanishing β_{HRS} value, and (ii) the heterocoupled BN1-3 and BN1-2 clearly show an increased HRS response. Concerning the first observation, the noncentrosymmetry of the binaphthalene molecules accounts for the nonvanishing HRS response, which originates from octopolar contributions. More importantly, the increase in β_{HRS} value of BN1-3 can only be explained by the charge-transfer interaction between the two oligomers. Therefore, these observations provide direct proof for the interaction between the electron-rich oligothiophene and the electron-poor oligothiazole.²⁴

The sensitivity of the HRS technique for the charge-transfer interaction can be correlated with eqs 4 and 5:²⁵

$$\alpha \propto \frac{M^2}{E} \quad (4)$$

$$\beta \propto \frac{M^2 \Delta\mu}{E} \quad (5)$$

in which M is the oscillator strength, E is the energy difference between ground and excited states, and $\Delta\mu$ is the difference in dipole moment between ground and excited states. The transition studied is in fact transition B in Scheme 5. From the UV–vis spectra, it is clear that M is rather small for this transition. However, the large change in dipole moment that accompanies the charge transfer results in a significant $\Delta\mu$, increasing the sensitivity of the HRS technique for such transitions. It should be noted that because $\Delta\mu = 0$ for the transition between the stacked oligomers in the homocoupled binaphthalene compounds, this transition cannot contribute to the overall HRS response in these molecules, making this contribution unique to heterocoupled binaphthalene compounds. As a consequence, the combination of the high sensitivity and the selectivity for charge-transfer interactions renders HRS a particularly interesting technique to monitor such interactions. It should moreover be noticed that this observation provides, to the best of our knowledge, the first example of a HRS response originating from through-space charge-transfer interactions, consistent with earlier published, computational data with respect to the role of intermolecular interactions within donor/acceptor π -electron chromophore molecules.¹²

CONCLUSIONS

In this work, we have described the synthesis and the properties of a series of chiral X-type binaphthalene derivatives (BN1-1, BN2-2, BN3-3, BN1-2, and BN1-3) as suitable model compounds to monitor different types of (induced) interchain interactions between two π -conjugated oligomers. NMR spectroscopic studies on BN2-2 have shown that the binaphthalene-linked quinquethiophenes influence each other through ring current effects, unequivocally indicating their close proximity due to attractive π -interactions. Electronic spectral and voltammetric measurements have revealed that the two stacked quinquethiophenes of BN2-2 undergo delocalization in the first one-electron oxidation state and π -dimeric interactions in the second one-electron oxidation state. This evidence confirms the role of the binaphthalene unit as a suitable pincer molecule to interconnect two π -conjugated oligomers of similar bulkiness in a direct through-space manner. By synthesizing heterocoupled binaphthalene derivatives BN1-2 and BN1-3, constituted of oligothiophenes of different electron-richness, we have successfully expanded this concept. The emission spectrum of BN1-3 shows a full quenching of the fluorescence as a result of charge transfer. Hyper-Rayleigh scattering experiments unambiguously reveal a significant enhancement of the second-order hyperpolarizability β resulting from a direct through-space charge-transfer interaction between the p-type and the n-type oligomers. To the best of our knowledge, these experimental HRS values are the first published in the context of a direct through-space charge-transfer interaction between a p-type and an n-type conjugated oligomer.

ASSOCIATED CONTENT

S Supporting Information. Detailed ¹H spectra of all the synthesized (bi)naphthalene derivatives, NOESY spectrum of BN2-2, cyclic voltammograms of all (bi)naphthalene compounds, UV–vis and CD spectra of the chemical oxidation experiment on BN2-2, and a UV–vis superposition spectrum of BN1-3. This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

guy.koeckelberghs@chem.kuleuven.be

ACKNOWLEDGMENT

We are grateful to the Katholieke Universiteit Leuven (GOA), the Fund for Scientific Research (FWO-Vlaanderen). D.C. is a doctoral fellow of the IWT, and G.K. and I.A. are postdoctoral fellows of the Fund for Scientific Research (FWO-Vlaanderen).

REFERENCES

- (1) (a) Mishra, A.; Ma, C.-Q.; Bäuerle, P. *Chem. Rev.* **2009**, *109*, 1141 and references therein. (b) Hoeben, F. J. M.; Jonkheijm, P.; Meijer, E. W.; Schenning, A. P. H. J. *Chem. Rev.* **2005**, *105*, 14911 and references therein.
- (2) Hunter, C. A.; Sanders, J. K. M. *J. Am. Chem. Soc.* **1990**, *112*, 5525.
- (3) (a) Cornil, J.; Santos, D. A. D.; Crispin, X.; Silbey, R.; Brédas, J.-L. *J. Am. Chem. Soc.* **1998**, *120*, 1289. (b) Langeveld-Voss, B. M. W.; Beljonne, D.; Shuai, Z.; Janssen, R. A. J.; Meskers, S. C. J.; Meijer, E. W.; Brédas, J.-L. *Adv. Mater.* **1998**, *10*, 1343.
- (4) (a) Brédas, J.-L.; Street, G. B. *Acc. Chem. Res.* **1985**, *18*, 309. (b) Heeger, A. J.; Kivelson, S.; Schrieffer, J. R.; Su, W. P. *Rev. Mod. Phys.* **1998**, *60*, 781.
- (5) (a) Kaikawa, T.; Takimiya, K.; Aso, Y.; Otsubo, T. *Org. Lett.* **2000**, *2*, 4197. (b) Satou, T.; Sakai, T.; Kaikawa, T.; Takimiya, K.; Otsubo, T.; Aso, Y. *Org. Lett.* **2004**, *6*, 997. (c) Sakai, T.; Satou, T.; Kaikawa, T.; Takimiya, K.; Otsubo, T.; Aso, Y. *J. Am. Chem. Soc.* **2005**, *127*, 8082.
- (6) Knoblock, K. M.; Silvestri, C. J.; Collard, D. M. *J. Am. Chem. Soc.* **2006**, *128*, 13680.
- (7) (a) Song, C.; Swager, T. M. *Org. Lett.* **2008**, *10*, 3575. (b) Takita, R.; Song, C.; Swager, T. M. *Org. Lett.* **2008**, *10*, 5003.
- (8) Cornelis, D.; Peeters, H.; Zrig, S.; Andrioletti, B.; Rose, E.; Verbiest, T.; Koeckelberghs, G. *Chem. Mater.* **2008**, *20*, 2133.
- (9) Cornelis, D.; Verbiest, T.; Koeckelberghs, G. *Chem.-Eur. J.* **2010**, *16*, 10963.
- (10) Wang, S.; Bazan, G. C. *Chem. Phys. Lett.* **2001**, *333*, 437.
- (11) (a) Zyss, J.; Ledoux, I.; Volkov, S.; Chernyak, V.; Mukamel, S.; Bartholomew, G. P.; Bazan, G. C. *J. Am. Chem. Soc.* **2000**, *122*, 11956. (b) Bartholomew, G. P.; Bazan, G. C. *J. Am. Chem. Soc.* **2002**, *124*, 5183.
- (12) (a) Di Bella, S.; Ratner, M. A.; Marks, T. J. *J. Am. Chem. Soc.* **1992**, *114*, 5842. (b) Di Bella, S.; Fragalá, I. L.; Ratner, M. A.; Marks, T. J. *J. Am. Chem. Soc.* **1993**, *115*, 682.
- (13) Bao, D.; Millare, B.; Xia, W.; Steyer, B. G.; Gerasimenko, A. A.; Ferreira, A.; Contreras, A.; Vullev, V. I. *J. Phys. Chem. A* **2009**, *113*, 1259.
- (14) Olbrechts, G.; Strobbbe, R.; Clays, K.; Persoons, A. *Rev. Sci. Instrum.* **1998**, *69*, 2233.
- (15) (a) Ōi, S.; Matsuzaka, Y.; Yamashita, J.; Miyano, S. *Bull. Chem. Soc. Jpn.* **1989**, *62*, 956. (b) Furutani, T.; Hatsuda, M.; Imashiro, R.; Seki, M. *Tetrahedron: Asymmetry* **1999**, *10*, 4763.
- (16) Bedworth, P. V.; Cai, Y.; Jen, A.; Marder, S. R. *J. Org. Chem.* **1996**, *61*, 2242.
- (17) Hou, J.; Yang, C.; Li, Y. *Synth. Met.* **2005**, *153*, 93.

(18) Rathore, R.; Kumar, A. S.; Lindeman, S. V.; Kochi, J. K. *J. Org. Chem.* **1998**, *63*, 5847.

(19) (a) Seth, J.; Palaniappan, V.; Wagner, R. W.; Johnson, T. E.; Lindsey, J. S.; Bocian, D. F. *J. Am. Chem. Soc.* **1996**, *118*, 11194. (b) Wilson, T. M.; Tauber, M. J.; Wasielewski, M. R. *J. Am. Chem. Soc.* **2009**, *131*, 8952. (c) Wilson, T. M.; Hori, T.; Yoon, M.-C.; Aratani, N.; Osuka, A.; Kim, D.; Wasielewski, M. R. *J. Am. Chem. Soc.* **2010**, *132*, 1383.

(20) Malessa, M.; Heck, J.; Kopf, J.; Garcia, M. H. *Eur. J. Inorg. Chem.* **2006**, *4*, 1667.

(21) Hendrickx, E.; Vinckier, A.; Clays, K.; Persoons, A. *J. Phys. Chem.* **1996**, *100*, 19672.

(22) Zyss, J.; Ledoux, I. *Chem. Rev.* **1994**, *94*, 77.

(23) (a) Oudar, J. L.; Chemla, D. S. *J. Phys. Chem.* **1977**, *66*, 2664. (b) Wang, C. H. *J. Phys. Chem.* **2000**, *112*, 1917.

(24) β_{HRS} values of **N1**, **N2**, and **N3** are 430 ± 30 , 530 ± 75 , and $427 \pm 30 \times 10^{-30}$ esu, respectively. However, because the symmetry of the model compounds and the BNs is significantly different and different resonant enhancements are present, the β_{HRS} values cannot be compared. The depolarization ratios are 1.5–1.6.

(25) Interrante, L. V., Hampden-Smith, M. J., Eds. *Chemistry of Advanced Materials: an Overview*; Wiley VCH, Inc.: New York, 1997.