

## Strong and Reversible Binding of Carbon Dioxide in a Green Metal–Organic Framework

Jeremiah J. Gassensmith,<sup>†</sup> Hiroyasu Furukawa,<sup>‡</sup> Ronald A. Smaldone,<sup>†</sup> Ross S. Forgan,<sup>†</sup> Youssry Y. Botros,<sup>†,§,||,⊥</sup> Omar M. Yaghi,<sup>‡,#</sup> and J. Fraser Stoddart<sup>\*,†,#</sup>

<sup>†</sup>Department of Chemistry and <sup>§</sup>Department of Materials Science, Northwestern University, 2145 Sheridan Road, Evanston, Illinois 60208-3113, United States

<sup>‡</sup>Department of Chemistry and Biochemistry, University of California, Los Angeles, 607 Charles E. Young Drive East, Los Angeles, California 90095-1569, United States

<sup>||</sup>Intel Labs, Building RNB-6-61, 2200 Mission College Boulevard, Santa Clara, California 95054-1549, United States


<sup>⊥</sup>National Center for Nano Technology Research, King Abdulaziz City for Science and Technology, P.O. Box 6086, Riyadh 11442, Kingdom of Saudi Arabia

<sup>#</sup>NanoCentury KAIST Institute and Graduate School of EEWs (WCU), Korea Advanced Institute of Science and Technology (KAIST), 373-1 Guseong Dong, Yuseong Gu, Daejeon 305-701, Republic of Korea

**S** Supporting Information

**ABSTRACT:** The efficient capture and storage of gaseous CO<sub>2</sub> is a pressing environmental problem. Although porous metal–organic frameworks (MOFs) have been shown to be very effective at adsorbing CO<sub>2</sub> selectively by dint of dipole–quadrupole interactions and/or ligation to open metal sites, the gas is not usually trapped covalently. Furthermore, the vast majority of these MOFs are fabricated from nonrenewable materials, often in the presence of harmful solvents, most of which are derived from petrochemical sources. Herein we report the highly selective adsorption of CO<sub>2</sub> by CD-MOF-2, a recently described green MOF consisting of the renewable cyclic oligosaccharide  $\gamma$ -cyclodextrin and RbOH, by what is believed to be reversible carbon fixation involving carbonate formation and decomposition at room temperature. The process was monitored by solid-state <sup>13</sup>C NMR spectroscopy as well as colorimetrically after a pH indicator was incorporated into CD-MOF-2 to signal the formation of carbonic acid functions within the nanoporous extended framework.

In view of the predicted detrimental effects of CO<sub>2</sub> emission, capture of CO<sub>2</sub> from gaseous waste streams has become an urgent scientific objective.<sup>1</sup> Recently, several approaches toward the capture of CO<sub>2</sub> have employed porous metal–organic frameworks (MOFs)<sup>2</sup> assembled by linking organic and inorganic building blocks. While these advances in the technology of CO<sub>2</sub> capture are noteworthy<sup>3</sup> for their high storage capacity, the vast majority of these MOFs are fabricated from nonrenewable materials in harmful solvents, many of which are derived from petrochemical sources.<sup>4</sup> We recently reported<sup>5</sup> the discovery of a series of MOFs composed of  $\gamma$ -cyclodextrin ( $\gamma$ -CD) (Figure 1a), a product prepared<sup>6</sup> microbologically from starch (amylose) and thus obtained from atmospheric carbon and fixed by photosynthesis. The  $\gamma$ -CD tori are coordinated to each other by alkali metal cations in units of six, i.e., ( $\gamma$ -CD)<sub>6</sub> (Figure 1b), forming three-dimensional (3D) body-centered-cubic (bcc) extended structures. These CD-MOFs, which are crystallized from water and either methanol or

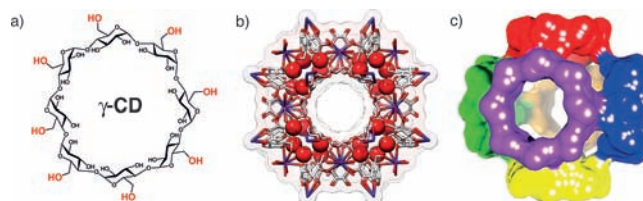


**Figure 1.** (a) Structural formula of  $\gamma$ -cyclodextrin ( $\gamma$ -CD) with the primary hydroxyl groups colored red. (b) Stick representation of a single cubic ( $\gamma$ -CD)<sub>6</sub> unit of the extended framework of activated CD-MOF-2. The primary faces of the six  $\gamma$ -CD tori point inward, while the secondary faces are oriented outward and are coordinated by 24 Rb<sup>+</sup> cations to another six ( $\gamma$ -CD)<sub>6</sub> units, forming a 3D extended bcc structure wherein gases may pass through portals defined by (i) cylindrical channels of aligned CD tori with diameters of  $\sim$ 0.9 nm and (ii) smaller aligned triangular-shaped windows. The spherical inner cavities of the ( $\gamma$ -CD)<sub>6</sub> cubes have a diameter of  $\sim$ 1.7 nm and are lined with 24 primary hydroxyl groups, whose O atoms are shown as red spheres. (c) Space-filling representation of the ( $\gamma$ -CD)<sub>6</sub> unit in which the six  $\gamma$ -CD rings forming the sides of the cube are shown in different colors.

ethanol, are inexpensive and, importantly, “green” in the sense that they can be synthesized from renewable sources that are themselves derived from water, CO<sub>2</sub>, and nontoxic metal salts. We seek to apply this green material in the international green initiative to find methodologies for trapping CO<sub>2</sub> in exhaust gases produced by combustion of organic matter. MOFs have been considered for this task, and there are broadly two distinct mechanisms by which reversible CO<sub>2</sub> capture occurs within these frameworks. One method is binding of CO<sub>2</sub> to vacant coordination sites on metal atoms.<sup>7</sup> While this approach has led to materials with high selectivity for CO<sub>2</sub>, the effect of water (a combustion product) on binding is yet to be determined. Another method uses weakly nucleophilic or polar functional groups that bind CO<sub>2</sub> in a physisorptive manner by means of dipole interactions.<sup>8</sup> While this method is likely to be far less

**Received:** July 13, 2011

**Published:** August 30, 2011

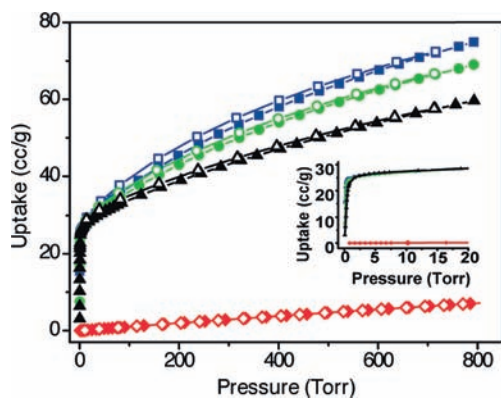

**Figure 2.** Gas adsorption isotherms for activated CD-MOF-2, illustrating the uptake of  $\text{CO}_2$  measured consecutively at 273 K (blue squares), 283 K (green circles), and 298 K (black triangles) to be contrasted with the uptake of  $\text{CH}_4$  at 298 K (red diamonds). Solid symbols indicate gas sorption and open symbols gas desorption. The initial steep rises observed at very low  $\text{CO}_2$  pressures reach the same value of  $\sim 23$  cc/g regardless of temperature and are believed to be characteristic of a chemisorption process.<sup>11</sup>


affected by water, the constituent materials are typically toxic and the selectivity for  $\text{CO}_2$  over other gases is smaller than for methods using open metal sites. Fixing  $\text{CO}_2$  as carbamates by using pools of amines<sup>9</sup> has been explored extensively, but the carbamate end product is thermodynamically very stable, making recycling impractical because heat (and thus more energy) is needed to liberate the  $\text{CO}_2$  and regenerate the free amine. Nevertheless, inspired by the notion of using weakly nucleophilic functional groups to fix  $\text{CO}_2$  chemically and reversibly, we found in CD-MOF-2 a surfeit of free alcohol groups (Figure 1a) and anions<sup>10</sup> to help sustain carbonic acid formation.

Initial  $\text{CO}_2$  gas-uptake experiments with CD-MOF-2 revealed an atypically strong affinity between  $\text{CO}_2$  and the MOF at low pressures, an observation that is indicative of a chemisorptive process.<sup>11</sup> To determine the role a chemisorptive process might have on gas adsorption, isotherms were measured for both  $\text{CO}_2$  and  $\text{CH}_4$  with CD-MOF-2 at incremental temperatures (Figure 2). The total uptake of  $\text{CO}_2$  in the low-pressure region ( $<1$  Torr) was clearly unaffected by temperature over the range 273–298 K, with a notable inflection point at  $\sim 23$   $\text{cm}^3/\text{g}$  regardless of the sample temperature. At these low pressures, the selectivity (as the ratio of the initial slopes) for  $\text{CO}_2$  over  $\text{CH}_4$  was nearly 3000-fold, a considerable difference that is unmatched in the literature as far as we can tell.<sup>12</sup>

Additionally, the steep slopes of the isotherms in this region (Figure 2 inset) suggest a strong binding event that would equate with the formation of a covalent bond. Notably, the abrupt transition in higher-pressure regimes ( $>1$  Torr) becomes much more dependent upon temperature, as indicated by the 30% greater uptake of  $\text{CO}_2$  at 273 K than at 298 K. These observations are consistent with covalent bond formation occurring preferentially at low pressures and giving way to physisorption at elevated pressures, with the change in uptake mechanism occurring when the  $\text{CO}_2$  content of the MOF is  $\sim 23$   $\text{cm}^3/\text{g}$ . We were able to obtain these isotherms repeatedly on the same sample, showing the process to be fully reversible at room temperature.

Alkylcarbonic acids are known<sup>13</sup> to form as a result of the reaction between  $\text{CO}_2$  and free primary alcohol groups. Although it has been pointed out<sup>14</sup> that the addition of nucleophilic groups,<sup>15</sup> specifically primary amines, to MOFs through the rational design of struts<sup>16</sup> or by way of postsynthetic modification improves  $\text{CO}_2$  capture, to our knowledge no spectroscopic evidence has been provided for the formation of the


resultant organic acids. The free hydroxyl groups<sup>17</sup> located on each individual  $\gamma$ -CD torus seem to be capable of serving as reactive functional groups for reversible carbonic acid formation (Figure 3a). Spectroscopic evidence showing the solid-state reactivity of  $\gamma$ -CD with  $\text{CO}_2$  was obtained by cross-polarization magic-angle-spinning (CP/MAS)  $^{13}\text{C}$  NMR spectroscopy. For the solid-state NMR spectroscopic experiments, crystalline samples were activated by exchanging the aqueous methanolic solution with dichloromethane before being evacuated and dried at low pressure ( $<2.0 \times 10^{-3}$  Torr) for 2 days to remove all of the remaining water. The activated CD-MOF was exposed to an atmosphere of dry  $\text{CO}_2$  for 10 min and transferred into an airtight zirconium solid-state NMR rotor. The  $^{13}\text{C}$  NMR spectrum of a crystalline sample of activated CD-MOF-2 (Figure 3b, bottom) shows separate peaks for C1 and C1' as well as for C4 and C4' as a result of the commuted symmetry induced by the alternating  $\text{Rb}^+$  cations on the primary and secondary faces of the  $\gamma$ -CD tori. Upon exposure to  $\text{CO}_2$ , a new peak<sup>18</sup> centered at 158 ppm emerged (Figure 3b, top), consistent with formation of a carbonate.<sup>19</sup> To rule out the possibility that  $\text{OH}^-$  counterions of CD-MOF-2 are the reactive agents, forming carbonate anions<sup>20</sup> by reaction with  $\text{CO}_2$ , we examined CD-MOFs prepared from  $\text{RbF}$  or potassium benzoate that are isostructural with CD-MOF-2 but contain non-nucleophilic and weakly basic counterions. The CP/MAS spectra of both MOFs showed identical resonances at 158 ppm, precisely the chemical shift found in CD-MOF-2 upon exposure to  $\text{CO}_2$ .

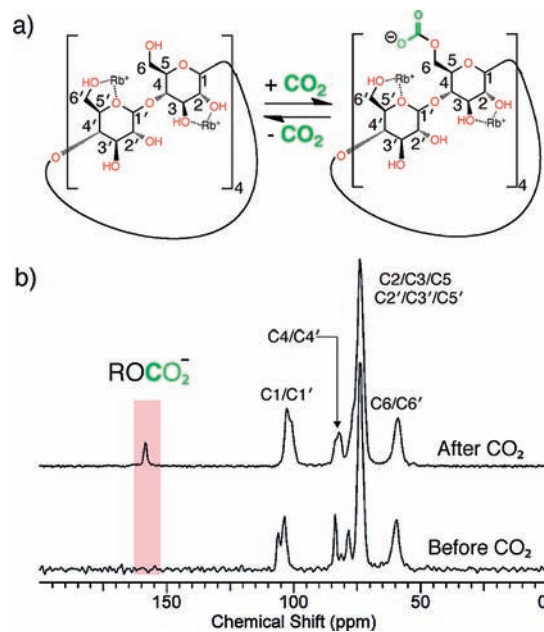

**Figure 3.** (a) Schematic diagram illustrating the equilibrium proposed to exist during the chemisorption of  $\text{CO}_2$  by CD-MOF-2, expressed in the context of the structural formula of one of the four repeating maltosyl units present in a single  $\gamma$ -CD torus. (b) CP/MAS  $^{13}\text{C}$  NMR spectra (400 MHz, room temperature) of activated CD-MOF-2 before (bottom) and after (top) exposure to  $\text{CO}_2$ . Upon exposure to  $\text{CO}_2$ , CD-MOF-2 shows a new peak at 158 ppm due to the formation of carbonic acid functions. This additional resonance is accompanied by changes in the chemical shifts of other peaks in the spectrum, supporting the observation that a chemical reaction between the gaseous  $\text{CO}_2$  and the framework of activated CD-MOF-2 has occurred. Gaseous  $\text{CO}_2$  is not detected by this CP/MAS NMR method but is usually observed as a very sharp singlet at 126 ppm in direct-polarization experiments.


We speculate that this favorable reactivity arises because the  $\gamma$ -CD units of CD-MOF-2 possess a significant number of accessible hydroxyl groups that define the circumference of a large (1.7 nm diameter) pore and have a high capacity for CO<sub>2</sub> relative to ambient pressures. These large local reactant concentrations facilitate the formation of bound CO<sub>2</sub> molecules in ways reminiscent<sup>21</sup> of the enhanced reactivity observed within supramolecular host/guest complexes that arises from the greater local concentration within a supramolecular ensemble, which can increase the reactivity by orders of magnitude in some cases.

If we are correct in assuming that formation of a carbonate ester by reaction with a hydroxyl group of a  $\gamma$ -CD occurs as the primary mechanism, it should be possible to detect the CO<sub>2</sub> uptake using an inexpensive and readily available pH indicator. Thus, methyl red, a zwitterionic azobenzene-based pH indicator, was diffused into the pores of CD-MOF-2 by suspension in a CH<sub>2</sub>Cl<sub>2</sub> solution of the dye. The red solution was decanted, and brilliant yellow crystals were obtained after washing and drying in vacuo (Figure 4a). The yellow color arises from the incorporated methyl red, which undergoes partial anion metathesis (and thus deprotonation) with the counterions in the pore structure, an observation consistent with previous findings.<sup>5a</sup> The dried crystals were transferred to a scintillation vial, which was then exposed to both dry (from a tank) and humid (from sublimed dry ice) CO<sub>2</sub>. The initial color change from yellow to orange/red occurred quickly (Figure 4b), regardless of the CO<sub>2</sub> source, and after 5 min, no further color change could be discerned by the naked eye. When the source of CO<sub>2</sub> was removed, the crystals reverted to a yellow color (Figure 4c), indicating that the transient carbonic acid function had returned to the alcohol, liberating CO<sub>2</sub>. This Le Châtelier-like process was repeated more than 10 times with no apparent fatigue observed on the material.

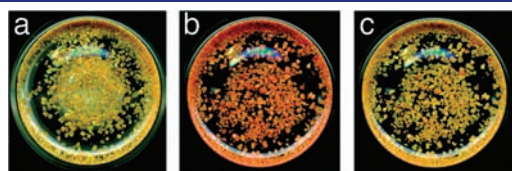

**Figure 4.** Photographs of crystalline activated CD-MOF-2 samples with incorporated methyl red at selected time intervals during CO<sub>2</sub> sorption and desorption processes. (a) Yellow crystals of activated CD-MOF-2 prior to CO<sub>2</sub> exposure. It is postulated that interstitial OH<sup>-</sup> counterions (CD-MOF-2 is prepared from  $\gamma$ -CD and RbOH) maintain a basic environment within the framework, leading to deprotonation of the methyl red dye. (b) Red crystals obtained after exposure of the yellow crystals from (a) to CO<sub>2</sub> over the course of 5 min. It is proposed that chemisorption of CO<sub>2</sub> at the many OH groups facing into the cavities of the ( $\gamma$ -CD)<sub>6</sub> units results in the formation of carbonic acid functions throughout the extended framework, producing an acidic environment that protonates the dye, turning it red. (c) Crystals that reverted back to yellow following removal of the CO<sub>2</sub> atmosphere, allowing ambient air to enter the vial over the course of 5 min. It is hypothesized that the metastable carbonic acid species dissociate and release CO<sub>2</sub>, returning the interior of the framework to a basic environment.

This strong uptake of CO<sub>2</sub> occurs only when the  $\gamma$ -CD tori are arranged in the solid state as CD-MOF.<sup>22</sup> Pulverizing the crystals of this MOF turned it into an amorphous powder, as determined by powder X-ray diffraction (PXRD) measurements (Figure 5a),<sup>23</sup> and quelled the carbonate formation, as determined by solid-state NMR spectroscopy. The surface accessibility of these hydroxyl groups in the crystalline state far exceeds

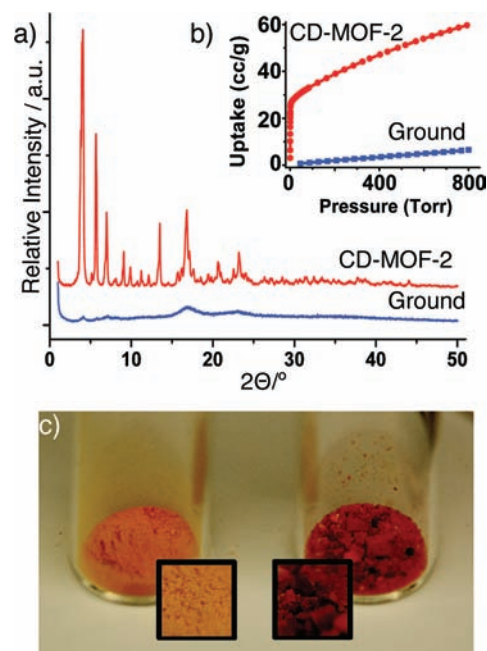

**Figure 5.** (a) PXRD analysis of pristine CD-MOF-2 (red, top) and a sample ground in a mortar and pestle for 7 min (blue, bottom). The grinding process reduced CD-MOF-2 into an amorphous powder, as reflected in the diffraction pattern. (b) CO<sub>2</sub> uptake isotherms (298 K) for crystalline CD-MOF-2 (red circles) and a sample ground into an amorphous powder (blue squares). The powdered sample exhibited very little CO<sub>2</sub> sorption and no steep rise in the low-pressure region. (c) Photograph of activated CD-MOF-2 with incorporated methyl red that was (left) ground to an amorphous powder or (right) allowed to remain pristine and then exposed to CO<sub>2</sub> for 5 min. The insets show magnified images. No color change was evident in the amorphous sample, while the crystalline material underwent the expected change to a red color.

that in the amorphous state, as determined (Figure 5b) by Langmuir and BET analysis [see Figure S3 in the Supporting Information (SI)]. Additionally, no evidence of carbonate formation was observed by CP/MAS NMR spectroscopy of pure  $\gamma$ -CD after exposure to CO<sub>2</sub>. We repeated the CO<sub>2</sub> uptake color-change experiments (Figure 5c) on pulverized CD-MOF-2 and found that the amorphous material did not change color upon exposure to CO<sub>2</sub>, in contrast to a pristine crystalline sample.

In conclusion, we have established that CD-MOF-2 is highly selective for the absorption of CO<sub>2</sub> at low pressures.<sup>24</sup> This selectivity is believed to be the result of chemisorption and to rely upon the free hydroxyl groups present in CD-MOF-2, which act as reactive hotspots for the formation of carbonic acid groups when CO<sub>2</sub> diffuses into the framework. Furthermore, the formation of an inherently acidic product as a result of this chemisorption allowed for the detection of CO<sub>2</sub> colorimetrically by swapping anions with a small-molecule pH indicator within the MOF structure. We have also shown that the strong and selective uptake of CO<sub>2</sub> is a property unique to nanoporous crystalline CD-MOF-2 and is not observed for other CD-based mixtures with amorphous morphologies. The fact that CD-MOFs can be made from environmentally benign materials whose synthesis is essentially carbon-neutral and have the demonstrated ability to absorb CO<sub>2</sub> from the atmosphere makes them promising materials for carbon fixation.

## ■ ASSOCIATED CONTENT

**S Supporting Information.** Synthesis and characterization of all compounds and additional experimental results. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## ■ AUTHOR INFORMATION

## Corresponding Author

stoddart@northwestern.edu

## ■ ACKNOWLEDGMENT

This research was supported in the U.S. by the National Science Foundation under Grant CHE-0924620 and in the U.K. by the Engineering and Physical Research Council under Grant EP/H003517/1. In addition, the authors thank our joint collaborators Dr. Turki S. Al-Saud and Dr. Mohamed B. Alfageeh from KACST in Saudi Arabia for funding and support and the Non-Equilibrium Energy Research Center (NERC), which is an Energy Frontier Research Center (EFRC) funded by the U.S. Department of Energy, Office of Basic Energy Sciences (DOE-BES) under Award DE-SC0000989. O.M.Y. was supported by the Center for Gas Separations Relevant to Clean Energy Technologies, an EFRC funded by DOE-BES under Award DE-SC0001015. O.M.Y. and J.F.S. were supported by the WCU Program (NRF R-31-2008-000-10055-0) funded by the Ministry of Education, Science and Technology, Korea.

## ■ REFERENCES

- (1) Service, R. *Science* **2004**, *305*, 962.
- (2) (a) Eddaoudi, M.; Li, H.; Yaghi, O. M. *J. Am. Chem. Soc.* **2000**, *122*, 1391. (b) Millward, A. R.; Yaghi, O. M. *J. Am. Chem. Soc.* **2005**, *127*, 17998. (c) Arstad, B.; Fjellvag, H.; Kongshaug, K. O.; Swang, O.; Blom, R. *Adsorption* **2008**, *14*, 755. (d) Caskey, S. R.; Wong-Foy, A. G.; Matzger, A. J. *J. Am. Chem. Soc.* **2008**, *130*, 10870. (e) Dietzel, P. D. C.; Johnsen, R. E.; Fjellvag, H.; Bordiga, S.; Groppo, E.; Chavan, S.; Blom, R. *Chem. Commun.* **2008**, 5125. (f) Llewellyn, P. L.; Bourrelly, S.; Serre, C.; Vimont, A.; Daturi, M.; Hamon, L.; De Weireld, G.; Chang, J.-S.; Hong, D.-Y.; Hwang, Y. K.; Jung, S. H.; Férey, G. *Langmuir* **2008**, *24*, 7245. (g) Banerjee, R.; Furukawa, H.; Britt, D.; Knobler, C.; O'Keeffe, M.; Yaghi, O. M. *J. Am. Chem. Soc.* **2009**, *131*, 3875. (h) Chen, S.; Zhang, J.; Wu, T.; Feng, P.; Bu, X. *J. Am. Chem. Soc.* **2009**, *131*, 16027. (i) Keskin, S.; Sholl, D. S. *Ind. Eng. Chem. Res.* **2009**, *48*, 914. (j) Bae, Y.-S.; Farha, O. K.; Hupp, J. T.; Snurr, R. Q. *J. Mater. Chem.* **2010**, *19*, 2131.
- (3) (a) Sadakiyo, M.; Yamada, T.; Kitagawa, H. *J. Am. Chem. Soc.* **2009**, *131*, 9906. (b) An, J.; Rosi, N. L. *J. Am. Chem. Soc.* **2010**, *132*, 5578. (c) Morris, W.; Leung, B.; Furukawa, H.; Yaghi, O. K.; He, N.; Hayashi, H.; Houndonougbo, Y.; Asta, M.; Laird, B. B.; Yaghi, O. M. *J. Am. Chem. Soc.* **2010**, *132*, 11006.
- (4) While most reported MOFs utilize struts derived from petrochemical sources, there is a recent trend in research in which biologically relevant and naturally-derived materials are being incorporated into frameworks, although they very often have toxic transition metals serving as their secondary building units. For a review of these new "MBioFs", see: Imaz, I.; Rubio-Martínez, M.; An, J.; Solé-Font, I.; Rosi, N. L.; Maspoch, D. *Chem. Commun.* **2011**, 47, 7287.
- (5) (a) Smaldone, R. A.; Forgan, R. S.; Furukawa, H.; Gassensmith, J. J.; Slawin, A. M. Z.; Yaghi, O. M.; Stoddart, J. F. *Angew. Chem., Int. Ed.* **2010**, *49*, 8630. (b) Han, S.; Wei, Y.; Valente, C.; Forgan, R. S.; Gassensmith, J. J.; Smaldone, R. A.; Nakanishi, H.; Coskun, A.; Stoddart, J. F.; Grzybowski, B. A. *Angew. Chem., Int. Ed.* **2011**, *50*, 276.
- (6) Dodziuk, H. *Cyclodextrins and Their Complexes*; Wiley-VCH: Weinheim, Germany, 2006.
- (7) Britt, D.; Furukawa, H.; Wang, B.; Glover, T. G.; Yaghi, O. M. *Proc. Natl. Acad. Sci. U.S.A.* **2009**, *106*, 20637.
- (8) Vaidhyanathan, R.; Iremonger, S. S.; Shimizu, G. K. H.; Boyd, P. G.; Alavi, S.; Woo, T. K. *Science* **2010**, *330*, 650.
- (9) (a) Versteeg, G. F.; Van Swaalj, W. J. *Chem. Eng. Data* **1988**, *33*, 29. (b) Arstad, B.; Blom, R.; Swang, O. *J. Phys. Chem. A* **2007**, *111*, 1222.
- (10) The counterions associated with the alkali metal cations that hold the  $\gamma$ -CD units together in CD-MOFs are retained within the framework.<sup>5a</sup> In the case of CD-MOF-2 obtained from RbOH, it was not possible to detect the presence of the counterions by X-ray crystallography, and the fact that the OH<sup>-</sup> anions are not bound to the Rb<sup>+</sup> cations suggests that the metal centers are coordinatively saturated and unable to bind guests. However, for CD-MOFs prepared from <sup>1</sup>H NMR-active alkali metal salts such as potassium benzoate, the counterions were clearly visible in the <sup>1</sup>H NMR spectra of redissolved samples in D<sub>2</sub>O as well as in the solid-state <sup>13</sup>C CP/MAS NMR spectra described in this communication (see the SI).
- (11) (a) Lee, K. B.; Beaver, M. G.; Caram, H. S.; Sircar, S. *AICHE J.* **2007**, *53*, 2824. (b) Southon, P. D.; Price, D. J.; Nielsen, P. K.; McKenzie, C. J.; Kepert, C. J. *J. Am. Chem. Soc.* **2011**, *133*, 10885.
- (12) (a) Jin, Y.; Voss, B.; Noble, R. D.; Zhang, W. *Angew. Chem., Int. Ed.* **2010**, *49*, 6348. (b) Farha, O. K.; Yazaydin, A. O.; Eryazici, I.; Malliakas, C.; Hauser, B.; Kanatzidis, M. G.; Nguyen, S. T.; Snurr, R. Q.; Hupp, J. T. *Nat. Chem.* **2010**, *2*, 944. (c) D'Alessandro, D. M.; Smitand, B.; Long, J. R. *Angew. Chem., Int. Ed.* **2010**, *49*, 6058. (d) Jin, Y.; Voss, B. A.; Jin, A.; Long, H.; Noble, R. D.; Zhang, W. *J. Am. Chem. Soc.* **2011**, *133*, 6650.
- (13) West, K.; Wheeler, C.; McCarney, J.; Griffith, K.; Bush, D.; Liotta, C.; Eckert, C. *J. Phys. Chem. A* **2001**, *105*, 3947.
- (14) Dell'Amico, D. B.; Calderazzo, F.; Labella, L.; Marchetti, F.; Pampaloni, G. *Chem. Rev.* **2003**, *103*, 3857.
- (15) Demessence, A.; D'Alessandro, D. M.; Foo, M. L.; Long, J. R. *J. Am. Chem. Soc.* **2009**, *131*, 8784.
- (16) Vaidhyanathan, R.; Iremonger, S. S.; Dawson, K. W.; Shimizu, G. K. H. *Chem. Commun.* **2009**, 5230.
- (17) While we hypothesize that this chemisorption process occurs at the primary hydroxyl groups on the basis of the well-established principle that they are more reactive than their secondary counterparts, we cannot rule out the possibility of reactions involving the secondary hydroxyl groups. In addition, it is well-known that CDs can be functionalized selectively on their primary faces as a result of their increased nucleophilicity. See: Boger, J.; Corcoran, R. J.; Lehn, J.-M. *Helv. Chim. Acta* **1978**, *61*, 2190.
- (18) When <sup>13</sup>CO<sub>2</sub> was used, the peak at 158 ppm was much larger, confirming that the resonance originated from CO<sub>2</sub> (see Figure S6).
- (19) Kwak, J. H.; Hu, J. Z.; Hoyt, D. W.; Sears, J. A.; Wang, C.; Rosso, K. M.; Felmy, A. R. *J. Phys. Chem. C* **2010**, *114*, 4126.
- (20) The reversibility of CO<sub>2</sub> uptake is further evidence that the OH<sup>-</sup> counterions do not react with CO<sub>2</sub> to form bicarbonate anions, as it is highly unlikely and thermodynamically unfavorable for the reverse process (dissociation of a bicarbonate anion into a gaseous CO<sub>2</sub> molecule and a OH<sup>-</sup> ion) to occur.
- (21) (a) Conn, M.; Rebek, J., Jr. *Chem. Rev.* **1997**, *97*, 1647. (b) Vriezema, D. M.; Aragonès, M. C.; Elemans, J. A. A. W.; Cornelissen, J. J. L. M.; Rowan, A. E.; Nolte, R. J. M. *Chem. Rev.* **2005**, *105*, 1445. (c) Smaldone, R. A.; Moore, J. S. *J. Am. Chem. Soc.* **2007**, *129*, 5444. (d) Gassensmith, J. J.; Lee, J.-J.; Noll, B. C.; Smith, B. D. *New J. Chem.* **2008**, *32*, 843. (e) Inokuma, Y.; Yoshioka, S.; Fujita, M. *Angew. Chem., Int. Ed.* **2010**, *47*, 8912. (f) Inokuma, Y.; Kawano, M.; Fujita, M. *Nat. Chem.* **2011**, *3*, 349.
- (22) As a control, the same experiment was performed on crystals of MOF-5 that were loaded with methyl red and exposed to NH<sub>3</sub> gas to form the (deprotonated) ammonium azo dye salt. MOF-5 is free of hydroxyl groups capable of forming an acid moiety to elicit a pH-based color change and thus would not be expected to demonstrate chemisorption. The presence of CO<sub>2</sub> had no effect on the crystal color.
- (23) The effect of grinding on the crystallinity of CD-MOF-2 was determined by pulverizing a dry sample with a mortar and pestle and recording PXRD patterns at differing time intervals (see the SI). Seven minutes of grinding reduced CD-MOF-2 to an amorphous powder.
- (24) There is a strong correlation between the amount of pure CO<sub>2</sub> adsorbed at low total pressure and the amount of CO<sub>2</sub> adsorbed at low partial pressure under atmospheric conditions. See: Yang, R. T. *Adsorbents: Fundamentals and Applications*; Wiley: Hoboken, NJ, 2003.