

Synthesis and characterization of cobalt(II) complexes of croconate and dicyanomethylene-substituted derivatives †

Frédéric Dumestre,^a Brigitte Soula,^a Anne-Marie Galibert,^a Paul-Louis Fabre,^{*a}
 Gérald Bernardinelli,^b Bruno Donnadiou^c and Paule Castan^a

^a Laboratoire de Chimie Inorganique, Université Paul Sabatier, 118 route de Narbonne, 31062 Toulouse Cedex 04, France


^b Laboratoire de Cristallographie, 24 Quai E. Ansermet, CH-1211 Geneva 4, Switzerland

^c Laboratoire de Chimie de Coordination, UPR CNRS 8241, 205 route de Narbonne, 31077 Toulouse, France

Received 5th October 1998, Accepted 15th October 1998


The crystal structures of cobalt(II) complexes of croconate $[\text{CoL}^1(\text{H}_2\text{O})_3]$ **1** ($\text{L}^1 = \text{C}_5\text{O}_5^{2-}$) and croconate violet $\text{K}_2[\text{CoL}^2(\text{H}_2\text{O})_2] \cdot 2\text{H}_2\text{O}$ **2** [$\text{L}^2 = 3,5$ -bis(dicyanomethylene)cyclopentane-1,2,4-trionate] have been determined. Complex **1** consists of infinite zig-zag chains constituted by one metal atom, one croconate acting as a bridge and three water molecules. Moreover these chains, parallel to the *c* axis, are stacked with metal–metal distances of 7.9891(3) Å inside a chain and 5.0035(6) Å between chains. Complex **2** consists of dianionic and mononuclear entities in which the ligand is O-co-ordinated. The magnetic properties of **1** and **2** have been investigated in the 4–300 K temperature range ($\mu_{\text{eff}} = 3.65$ to 5.02 μ_{B} for **1** and $\mu_{\text{eff}} = 4.00$ to 4.90 μ_{B} for **2**). Their redox properties are discussed and compared to those of the free ligands.

The dianion of croconic acid (4,5-dihydroxycyclopent-4-ene-1,2,3-trione), $(\text{C}_5\text{O}_5)^{2-}$, is one of the cyclic aromatic oxocarbons $(\text{CO})_n^{2-}$ characterized by extensive delocalization of the π electrons all over the ring. Though croconate (C_5) and rhodizonate (C_6) oxocarbons were first synthesized more than 170 years ago,² and copper(II) croconate was first reported by Gmelin in 1841,³ their co-ordination chemistry remained poorly understood until the rebirth of the field following the discovery of squaric acid (C_4) in 1959.⁴ Only a few structures of croconate complexes with first row transition-metal ions are known: $[\text{M}(\text{C}_5\text{O}_5)(\text{H}_2\text{O})_3]$ ($\text{M} = \text{Cu}^{\text{II}}, \text{Zn}^{\text{II}}, \text{Mn}^{\text{II}}, \text{Fe}^{\text{II}}$),^{5–7} and also some complexes with croconate associated with another ligand such as imidazole,⁸ histamine,⁹ 2,2'-bipyridine¹⁰ or the bis(2-pyridyl-carbonyl)amido anion.¹¹ Available structural data dealing with transition-metal croconate complexes show that this ligand can act either as a terminal (I)^{8–10} or as a bridging ligand (II and III).^{5–7,11}

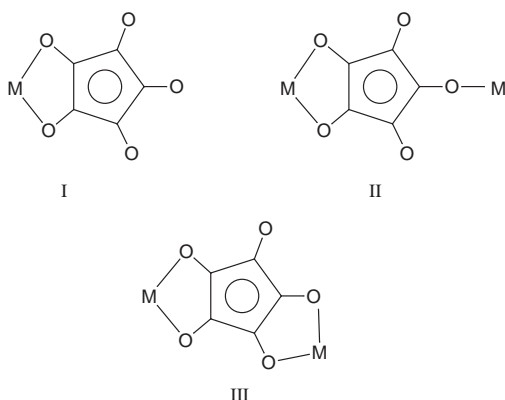

Several species have been synthesized in which the original carbonyl oxygen atoms are either partially or completely replaced by sulfur, nitrogen, or dicyanomethylene; these are called pseudo-oxocarbons.¹² Among these compounds,

croconate blues [2,4,5-tris(dicyanomethylene)cyclopentane-1,3-dionate salts] and croconate violets [3,5-bis(dicyanomethylene)cyclopentane-1,2,4-trionate salts],^{13–17} condensation derivatives of croconic acid and malononitrile (NCCH_2CN) are intriguing materials. These dyes display a strong absorption in the visible region and reversible electrochemical behavior^{18,19} as well as some typical semiconductor properties.^{20,21} However, the co-ordination chemistry of these ligands has received little attention up to now in spite of a formal analogy with the doubly reduced TCNQ (7,7,8,8-tetracyanoquinodimethane) and a structure similar to the one involved in organic semiconductors.

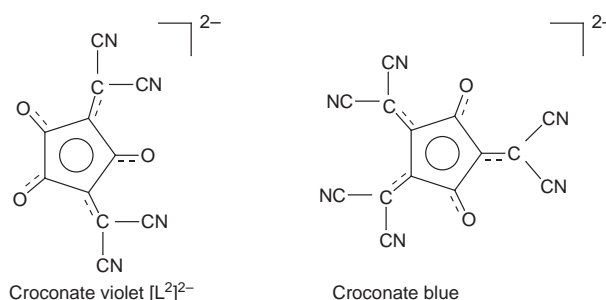

To our knowledge, only two structures of 2-dicyanomethylene-4,5-disulfanylcyclopent-4-ene-1,3-dionate (L^3) with first row transition-metal ions are known to us: $[\text{M}(\text{L}^3)_2]^{2-}$ ($\text{M} = \text{Cu}^{\text{II}}, \text{Pd}^{\text{II}}$),^{22,23} and no report concerning metal complexes with dicyanomethylene derivatives of croconic acid itself has been published so far.

This contribution respectively describes the preparation, redox properties and structural characterizations of cobalt(II) complexes of croconic acid (H_2L^1) and croconate violet (K_2L^2).

Experimental

Reactants and methods

The chemicals and solvents were of reagent grade or Aldrich Electrochemical grade for electrochemistry. Croconic acid

† Pseudo-oxocarbons. Part 2.¹

Table 1 Summary of crystal data, intensity measurements and structure refinement for [CoL¹(H₂O)₃] **1** and K₂[CoL₂(H₂O)₂]**2**·2H₂O **2**

Compound	1	2
Formula	[Co(C ₅ O ₈)(H ₂ O) ₃] _n	[K ₂ Co(C ₁₁ N ₄ O ₃) ₂ (H ₂ O) ₄] _{0.5}
Color	Purple	Red-brown
<i>M</i>	253.0	340.7
Crystal system	Orthorhombic	Monoclinic
Space group	<i>Pbca</i>	<i>P2₁/n</i>
<i>a</i> /Å	11.869(2)	10.4257(7)
<i>b</i> /Å	8.114(2)	10.7946(6)
<i>c</i> /Å	15.393(3)	11.7045(6)
β /°		108.726(3)
<i>U</i> /Å ³	1482.5(2)	1247.5(1)
<i>Z</i>	8	4
<i>D</i> _c /g cm ⁻³	2.267	1.881
<i>A</i> * _{min} , <i>A</i> * _{max}	3.897, 6.277	3.398, 6.585
<i>F</i> (000)	1019	682
μ /mm ⁻¹	2.33	9.075
<i>hkl</i> Ranges	0 to 13, 0 to 9, 0 to 17	-10 to 10, 0 to 11, 0 to 12
<i>T</i> /K	180	200
Scan range, 2θ /°	2.9–48.4	2–110
No. measured reflections	9095	1616
No. independent reflections	1128	1528
No. observed reflections	951 ($[F_o \geq \sigma(F_o)]$)	1315 ($[F_o \geq 4\sigma(F_o)]$)
No. parameters	152	209
Weighting scheme, ω	Chebyshev	$1/[\sigma^2(F_o) + 0.0005(F_o^2)]$
Max. and min. $\Delta F/e \text{ \AA}^{-3}$	1.35, 0.87	0.64, 0.44
Goodness of fit <i>S</i>	1.01	2.35
<i>R</i> , <i>R</i> _w	0.051, 0.064	0.035, 0.040

(H₂L¹), its potassium salt (K₂L¹) and the potassium salt of croconate violet (K₂L²) were prepared according to the procedures described by Fatiadi.^{14,15,24} IR spectra were recorded on a Perkin-Elmer 983 G spectrometer coupled with a Perkin-Elmer infrared data station. Samples were run in the solid state in nujol mulls. UV/VIS spectra were registered on a Roucaire Shimadzu UV-3100 spectrophotometer in DMF at concentrations from 10⁻⁵ to 10⁻⁶ mol L⁻¹. Magnetic susceptibility measurements, in the 4–300 K temperature range were carried out on polycrystalline samples with a Faraday-type magnetometer equipped with a continuous-flow Oxford Instruments cryostat. HgCo(NCS)₄ was used as a calibrant (susceptibility at 20 °C, 16.44 × 10⁻⁶ cm³ mol⁻¹). The molar susceptibilities were corrected for ligand diamagnetism using Pascal's constants.²⁵ The corrections were estimated at -236 × 10⁻⁶ and -270 × 10⁻⁶ cm³ mol⁻¹ for **1** [CoL¹(H₂O)₃] and **2** K₂[CoL₂(H₂O)₂]**2**·2H₂O respectively.

Electrochemical measurements were carried out with a home-made potentiostat or an Autolab (EcoChemie) controlled by a PC at room temperature. The electrochemical cell (10 cm³) was a conventional one with three electrodes: working electrode, Pt (diameter 2 mm, EDI Tacussel) for rotating disc electrode experiments (LSV, linear sweep voltammetry) and Pt (disc diameter 0.5 mm) for cyclic voltammetry experiments (CV); counter electrode, Pt wire; and reference electrode, double junction SCE. The experiments were carried out in DMF-Bu₄NPF₆ 0.1 mol L⁻¹ under an argon atmosphere; DMF and Bu₄NPF₆ were used without further purification. A solution of Bu₄NPF₆ was scanned before use to check the purity of the solvent. The reported *E*₁ values were determined from stationary experiments at a rotating electrode (LSV).

Preparation of a cobalt(II) croconate, [CoL¹(H₂O)₃] **1**

The compound was obtained according to West²⁶ by reaction in the dark of dipotassium croconate (K₂L¹) and CoCl₂·6H₂O in water. The product was recrystallized from water as purple crystals (yield ca. 60%) (Found: C, 23.26; H, 2.22. Calc. for C₅H₆CoO₈: C, 23.73; H, 2.39%).

Preparation of a cobalt(II) croconate violet, K₂[CoL₂(H₂O)₂]**2**·2H₂O **2**

The compound was obtained by reaction of dipotassium

croconate violet (K₂L²) (0.332 g, 1 mmol) in a water-acetonitrile mixture (50:50 cm³) with CoCl₂·6H₂O (0.238 g, 1 mmol) dissolved in water (100 cm³). The addition of the ligand to the metal salt is accompanied by a color change from pink to red. Suitable red-brown crystals were obtained after standing the solution for a few days under slow evaporation, at room temperature (yield ca. 40%) (Found: C, 37.61; H, 1.10; N, 15.92. Calc. for C₂₂H₈CoN₈O₁₀K₂: C, 38.77; H, 1.18; N, 16.44%).

Crystallography

Crystal data, intensity measurements and structure refinement are summarized in Table 1. For **1** unit-cell parameters and diffracted intensities were measured at 180 K with the scan rotation ϕ mode on a STOE-I.P.D.S. (imaging plate diffraction system) diffractometer equipped with an Oxford cryosystems cooler device. The crystal to detector distance was 80 mm. Mo-K α radiation (λ 0.71073 Å) was employed as X-ray source. Numerical absorption corrections were applied to the data.²⁷ The structure was solved by direct methods (SIR 92)²⁸ and refined by least-squares procedures on *F*_o. Hydrogen atoms were located on a difference Fourier map and isotropically refined with an isotropic thermal parameter fixed at 20% higher than those of their connected oxygen atoms. Atomic scattering factors and anomalous dispersion terms are taken from ref. 29. The plot of the molecule together with the labelling scheme are shown in Fig. 1. Selected interatomic distances and angles are listed in Table 2.

For **2** a small crystal was mounted on a glass fiber with RS3000 oil. Graphite monochromatized Cu-K α radiation (λ 1.5418 Å) was employed as X-ray source. Unit-cell parameters and diffracted intensities were measured at 200 K with the scan mode ω - 2θ on a STOE-STADI 4 diffractometer. The structure was solved by direct methods (MULTAN 87)³⁰ and refined by XTAL 3.2 program.³¹ Absorption corrections by analytical integration³² were applied to the data. Atomic scattering factors and anomalous dispersion terms are taken from ref. 28. All H atom co-ordinates were refined using *U*_{iso} 0.05 Å². The plot of the molecule together with the labelling scheme are shown in Fig. 2 and 3. Selected interatomic distances and angles are listed in Table 2.

CCDC reference number 186/1202.

Table 2 Selected interatomic distances (Å) and bond angles (°) with estimated standard deviations in parentheses for **1** and **2**

Complex 1				Complex 2			
Metal environment							
Co–O1	2.103(3)	Co–O6	2.025(3)	Co–O1	2.122(3)	K–O1	2.794(3)
Co–O2	2.152(3)	Co–O7	2.111(3)	Co–O2	2.109(3)	K–N4	2.899(4)
Co–O4	2.103(2)	Co–O8	2.082(3)	Co–O4	2.048(3)	K–O5	2.801(3)
				Co–K	3.7314(9)	K–O3	2.888(3)
						K–O2	2.883(3)
Bond angles							
O1–Co–O2	80.8(1)			O1–Co–O2	82.2(1)		
O2–Co–O4	171.6(1)			O4–Co–O1	90.0(1)		
O1–Co–O4	90.8(1)			O4–Co–O2	89.1(1)		
O2–Co–O6	90.5(1)			K–Co–O1	132.12(8)		
O4–Co–O6	97.9(1)			K–Co–O2	129.74(7)		
O1–Co–O7	92.1(1)			K–Co–O4	94.23(9)		
O2–Co–O7	94.2(1)						
O4–Co–O7	86.0(1)						
O2–Co–O8	92.97(9)						
O4–Co–O8	86.7(1)						
O6–Co–O8	90.5(1)						
O6–Co–O7	90.7(1)						
Ligands							
O1–C1	1.256(5)	C1–C2	1.437(5)	O1–C1	1.265(5)	C2–C3	1.432(6)
O2–C2	1.259(5)	C1–C5	1.453(5)	O2–C2	1.258(5)	C3–C4	1.470(5)
O3–C3	1.237(5)	C2–C3	1.457(5)	O3–C4	1.227(5)	C3–C6	1.377(6)
O4–C4	1.248(4)	C3–C4	1.481(5)	N1–C7	1.143(6)	C4–C5	1.473(6)
O5–C5	1.256(4)	C4–C5	1.466(5)	N2–C8	1.150(6)	C5–C9	1.379(5)
				N3–C10	1.148(6)	C6–C7	1.429(6)
				N4–C11	1.153(6)	C6–C8	1.426(6)
				C1–C2	1.457(5)	C9–C10	1.440(6)

Results and discussion

Chemistry

As already mentioned, the cobalt(II)–croconate complex has been obtained according to West and Niu.²⁶ During their synthesis, they obtained an unidentified pink by-product the analytical data for which fit with the formula of a cobalt–oxalate complex. A few years ago, we reported on the easy photo-oxidation of croconic acid into oxalic and mesoxalic (HO₂CCOCO₂H) acids corresponding to croconic ring breaking.³³ So, we think that the pink oxalate complex may result from the same process. To prevent this oxidation, the synthesis of **1** was performed in the dark.

Since the formula of **2** implies two ligands per metallic ion, we attempted to prepare a croconate complex with two ligands using a large excess of croconate ion. In fact, only the complex ML¹(H₂O)₃ was obtained.

Crystal structure of **1**

Preliminary studies on the structure of copper(II), zinc(II) and manganese(II) croconate reveal that although these compounds are isostructural, they are not strictly isomorphous.^{5,6} The similarity of the powder diffraction patterns indicates that the croconate complexes of divalent metal ions, nickel(II) and cobalt(II) must have the same structure, although the degree of distortion around the metal ion might vary.

Cobalt(II) croconate consists of infinite chains with an asymmetric repeating unit constituted by one metal, one croconate and three water molecules (Fig. 1). The zig-zag chains are parallel to the *c* axis. Consequently, two neighbouring cobalt(II) ions are separated by a croconate ion with a Co...Co distance of 7.9891(3) Å inside a chain. The close packing involved hydrogen bonds inducing a Co...Co inter-chain distance of 5.0035(6) Å. Each cobalt(II) is co-ordinated to three water molecules, two adjacent oxygen atoms of one croconate ring acting as a chelating ligand (O1 and O2) and a single oxygen (O4) of a second croconate ring. The difference observed between Co–O1 (2.103(3) Å) and Co–O2 (2.152(3) Å)

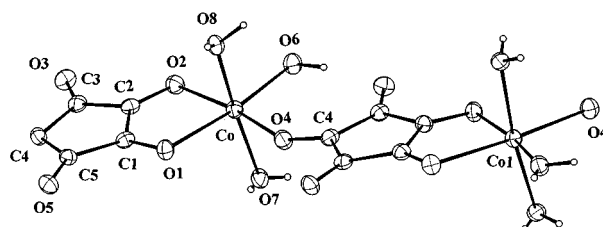


Fig. 1 Crystal structure of the complex [CoL¹(H₂O)₃]_n.

distances confirms the intrinsic tendency of croconate to coordinate as an asymmetric bidentate ligand already reflected in the structure of the copper complex; in contrast Co–O4 and Co–O1 distances are comparable. Two of the five oxygen atoms of the croconate ring (O3 and O5) are not metal-co-ordinated. There is no significant difference between the Co–carbonyl and Co–OH₂ bond distances. Analogously, in the croconate ligand, the C–O bond distances for the free or the co-ordinated oxygen atoms are comparable. The average metal–oxygen distance for the cobalt(II) compound is 2.096 Å and the bond anisotropy is much smaller than in the copper(II) complex. The interchain interactions *via* strong hydrogen bonding are analogous to those evidenced for the isostructural metal(II) complexes already described.



Crystal structure of **2**

The structure is made of discrete dianionic mononuclear and symmetrical entities of [CoL²₂(H₂O)₂]²⁻ and potassium ions. A plot of the [CoL²₂(H₂O)₂]²⁻ in the structure is presented in Fig. 2. The cobalt atom sits on the inversion centre. It is surrounded by four oxygen atoms of two croconate violet ligands and two water molecules. It is located at the centre of the plane defined by the five ring carbon atoms, the two exocyclic olefinic carbon atoms, and the three oxygen atoms of each ligand. As expected for a cobalt(II) complex, we can observe a tetragonally distorted octahedral geometry with two bond lengths (Co–water) shorter than the four others. Moreover, as underlined in

Table 3 Hydrogen bonds for complex **2**

Donor–H	Donor...Acceptor	H...Acceptor	Donor–H...Acceptor
O4–H42 0.74(5)	O4...O5 (0) 2.769(5)	H42...O5 (0) 2.04(5)	O4–H42...O5 (0) 169(5)
O4–H41 0.81(5)	O4...N3 (1) 2.866(5)	H41...N3 (1) 2.07(5)	O4–H41...N3 (1) 167(4)
O4–H42 0.74(5)	O4...O2 (2) 2.916(4)	H42...O2 (2) 2.76(5)	O4–H42...O2 (2) 94(4)
O5–H51 0.79(5)	O5...N2 (3) 2.863(6)	H51...N2 (3) 2.18(5)	O5–H51...N2 (3) 144(4)
O5–H52 0.75(5)	O5...O3 (4) 2.813(5)	H52...O3 (4) 2.31(5)	O5–H52...O3 (4) 126(4)

Equivalent positions: (0) x, y, z ; (1) $3/2 - x, y - 1/2, 1/2 - z$; (2) $1 - x, 1 - y, 1 - z$; (3) $3/2 - x, 1/2 + y, 1/2 - z$; (4) $1 - x, y, z$.

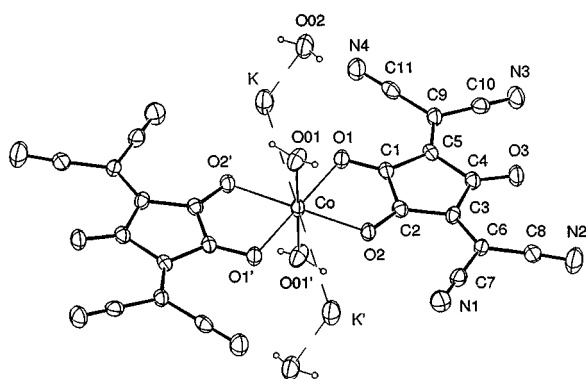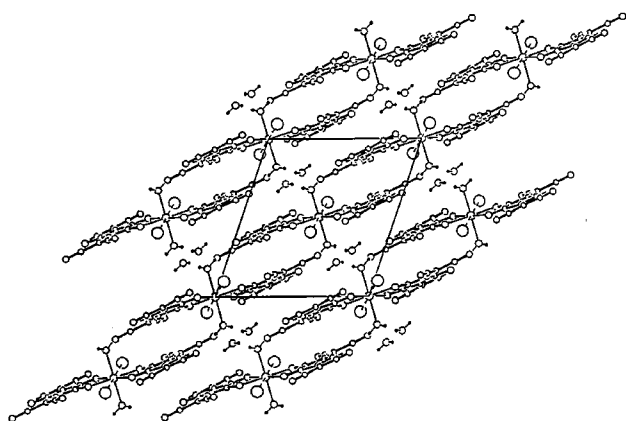**Fig. 2** Crystal structure of the complex $K_2[CoL_2(H_2O)_2] \cdot 2H_2O$.**Fig. 3** View of the packing in $K_2[CoL_2(H_2O)_2] \cdot 2H_2O$ in the ac plane.

the description of the structure of **1**, the croconate ligand coordinates in an asymmetrical bidentate fashion: in particular, the two Co–O bond distances being 2.122(3) and 2.109(3) Å. The ligand is not strictly planar: the three oxygen atoms and the two methylene carbon atoms lie in the plane of the ring, whereas the two dicyanomethylene groups are rotated, in the same direction, away from the plane of the ring with 4.7° and 5.2° angles. A similar twist of the dicyanomethylene groups out of the ring plane has been observed in the free ligand¹⁶ and in TCNQ.^{34,35} In the free ligand,¹⁶ the mean C–C bond length is 1.450 Å lying between 1.437(7) Å (C2–C3) and 1.472(9) Å (C1–C2); in the complex, the mean distance of 1.453 Å is comparable. The carbon ring is not affected by complexation and the values obtained for the C–C bond distances agree with those calculated for the ideal planar geometry. As expected for a delocalized ring, the three C–O bond lengths are identical in the free ligand (average value 1.244 Å) but the complexation

induces a partial localization of the π electrons. This assumption is supported by “the ketonic” bond length of the uncoordinated oxygen atom (1.227(5) Å) compared to the longer C–O bond distances of the oxygen atoms co-ordinated to the cobalt (average value 1.27 Å). It may be underlined that this difference is not evidenced in **1**. Of particular interest are the strong intermolecular hydrogen bonds, Table 3. These involve water molecules and the croconate oxygen O3 which do not participate in complexation evidenced by the O...O distance of 2.813(5) Å and also the nitrogen atoms of the cyano groups. All the oxygen atoms of the ligands are co-ordinated to a potassium atom which is also linked to the crystallisation water molecule.

The sites of co-ordination of either the oxygen or nitrogen of dicyanomethylene groups may be related to a number of parameters: the charge distribution on the oxygen and nitrogen atoms, the soft or hard character of the metal, the geometry of the ligand. In the dicyanomethylene trionate complex **2** the co-ordination occurs only *via* the oxygen atoms. However, we have recently isolated Cu(I) and Cu(II) complexes involving dicyanomethylene pseudo-oxocarbons derived from squaric acid.¹ In these complexes, metal atoms are always co-ordinated by the nitrogen atoms of the dicyanomethylene groups.

IR and electronic spectroscopies

In **1**, the most relevant IR features are those associated with the chelating croconate. Our spectra are in agreement with the West and Niu analysis.²⁶ A broad and intense absorption in the 3400–3000 cm^{-1} range is attributed to the OH stretching frequency of the water molecules. Bands at 1740 and 1724 cm^{-1} are assigned to the unco-ordinated carbonyl groups which exhibit a strong double-bond character. The co-ordinated CO groups are characterized by medium absorptions at 1682 and 1660 cm^{-1} . A very strong and broad peak centered at 1500 cm^{-1} is attributed to vibrational modes representing mixtures of C–O and C–C stretching motions. This absorption is characteristic of the salts of $C_nO_n^{2-}$ ions.³⁶

The vibrational spectrum of croconate violet has been analyzed by Fatiadi.^{13–17} It shows a band at 2198 cm^{-1} attributed to $\nu(CN)$ stretching frequencies. In **2**, this vibration, observed at 2208 cm^{-1} , is slightly shifted and confirms that the nitrile groups are not engaged in the complexation with Co. Moreover, the band at 1674 cm^{-1} in the free ligand, attributed by Fatiadi to the carbonyl groups, completely disappears in the cobalt complex, even though one of the ring carbonyl groups remains free and is not implicated in the co-ordination. In the group of bands at 1615, 1572 and 1521 cm^{-1} the problem of the vibrational assignments appeared as difficult due to the strong coupling of the C=O oscillators and to the C=O and C=C coupling. In the complex these bands are not significantly

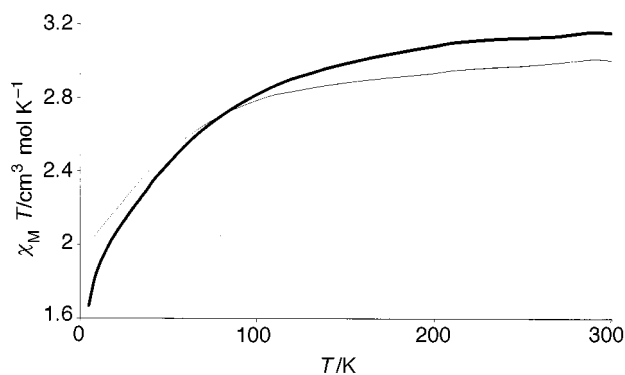


Fig. 4 Temperature dependence of $\chi_M T$ for $[\text{CoL}^1(\text{H}_2\text{O})_3]_n$ (—) and $\text{K}_2[\text{CoL}^2(\text{H}_2\text{O})_2] \cdot 2\text{H}_2\text{O}$ (---).

shifted by complexation and remain practically unchanged (1609, 1562 and 1515 cm^{-1}).

Owing to their strong absorption in the visible spectrum, the croconate dyes have been investigated for their photophysical properties.³⁷ In DMF, croconate ion is yellow and displays a characteristic absorption at 334 nm ($\epsilon = 24000 \text{ L mol}^{-1} \text{ cm}^{-1}$) and croconate violet is a dye characterized by a strong absorption in the visible spectrum at 534 nm ($\epsilon = 88000 \text{ L mol}^{-1} \text{ cm}^{-1}$). As concerns the cobalt complexes, high-spin six-co-ordinated octahedral or pseudo-octahedral cobalt(II) species will exhibit three allowed transitions.³⁸ However, ν^1 corresponding to the ${}^4\text{T}_{1g} \rightarrow {}^4\text{T}_{2g}$ transition was not observed within the wavelength sweep from UV to near IR. The other transitions are hidden by the absorption bands of the ligands. The UV/VIS spectra of the cobalt complexes present the same pattern as the ligands (complex **1**, 328 nm ($\epsilon = 21500 \text{ L mol}^{-1} \text{ cm}^{-1}$) and complex **2**, 532 nm ($\epsilon = 66000 \text{ L mol}^{-1} \text{ cm}^{-1}$)).

Magnetic properties

Most six-co-ordinated cobalt(II) complexes fall into two classes: those with magnetic moments which lie in the range 4.8–5.6 μ_B and are referred to as “high-spin” and those with moments in the range 1.73–2.0 μ_B which are referred to as “low-spin”. However, there has been found between these two classes a number of six-co-ordinated cobalt(II) compounds which have intermediate magnetic moments at room or lower temperatures. These thermally induced spin conversions $S = 3/2 \leftrightarrow S = 1/2$ were generally found to be gradual, often extending over more than 100 K.^{39–41}

The ground state of the free Co(II) ion is ${}^4\text{F}$, but the orbital degeneracy is removed in an octahedral crystal field giving one ${}^4\text{A}$ and two ${}^4\text{T}$ levels with the lowest-lying state being ${}^4\text{T}_{1g}$.³⁸ The temperature dependence of the product $\chi_M T$ (χ_M denoting the molar magnetic susceptibility) for the complexes **1** and **2** is plotted in Fig. 4. The $\chi_M T$ values ($\chi_M T = 3.006 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$, $\mu_{\text{eff}} = 4.90 \mu_B$) obtained at 300 K for **2** with a continuous decrease upon cooling are typical of cobalt(II) high-spin species. At 4 K, the μ_{eff} for **2** lies in the range expected for high-spin cobalt(II) ($\mu_{\text{eff}} = 4.00 \mu_B$). In light of crystallographic measurements, it is clear that there is a distortion from octahedral symmetry in **2**. However, the poor distortion value (0.05 Å) indicates that only the spin–orbit coupling has to be taken into account and that Jahn–Teller stabilization is small as expected.⁴²

Recent reports on magnetic studies of some chain and layered six-co-ordinated cobalt(II) compounds show⁴³ that, at low temperature, these magnetic systems behave as collections of Ising chain $S = 1/2$ effective spins coupled usually by ferromagnetic^{44–46} but also antiferromagnetic interactions.⁴⁷ For such species, the degeneracy of the ${}^4\text{T}_{1g}$ ground triplet is removed by the combined action of spin–orbit coupling and axial or rhombic distortions of the crystal field, giving six Kramers doublets with an effective nonisotropic $S = 1/2$ ground state.



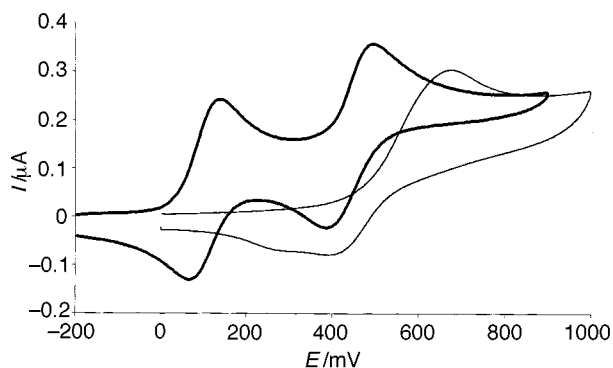


Fig. 5 Cyclic voltammograms at a Pt disc electrode (diameter 0.5 mm) in DMF– Bu_4NPF_6 0.1 mol L^{-1} : $[\text{PPh}_4]_2\text{C}_5\text{O}_5$, 1.2 mmol L^{-1} (—); complex **1**, 1 mmol L^{-1} (---); potential scan speed 0.1 V s^{-1} , potentials are measured versus SCE.

For complex **1**, $\chi_M T = 3.15 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$ ($\mu_{\text{eff}} = 5.02 \mu_B$) at 300 K and $1.67 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$ ($\mu_{\text{eff}} = 3.65 \mu_B$) at 4 K. This last value is lower than the spin-only value for a high-spin cobalt(II) complex but far from the value generally observed at low temperature for a Ising $S = 1/2$ chain ($\mu_{\text{eff}} = 2.0 \mu_B$). A possible interpretation of our experimental results requires that a proportion of cobalt(II) is in the low-spin form at low temperature. Another interpretation is to involve exchange antiferromagnetic interactions between the paramagnetic centres. Magnetic properties of isostructural croconate complexes have been investigated in the past few years and magnetic exchanges have been evidenced.^{6,7} For manganese(II) croconate complexes two studies have been performed. In the first, in our own work,⁸ we suggested that spin–spin interactions are likely to occur between manganese ions of neighbouring chains. In the second, Gatteschi *et al.*⁷ neglects interchain interactions favouring a weak antiferromagnetic coupling between the spins *via* the croconate ligand ($J = 0.22 \text{ cm}^{-1}$). However, it may be underlined that some values, slightly lower than the spin-only value, have been observed in mononuclear complexes which do not exhibit any spin transition, deviations at the spin-only value being accounted for by axial distortion of the cobalt(II) octahedral environment.^{38,41}


Redox properties

Complex 1. In organic solvents, the electrochemical oxidation of the croconate dianion is well known.^{18,33} Under non-stationary conditions at a Pt electrode, the voltammogram shows two oxidation waves (Fig. 5) which appear mono-electronic and reversible. The oxidation process is expressed by two successive electron transfers with a high electron transfer rate:



The orange radical anion $\text{C}_5\text{O}_5^{\cdot -}$ is very stable (few hours). Its potential domain ($E_2^{\cdot} - E_1^{\cdot}$) depends on the solvent: 0.53 V in CH_3CN and 0.34 V in DMF. The radical anion $\text{C}_5\text{O}_5^{\cdot -}$ is less stable in DMF than in CH_3CN .

Moreover, a reduction process is observed around -1.9 V . Under slow potential scan speed the process is irreversible and the peak current is twice that of the oxidation peak. By increasing the potential scan speed at a 50 μm Pt electrode, the reduction process appeared reversible (in the range 100 V s^{-1} up to 2500 V s^{-1}). Taking into account the results, the reduction process may be expressed by:



In the electroactivity domain of DMF, the cyclic voltammogram of **1** is restricted to an oxidation process (Fig. 5). At a



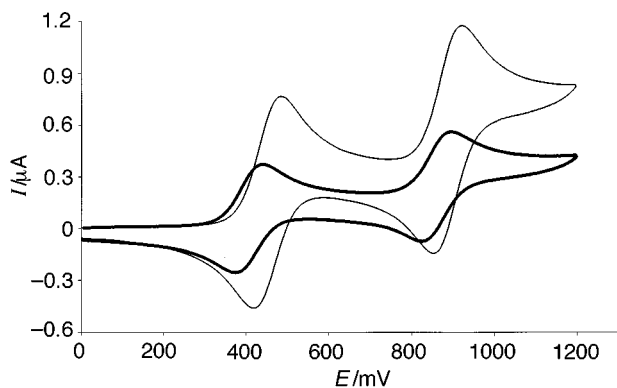


Fig. 6 Cyclic voltammograms at a Pt disc electrode (diameter 0.5 mm) in DMF–Bu₄NPF₆ 0.1 mol L⁻¹; K₂L² 1 mmol L⁻¹; (—); complex **2** 1 mmol L⁻¹ (---); potential scan speed 0.1 V s⁻¹, potentials are measured *versus* SCE.



rotating disc electrode, two nearly equal waves were observed with $E_1^1 = 0.62$ V and $E_2^1 = 0.83$ V. The pattern of the cyclic voltammogram (Fig. 5) shows that the process is complex. According to the variations of the voltammograms as a function of the potential scan speed, the process may be classified as a bielectronic process with close potentials. In fact, this electrochemical process matches the oxidation of the C₅O₅²⁻ ligand. In Fig. 5, the mean oxidation peak current of **1** is nearly the sum of the oxidation peak currents of free C₅O₅²⁻. Owing to complexation, the potentials E_1^1 and E_2^1 are shifted towards anodic potentials and get close together:




Simulation curves with the Gosser program⁴⁸ gave an approximation of the electrooxidation mechanism. It can be assumed to be two electron transfers with slow electron transfer rates which are coupled to chemical reactions such as the decomplexation of the radical complex. As a consequence, the potential domain of the radical anion C₅O₅^{·-} is reduced and the bound C₅O₅^{·-} is unstable. Such a case was already observed in the study of platinum complexes with squarate and croconate dianions: the electrochemical measurements did not show the radical anion step.⁴⁹ According to the potential displacement as a function of complexation,⁵⁰ the positive shift of the redox potentials of C₅O₅²⁻ shows that the complex formation constants of the C₅O₅^{·-} radical anion and the neutral C₅O₅ are lower than the one of the C₅O₅²⁻ dianion.

In the cathodic domain, the reduction of the C₅O₅²⁻ dianion in the complex was not observed. This is in agreement with the decrease of the co-ordination properties of the C₅O₅²⁻ dianion upon oxidation or reduction.

Complex 2. The electrochemical oxidation of croconate violet ([L²]²⁻) has already been reported.¹⁸ Under non stationary conditions at a Pt electrode, the voltammogram shows two oxidation waves (Fig. 6) that appear mono-electronic and reversible. The oxidation process is expressed by the two successive electron transfers with high electron transfer rate:





Moreover, a mono-electronic reduction process is observed at $E_1^2 = -1.49$ V which also appears reversible (quasi reversible in CH₃CN, $E_1^2 = -1.53$ V):



The radical anion [L²]^{·-} is very stable. Its potential domain ($E_2^1 - E_1^1$) depends on the solvent: 0.66 V in CH₃CN and 0.45 V in DMF. The radical anion [L²]^{·-} is less stable in DMF than in CH₃CN. On the contrary, the radical trianion [L²]^{· 3-} is only stable over the time scale of the cyclic voltammetry. By comparison of the voltammograms of the C₅O₅²⁻ dianion (Fig. 5) and the [L²]²⁻ dianion (Fig. 6), it is observed that the dicyanomethylene groups shift the redox potentials towards anodic potentials.

In the electroactivity domain of DMF, the cyclic voltammogram of **2** presents the same oxidation process as the free ligand (Fig. 6). The reduction process of the ligand is not present in the complex. The electrochemical study was restricted to the oxidation processes. Under stationary conditions, at a Pt disc electrode (Fig. 6), the voltammogram of the complex presents two oxidation waves: a first oxidation wave with $E_1^1 = 0.45$ V and a second one with $E_2^1 = 0.93$ V. These values match the potentials of the free ligand oxidation (0.45 V and 0.90 V). Furthermore, the comparison between the peak current intensities in Fig. 6 shows that while the free ligand oxidation proceeds through two successive mono-electronic transfers, the oxidation of **2** proceeds through two bielectronic transfers (the oxidation of the two [L²]²⁻ ligands). Taking into account the Randles–Sevcik equation in which the peak current is related to $n^{3/2}$, number of transferred electrons, it appears that the oxidations of the two [L²]²⁻ ligands are independent. This may be expressed by:



According to the potential displacement as a function of complexation⁵⁰ and taking into account the disappearance of the reduction peak of the free ligand ($E_1^1 = -1.49$ V) on the voltammogram of **2**, it can be postulated that the complex is not dissociated in DMF. This was confirmed by conductimetric measurements. Furthermore, the invariability of the redox potentials of the oxidations shows that the formation constants of Co(II) with [L²]²⁻, [L²]^{·-} or L² species are of the same order of magnitude. This is in favour of the contribution of the dicyanomethylene groups in the stabilization of the charge. In particular, the radical would be localized on the dicyanomethylene group as in the 3,4-bis(dicyanomethylene)cyclobutane-1,2-dione radical anion.⁵¹

Finally, the electrochemical behaviour at a Pt electrode of complexes **1** and **2** is limited to the oxidation of the ligands. No reduction or oxidation of Co(II) was observed. The disappearance of the electrochemical reduction of the ligands in the complexes confirmed their complexation in solution. Moreover, the electrochemical behaviours of complexes **1** and **2** are quite different. In complex **2**, the oxidation process corresponds to the oxidation of two independent [L²]²⁻ ligands while in complex **1** the oxidation of the C₅O₅²⁻ dianions is perturbed by Co(II) complexation. If the introduction of dicyanomethylene groups shifts the oxidation potentials towards anodic potentials, it also increases the potential domain of the radical (0.34 V to 0.45 V in the free ligands and 0.21 V to 0.48 V in the complexes). The positive shift of the oxidation potentials is in agreement with the polarographic data of quinones and dicyanomethylene substituted quinones.⁵² But in this latter case the potential domain of the “semiquinone” radical is decreased. However, this radical stabilization is encouraging for the synthesis and characterization of metal–radical ligand complexes.

Acknowledgements

We gratefully acknowledge A. Mari, Laboratoire de Chimie de Coordination du CNRS, Toulouse, for technical assistance with magnetic measurements.

References

- 1 Part 1. C. Pena, A. M. Galibert, B. Soula, P. L. Fabre, G. Bernardinelli and P. Castan, *J. Chem. Soc., Dalton Trans.*, 1998, 239.
- 2 L. Gmelin, *Ann. Phys. (Leipzig)*, 1825, 431.
- 3 L. Gmelin, *Justus Liebigs Ann. Chem.*, 1841, **37**, 58.
- 4 S. Cohen, J. R. Lacher and J. D. Park, *J. Am. Chem. Soc.*, 1959, **81**, 3480.
- 5 M. D. Glick, G. L. Downs and L. F. Dahl, *Inorg. Chem.*, 1964, **3**, 1712.
- 6 M. D. Glick and L. F. Dahl, *Inorg. Chem.*, 1966, **5**, 289.
- 7 A. Cornia, A. C. Fabretti, A. Giusti, F. Ferraro and D. Gatteschi, *Inorg. Chim. Acta*, 1993, **212**, 87.
- 8 D. Deguenon, G. Bernardinelli, J. P. Tuchagues and P. Castan, *Inorg. Chem.*, 1990, 3031.
- 9 P. Castan, D. Deguenon and F. Dahan, *Acta Crystallogr., Sect. A*, 1991, **47**, 2656.
- 10 I. Castro, J. Sletten, J. Faus and M. Julve, *J. Chem. Soc., Dalton Trans.*, 1992, 2271.
- 11 I. Castro, J. Sletten, J. Faus, M. Julve, Y. Journaux, F. Lloret and S. Alvarez, *Inorg. Chem.*, 1992, **31**, 1889.
- 12 R. West, *Oxocarbons*, Academic Press, New York, 1980.
- 13 A. J. Fatiadi, *J. Am. Chem. Soc.*, 1978, **100**, 2586.
- 14 A. J. Fatiadi, *Synthesis*, 1978, **3**, 165.
- 15 A. J. Fatiadi, *J. Org. Chem.*, 1980, **45**, 1338.
- 16 V. L. Himes, A. D. Mighell, C. R. Hubbard and A. Fatiadi, *J. Res. Natl. Bur. Stand. (US)*, 1980, **85**, 87.
- 17 A. J. Fatiadi, *Oxocarbons*, Academic Press, New York, 1980.
- 18 L. M. Doane and A. J. Fatiadi, *J. Electroanal. Chem. Interfacial Electrochem.*, 1982, **135**, 193.
- 19 P. V. Kamat and M. A. Fox, *J. Electroanal. Chem. Interfacial Electrochem.*, 1983, **159**, 49.
- 20 P. V. Kamat and M. A. Fox, *Chem. Phys. Lett.*, 1982, **92**, 595.
- 21 P. V. Kamat, M. A. Fox and A. J. Fatiadi, *J. Am. Chem. Soc.*, 1984, **106**, 1191.
- 22 N. Venkatalakshmi, B. Varghese, S. Lalitha, R. F. X. Williams and P. T. Manoharan, *J. Am. Chem. Soc.*, 1989, **111**, 5748.
- 23 W. B. Heuer and W. H. Pearson, *J. Chem. Soc., Dalton Trans.*, 1996, 3507.
- 24 A. Fatiadi, H. S. Isbell and W. F. Sager, *J. Res. Natl. Bur. Stand., Sect. A*, 1963, **67**, 153.
- 25 P. W. Selwood, *Magnetochemistry*, Interscience, New York, 1956.
- 26 R. West and H. Y. Niu, *J. Am. Chem. Soc.*, 1963, **85**, 2586.
- 27 X-Shape, a program for numerical Absorption correction (version 1.01), STOE and Cie, GMBH, Darmstadt, Germany, 1996.
- 28 A. Altomare, G. Carasciano, G. Giacovazzo, A. Guagliardi, M. C. Burla, G. Polidori and M. Camalli, *J. Appl. Crystallogr.*, 1994, **27**, 435.
- 29 *International Tables for X-Ray Crystallography*, Kynoch Press, Birmingham, 1974, vol.4.
- 30 P. Main, S. J. Fiske, S. E. Hull, L. Lessinger, G. Germain, J. P. Declercq and M. M. Woolfson, *MULTAN 87*, A system of Computer Programs for the Automatic Solution of Crystal Structures from X-Ray Diffraction Data, Universities of York and Louvain-la-Neuve, 1987.
- 31 S. R. Hall and J. M. Steward (Editors), *XTAL3.2 Users Manual*, Universities of Western Australia and Maryland, 1992.
- 32 E. Blanc, D. Schwaezenbach and H. D. Flack, *J. Appl. Crystallogr.*, 1991, **24**, 1035.
- 33 P. L. Fabre, P. Castan, D. Deguenon and N. Paillous, *Can. J. Chem.*, 1995, **73**, 129.
- 34 T. J. Kistenmacher, T. E. Phillipps, D. O. Cowan, J. P. Ferraris, A. N. Bloch and T. O. Poehler, *Acta Crystallogr., Sect. B*, 1976, **32**, 539.
- 35 T. J. Kistenmacher, T. E. Phillipps and D. O. Cowan, *Acta Crystallogr., Sect. B*, 1974, **30**, 763.
- 36 M. Ito and R. West, *J. Am. Chem. Soc.*, 1963, **85**, 2580.
- 37 P. V. Kamat and M. A. Fox, *J. Photochem.*, 1984, **24**, 285.
- 38 L. Banci, A. Bencini, C. Benelli, D. Gatteschi and C. Zanchini, *Struct. Bonding (Berlin)*, 1982, **52**, 37.
- 39 J. Zarenbowitch, R. Claude and O. Kahn, *Inorg. Chem.*, 1985, **24**, 1576.
- 40 J. Zarenbowitch, R. Claude and P. Thuery, *New J. Chem.*, 1985, **9**, 467.
- 41 J. Zarenbowitch and O. Kahn, *Inorg. Chem.*, 1984, **23**, 589 and refs. therein.
- 42 F. S. Ham, *Phys. Rev.*, 1965, **138**, 1727.
- 43 W. E. Hatfield, W. E. Estes, W. E. Marsh, M. W. Pickens, L. W. Ter Haar and R. R. Weller, in *Extended Linear Chain Compounds*, ed. J. S. Miller, Plenum Press, New York and London, vol. 3, p. 43.
- 44 S. Angelov, M. Drillon, E. Zhecheva, R. Stoyanova, M. Belaiche, A. Derory and A. Herr, *Inorg. Chem.*, 1992, **31**, 1514.
- 45 W. Zhang, C. P. Landee, M. M. Turnbull and R. D. Willett, *J. Appl. Phys.*, 1993, **73**, 5379.
- 46 W. Zhang, J. R. Jeitler, M. M. Turnbull, C. P. Landee, M. Wei and R. D. Willett, *Inorg. Chim. Acta*, 1997, **256**, 183.
- 47 G. De Munno, T. Poerio, M. Julve, F. Lloret and G. Viau, *New J. Chem.*, 1998, 299.
- 48 D. K. Gosser, *Cyclic Voltammetry Simulation and Analysis of Reaction Mechanisms*, VCH, New York, 1993.
- 49 P. Castan, D. Deguenon, P. L. Fabre and G. Bernardinelli, *Polyhedron*, 1992, **11**, 901.
- 50 B. Trémillon, *Electrochimie analytique et réactions en solution*, Masson, Paris, vol. 2, 1993.
- 51 G. Farnia, B. Lunelli, F. Marcuzzi and G. Sandona, *J. Electroanal. Chem. Interfacial Electrochem.*, 1996, **404**, 261.
- 52 K. Wallenfels, K. Friedrich, J. Rieser, W. Ertel and H. K. Thieme, *Angew. Chem., Int. Ed. Engl.*, 1976, **15**, 261.

Paper 8/07687A