Design and synthesis of flavin-conjugated peptides and assembly on a gold electrode



Seiji Sakamoto,^{†,}^a Haruhiko Aoyagi,^a Naotoshi Nakashima^a and Hisakazu Mihara^{*,b}

^a Department of Applied Chemistry, Faculty of Engineering, Nagasaki University, Nagasaki 852, Japan

^b Department of Bioengineering, Faculty of Bioscience and Biotechnology, Tokyo Institute of Technology, Midori-ku, Yokohama 226, Japan

Flavin-conjugated peptides composed of one or two amphiphilic α -helix segments have been designed and synthesized. 7-Acetyl-10-methylisoalloxazine (Fla) as a model flavin has been introduced on the side chain of Cys at the 6th, 7th or 8th position of each α -helical 14-peptide. A CD study in aqueous solution revealed that the position of Fla on the peptide strongly influenced the peptide secondary structure. Additionally, CD spectra indicated that the Fla in the peptides was oriented in a different manner depending on the position when the peptide took on the α -helix structure. Furthermore, the flavin-conjugated peptides have been adsorbed on a gold surface through the sulfide linkage, as a basic study for peptidyl devices in the future. By the use of Fla as an electrochemical probe, we examined properties of the peptide assembled on the gold electrode. The cyclic voltammetry measurements revealed that the functional group, Fla, was redox-active on the electrode and the peptide bound on the surface in a monolayer. Moreover, the flavin-conjugated peptide could mediate the electron transfer from the electrode to Fe(CN)₆³⁻ ion or cytochrome c in a vector manner. The redox-active probe, Fla, has been demonstrated to provide significant information about the assembly and function of the α -helix peptides on the gold electrode surface by electrochemical measurements.

The high selectivity and efficiency of natural proteins arise from their regulation of the positions of functional groups and chromophores in the defined 3D structure. Along with this aspect, much attention has been focused on the organization of functionalities in the 3D structure by *de novo* design methods. Considerable efforts in the design of artificial proteins have been devoted to the construction of the 3D structures of polypeptides¹⁻⁵ and the introduction of functional chromophores.⁶⁻¹¹ For example, DeGrado, Dutton and coworkers reported the design and synthesis of artificial polypeptides which have iron protoporphyrin IX in a 4 α -helix bundle structure.⁸ We also demonstrated that the organization of oriented functionalized chromophores, such as pyrene,⁹ quinone, viologen, ruthenium trisbipyridine complex,^{10 α} flavin and porphyrins,^{10b d} could be accomplished by the use of designed peptide scaffolds.

On the other hand, in order to use functionalized artificial polypeptides as chemical sensors and electronic devices, methods will be required for the assembly of peptides with regulated orientation on material surfaces such as metal electrodes. Several rational methods for the alignment of organic compounds, such as Langmuir-Blodgett (LB) films and selfassembled monolayers (SAMs), have been investigated and utilized for the surface design. In particular, SAMs utilizing the high affinity of a thiol group for gold or silver, have some advantages such as stability and simplicity of preparation. Additionally, SAMs can control the orientation of molecular units. By the use of these properties, several SAMs of functionalized molecules such as resorcin[4]arene,¹² cyclodextrin,¹³ DNA,¹⁴ porphyrin¹⁵ and other photo-active molecules¹⁶ were constructed on a gold surface and investigated for the design of chemical and electrochemical sensors. However, so far, there

are only a few examples of studies of peptide assembly on a gold surface.¹⁷ Recently, Whitesell and Chang demonstrated the construction of an oriented α -helical peptide monolayer of polyalanine and polyphenylalanine on a gold surface through the S-Au bond.^{17a} In their report, they investigated the secondary structure, orientation and thickness of the assembly of the peptide on a gold surface by Fourier transform infrared (FT-IR) techniques. However, because the peptide layer was built by the polymerization of *N*-carboxyanhydrides of amino acids, this method is not generally applicable for the *de novo* designed polypeptides which have designed amino acid sequences, 3D structures and functionalized chromophores. Thus, development of a method for constructing the assembly of functional polypeptides is required for peptidyl devices in future.

As a basic study for the assembly of a functionalized polypeptide, we attempted the adsorption of a designed α -helical peptide through a sulfide linkage on a gold electrode surface. To examine the properties of the peptide fixed on the gold surface by a conventional electrochemical method, we introduced a functionalized chromophore, 7-acetyl-10-methylisoalloxazine (Fla)^{10d.18} as a model flavin, into an α -helix segment. It is known that flavin itself is redox-active on an electrode. although many biological molecules are redox-inactive. So far, direct immobilization of flavin on an electrode by physical 19-21 and chemical adsorption methods^{22,23} and by an LB method²⁴ has been extensively studied. Thus, we utilized a flavin as an electrochemical probe to examine the properties of peptides bound on a gold electrode surface. In the present study, we designed and synthesized flavin-conjugated peptides composed of one or two amphiphilic α -helix segments (Fig. 1). The flavinconjugated peptides were adsorbed on a gold electrode surface through a sulfide linkage. By the use of cyclic voltammetry techniques, we examined the packing mode, the occupied area and other electrochemical properties of the peptides assembled on the electrode surface.

[†] Present address: Department of Bioengineering, Faculty of Bioscience and Biotechnology, Tokyo Institute of Technology, Midori-ku, Yokohama 226, Japan.

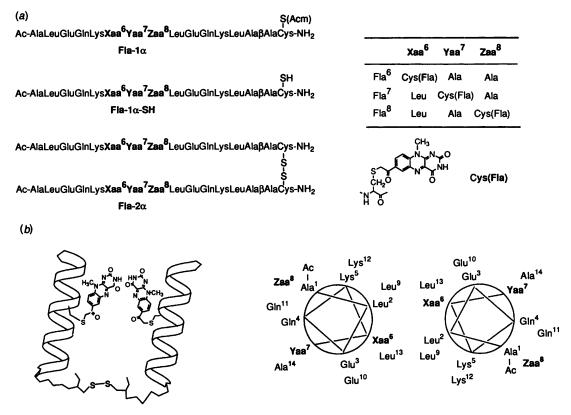


Fig. 1 Structure of the flavin-conjugated peptides. Fla-1 α , Fla-1 α -SH and Fla-2 α . (a) Amino acid sequence of the Fla-1 α , Fla-1 α -SH and Fla-2 α and structure of Cys(Fla). (b) Illustration of two- α -helix peptide structures and helix wheel drawings of the two 14-peptides in coiled-coil form.

Results and discussion

Design and synthesis

The 14-peptide was designed to take an amphiphilic α -helical structure employing Ala, Gln, Glu, Leu and Lys residues which tend to form an α -helix (Fig. 1). The Leu residues were deployed on the α -helix segment in the same manner as hydrophobic amino acids in coiled-coil proteins to define the packing mode between the two α -helix segments.²⁵ Coiled-coil sequences in proteins consist of heptad repeats containing two characteristic hydrophobic positions, *i.e.* $(-a-b-c-d-e-f-g-)_n$ in which the a and d residues are hydrophobic ones such as Leu. The 14peptide consists of two repeats of the sequence c-d-e-f-g-a-b where the a and d residues are Leu, f is hydrophilic Gln, b and c are Ala, e is Glu and g is Lys. The Glu of e and Lys of g positions were arranged to be able to form salt bridges between the two α -helix segments. To increase the stability of the α -helix structure, the N-terminal amino and C-terminal carboxy group were acetylated and amidated, respectively. Though the 14peptide is not long enough to form a coiled-coil structure, 14 residues in length would be sufficient to stabilize an α -helix structure (four turns in the α -helix at the maximum).^{9a} To construct a parallel two α -helix structure, the two segments were dimerized by the disulfide linkage of Cys¹⁶ residues with a flexible spacer of β -Ala. To evaluate the differences of α -helicity depending on the positions of flavin on the peptide scaffold, Fla was introduced on the side chain of Cys at the 6th, 7th or 8th position in each peptide instead of Leu or Ala. When the peptides take an α -helix structure, each Fla should exist under different environments on the amphiphilic α -helical structure. That is, it is expected that Fla in the Fla⁶-1a is on the hydrophobic face of the amphiphilic α -helix. On the other hand, Fla in the Fla⁷- and Fla⁸-1 α are on the hydrophilic face.

The peptide synthesis was carried out manually by solidphase synthesis using an Fmoc-strategy (Fmoc, 9fluorenylmethyloxycarbonyl).²⁶ The acetyl 16-peptides were synthesized by stepwise elongation of Fmoc-amino acids on the

4-(2',4'-dimethoxyphenylaminomethyl)phenoxy resin (NH-SAL resin)²⁷ with different protecting groups on Cys [Cys at the 6th, 7th or 8th position was protected with the trityl (Trt) group and Cys at the 16th position was protected with the acetamidomethyl (Acm) group]. Removal of the protecting groups except for the Acm group and cleavage from the resin were carried out with trifluoroacetic acid (TFA). After HPLC purification of each acetyl 16-peptide, 7a-bromoacetyl-10methylisoalloxazine was reacted with the Cys⁶, Cys⁷ or Cys⁸ side chain of the partially protected [Cys(Acm)¹⁶] peptides.^{104,18} The flavin-conjugated 16-peptides (Fla⁶-1a, Fla⁷-1a and Fla⁸-1a) were purified by gel filtration to remove unreacted or hydrolysed flavin derivatives. Fla-1a-peptides were treated with AgBF₄ in the presence of anisole as a scavenger to remove the Acm protecting group of Cys at the 16th position.²⁸ After purification by gel filtration, Acm-deprotected peptides (Fla-1a-SH) were obtained without considerable amounts of byproducts (>95% purity on HPLC). These Fla⁶, Fla⁷ and Fla⁸-1a-SH were used for adsorption on a gold electrode. Subsequently, each Fla-1a-SH was dimerized by air oxidation to give the Fla-2 α peptide. The Fla-2 α peptides were purified by gel filtration to remove the unreacted 1a-peptides. All the peptides and intermediates synthesized were identified by amino acid analysis, matrix assisted laser desorption ionization timeof-flight mass spectrometry (TOFMS) and fast atom bombardment mass spectrometry (FABMS). To determine apparent molecular weights of the peptides in aqueous solution, the peptide samples $(2.0 \times 10^{-5} \text{ mol dm}^{-3})$ were passed through a Pharmacia Superdex 75HR column (10×300 mm, 5.0×10^{-2} mol dm⁻³ phosphate buffer, pH 7.0) calibrated with protein molecular weight markers. The peptides gave a slightly large apparent molecular weight (3200 and 6300 for 1 α and 2 α peptides, respectively) as compared to the theoretical one (2100 and 4000 for 1 α and 2 α peptides, respectively). It is reasonably considered that Fla-1a- and Fla-2a-peptides are in a monomeric form in buffer, because the peptides take a relatively extended conformation.

UV-VIS and fluorescence spectra

The Fla-1 α -peptides showed UV–VIS spectra with three absorption maxima at 288–289, 350 and 430 nm in buffer. Similarly, UV–VIS spectra of the Fla-2 α -peptides were composed of three absorption maxima at 286–288, 350 and 430 nm. Except for slight differences, all flavin-conjugated peptides showed similar absorption spectra to Fla with three absorption maxima at 282, 349 and 427 nm in buffer as reported by Kaiser *et al.*^{18 α} These results indicate that Fla is introduced into the peptide without unfavourable side-reactions.

Fluorescence spectra of the Fla-1 α , Fla-2 α peptides and Fla were also examined. The relative fluorescence intensities of peptides and Fla are listed in Table 1. Fluorescence emission peaks at 505 nm of all peptides in buffer were quenched in 6–10% intensities as compared to that of Fla. This is attributed to the flavin linked to the peptide with sulfur as reported by Kaiser *et al.*^{18*a*,29} Hence, flavin was demonstrated to be on the Cys side chain. The relative fluorescence intensities of peptides in trifluoroethanol (TFE) were increased as compared with those in buffer, but diminished as compared with that of Fla. Moreover, the Fla in each peptide showed a fluorescence emission with different intensity depending on its position in the peptide scaffold. Presumably, this fact indicates that the Fla in each peptide exists under different environments on the amphiphilic α -helix structure.

CD study

The CD spectra of the synthetic peptides in buffer and TFE solutions were examined and the results are shown in Fig. 2. In buffer, all the Fla-1 α peptides showed low α -helicity (13–15%) calculated from an ellipticity at 222 nm (-4000 to -4600 deg cm² dmol⁻¹) (Table 2).³⁰ The 16-peptide is not long enough to form stable hydrogen bonds for α -helix structure formation in aqueous solution.^{9a} On the other hand, the α -helicity of each Fla-2a in buffer was higher than that of the corresponding Fla- 1α . However, the flavin position in the peptide differently affects the α -helix conformation (Fla⁶-2 α , 20%; Fla⁷-2 α , 28%; Fla⁸-2 α , 46%). It is considered that the stabilization of the α helix is mainly attained by the intramolecular interaction between the hydrophobic face of the amphiphilic α -helical segments.¹⁻¹⁰ Because Fla⁶-2 α has only six Leu residues, two residues less than Fla⁷- and Fla⁸-2 α , the α -helicity was lower than that of the others. It is noteworthy that Leu⁶- 2α , which is a non-Fla peptide, has 55% helicity in the buffer solution. Another possible factor is that the relatively large and hydrophilic Fla was introduced at the hydrophobic Leu⁶ position in the 2α -helix structure. The hydrophobic interaction between the two α -helices of Fla⁶-2 α was disrupted by the introduced Fla group. When the α -helicity of Fla⁷-2 α is compared with that of Fla⁸-2 α , the former is lower than the latter. This result cannot be explained only by the hydrophobic effect between the two

Table 1 Relative fluorescence intensities of 7-acetyl-10-methylisoalloxazine and flavin-conjugated peptides a

	7.4 1.10 1.1	Fla ⁶		Fla ⁷		Fla ⁸	
Solvent	7-Acetyl-10-methyl- isoalloxazine (Fla)	1α	2α	lα	2α	1α	2α
Buffer	100	7.4	8.4	7.8	6.4	9.5	6.4
TFE	143	32.5	27.5	16.9	15.6	24.6	17.6

^a Intensity of Fla in buffer taken as 100. Measured in 2.0×10^{-2} mol cm⁻³ Tris•HCl buffer, pH 7.4 or trifluoroethanol at the flavin concentration of 2.0×10^{-5} mol dm⁻³ at 25 °C; excitation 430 nm, emission 510 nm.

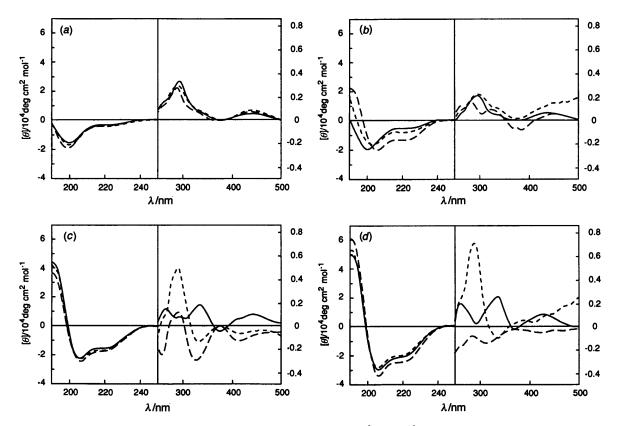


Fig. 2 CD spectra of Fla-1 α - [(a) and (b)] and Fla-2 α -peptides [(c) and (d)] in 2.0 × 10⁻² mol dm⁻³ Tris•HCl buffer, pH 7.4 [(a) and (c)] and TFE [(b) and (d)]. (----) Fla⁶-1 α and 2 α peptides; (----) Fla⁸-1 α and 2 α peptides. [0] at the amide region is the mean residual weight ellipticity, and [0] at the flavin absorption region is the molar ellipticity for Fla. [Fla-1 α] = 2.0 × 10⁻⁵ mol dm⁻³, [Fla-2 α] = 1.0 × 10⁻⁵ mol dm⁻³; 25 °C.

Table 2 a-Helix content (%) of Fla-1a- and Fla-2a-peptides"

	Solvent		
Peptide	Buffer	TFE	
Fla ⁶ -1a	13	52	
Fla ⁷ -1a	15	56	
Fla ⁸ -1α	14	59	
Leu ⁶ -la	16	68	
Fla ⁶ -2a	20	67	
Fla ⁷ -2a	28	64	
Fla ⁸ -2α	46	68	
Leu ⁶ -2a	55	67	

^e The concentrations of 1a and 2a peptides were 2.0×10^{-5} mol dm⁻³ and 1.0×10^{-5} mol dm⁻³, respectively.

 α -helix segments. Flavin in some flavoproteins, such as glucose oxidase³¹ and lipoamide dehydrogenase,³² is known to form hydrogen bonds with the main chain amides. It is possible that such hydrogen bonds are differently formed and thus affect the α -helicity depending on the position of flavin on the peptide. Consequently, these results indicate that the position of Fla in the peptides influences the secondary structure of peptides in aqueous solution. On the other hand, all Fla-1 α and Fla-2 α peptides showed a typical α -helix CD pattern in TFE. TFE is known to be an α-helix forming solvent and affects the hydrophobic interaction between α -helical segments causing them to be separated.^{25a} In TFE, all the peptides have similar potential to form an α -helix. Additionally, FT-IR spectra of Fla-1 α -SH in cast films, which were prepared from TFE solution, exhibited narrow absorption peaks for the amide I and II bands; Fla⁶-1a-SH 1656 and 1547 cm⁻¹, Fla⁷-1α-SH 1651 and 1541 cm⁻¹, Fla⁸-1α-SH 1654 and 1544 cm⁻¹ for amide I and II bands, respectively. These wavenumbers corresponding to amide I and II bands were characteristic for an α -helix rather than a random structure.33

Flavins on the Fla-1a peptides in buffer showed induced CD spectra at wavelengths corresponding to the UV spectra. Because Fla-1a peptides in buffer were almost in a random structure, flavins on Cys side chains were thought to move freely and not to be oriented in a particular position. However, flavins on the Fla-1a peptides in TFE showed different CD spectra depending on their positions. This result indicates that the flavin on each peptide is fixed in a particular orientation when the peptides are in an α -helix structure. The interaction between Fla and the peptide side chains in an α -helix structure may contribute to the different orientation of Fla. There were some differences among CD spectra in the flavin region of Fla-2a peptides in buffer. These differences were probably due to the distinct α -helicity of each peptide caused by the inter-helix hydrophobic interaction. In a similar manner to Fla-1a, flavins on the Fla-2a also showed different CD spectra in TFE. Consequently, these results suggested that flavins conjugated with peptides were arranged in different orientations depending on their positions when the peptides took an α -helix structure.

Modification of gold electrode with Fla-1a-SH

To adsorb the flavin-conjugated peptides on a gold surface through the sulfide linkage, a polished gold disk electrode was immersed in a solution of Fla-1 α -SH (1.0 × 10⁻³ mol dm⁻³) in TFE or water for 10 h at 25 °C. Because we thought that Fla-1 α -SH was more easily adsorbed than Fla-1 α , we used Fla-1 α -SH for the modification of a gold electrode. Subsequently, to avoid the non-specific physical adsorption of peptides, the electrode was sonicated in TFE and water. Fla-1 α -SH-modified electrodes which were obtained by immersion in aqueous solution almost completely blocked the direct electron transfer between the electrode and Fe(CN)₆³⁻ in solution. This was detected by the blocking ability of the heterogeneous electron

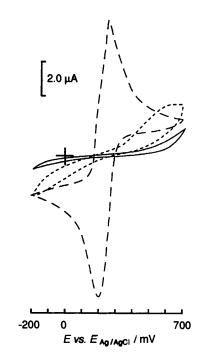


Fig. 3 Cyclic voltammograms for Fla⁶-1 α -SH-modified gold electrode prepared in aqueous solution (——), Fla⁶-1 α -SH modified gold electrode prepared in TFE solution (----) and bare gold (unmodified) electrode (---). Measured in 2.0 × 10⁻³ mol dm⁻³ K₃[Fe(CN)₆]-0.1 mol dm⁻³ phosphate buffer, pH 7.0 at 100 mV s⁻¹ sweep rate at 25 °C.

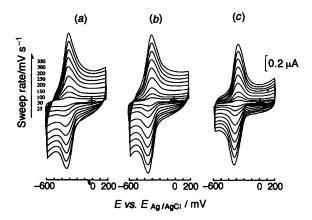


Fig. 4 Cyclic voltammograms for gold electrodes modified with the Fla-peptides in 0.1 mol dm⁻³ phosphate buffer, pH 7.0 at 25 °C; (a) Fla⁶-1 α -SH, (b) Fla⁷-1 α -SH, (c) Fla⁸-1 α -SH

transfer between the peptide–gold electrode and $Fe(CN)_6^{3-}$ in solution (Fig. 3). On the other hand, when the peptides were adsorbed in TFE, a disordered submonolayer was obtained on the electrode, resulting in insufficient blocking of the electron transfer. In TFE, hydrophobic interaction between peptides is cancelled in adsorption processes, and disordered layers might be formed. In water, on the contrary, hydrophobic interaction between peptides is stronger than that in TFE, and peptides would be organized in a closely packed mode on the electrode surface. Thus, for cyclic voltammetry measurements, we used the modified electrode which was prepared in the aqueous solution of Fla-1 α -SH.

Electrochemical characterization of modified electrodes

Fig. 4 shows typical cyclic voltammograms at various sweep rates obtained for Fla-1 α -SH-modified gold electrodes in 0.1 mol dm⁻³ phosphate buffer, pH 7.0. Each Fla-1 α -SH-modified electrode showed a well-defined redox peak at *ca.* -320 mV (*vs.* Ag/AgCl). The *E*° value of Fla was comparable to the reported

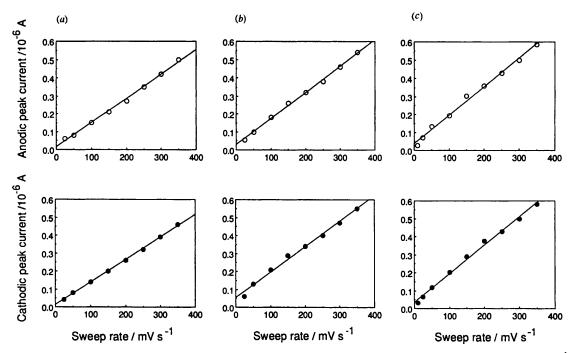


Fig. 5 Plots of anodic and cathodic peak currents as a function of the sweep rate for Fla-peptide modified electrodes in 0.1 mol dm⁻³ phosphate buffer, pH 7.0 at 25 °C; (a) Fla⁶-1 α -SH, (b) Fla⁷-1 α -SH, (c) Fla⁸-1 α -SH

Table 3 Redox potential and area occupied per Fla-la-SH molecule bound on an electrode surface a

Pept	ide	Solvent for adsorption	Redox potential/mV	Adsorbed amount/10 ⁻¹¹ mol cm ⁻²	Molecular occupied area/Å ²
Fla ⁶	-lα-SH	TFE	-323	4.0	420
		H ₂ O	-319	10.7	155
Fla ⁷	-lα-SH	TFE	-322	6.0	280
		H ₂ O	-329	10.7	155
Fla ⁸	-lα-SH	TFE	-320	4.0	420
		H₂O	-314	12.3	135

^a Measured in 0.1 mol dm⁻³ phosphate buffer, pH 7.0, at 25 °C. Surface area of Au disk electrode was 2.01 mm²; reference electrode was Ag/AgCl.

one (-300 mV vs. Ag/AgCl), which was measured in solution.^{18a} Fig. 5 shows the plots of anodic and cathodic peak currents as a function of the sweep rate. The linearity of these plots indicates that the voltammetric responses arise from surface-bound molecules. These results demonstrate that the Fla-peptides are successfully immobilized and redox-active on the gold electrode. In addition to these results, values of anodic and cathodic peak currents were approximately equal, and the peak potentials were independent of the sweep rate, indicating that Fla-1 α -SH on a gold electrode caused almost reversible redox reaction in the buffer solution.

Integration of the redox peak afforded an electro-active Fla- 1α -SH coverage of $10.7-12.3 \times 10^{-11}$ mol cm⁻², based on the surface area of the electrode (Table 3). The occupied area per peptide was 155, 155 and 135 Å², respectively, for Fla⁶-, Fla⁷and Fla⁸-1a-SH, respectively, which corresponded well to the theoretical area of the α -helical peptide adsorbed through the sulfide bond in the monolayer. Because FT-IR spectra of the Fla-1a-SH cast film were characteristic of an a-helix, Fla-1a-SH bound on the electrode might take an α -helix structure. The area occupied per Fla⁸-1 α -SH molecule was slightly lower than that of Fla⁶- and Fla⁷-1a-SH. As mentioned in the discussion on the CD spectra, the position of Fla in the peptides influences the secondary structure of peptides in aqueous solution. Therefore, the closer packing of Fla⁸-1α-SH may be attributed to the difference in the secondary structure on the surface. In contrast, when a gold disk electrode was immersed in a solution of peptide in TFE, the peptides adsorbed at $4.0-6.0 \times 10^{-11}$ mol cm⁻². In this case, the area occupied by the peptides varied from 280

to 420 Å², 1.8–3.1 times larger than those adsorbed in water. This result is consistent with incomplete blocking ability against the direct electron transfer from the electrode to $Fe(CN)_6^{3-}$ ion as described above. The peptides adsorbed in TFE were loosely packed on the gold surface. Therefore, it is concluded that the hydrophobic interaction between peptides is important for the peptide adsorption process on a gold surface with a sulfide linkage.

Catalytic reduction of $Fe(CN)_6^{3-}$ ion and cytochrome c by Fla-1 α -SH-modified electrode

The ability of flavin to act as a redox-active coenzyme makes it possible to mediate the electron transfer from a two-electron reductant such as NADH to a one-electron oxidant such as haem-Fe^{III} in proteins. Hence, it is reasonable to expect that the flavin-conjugated peptides on the electrode play a role as a mediator for reduction of $Fe(CN)_6^{3-}$ ion or cytochrome c. Fig. 6 shows the cyclic voltammograms of Fla-1a-SH-modified electrodes in the presence of $Fe(CN)_6^{3-}$ ion in the range of 700 to -600 mV. As seen in Fig. 3, the direct electron transfer between $Fe(CN)_6^{3-}$ ion and the electrode was almost completely blocked by the peptide monolayer on the gold surface. Another notable CV result in the presence of $Fe(CN)_6^{3-1}$ ion was the drastic enhancement in the peak at the reduction potential (around -330 mV) of Fla-1 α -SH. This result is ascribed to the catalytic reduction of $Fe(CN)_6^{3-}$ ion in the bulk solution through the flavin on the peptide. That is, Fla-1a-SH on the electrode could mediate the electron transfer from the electrode to $Fe(CN)_6^{3-1}$ ion in a vector manner.

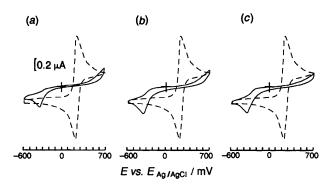


Fig. 6 Cyclic voltammograms for the gold electrodes modified with the flavin-conjugated peptides (----) and bare gold (unmodified) electrode (---) in 2.0×10^{-3} mol dm⁻³ K₃[Fe(CN)₆]-0.1 mol dm⁻³ phosphate buffer, pH 7.0 at 25 °C; (a) Fla⁶-1a-SH, (b) Fla⁷-1a-SH, (c) Fla⁸-1a-SH. The sweep rate was 100 m V s⁻¹.

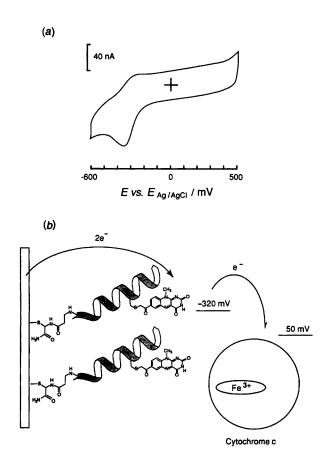


Fig. 7 (a) Cyclic voltammogram for the gold electrode modified with the Fla⁸-1 α -SH in 5.0 × 10⁻⁵ mol dm⁻³ cyctochrome c–0.1 mol dm⁻³ phosphate buffer, pH 7.0 at 25 °C; the sweep rate was 10 mV s⁻¹. (b) Illustration of the electron transfer from the electrode to cyctochrome c mediated by Fla-1 α -SH bound on the gold surface.

Fig. 7 shows the cyclic voltammogram of the Fla⁸-1 α -SHmodified electrode in the presence of cytochrome c in the buffer. In a similar manner to the Fe(CN)₆³⁻ ion, the cyclic voltammogram showed an enhancement in the peak at the reduction potential (-325 mV) of Fla⁸-1 α -SH. This result indicated the catalytic reduction of cytochrome c by the flavin on the peptide. Although the detailed mechanism on the interaction or electron transfer between cytochrome c and Fla-1 α -SH bound on the electrode remains unknown, the Fla-peptide on the electrode could mediate the electron transfer from the electrode to the haem protein in a vector manner.

It has been demonstrated that flavin-conjugated a-helix peptides are adsorbed on a gold electrode surface through the sulfide linkage. This is the first example of the adsorption of peptides conjugated with functionalized chromophores on a gold surface. The cyclic voltammetry revealed that the functional group, flavin, was redox-active on the electrode. By the use of flavin as an electrochemical probe, we could obtain information about the peptide assembly and properties on the gold surface. Additionally, the flavin-conjugated peptides could mediate the electron transfer from the electrode to $Fe(CN)_6^{3-}$ ion or cytochrome c in a vector manner. Though the detailed study on the orientation and the conformation of peptides on an electrode surface could be carried out to elucidate the relationship between the oriented functional group in the polypeptide 3D structure and electronic functions, the information obtained by future efforts will realize the application of the de novo designed functional polypeptides to new intelligent materials, such as electronic devices and chemical sensors.

Experimental

Materials and methods

All chemicals and solvents were of reagent or HPLC grade. Amino acid derivatives and reagents for peptide synthesis were purchased from Watanabe Chemical Co. (Hiroshima, Japan). Solid-phase peptide synthesis was carried out manually in a polypropylene column. Matrix assisted laser desorption timeof-flight mass spectra (TOFMS) were measured on a Shimadzu MALDI III mass spectrometer by using 3,5-dimethoxy-4hydroxycinnamic acid as a matrix. Fast atom bombardment mass spectra (FABMS) were recorded on a JEOL JMS-DX-300 mass spectrometer equipped with JEOL JMA-3100 mass data analysis system by using threo-1,4-dimercaptobutane-2,3-diol (DTT) as a matrix and xenon for bombardment. Amino acid analyses were carried out on a JEOL JLC-300 system with ninhydrin detection after hydrolysis in 6.0 mol dm⁻³ HCl at 110 °C for 24 h in a sealed tube. HPLC was carried out on a Wakosil 5C18 column (Wako Pure Chemical Industries) (4.6 × 150 mm) or a YMC ODS A-323 column (YMC Co.) (10 × 250 mm) by employing a Hitachi L-7100 intelligent pump equipped with a Hitachi L-7400 UV-VIS detector and a Hitachi D-7500 chromato-integrator. Solvent systems for HPLC are shown in the text. FT-IR spectra were recorded on a Perkin-Elmer 1600 series FT-IR spectrometer using Fla-1a-SH cast film formed from TFE solution on a calcium fluoride plate.

7a-Bromoacetyl-10-methylisoalloxazine. 7-Acetyl-10-methylisoalloxazine^{18a} was a gift from Professor Norikazu Nishino, Kyushu Institute of Technology. 7a-Bromoacetyl-10methylisoalloxazine was synthesized according to the method of Levine and Kaiser with some modifications.^{18a} 7-Acetyl-10methylisoalloxazine (Fla) (135 mg, 0.5×10^{-3} mol) was dissolved in acetic acid (15 cm³) at 85-90 °C. Bromine in acetic acid (0.25 mol dm⁻³, 2.0 cm³, 1.0 equiv.) was added dropwise to the solution over 20 min. The solution was then stirred for an additional 10 min at 85-90 °C and cooled to room temperature resulting in the precipitation of the product. The crystals were filtered and washed with diethyl ether. The crystals contained a small amount (<5% on HPLC) of starting material and dibrominated flavin in the acetyl group. Because the presence of a small amount of the by-products did not have a significant effect on the modification of the peptide by 7α -bromoacetyl-10methylisoalloxazine, the modifying reagent was used without further purification.

Peptide synthesis

Cys⁶-, Cys⁷- and Cys⁸-1a. Fmoc-Ala-Leu-Glu(OBu')-Gln-(Trt)-Lys(OBu')-Cys(Trt)-Ala-Ala-Leu-Glu(OBu')-Gln(Trt)- $\label{eq:basic} Lys(Boc)-Leu-Ala-\beta Ala-Cys(Acm)-NH-SAL resin, Fmoc-Ala-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Cys(Trt)-Ala-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-\beta Ala-Cys(Acm)-NH-SAL resin and Fmoc-Ala-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Leu-Glu(OBu')-Gln(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Lys(Trt)-Lys(Boc)-Leu-Ala-Cys(Trt)-Lys(Trt)-Lys(Trt)-Ly$

Ala-BAla-Cys(Acm)-NH-SAL resin (Bu', tert-butyl; Trt, trityl; Boc, tert-butyloxycarbonyl; Acm, acetamidomethyl) were synthesized manually by stepwise elongation of Fmoc-amino acids on 4-(2',4'-dimethoxyphenylaminomethyl)phenoxy resin (NH-SAL resin).²⁷ The following procedure was repeated from Fmoc-NH-SAL resin (0.50 g, 0.24 mmol amine); (i) washing with 1-methyl-2-pyrrolidone (NMP) (×5), (ii) washing with 20% piperidine (PPD)-NMP (×1), (iii) deprotection with 20%PPD-NMP (15 min), (iv) washing with NMP (×10), (v) coupling with Fmoc-AA [Fmoc-Ala·H₂O, Fmoc-β-Ala, Fmoc-Cys(Acm), Fmoc-Cys(Trt).0.5EtOAc, Fmoc-Gln(Trt), Fmoc-Glu(OBu')·H₂O, Fmoc-Leu, Fmoc-Lys(Boc)] (4.0 equiv.), benzotriazol-1-yloxytris(dimethylamino)phosphonium hexafluorophosphate (BOP) (4.0 equiv.), 1-hydroxybenzotriazole hydrate (HOBt·H₂O) (4.0 equiv.) and dipropan-2ylethylamine (DIEA) (8.0 equiv.) in NMP (15 min), (vi) washing with NMP (×5). Solvent volumes were 2.0 cm³. Coupling efficiency was checked by the Kaiser test.³⁴ To synthesize Acpeptide resin, the Fmoc-deprotected peptide resin was treated with acetic anhydride (10 equiv.) and DIEA (5.0 equiv.) in dichroromethane for 20 min.

To remove the resin and protecting groups except for the Acm group, the peptide resin was stirred in TFA (9.6 cm³) in the presence of *m*-cresol (0.24 cm³), ethane-1,2-dithiol (0.72 cm³) and thioanisole (1.44 cm³) as scavengers for 1 h at 25 °C. The resin was filtered and washed five times with TFA. The solvent was evaporated and the residues were solidified with diethyl ether in an ice-bath to give crude peptides: Cys⁶-1a [420 mg (99%)], Cys⁷-1a- [360 mg (84%)] and Cys⁸-1a [360 mg (82%)].

All crude peptides were purified by HPLC on a YMC ODS A-323 column (10 × 250 mm) using a linear gradient of 30–50% acetonitrile–0.1% TFA (30 min) to give the product with a single peak on analytical HPLC (Wakosil 5C18, 4.6 × 150 mm with a linear gradient of 20–60% acetonitrile–0.1% TFA over 30 min): Cys⁵-1 α (48%), Cys⁷-1 α (35%) and Cys⁸-1 α (37%). Peptides were identified by the molecular ion peak (M + H)⁺, (M + Na)⁺ and (M + K)⁺ on FAB-MS; Ac-Ala-Leu-Glu-Gln-Lys-Cys-Ala-Ala-Leu-Glu-Gln-Lys-Leu-Ala- β Ala-Cys(Acm)-NH₂, *m*/*z* 1801 [(M + H)⁺], 1823 [(M + Na)⁺] and 1839 [(M + K)⁺]; Ac-Ala-Leu-Glu-Gln-Lys-Leu-Cys-Ala-Leu-Glu-Gln-Lys-Leu-Ala- β Ala-Cys(Acm)-NH₂, *m*/*z* 1844 [(M + H)⁺]; Ac-Ala-Leu-Glu-Gln-Lys-Leu-Ala-Cys-Leu-Glu-Gln-Lys-Leu-Ala- β Ala-Cys(Acm)-NH₂, *m*/*z* 1844 [(M + H)⁺].

Fla⁶-, Fla⁷- and Fla⁸-1 α . To a solution of 7 α -bromoacetyl-10methylisoalloxazine (17 mg, 5.0×10^{-5} mol) in TFE (5.0 cm³), Cys-la peptide (45 mg, 2.5×10^{-5} mol) in 0.1 mol dm⁻³ Tris·HCl buffer, pH 7.5 (5.0 cm³) was added in one portion. The solution was stirred at room temperature for 3-4 h, keeping the pH of the solution at 7.5. The solvent was evaporated and the residues were dissolved in 10% acetic acid (1.0 cm³). Subsequently, the peptide solution was subjected to a Sephadex G-25 gel permeation column $(2.2 \times 45 \text{ cm})$ pre-equilibrated with 10% acetic acid. The column was eluted with 10% acetic acid and the desired fractions were collected. The peptide conjugated with flavin was detected by the absorption at 350 nm. After evaporation, the residue was dissolved in water. The aqueous solution was lyophilized to give the product with a single peak on analytical HPLC (Wakosil 5C18, 4.6 × 150 mm with a linear gradient of 20-60% acetonitrile-0.1% TFA over 30 min): Fla⁶-1 α [37 mg (70%)], Fla⁷-1 α [36 mg (68%)] and Fla⁸-1a [38 mg (72%)]; TOFMS; Ac-Ala-Leu-Glu-Gln-Lys-Cys(Fla)-Ala-Ala-Leu-Glu-Gln-Lys-Leu-Ala-BAla-Cys(Acm)-NH₂ (Fla⁶-1 α), *m/z* 2072.4 [(M + H)⁺] (calc. 2071.4); Ac-Ala-Leu-Glu-Gln-Lys-Leu-Cys(Fla)-Ala-Leu-Glu-Gln-Lys-Leu-Ala- β Ala-Cys(Acm)-NH₂ (Fla⁷-1 α), m/z 2114.1 [(M + H)⁺]

(calc. 2113.5); Ac-Ala-Leu-Glu-Gln-Lys-Leu-Ala-Cys(Fla)-Leu-Glu-Gln-Lys-Leu-Ala-βAla-Cys(Acm)-NH₂ $(Fla^8-l\alpha)$. m/z 2113.8 [(M + H)⁺] (calc. 2113.5); Fla⁶-1a (2.0 × 10⁻⁵ mol dm⁻³), $\lambda_{max}(2.0 \times 10^{-2} \text{ mol dm}^{-3} \text{ Tris} \cdot \text{HCl buffer, pH 7.4})/\text{nm}$ 430 (ε/dm^3 mol⁻¹ cm⁻¹ 10 900), 349 (5010) and 289 (30 100); λ_{max} (TFE)/nm 430 (11 200), 349 (5060) and 288 (35 100); Fla⁷- 1α (2.0 × 10⁻⁵ mol dm⁻³), λ_{max} (Tris·HCl buffer, pH 7.4)/nm 430 (10 900), 349 (5200) and 289 (30 700); $\lambda_{max}(TFE)/nm$ 430 (11 200), 349 (5200) and 288 (34 500); Fla^{8} -1 α (2.0 × 10⁻⁵ mol dm⁻³), λ_{max} (Tris·HCl buffer, pH 7.4)/nm 430 (10 900), 349 (5190) and 289 (31 500); λ_{max} (TFE)/nm 430 (11 200), 349 (5830) and 288 (34 400); amino acid analysis; Fla⁶-la: Ala_{4.00} (4), $\operatorname{Glu}_{3.94}(4)$, $\operatorname{Leu}_{3.02}(3)$, $\operatorname{Lys}_{1.96}(2)$; $\operatorname{Fla}^7-1\alpha$: $\operatorname{Ala}_{3.00}(3)$, $\operatorname{Glu}_{4.10}(4)$, Leu_{3.98} (4), Lys_{1.95} (2); Fla⁸-1a: Ala_{3.00} (3), Glu_{3.94} (4), Leu_{3.99} (4), Lys_{2.02} (2).

Fla⁶-, Fla⁷- and Fla⁸-1α-SH. To remove the Acm group of Cys¹⁶ in each peptide, Fla-1 α -peptide (21 mg, 1.0×10^{-5} mol) was dissolved in TFA (2.0 cm³) and the solution was stirred with AgBF₄ (20 equiv.) in the presence of anisole (10 equiv.) at 0 °C for 1 h. The peptide-Ag salt, precipitated with diethyl ether, was stirred with DTT (40 equiv.) in 10% acetic acid at room temperature for 3 h. After centrifugation, the supernatant was subjected to a Sephadex G-25 gel permeation column $(2.2 \times 45 \text{ cm})$ preequilibrated with 10% acetic acid. The column was eluted with 10% acetic acid and the desired fractions were collected. After evaporation, the residues were dissolved in water. The aqueous solution was lyophilized to give the product with a single peak on analytical HPLC (Wakosil 5C18, 4.6×150 mm with a linear gradient of 20-60% acetonitrile-0.1% TFA over 30 min): Fla6-1a-SH [12 mg (60%)], Fla⁷-1α-SH [13 mg (64%)], Fla⁸-1α-SH [16 mg (78%)]; TOFMS: Ac-Ala-Leu-Glu-Gln-Lys-Cys(Fla)-Ala-Ala-Leu-Glu-Gln-Lys-Leu-Ala- β Ala-Cys-NH₂, m/z 2000.6 [(M + H)] (calc. 2000.3); Ac-Ala-Leu-Glu-Gln-Lys-Leu-Cys(Fla)-Ala-Leu-Glu-Gln-Lys-Leu-Ala-βAla-Cys-NH₂, m/z 2042.3 [(M + H)⁺] (calc. 2042.4); Ac-Ala-Leu-Glu-Gln-Lys-Leu-Ala-Cys-(Fla)-Leu-Glu-Gln-Lys-Leu-Ala-βAla-Cys-NH₂, m/z 2044.4 $[(M + H)^{+}]$ (calc. 2042.4); FT-IR (cast film from TFE solution); Fla⁶-1 α -SH, amide I 1656 cm⁻¹, amide II 1547 cm⁻¹; Fla⁷-1 α -SH, amide I 1651 cm⁻¹, amide II 1541 cm⁻¹; Fla⁸-1 α -SH, amide I 1654 cm⁻¹, amide II 1544 cm⁻¹.

Fla⁶-, Fla⁷- and Fla⁸-2a. To form a disulfide bond by air oxidation, Fla-1 α -SH (12 mg, 6.0 × 10⁻⁶ mol) was dissolved in TFE (0.5 cm³) and to the solution was added 0.1 mol dm^{-3} Tris·HCl buffer, pH 8.0 (0.5 cm³). The peptide solution was vigorously stirred at room temperature for 24 h. The reaction was stopped by the addition of 10% acetic acid (1.0 cm³) and the peptide was purified by gel filtration with Sephadex G-25 $(2.2 \times 45 \text{ cm}, 10\% \text{ acetic acid})$. The desired fractions were collected and the solvent was evaporated. The residues were dissolved in water and the aqueous solution was lyophilized to give the 2 α -peptides: Fla⁶-2 α [6.4 mg (54%)], Fla⁷-2 α [7.8 mg (63%)], Fla⁸-2 α [7.8 mg (63%)]; TOFMS; Fla⁶-2 α , m/z 4001.4 $[(M + H)^+]$ (calc. 3997.6); Fla⁷-2 α , m/z 4086.8 $[(M + H)^+]$ (calc. 4081.8); Fla⁸-2 α , m/z 4086.6 $[(M + H)^+]$ (calc. 4081.8); Fla⁶-2 α (1.0 × 10⁻⁵ mol dm⁻³), $\lambda_{max}(2.0 \times 10^{-5})$ 10^{-2} mol dm⁻³ Tris·HCl buffer, pH 7.4)/nm 430 (ϵ /dm³ mol⁻¹ cm⁻¹ 21 000), 349 (12 280) and 286 (62 000); λ_{max} (TFE)/nm 431 (22 400), 349 (12 180) and 286 (69 000); $Fla^7-2\alpha$ (1.0 × 10⁻⁵ mol dm⁻³), λ_{max} (Tris·HCl buffer, pH 7.4)/ nm 430 (21 200), 349 (10 780) and 288 (62 200); λ_{max} (TFE)/ nm 432 (22 400), 349 (11 340) and 287 (69 800); $Fla^{8}-2\alpha$ (1.0 × 10⁻⁵ mol dm⁻³), λ_{max} (Tris·HCl buffer, pH 7.4)/nm 430 (19 080), 349 (12 500) and 287 (58 200); λ_{max} (TFE)/nm 432 (22 000), 349 (14 060) and 285 (69 000); amino acid analysis; Fla⁶-2a: Ala_{8.00} (8), Glu_{7.84} (8), $Leu_{6.06}(6), Lys_{3.76}(4); Fla^{7}-2\alpha: Ala_{6.00}(6), Glu_{7.90}(8), Leu_{7.96}(8),$ Lys_{3.88} (4); Fla⁸-2 α : Ala_{6.00} (6), Glu_{7.92} (8), Leu_{8.00} (8), Lys_{3.92} (4).

Fluorescence measurements

Fluorescence spectra were measured on a Hitachi F-3010

fluorescence spectrophotometer. Peptides were dissolved in 2.0×10^{-2} mol dm⁻³ Tris·HCl buffer (pH 7.4) or TFE in Fla-1 α and Fla-2 α concentrations of 2.0×10^{-5} and 1.0×10^{-5} mol dm⁻³, respectively.

CD measurements

CD spectra were recorded on a Jasco J-720 spectropolarimeter using a quartz cell with 1.0 of 10 mm pathlength. Peptides were dissolved in 2.0×10^{-2} mol dm⁻³ Tris·HCl buffer (pH 7.4) or TFE in Fla-1 α and Fla-2 α concentrations of 2.0×10^{-5} and 1.0×10^{-5} mol dm⁻³, respectively.

CV measurements

Fla-1a-SH modified electrodes were prepared by the following procedure. A gold disk working electrode (Bioanalytical System, surface area 2.01×10^{-2} cm²) was polished with diamond paste (particle size 10×10^{-5} m) and sonicated in water for 10 min using a bath type sonicator (Yamato Branson 3200). Again, the gold electrode was polished with alumina powder (particle size 4.0×10^{-8} m) and rinsed with water and then acetone. Subsequently, the electrode was immersed in Fla-1 α -SH (1.0 × 10⁻³ mol dm⁻³) in water for 10 h, and then sonicated in TFE and water for 10 min, respectively, to remove the non-specifically bound peptides. Cyclic voltammograms were measured in deoxygenated 0.1 mol dm⁻³ phosphate buffer, pH 7.0, as a supporting electrolyte. A home-made singlecompartment glass cell was used for the experiment. A gold electrode was used as the counter-electrode. Ag/AgCl (SCE - 49 mV) was used as the reference electrode. The experiments were carried out in Huso Electro Chemical System 315B Cyclic Voltammograph equipped with Graphtec WX1000. Bovine heart cytochrome c for cyclic voltammetry measurements was purchased from Sigma and purified with an ion exchange CM-25 column.

Acknowledgements

We are grateful to Dr N. Nishino, Kyushu Institute of Technology, for the generous gift of 7-acetyl-10-methylisoalloxazine and to Dr T. Sagara, Nagasaki University, for helpful suggestions. This work was funded in part by a Grant-in-Aid for Scientific Research from the Ministry of Education, Science, Culture and Sports, Japan.

References

- 1 S. F. Betz, D. P. Raleigh and W. F. DeGrado, *Curr. Opin. Struct. Biol.*, 1993, 3, 601; W. F. DeGrado, Z. R. Wasserman and J. D. Lear, *Science*, 1989, 243, 622; L. Regan and W. F. DeGrado, *Science*, 1988, 241, 976.
- M. Mutter and S. Vuilleumier, Angew. Chem., Int. Ed. Engl., 1989, 28, 535; M. Mutter, G. G. Tuchscherer, C. Miller, K.-H. Altmann, R. I. Carey, D. F. Wyss, A. M. Labhardt and J. E. Rivier, J. Am. Chem. Soc., 1992, 114, 1463.
- 3 K. W. Hahn, W. A. Klis and J. M. Stewart, Science, 1990, 248, 1544.
- 4 M. Montal, M. S. Montal and J. M. Tomich, *Proc. Natl. Acad. Sci.* USA, 1990, **87**, 6929.
- 5 H. Morii, K. Ichimura and H. Uedaira, Chem. Lett., 1990, 1987; Proteins Str. Func. Genet., 1991, 11, 133; H. Morii, S. Honda, K. Ichimura and H. Uedaira, Bull. Chem. Soc. Jpn., 1991, 64, 396.
- 6 T. Sasaki and E. T. Kaiser, J. Am. Chem. Soc., 1989, 111, 380; T. Sasaki and E. T. Kaiser, Biopolymers, 1990, 29, 79; M. Leiberman and T. Sasaki, J. Am. Chem. Soc., 1991, 113, 1470; T. Sasaki and M. Lieberman, Tetrahedron, 1993, 49, 3677.
- 7 M. R. Ghadiri, C. Soares and C. Choi, J. Am. Chem. Soc., 1992, 114, 825; 4000.
- 8 C. T. Choma, J. D. Lear, M. J. Nelson, P. L. Dutton, D. E. Robertson and W. F. DeGrado, J. Am. Chem. Soc., 1994, 116, 856;

D. E. Robertson, R. S. Farid, C. C. Mosser, J. L. Urbauer, S. E. Mulholland, R. Pidikiti, J. D. Lear, A. J. Wand, W. F. DeGrado and P. L. Dutton, *Nature*, 1994, **368**, 425; F. Rabanal, W. F. DeGrado and P. L. Dutton, *J. Am. Chem. Soc.*, 1996, **118**, 473.

- 9 (a) H. Mihara, Y. Tanaka, T. Fujimoto and N. Nishino, J. Chem. Soc., Perkin Trans. 2, 1995, 1133; (b) H. Mihara, Y. Tanaka, T. Fujimoto and N. Nishino, J. Chem. Soc., Perkin Trans. 2, 1995, 1915; (c) H. Mihara, N. Nishino and T. Fujimoto, Chem. Lett., 1992, 1809; (d) S. Ono, N. Kameda, T. Yoshimura, C. Shimasaki, E. Tsukurimichi, H. Mihara and N. Nishino, Chem. Lett., 1995, 965; (e) N. Nishino, H. Mihara, Y. Tanaka and T. Fujimoto, Tetrahedron Lett., 1992, 33, 5767.
- (a) H. Mihara, N. Nishino, R. Hasegawa, T. Fujimoto, S. Usui, H. Ishida and K. Ohkubo, *Chem. Lett.*, 1992, 1813; (b) H. Mihara, Y. Haruta, S. Sakamoto, N. Nishino and H. Aoyagi, *Chem. Lett.*, 1996, 1; (c) H. Mihara, K. Tomizaki, T. Fujimoto, S. Sakamoto, H. Aoyagi and N. Nishino, *Chem. Lett.*, 1996, 187; (d) H. Mihara, K. Tomizaki, N. Nishino and T. Fujimoto, *Chem. Lett.*, 1993, 1533.
- 11 D. R. Benson, B. R. Hart, X. Zhu and M. B. Doughty, J. Am. Chem. Soc., 1995, 117, 8502.
- 12 E. U. Thoden van Velzen, J. F. J. Engbersen and D. N. Reinhoudt, J. Am. Chem. Soc., 1994, 116, 3597; K. D. Schierbaum, T. Weiss, E. U. Thoden van Velzen, J. F. J. Engbersen, D. N. Reinhoudt and W. Göpel, Science, 1994, 265, 1413; E. U. Thoden van Velzen, J. F. J. Engbersen, P. J. de Lange, J. W. G. Mahy and D. N. Reinhoudt, J. Am. Chem. Soc., 1995, 117, 6853.
- 13 M. T. Rojas, R. Königer, J. F. Stoddart and A. E. Kaifer, J. Am. Chem. Soc., 1995, 117, 336.
- 14 M. Maeda, K. Nakano, S. Uchida and M. Takagi, Chem. Lett., 1994, 1805.
- 15 T. Akiyama, H. Imahori and Y. Sakata, Chem. Lett, 1994, 1447.
- 16 M. Lion-Dagan, E. Katz and I. Willner, J. Am. Chem. Soc., 1994, 116, 7913.
- I7 (a) J. K. Whitesell and H. K. Chang, Science, 1993, 261, 73; (b)
 D. J. van den Heuvel, R. P. H. Kooyman, J. W. Drijfhout and
 G. W. Welling, Anal. Biochem., 1993, 215, 223.
- 18 (a) H. L. Levine and E. T. Kaiser, J. Am. Chem. Soc., 1978, 100, 7670; (b) S. E. Rokita and E. T. Kaiser, J. Am. Chem. Soc., 1986, 108, 4984; (c) D. Hilvert and E. T. Kaiser, J. Am. Chem. Soc., 1985, 107, 5805.
- 19 H. Durliat and M. Comtat, J. Biol. Chem., 1987, 262, 11497.
- 20 V. I. Birss, H. Elzanowska and R. A. Turner, Can. J. Chem., 1988, 66, 86.
- 21 L. Gorton and G. Johansson, J. Electroanal. Chem., 1980, 113, 151. 22 C. N. Durfor, B. A. Yenser and M. L. Bowers, J. Electroanal. Chem.,
- 22 C. N. Durfor, B. A. Yenser and M. L. Bowers, J. Electroanal. Chem., 1988, 244, 287.
- 23 S. Berchmans and R. Vijayavalli, Langmuir, 1995, 11, 286.
- 24 S. Ueyama, S. Isoda and M. Maeda, J. Electroanal. Chem., 1989, 264, 149; S. Ueyama, S. Isoda and M. Maeda, J. Electroanal. Chem., 1990, 293, 125.
- 25 (a) N. E. Zhou, B.-Y. Zhu, C. M. Kay and R. S. Hodges, *Biopolymers*, 1992, **32**, 419; (b) J. Talbot and R. S. Hodges, *Acc. Chem. Res.*, 1982, **15**, 224; (c) E. K. O'Shea, J. D. Klemm, P. S. Kim and T. Alber, *Science*, 1991, **254**, 539.
- 26 E. Atherton and R. C. Sheppard, Solid Phase Peptide Synthesis: A Practical Approach, IRL Press, Oxford, England, 1989.
- 27 H. Rink, Tetradrondron Lett, 1987, 28, 3787.
- 28 M. Yoshida, T. Tatsumi, Y. Fujiwara, S. Iinuma, T. Kimura, K. Akaji and Y. Kiso, *Chem. Pharm. Bull.*, 1990, 38, 1551.
- 29 M. C. Falk and D. B. McCormick, Biochemistry, 1976, 15, 646.
- 30 J. M. Scholtz, H. Qian, E. J. York, J. M. Stewart and R. L. Baldwin, *Biopolymers*, 1991, **31**, 1463.
- 31 V. Massey and G. Palmer, Biochemistry, 1996, 5, 3181.
- 32 A. Mattevi, G. Obmolova, K. Kalk, W. van Berkel and W. Hol, J. Mol. Biol., 1993, 230, 1200.
- 33 J. F. Rabolt, W. H. Moore and S. Krimm, *Macromolecules*, 1977, 10, 1065.
- 34 K. Kaiser, R. L. Colescott and C. T. Bossinger, Anal. Biochem., 1970, 34, 595.

Paper 6/03199D Received 7th May 1996 Accepted 26th June 1996