

Synthesis, Reactions and Catalytic Activities of Iridium Complexes intercalated into Montmorillonite

Chong Shik Chin,^{*a} Byeongno Lee,^a Ilye Yoo^a and Tae-hyun Kwon^b

^a Department of Chemistry, Sogang University, Seoul 121-742, Korea

^b Lucky R & D Center, Science Town, Dae Jeon 305-343, Korea

Reactions of cationic iridium(I) complexes, $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ **1** and $[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]\text{ClO}_4$ **2** (cod = cycloocta-1,5-diene) with water-swelled sodium montmorillonite have been shown to produce iridium complex-intercalated clays, $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ -montmorillonite **1c** and $[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]^+$ -montmorillonite **2c**. Compounds **1c** and **2c** react with CO to produce $[\text{Ir}(\text{CO})_2(\text{PPh}_3)_2]^+$ (from **1c**) and $[\text{Ir}(\text{CO})_2(\text{PPh}_3)]^+$ (from **2c**) intercalated clays. Reactions of **1c** and **2c** with H_2 produce cyclooctane and unknown iridium complexes remaining in the layers of the clay. While both the catalytic hydrogenation and isomerization (double-bond migration and *cis-trans* conversion) of olefins with **1** and **2** are in general retarded by intercalation of the catalysts, isomerization is relatively more suppressed than hydrogenation. Selective hydrogenation of the vinyl group of 4-vinylcyclohexene was found to be somewhat higher with **1c** than with **1**.

In the search for methods of improving selectivities in transition-metal-catalysed reactions, transition-metal complex-intercalated clays have been prepared and their catalytic activities investigated.¹⁻¹² Several studies have been made of rhodium complexes intercalated into the layers of smectite clays,⁷⁻¹² while there has been, to our knowledge, only one report on iridium complex-clay intercalation.⁶ We now report the intercalation of the complexes $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ and $[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]^+$ (cod = cycloocta-1,5-diene) into layers of montmorillonite together with their reactions with CO and H_2 and catalytic characteristics for hydrogenation and isomerization of olefinic groups. Montmorillonite-supported $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ and its reactions and catalytic activities is reported for comparison.

Experimental

Materials.—Sodium montmorillonite (Creek County, Wyoming, USA) was obtained from the Source Clay Mineral Repository, Clary Minerals Society. Elemental analysis (SiO₂, 55.6; Al₂O₃, 20.1; Fe₂O₃, 3.7; Na₂O, 2.8; MgO, 2.5; K₂O, 0.6; CaO, 0.5%) shows the cation-exchange capacity to be 121 milliequivalents of cation (M⁺) per 100 g of this clay. The complexes $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ **1**, $[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]\text{ClO}_4$ **2** and $[\text{Ir}(\text{cod})(\text{PhCN})_2]\text{ClO}_4$ **3** were prepared by the literature methods.¹³⁻¹⁵ Organic substrates, hex-1-ene, cod, 4-vinylcyclohexene, diphenylacetylene and but-3-en-2-ol from either Fluka or Aldrich were used as purchased.

Instrumentation.—Proton NMR, IR and electronic absorption and diffuse reflectance spectra were recorded on Varian EM-360A (at 60 MHz), Shimadzu IR-400 and UV-240 spectrophotometers, respectively. Electronic diffuse reflectance spectra of solid samples were obtained in alumina using a 204-52454 integrating sphere attachment. X-Ray diffraction (XRD) data were obtained on a Rigaku RAD-C diffractometer with nickel-filtered Cu-K α radiation and calibration with a silicon polycrystal as a standard. A Varian 3700 gas chromatograph with a column (4.8 m \times 0.32 mm) of 5% KOH on Carbowax 20M was used for analysis of the reaction mixtures.

Synthesis.—*Swelling of sodium montmorillonite.* Sodium montmorillonite (45 mg) was slowly added to distilled water (5

cm³) and the resulting mixture was stirred under N₂ for 30 min. It was used *in situ* for intercalation of the iridium complex without separation of the water-swelled clay and excess of water. For XRD measurements, the swelled montmorillonite was filtered off and dried under N₂ at room temperature for 1 h.

$[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ -montmorillonite 1c. A red solution of $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ (0.1 mmol, 93 mg) in methanol (30 cm³) was slowly added to the beige slurry of swelled montmorillonite (45 mg of clay in 5 cm³ of water) prepared as described above and the resulting mixture was stirred for 3 h under N₂ at room temperature. The reddish iridium-intercalated montmorillonite was then filtered off, washed with MeOH on a fritted glass filter (medium porosity) until the filtrate became colourless, and used in catalytic reactions without thorough drying. The sample was dried under N₂ at room temperature for 1 h for XRD analysis.

$[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]^+$ -montmorillonite 2c. This orange material (**2** is also orange) was prepared in the manner described for $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ -montmorillonite **1c**.

Attempt to prepare $[\text{Ir}(\text{cod})(\text{PhCN})_2]^+$ -montmorillonite. To the slurry of swelled montmorillonite (45 mg of clay in 5 cm³ water) was added a yellow solution of $[\text{Ir}(\text{cod})(\text{PhCN})_2]\text{ClO}_4$ (0.1 mmol) in MeOH (30 cm³) and the resulting mixture was stirred under N₂ at room temperature for 3 h. The yellow solid was filtered off, washed with MeOH on a fritted glass filter until the filtrate became colourless and dried under N₂ at room temperature for 1 h for XRD analysis.

Stoichiometry of the intercalation of $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$. A methanol solution (25 cm³) containing $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ (0.04 mmol) was mixed with a slurry of montmorillonite (20 mg) swelled with water (5 cm³) and stirred for 3 h under nitrogen at room temperature. The absorbance of the supernatant was measured as 0.270 (in a 1 cm path length cell) at 491 nm {see Fig. 1 for the electronic absorption spectrum of $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ } while the absorbance of a methanol (25 cm³)-water (5 cm³) solution containing $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ (0.04 mmol) at 491 nm was found to be 0.373. These data suggest that 1 mmol of $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ reacts with ca. 1.8 g of sodium montmorillonite to give $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ -montmorillonite **1c** containing ca. 0.55 mmol Ir per gram of clay.

$[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ adsorbed on montmorillonite 1s. This compound was prepared in a similar manner to that of **1c** except

that water was never used since **1c** is obtained only when water is used (see below).

Stoichiometry of the adsorption of [Ir(cod)(PPh₃)₂]⁺ by montmorillonite. The stoichiometry, 1 mmol of [Ir(cod)(PPh₃)₂]⁺ to ca. 5.2 g of clay, was determined by measuring the difference between the absorbances of [Ir(cod)(PPh₃)₂]⁺ at 491 nm before and after addition of the clay as described above for the stoichiometry of the intercalation. A similar value, 1 mmol of Ir⁺ to ca. 5.5 g clay, was also obtained by gravimetric analysis carried out by measuring the difference between the weights of sodium montmorillonite and montmorillonite-supported [Ir(cod)(PPh₃)₂]⁺ **1s**. The air-dried sodium montmorillonite used in this study may contain a small amount of water, and a small amount of **1c** may be formed during the measurements.

Reactions.—[Ir(cod)(PPh₃)₂]⁺–montmorillonite **1c** with CO. A suspension of compound **1c** (120 mg) in CHCl₃ (10 cm³) was stirred under atmospheric pressure of CO at room temperature for 10 h. The initially reddish suspension turned white within 10 min. A white solid was filtered off and washed thoroughly with CHCl₃. The ¹H NMR spectrum of the less-volatile material obtained by evaporating the filtrate showed signals due to cycloocta-1,5-diene.

[Ir(cod)(PPh₃)(PhCN)]⁺–montmorillonite **2c** and [Ir(cod)(PhCN)_n]⁺–montmorillonite **3c** with CO. These reactions were carried out in the same manner as described above. The orange **2c** turned white while yellow **3c** turned dark brown. Proton NMR and gas chromatographic analysis showed cod and PhCN in the filtrates. Only a small amount of PhCN was found in the filtrate from the reaction of **3c**.

Compound 1c with H₂. A suspension of compound **1c** (66 mg) in CDCl₃ (5 cm³) was stirred under atmospheric pressure of H₂ at room temperature for 10 h. The reddish suspension turned white within 5 min and then dark grey within 3 h. The supernatant obtained upon centrifugation was found to contain cyclooctane according to ¹H NMR and GC analysis.

Compounds 2c and 3c with H₂. These reactions were carried out in the same manner as described above. Proton NMR and GC analysis showed cyclooctane and PhCN to be present in the supernatants.

Compound 1c with NaClO₄. Sodium perchlorate (0.1 g, 0.8 mmol) in water (5 cm³) was added to the slurry of compound **1c** [145 mg containing 0.055 mmol (45 mg) of the iridium complex] in a mixture of MeOH (20 cm³) and CH₂Cl₂ (10 cm³) and the resulting mixture was stirred for 15 h under N₂ at room temperature. The filtrate obtained using a medium-porosity fritted glass filter was extracted several times with water to remove the unreacted NaClO₄ and evaporated under vacuum to obtain a small amount (ca. 5 mg) of red solid identified as [Ir(cod)(PPh₃)₂]ClO₄ **1** by ¹H NMR, infrared and visible-region electronic absorption spectra.

Catalytic Hydrogenations.—With [Ir(cod)(PPh₃)₂]⁺–montmorillonite **1c**. Compound **1c** (66 mg) containing [Ir(cod)(PPh₃)₂]⁺ (0.025 mmol) and hex-1-ene (2.5 mmol) in CDCl₃ (5 cm³) were stirred under atmospheric pressure of H₂ at 25 °C. A part (ca. 0.5 cm³) of the mixture was taken out of the reactor at intervals and the supernatant obtained by centrifugation was analysed by ¹H NMR spectroscopy. Disappearance of the starting material hex-1-ene could readily be followed by the disappearance of the multiplets at δ 5.70 and 4.90. The isomerization product hex-2-ene was measured by the multiplet at δ 5.40. Hydrogenation of both hex-1-ene and -2-ene to produce hexane could be followed by the disappearance of the multiplets at δ 5.70 and 4.90 of hex-1-ene and δ 5.40 of hex-2-ene and also by the disappearance of the multiplet at δ 2.0 for both hex-1-ene and -2-ene.


*With montmorillonite-supported [Ir(cod)(PPh₃)₂]⁺ **1s** and with swelled sodium montmorillonite.* These reactions were carried out in the same manner.

*With [Ir(cod)(PPh₃)₂]ClO₄ **1**.* These homogeneous catalytic reactions were carried out in the manner described for **1c**. Separation of soluble catalysts was not necessary for the product analysis by ¹H NMR spectroscopy unless the signals due to the catalysts interfered.

Isomerization of But-3-en-2-ol with Compounds 1, 1c, 2 and 2c.—These experiments were carried out in the manner described above for the hydrogenation with **1c** except that they were carried out under N₂ (in the absence of H₂). The disappearance of but-3-en-2-ol was followed by the disappearance of the signals at δ 4.0–6.0 due to the olefinic protons, and the formation of ethyl methyl ketone was followed by the appearance of the signal at δ 2.12 due to COCH₃.

Results and Discussion

Reactions of [Ir(cod)(PPh₃)₂]ClO₄ **1** and [Ir(cod)(PPh₃)(PhCN)]ClO₄ **2** with sodium montmorillonite swelled with water produced the intercalated iridium compounds [Ir(cod)(PPh₃)₂]⁺–montmorillonite **1c** and [Ir(cod)(PPh₃)(PhCN)]⁺–montmorillonite **2c** through cation exchange between the Na⁺ of the clay and [Ir(cod)L₂]⁺ [L₂ = (PPh₃)₂ or (PPh₃)(PhCN)], see equation (1). A rhodium analogue



[Rh(cod)(PPh₃)₂]⁺–hectorite was previously reported.⁷ Attempts to prepare [Ir(cod)(PhCN)₂]⁺–montmorillonite have also been carried out by the reaction of [Ir(cod)(PhCN)₂]ClO₄ **3** with the swelled sodium montmorillonite. The yellow solid isolated, however, does not seem to contain intact [Ir(cod)(PhCN)₂]⁺ (see below). According to the X-ray diffraction data, the intercalation of iridium complexes **1** and **2** into layers of sodium montmorillonite does not occur in the absence of water and samples are best prepared from the reaction of iridium complexes with water-swelled clay. Expansion of interlayer distances by swelling with water may facilitate intercalation of the iridium complexes. In MeOH or CH₂Cl₂ in the absence of water, however, significant amounts of **1–3** seem to be adsorbed on the surfaces of the clay.

Characterization of Iridium Complexes intercalated into Montmorillonite.—*Stoichiometry.* The observed ratio, Ir (in mmol):sodium montmorillonite (in g), of ca. 0.55:1 for the intercalation compound **1c** (see Experimental section) corresponds to ca. 46% of the cation-exchange capacity (ca. 120 milliequivalents of M⁺ per 100 g) of the clay being replaced by Ir⁺. Elemental analysis (C, 16.75%) gives a similar ratio 0.51:1. The fact that the montmorillonite-supported compound **1s** (for which no expansion of the basal spacing was observed) contains ca. 0.19 mmol of the iridium complex per gram of clay suggests that ca. 19/55 of the iridium complex in **1c** is adsorbed (not intercalated) on the edge of the clay. A cation-exchange limit of ca. 22% was reported for [Rh(cod)(PPh₃)₂]⁺–hectorite⁷ with a basal spacing of 17.7 Å which allows only monolayer intercalation, while 100 and 160% of the cation-exchange capacity of sodium–montmorillonite were found to be replaced by Λ-[Ru(phen)₃]²⁺ and *rac*-[Ru(phen)₃]²⁺ (phen = 1,10-phenanthroline) with basal spacings expanded up to 17.8 and 29.7 Å, respectively.³

Electronic Spectra.—Electronic diffuse reflectance spectra of compounds **1c** and **2c** show three bands at practically the same wavelengths as those of **1** and **2** (see Fig. 1), which suggests intact Ir(cod)(PPh₃)₂ and Ir(cod)(PPh₃)(PhCN) moieties in **1c** and **2c**, respectively. The spectrum of **3c** (the reaction product of **3** with water-swelled sodium montmorillonite) does not show a

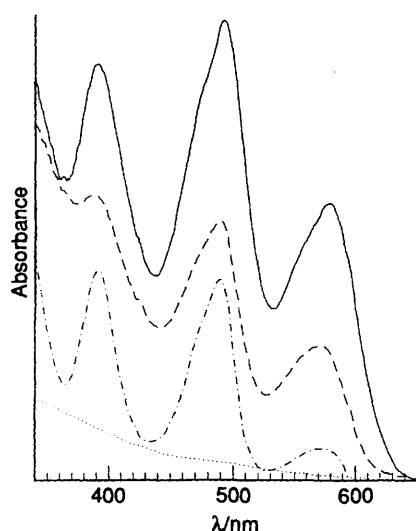


Fig. 1 Electronic diffuse reflectance spectra of $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]\text{ClO}_4$ 1 (—), $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ -montmorillonite 1c (---), sodium montmorillonite (···) in alumina and the absorption spectrum of 1 (— · — · —) in methanol. Different concentrations were chosen for each sample for clarity

Table 1 Basal spacings (001) of iridium complexes intercalated in montmorillonite

Compound	001 spacing ^a /Å
Sodium montmorillonite	9.4
Sodium montmorillonite-water ^b	12.9
$[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ -montmorillonite 1c	24.9
$[\text{Ir}(\text{CO})_x(\text{PPh}_3)_2]^+$ -montmorillonite ^c	22.3
$[\text{Ir}(\text{PPh}_3)_2]^+$ -montmorillonite ^d	18.2
$[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]^+$ -montmorillonite 2c	21.5
$[\text{Ir}(\text{CO})_y(\text{PPh}_3)]^+$ -montmorillonite ^e	20.7
$[\text{Ir}(\text{cod})(\text{PhCN})_n]^+$ -montmorillonite 3c ^f	18.2
$[\text{Ir}(\text{CO})_z]^+$ -montmorillonite ^g	17.1




^a Average values of several samples. ^b Sodium montmorillonite swelled with water. ^c The reaction product of compound 1c with CO. ^d The reaction product of compound 1c with H₂. ^e The reaction product of compound 2c with CO. ^f The isolated solid from the reaction of $[\text{Ir}(\text{cod})(\text{PhCN})_2]\text{ClO}_4$ 3 with sodium montmorillonite (see text for characterization). ^g The reaction product of compound 3c with CO.

band in the visible region while 3 shows three bands at 369, 442 and 496 nm in CH₂Cl₂. This indicates that the $\text{Ir}(\text{cod})(\text{PhCN})_2$ moiety is not maintained during cation exchange between 3 and sodium montmorillonite. It should be mentioned, however, that cod and PhCN were found in the reaction mixture of 3c with CO and H₂ (see reactions below and Experimental section).

X-Ray Diffraction Data.—The X-ray diffraction data in Table 1 unambiguously demonstrate intercalation of the iridium complexes into the clay. The basal spacings of 24.9 and 21.5 Å observed for 1c and 2c are very close to the sums (24.9 and 22.4 Å) of those for water-swelled sodium montmorillonite (12.9 Å) and the molecular models of $[\text{Ir}(\text{cod})(\text{PPh}_3)_2]^+$ (12.0 Å) and $[\text{Ir}(\text{cod})(\text{PPh}_3)(\text{PhCN})]^+$ (9.5 Å), respectively. The basal spacing (18.2 Å) observed for 3c (the product of the reaction of 3 with sodium montmorillonite) is also close to the sum (17.9 Å) of 12.9 and 5.0 Å {from the molecular model of $[\text{Ir}(\text{cod})(\text{PhCN})_2]^+$ }. Although the XRD data for 3c suggest intercalation of an iridium complex into the clay, the electronic absorption spectrum is not consistent with a $\text{Ir}(\text{cod})(\text{PhCN})_2$ moiety. Therefore 3c is denoted by $[\text{Ir}(\text{cod})(\text{PhCN})_n]^+$ -montmorillonite since 3c seems to contain both cod and PhCN (see reactions with CO in Experimental section).

The interlayer distance (24.9 Å) observed for compound 1c is certainly larger than that (17.7 Å) observed for the rhodium analogue $[\text{Rh}(\text{cod})(\text{PPh}_3)_2]^+$ -hectorite prepared in acetone.⁷ Reactions with CO cause slight decreases in the basal spacings of 2c and 3c (see Table 1), which may be understood as replacement of cod and PhCN with CO as observed (see Experimental section). The relatively large decrease (2.6 Å) observed for the product of the reaction of 1c with CO may be understood in terms of replacement of cod with CO and rearrangement of the two PPh₃, possibly from *cis* (in 1c) to *trans* {in $[\text{Ir}(\text{CO})_x(\text{PPh}_3)_2]^+$ -montmorillonite} to each other. The larger decrease in basal spacing observed for the product of the reaction of 1c with H₂ (see Table 1) may be explained by desorption of cod probably immediately after its hydrogenation to cyclooctane. It might be safely said that the reactions of 1c, 2c and 3c with CO and H₂ do not cause desorption of iridium from the layers of the clay.

Reactions.—With CO. The iridium complex-intercalated montmorillonites 1c–3c react with CO to give Ir–CO complexes which are still in between the layers of the clay according to the X-ray diffraction data in Table 1. The products obtained show strong absorption bands due to terminal CO at 1991 and 1993 (white solid from 1c), 2047 and 1994 (white solid from 2c) and 2055 cm⁻¹ (somewhat broad) (dark brown solid from 3c) in Nujol. As mentioned above, cod and PhCN in 1c–3c are replaced by CO [equations (2)–(4)]. We have found that the





replacement of cod and PhCN with CO (probably more than one CO) readily occurs also for the non-intercalated compounds 1–3,^{13,16} and it has been known that cod coordinated to iridium(I) is readily replaced by CO.¹⁷

We also found that the reaction of non-intercalated iridium complex 1 with CO in solution produces a white solid $[\text{Ir}(\text{CO})_3(\text{PPh}_3)_2]\text{ClO}_4$ ¹⁸ which reacts further with water-swelled sodium montmorillonite to give a white solid which showed infrared bands at 1991 and 1993 cm⁻¹.

It has been found that reactions of compounds 1c and 2c with CO liberate small amounts of PPh₃ and the desorption of PPh₃ became significant at longer reaction times with slight shifts of $\nu(\text{CO})$.

With H₂. Reactions of iridium–clay compounds 1c–3c with H₂ produce cyclooctane [equations (5) (L = PPh₃ or PhCN) and (6)]. The isolated products do not show infrared bands



attributable to $\nu(\text{Ir}-\text{H})$. The products from the reactions of 1c and 2c show bands due to Ir–PPh₃ [equation (5)] and a basal spacing of 18.2 Å was found for the product of reaction of 1c. On the other hand, the product from the reaction of 3c shows only the infrared bands of the clay. This reaction produces metallic


Table 2 Catalytic hydrogenation and isomerization of olefins with [Ir(cod)(PPh₃)₂]ClO₄ **1**, [Ir(cod)(PPh₃)₂]⁺-montmorillonite **1c**, [Ir(cod)(PPh₃)(PhCN)]ClO₄ **2** and [Ir(cod)(PPh₃)(PhCN)]⁺-montmorillonite **2c**, under an atmospheric pressure of H₂ at 25 °C in CDCl₃. Mole ratios of substrates to Ir were 200 for 4-vinylcyclohexene, 100 for hex-1-ene and but-3-en-2-ol, 50 for cod and 20 for diphenylacetylene using 0.025 mmol of Ir

Catalyst	Substrate	t/h	Product (%)
Clay ^a 1c	Hex-1-ene	1	Hexane (15), no hex-2-ene
		1	Hexane (37), hex-2-ene (63)
		7	Hexane (100)
1s^b 1		1	Hexane (13), hex-2-ene (54)
		0.2	Hexane (23), hex-2-ene (77)
2c		1	Hexane (9), hex-2-ene (41)
		7	Hexane (63), hex-2-ene (37)
		1.5	Hexane (100)
Clay ^a 1c	cod	24	No hydrogenation
		2	Cyclooctene (58)
		4	Cyclooctane (100)
1		1	Cyclooctene (42)
		2	Cyclooctane (100)
Clay ^a 1c	4-Vinylcyclohexene	24	No hydrogenation
		3	4-Ethylcyclohexene (44)
		5	4-Ethylcyclohexene (64), ethylcyclohexane (13)
1		3	4-Ethylcyclohexene (40), ethylcyclohexane (15)
		5	4-Ethylcyclohexene (41), ethylcyclohexane (59)
2c		5	4-Ethylcyclohexene (32)
		3	4-Ethylcyclohexene (30), ethylcyclohexane (5)
Clay ^a 1c	Diphenylacetylene	24	No hydrogenation
		2.5	<i>cis</i> -1,2-Diphenylethylene (100)
		5.5	<i>cis</i> -1,2-Diphenylethylene (72), <i>trans</i> -1,2-diphenylethylene (17), 1,2-diphenylethane (11)
1		0.5	<i>cis</i> -1,2-Diphenylethylene (100)
		1	<i>cis</i> -1,2-Diphenylethylene (13), <i>trans</i> -1,2-diphenylethylene (73), 1,2-diphenylethane (14)
Clay ^a 1c	But-3-en-2-ol	24	No reaction
		5	Ethyl methyl ketone (7)
		5	Ethyl methyl ketone ^c (65)
2c		4	Ethyl methyl ketone ^c (85)
		2	0.1 Ethyl methyl ketone (100)

^a A water-swelled sodium montmorillonite (45 mg) which could contain 0.025 mmol of [Ir(cod)(PPh₃)₂]⁺. ^b Montmorillonite-supported [Ir(cod)(PPh₃)₂]⁺ {151 mg which was found to contain 0.025 mmol of [Ir(cod)(PPh₃)₂]⁺. ^c Isomerisation is much faster under H₂ than under N₂. Hydrogenation of the carbonyl group of the ketone occurs very slowly.

iridium powders [equation (6)], as does the reaction of **3** with H₂.¹⁶ Metallic powders have been produced from the reactions of M-cod (M = Ir¹⁸ or Pt¹⁹) complexes with H₂.

[Ir(cod)(PPh₃)₂]⁺-montmorillonite **1c** with NaClO₄. A small amount of compound **1** was obtained from the reaction of **1c** with excess of NaClO₄ (see Experimental section), which suggests that the desorption of [Ir(cod)(PPh₃)₂]⁺ from **1c** is much less favoured in the equilibrium (7).

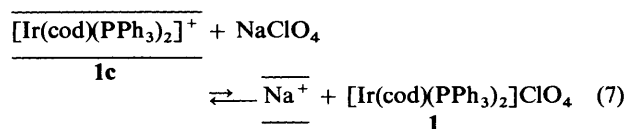

Catalysis.—The water-swelled sodium montmorillonite catalyses the hydrogenation of hex-1-ene, but it is not active for hydrogenation or isomerization of the other unsaturated

compounds in Table 2 under our experimental conditions. The catalytic hydrogenation and isomerization of olefins is, in general, considerably slower with **1c** and **2c** than with the soluble non-clay compounds **1** and **2** (see Table 2). The hydrogenation with iridium intercalated into the clay, **1c**, seems somewhat faster than that with the iridium supported on the clay, **1s**. Significant decreases in olefin hydrogenation rates were reported with Rh(PPh₃)_n⁺ between layers of hectorite.¹⁰ The hydrogenation of hex-1-ene and cycloocta-1,5-diene with **3c** was found to be rapid, which should be understood in terms of the heterogeneous catalysis by iridium metal powders since the reaction of **3c** with H₂ rapidly produces metallic powders of iridium [see equation (6)].

Intercalation of [Ir(cod)(PPh₃)₂]⁺ into the clay seems to depress more effectively the isomerization of hex-1-ene to -2-ene: the product ratio, hex-2-ene:hexane for the isomerization and hydrogenation of hex-1-ene is higher with compound **1** (3.3:1) than that with **1c** (1.7:1). A similar effect was prominent with [Rh(PPh₃)_n]⁺ in hectorite.¹⁰

Selective hydrogenation of the vinyl group of 4-vinylcyclohexene could be obtained to some extent by employing compounds **1c** and **2c** as catalysts: 4-ethylcyclohexene was the only product up to 44 and 32% of 4-vinylcyclohexene being hydrogenated with **1c** and **2c**, respectively, while a significant amount of ethylcyclohexane was always present in the reaction mixtures when **1** and **2** were used as catalysts (see Table 2).

Intercalation of [Ir(cod)(PPh₃)₂]⁺ into the clay seems to retard the *cis/trans* isomerization more effectively than the hydrogenation of 1,2-diphenylethylene. Both compounds **1** and **1c** catalyse the hydrogenation of diphenylacetylene to give the initial product *cis*-1,2-diphenylethylene which is isomerized to *trans*-1,2-diphenylethylene and hydrogenated to 1,2-diphenylethane. The ratio of *cis*- to *trans*-1,2-diphenylethylene in the reaction mixtures is considerably higher with **1c** (4.2:1) than with **1** (0.2:1) while about the same amounts (11% with **1c** and 14% with **1**) of 1,2-diphenylethane are produced (see Table 2).

Intercalation into the clay also suppresses the catalytic activities of the iridium complexes **1** and **2** for the isomerization of an unsaturated alcohol, but-3-en-2-ol, to give ethyl methyl ketone (see Table 2).

Finally it should be mentioned that compounds **1c** and **2c** released a small amount of PPh₃ and PhCN when they were stirred under the conditions for catalytic hydrogenation for more than 24 h.

Acknowledgements

We thank the Korea Science and Engineering Foundation for financial support and Lucky R & D Center for elemental analysis and X-ray diffraction measurements.

References

- B. M. Choudary and K. K. Rao, *Tetrahedron Lett.*, 1992, **33**, 121 and refs. therein.
- C. N. Rhodes, M. Franks, G. M. B. Parkes and D. R. Brown, *J. Chem. Soc., Chem. Commun.*, 1991, 804.
- M. Taniguchi, A. Yamagishi and T. Iwamoto, *Inorg. Chem.*, 1991, **30**, 2462.
- A. C. Cornelis, C. Dony, P. Laszlo and K. M. Nsunda, *Tetrahedron Lett.*, 1991, **32**, 1423.
- J. H. Clark, A. P. Kybett, D. J. Macquarrie, S. J. Barlow and P. Landon, *J. Chem. Soc., Chem. Commun.*, 1989, 1353.
- E. P. Giannelis and T. J. Pinnavaia, *Inorg. Chem.*, 1985, **24**, 3602 and refs. therein.
- F. Farzaneh and T. J. Pinnavaia, *Inorg. Chem.*, 1983, **22**, 2216.
- T. J. Pinnavaia, *ACS Symp. Ser.*, 1982, **192**, 241.
- M. Mozzei, W. Marconi and M. Riocci, *J. Mol. Catal.*, 1980, **9**, 381.
- T. J. Pinnavaia, R. Raythatha, J. G. Lee, L. J. Halloran and J. F. Hoffman, *J. Am. Chem. Soc.*, 1979, **101**, 6891.
- W. H. Quayle and T. J. Pinnavaia, *Inorg. Chem.*, 1979, **18**, 2840.
- T. J. Pinnavaia and P. K. Welty, *J. Am. Chem. Soc.*, 1975, **97**, 3819.

- 13 C. S. Chin and B. Lee, *J. Chem. Soc., Dalton Trans.*, 1991, 1323.
- 14 M. Green, T. A. Kuc and S. H. Taylor, *J. Chem. Soc. A*, 1971, 2334;
R. R. Schrock and J. A. Osborn, *J. Am. Chem. Soc.*, 1971, **93**, 3089;
V. W. Day, W. G. Klemperer and D. J. Main, *Inorg. Chem.*, 1990, **29**,
2345.
- 15 R. Uson, L. A. Oro, J. Artigas and R. Sariego, *J. Organomet. Chem.*,
1979, **179**, 65.
- 16 C. S. Chin and B. Lee, unpublished work.
- 17 M. J. Burk and R. H. Crabtree, *Inorg. Chem.*, 1986, **25**, 931.
- 18 D. A. Anton and R. H. Crabtree, *Organometallics*, 1983, **2**, 855; R. H.
Crabtree, M. F. Michelle, F. Mellea, J. M. Mihelcic and J. M. Quirk,
J. Am. Chem. Soc., 1982, **104**, 107.
- 19 T. R. Lee and G. M. Whitesides, *J. Am. Chem. Soc.*, 1991, **113**, 2568,
2576.

Received 7th September 1992; Paper 2/04804C