

This article was downloaded by:

On: 23 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Coordination Chemistry

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713455674>

A new vanadium Schiff base complex as catalyst for oxidation of alcohols

Mojtaba Bagherzadeh^a; Mojtaba Amini^a

^a Department of Chemistry, Sharif University of Technology, Tehran, Iran

Online publication date: 13 October 2010

To cite this Article Bagherzadeh, Mojtaba and Amini, Mojtaba(2010) 'A new vanadium Schiff base complex as catalyst for oxidation of alcohols', *Journal of Coordination Chemistry*, 63: 21, 3849 – 3858

To link to this Article: DOI: 10.1080/00958972.2010.520316

URL: <http://dx.doi.org/10.1080/00958972.2010.520316>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

A new vanadium Schiff base complex as catalyst for oxidation of alcohols

MOJTABA BAGHERZADEH* and MOJTABA AMINI

Department of Chemistry, Sharif University of Technology, PO Box 11155-3615,
Tehran, Iran

(Received 3 May 2010; in final form 19 July 2010)

The monoanionic bidentate Schiff base, *N*-(phenolyl)-benzaldimine (HL), has been employed to synthesize a new vanadium(IV) complex of general composition $[\text{VO}(\text{L})_2]$ (where L = O, N donor of Schiff base). The ligand and complex have been fully characterized by elemental analyses, molar conductance data, FT-IR, ^1H - and ^{13}C -NMR, and UV-Vis spectroscopies. Oxidation of alcohols to their corresponding aldehydes and ketones was conducted by this complex catalyst using Oxone as oxidant under biphasic reaction conditions ($\text{CH}_2\text{Cl}_2/\text{H}_2\text{O}$) and tetra-*n*-butylammonium bromide as phase transfer agent under air at room temperature.

Keywords: Bidentate Schiff base; Vanadium complex; Catalytic oxidation; Oxone


1. Introduction

Selective oxidation of alcohol to aldehydes and ketones is an important reaction in the laboratory and industry [1–4]. Traditionally, oxidizing reagents including dichromate and permanganate have been employed in order to accomplish this transformation [5, 6]. These reagents are moderately expensive, toxic, corrosive, unstable, without selectivity, dangerous to prepare, moisture-sensitive and tend to over-oxidize to carboxylic acids [7–9].


Transition metal complexes as catalysts in organic synthesis is an exciting field of research, and numerous reactions which are impossible to achieve by conventional synthetic methods have already been discovered [10–12]. There has been considerable interest in the chemistry of transition metal complexes of Schiff bases, due to the fact that Schiff bases stabilize many different metals in various oxidation states, controlling the performance of metals in useful transformations. Bidentate Schiff bases containing imine groups which can be used as modulators of structural and electronic properties of transition metal centers represent an important class of chelating ligands [13, 14].

Vanadium is an essential metal and exhibits great biological activity and potential medicinal applications when associated with certain metal–protein complexes, participating in oxygen transport, electron transfer reactions, or the storage of ions [15–19], creating enormous interest in study of systems containing this metal [20–28].

*Corresponding author. Email: bagherzadehm@sharif.edu



R, R' = alkyl, allyl, benzyl and H

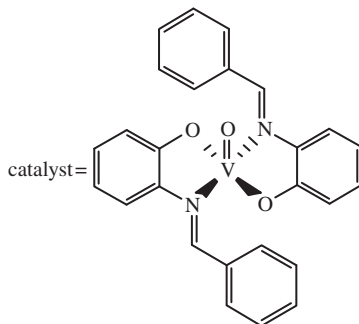

Scheme 1. The oxidation of alcohols by the $[\text{VO}(\text{L})_2]/\text{Oxone}/n\text{-Bu}_4\text{NBr}$ catalytic system.

However, activity of Schiff-base vanadium(IV) complexes toward catalytic oxidation in a homogeneous medium is not well documented with only a few vanadium(IV) Schiff-base complexes reported to be catalytically active toward alcohol oxidation [29].

In this article, we report the synthesis and characterization of the ligand, obtained from reaction of *benzaldehyde* with *o*-aminophenol, and its vanadium complex by physico-chemical methods and demonstrate the efficient and selective oxidation of alcohols to their corresponding aldehydes and ketones, using this bidentate Schiff-base vanadium complex under mild and biphasic conditions ($\text{CH}_2\text{Cl}_2/\text{H}_2\text{O}$) at room temperature with Oxone as oxidant (scheme 1).

2. Experimental

Chemical materials and solvents were purchased from Chemical companies, Fluka and Merck.

Elemental analyses (carbon, hydrogen, and nitrogen) were obtained from a Carlo ERBA Model EA 1108 analyzer. FT-IR spectra were obtained by using a Unicam Matson 1000 FT-IR spectrophotometer using KBr discs at room temperature. UV-Vis spectrum was recorded on a CARY 100 Bio VARIAN UV-Vis spectrophotometer in methanol. Molar conductances of the ligand and complex were determined in methanol ($ca\ 10^{-3}\ \text{mol L}^{-1}$) at room temperature using a Toa CM 405 conductivity meter. The ^1H - and ^{13}C -NMR spectra of the free ligand in CDCl_3 were obtained using a Bruker FT-NMR 500 MHz spectrometer. Melting points were taken on a Gallenkamp melting point apparatus. The reaction products of oxidation were determined and analyzed by a HP Agilent 6890 gas chromatograph equipped with a HP-5 capillary column (phenyl methyl siloxane $30\ \text{m} \times 320\ \mu\text{m} \times 0.25\ \mu\text{m}$) and flame-ionization detector.

2.1. Synthesis of *N*-(phenolyl)-benzaldimine

A solution of *o*-aminophenol (4.6 mmol, 0.50 g) in absolute EtOH (20 mL) was added to solution of benzaldehyde (4.6 mmol, 0.49 g) in absolute EtOH (20 mL) and the reaction mixture was refluxed at 80°C for 2 h. The solution was then evaporated to 15 mL and cooled to room temperature. The precipitated light yellow product was filtered off, washed with cooled ethanol and then dried in air. Yield: (87%); IR: 3329, 1623, 1580, 1481 cm⁻¹; ¹H-NMR (CDCl₃), δ: 8.75 (1H, s), 7.97 (2H, d), 7.54 (3H, m), 7.35 (1H, d), 7.27 (1H, t), 7.09 (1H, d), 6.97 (1H, t). ¹³C-NMR (CDCl₃): 157.58, 152.80, 136.30, 135.95, 132.13, 129.39, 129.32, 129.27, 120.56, 116.33, and 115.47. Elemental Anal. Calcd for C₁₃H₁₁NO: C, 79.19%; H, 5.58%; N, 7.11%. Found: C, 79.09%; H, 5.54%; N, 7.02%. UV-Vis (λ(ε, mol L⁻¹ cm⁻¹)): 216 (6559), 243 (10,543), 280 (5378), 341 (2612), Λ_M (Ω⁻¹ cm² mol⁻¹): 7.6, and m.p.: 87–89°C.

2.2. Synthesis of [VO(L)₂]

The ligand, HL (1.52 mmol) was dissolved in methanol (25 mL) and added to a methanol solution (20 mL) of [VO(acac)₂] (0.76 mmol) and the mixture was gently refluxed at 65°C for 3 h. After cooling, the resulting brown crystals were filtered and washed with cooled methanol and then dried in air. Yield: (63.17%). IR: 1595, 983 cm⁻¹, Elemental Anal. Calcd for C₂₆H₂₀N₂O₃V: C, 67.98%; H, 4.36%; N, 6.1%. Found: C, 67.81%; H, 4.39%; N, 6.02%. UV-Vis (λ(ε, mol L⁻¹ cm⁻¹)): 215, 238, 265, 430, 590, and Λ_M (Ω⁻¹ cm² mol⁻¹): 1.4.

2.3. Typical procedure

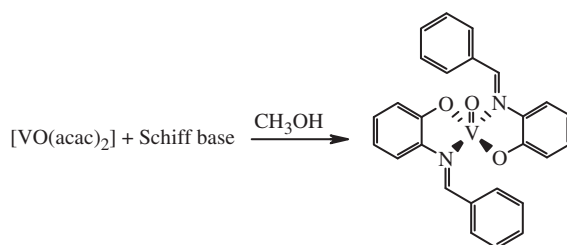
In a typical experiment, a solution of Oxone (0.2 mmol) in H₂O (5 mL) at room temperature was added to a solution of alcohol (0.2 mmol), tetra-*n*-butylammonium bromide (0.1 mmol), and [VO(L)₂] (0.01 mmol) in CH₂Cl₂ (1 mL), and the biphasic mixture stirred vigorously. Formation of products and consumption of substrates were monitored by GC. The identity of products was determined by comparison with authentic samples using gas–liquid chromatography. Oxidation product yields based on the oxidant were quantified by comparison with chlorobenzene.

3. Results and discussion

3.1. Complex characterization

A new vanadium(IV) complex, [VO(L)₂] (L = the anion of the Schiff base), has been prepared from [VO(acac)₂] (1 mol) and the Schiff base (2 mol) in methanol as shown in scheme 2. The complex is brown, stable to air and light and soluble in methanol, ethanol, acetonitrile, methylene chloride, DMF, and DMSO. The analytical data for the new complex (table 1) agrees very well with the proposed formula.

In order to study the binding mode of the Schiff base to vanadium in the new complex, IR spectra of the free ligand were compared with spectra of the vanadium complex. A strong band is observed in the free ligand at 1624 cm⁻¹, characteristic of

Scheme 2. Synthesis of complex [VO(L)₂].Table 1. Microanalytical and spectral data for HL and [VO(L)₂].

Ligand/complex	Solvent	UV-Vis		C, H, N			IR (cm ⁻¹)	Molar conductance
		λ (nm)	ϵ (mol L ⁻¹ cm ⁻¹)	C (%)	H (%)	N (%)		Λ_M (Ω^{-1} cm ² mol ⁻¹)
C ₁₃ H ₁₁ NO (HL) FW = 240.26 m.p. = 87–89°C	C ₂ H ₅ OH	216	(6559)	79.09	5.54	7.02	ν (O–H) 3330	7.6
		243	(10,543)	(79.19)	(5.58)	(7.11)	ν (C=N) 1624	
		280	(5378)					
		341	(2612)					
[VO(L) ₂] C ₂₆ H ₂₀ N ₂ O ₃ V FW = 458.94	C ₂ H ₅ OH	215, 238, 265		67.81	4.39	6.02	ν (O–H) Absent	1.4
		430, 590		(67.98)	(4.36)	(6.1)	ν (C=N) 1595	
							ν (V=O) 983	

azomethine (C=N) [30]. Coordination of the Schiff base to the metal through the azomethine nitrogen is expected to reduce the electron density in the azomethine and lower ν (C=N). In the spectra of the complex, ν (C=N) showed a negative shift to 1595 cm⁻¹, indicating coordination of the azomethine nitrogen to vanadium (table 1) [31, 32].

A medium intensity band, at 3330 cm⁻¹ in the free ligand due to ν (OH), was absent in the complex, indicating deprotonation of the Schiff base prior to coordination [31]. The complex exhibits characteristic and strong ν (V=O) at 983 cm⁻¹, indicating that there is no intermolecular interaction with participation of the oxovanadium moiety [30].

Molar conductivities of ligand and its complex in methanol were 7.6 and 1.4 Ω^{-1} cm² mol⁻¹, respectively, and are given in table 1. These results show that the ligand coordinates to the metal ions to form a neutral coordination compound. Molar conductances are much smaller than those of 1:1 electrolytes [33], thus they are considered to be non-electrolytes.

Electronic spectra of the ligand and its complex were recorded in EtOH (table 1). The ligand exhibits intraligand transitions at \sim 280 nm due to $\pi \rightarrow \pi^*$ transitions and at \sim 341 nm due to $n \rightarrow \pi^*$ transitions [34]. On complexation, these bands due to the azomethine are shifted to lower energy, supporting coordination of the imine nitrogen [34, 35]. In the spectra of the complex, new bands at 430 nm can be attributed to charge transfer bands (ligand to metal or metal to ligand) [36]. Bands at 590 nm in the complex come from the d–d transition of vanadium(IV).

Table 2. The effect of the nature of solvent/H₂O on the oxidation of benzylalcohol by the [VO(L)₂]/Oxone/*n*-Bu₄NBr catalytic system.^a

Entry	Solvent	Conversion (%) ^b
1	CH ₂ Cl ₂	91
2	CH ₃ Cl	79
3	CH ₃ CN	85
4	C ₆ H ₆	51
5	CH ₃ COCH ₃	81
6	CCl ₄	63
7	<i>n</i> -hexane	47

^aThe molar ratios for [VO(L)₂]:*n*-Bu₄NBr: benzylalcohol: Oxone are 1:10:20:20.

^bConversions (%) are measured after 5 min at room temperature.

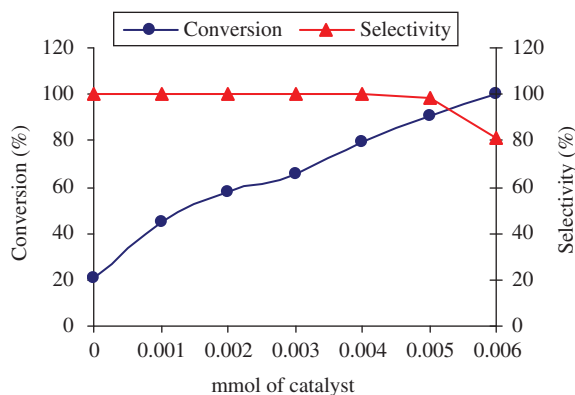


Figure 1. The effect of the amount of catalyst on oxidation of benzylalcohol by the [VO(L)₂]/Oxone/*n*-Bu₄NBr catalytic system. Reaction condition: benzylalcohol 0.2 mmol, Oxone 0.2 mmol, catalyst: *n*-Bu₄NBr = 0.1. Selectivity to benzaldehyde = (benzaldehyde% / (benzaldehyde% + benzoic acid%)) × 100.

3.2. Catalytic reaction

In order to evaluate catalytic activities of [VO(L)₂] for oxidation of alcohols, the reactions were optimized for oxidation of benzylalcohol through investigation of the influence of solvent, the amount of catalyst, and the amount of Oxone.

3.2.1. Effect of solvent on the oxidation of benzylalcohol. For finding the best solvent under biphasic reaction conditions, dichloromethane, chloroform, acetonitrile, benzene, acetone, carbon tetrachloride, and *n*-hexane were employed as solvents. Among the solvents examined, dichloromethane was found to be the best for this protocol (table 2).

3.2.2. Optimization of amount of catalyst. Figure 1 illustrates the effect of amount of catalyst on the conversion and the selectivity of benzylalcohol oxidation, at room temperature for 5 min in CH₂Cl₂/H₂O. The conversion of benzylalcohol increases with the addition of catalyst from 0.001 to 0.005 mmol. When the amount of catalyst is increased to 0.006 mmol, the selectivity of benzylalcohol oxidation reduces from 98% to

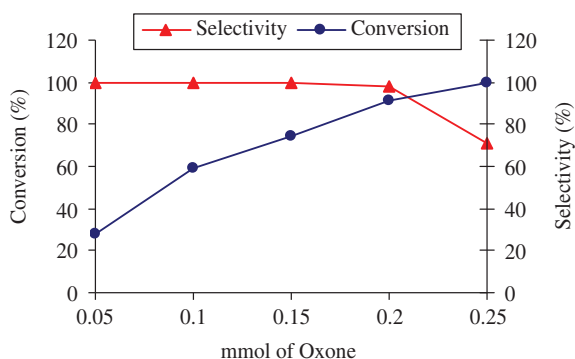


Figure 2. The effect of the amount of Oxone on oxidation of benzylalcohol by the $[\text{VO}(\text{L})_2]/\text{Oxone}/n\text{-Bu}_4\text{NBr}$ catalytic system. Reaction condition: benzylalcohol 0.2 mmol, catalyst 0.005 mmol, $n\text{-Bu}_4\text{NBr}$ 0.05 mmol.























81%. The reaction without catalyst proceeds only very slightly. Hence, the amount of catalyst enhances the reaction rate for selective oxidation of benzylalcohol.

3.2.3. Optimization of amount of Oxone. The amount of Oxone could also affect the conversion and benzaldehyde selectivity (figure 2). When the amount of Oxone was increased from 0.05 to 0.2 mmol, the conversion of benzylalcohol increased from 28% to 91%. With a further increase of Oxone to 0.25 mmol, the selectivity to benzaldehyde decreases from 98% to 71%, although the conversion of benzylalcohol also increased from 91% to 100%.

3.2.4. Oxidation of alcohols with Oxone catalyzed by $[\text{VO}(\text{L})_2]$. Reactions were performed at room temperature under air in $\text{CH}_2\text{Cl}_2/\text{H}_2\text{O}$ containing $[\text{VO}(\text{L})_2]$, tetra- n -butylammonium bromide, substrate, and Oxone in 1:10:20:20 molar ratio, respectively. The system was applicable for oxidation of a wide variety of primary and secondary alcohols to corresponding aldehydes and ketones (table 3).

Benzylalcohols were oxidized to give the corresponding aldehydes with 86–98% conversion (entries 1–8). Substrates having electron-donating and -withdrawing substituents in the aromatic ring were compatible with this protocol. The change of nature and site of substituents (methyl, methoxy, chloro, and nitro) in the aromatic ring of benzylalcohol to probe the electronic effects displayed no regular trends in the conversion. The catalytic oxidation system can over-oxidize aldehyde product to carboxylic acid (2% for benzylalcohol oxidation at 5 min, table 3, entry 1). With the increase in the reaction time up to 30 min, more reduction of selectivity was observed due to over-oxidation (e.g., 9% benzoic acid is formed in the benzylalcohol oxidation after 30 min). Aliphatic alcohols and secondary alcohols were less reactive in comparison to aromatic alcohols (entries 9–19). Secondary alcohols, e.g., diphenylmethanol and 1-phenylpropanol, could be converted to the corresponding ketones in 76–80% conversion (entries 9 and 10). Oxidations of borneol and 2-isopropyl-5-methylcyclohexanol require longer reaction time (30 min) to afford the corresponding ketones (entries 15 and 16).

Table 3. Oxidation of alcohols by the [VO(L)₂]-Oxone-*n*-Bu₄NBr catalytic system.^a

Entry	Substrate	Product	Conversion (%) ^b (TON) ^c	Selectivity to aldehyde (%) ^d
1			91(18.2)	98
2			95(19)	97
3			96(19.2)	96
4			91(18.2)	98
5			98(19.6)	97
6			86(17.2)	100
7			89(17.8)	100
8			92(18.4)	98
9			80(16)	100
10			76(15.2)	100
11			63(12.6)	100

(Continued)

Table 3. Continued.

Entry	Substrate	Product	Conversion (%) ^b (TON) ^c	Selectivity to aldehyde (%) ^d
12			68(13.6)	100
13			72(14.4)	100
14			75(15)	100
15			61 ^e (12.2)	100
16			59 ^e (11.8)	100
17			71(14.2)	100
18			63(12.6)	100
19			61(12.2)	100

^aThe molar ratio for [VO(L)₂]: *n*-Bu₄NBr: benzylalcohol: Oxone is 1:10:20:20.

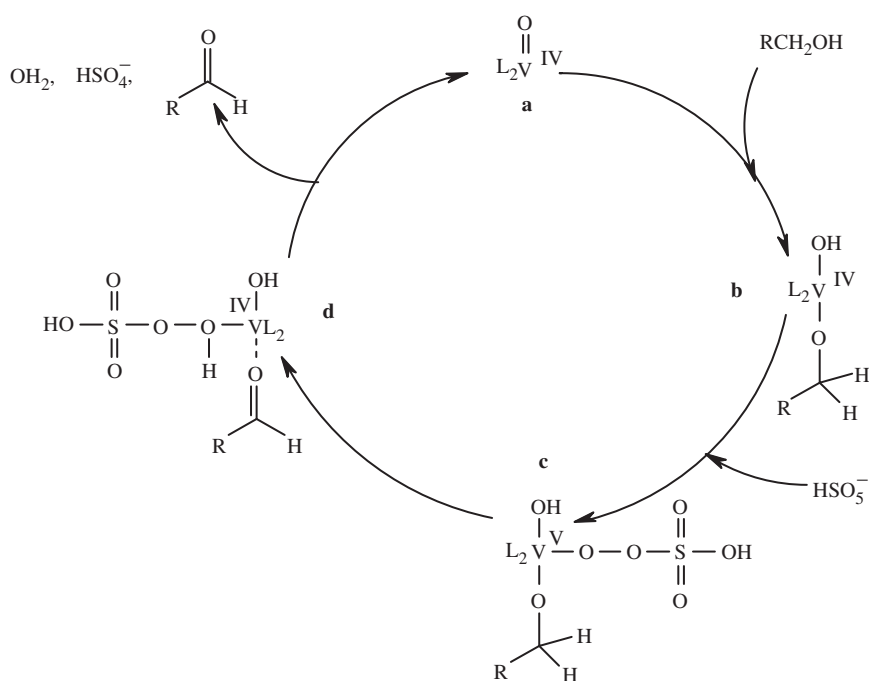
^bConversions (%) are measured relative to the starting alcohol after 5 min.

^cmmol of product/mmol of catalyst.

^dSelectivity to benzaldehyde = (aldehyde% / (aldehyde% + carboxylic acid%)) × 100.

^eThe reactions were run for 30 min at room temperature.

Exact mechanism for the catalytic oxidation of alcohols catalyzed by oxovanadium(IV) complex in the presence of Oxone is not clear at present. However, based on the nature of oxidation products, optimization results that indicate the reaction yield depends on both catalyst and oxidant concentration, and previously



Scheme 3. Proposed mechanism for alcohol oxidation by the $[\text{VO}(\text{L})_2]/\text{Oxone}/n\text{-Bu}_4\text{NBr}$ catalytic system.

reported mechanism [37, 38], a catalytic cycle is proposed in scheme 3. The alcohol can coordinate to $[\text{VO}(\text{L})_2]$, **a**, to provide the complex **b**. Then **b** reacts with Oxone to give a corresponding intermediate **c** that can readily undergo intramolecular hydrogen abstraction to give the intermediate **d**. Finally, with separation of aldehyde or ketone, water and hydrogen sulfate of intermediate **d** and regeneration of catalyst **a**, the catalytic cycle is completed.

4. Conclusion

The complex $[\text{VO}(\text{L})_2]$ has been synthesized and characterized by physico-chemical methods. We have demonstrated the effectiveness of a vanadium(IV) complex as catalyst for oxidation of different alcohols to carbonyl compounds with Oxone. Easy preparation, mild reaction condition, high yields of the products, short reaction time, no further oxidation to the corresponding carboxylic acids, high selectivity, and an inexpensive system make this catalytic system a useful method for oxidizing alcohols.

Acknowledgments

Financially support of this study by the Research Council of Sharif University of Technology is greatly appreciated.

References

- [1] T. Mallat, A. Baiker. *Chem. Rev.*, **104**, 3037 (2004).
- [2] M. Hudlucky. *Oxidations in Organic Chemistry*, ACS Monograph Series, American Chemical Society, Washington, DC (1990).
- [3] N. Thilagavathi, A. Manimaran, C. Jayabalakrishnan. *J. Coord. Chem.*, **63**, 1252 (2010).
- [4] M. Bagherzadeh. *Tetrahedron Lett.*, **44**, 8943 (2003).
- [5] R.A. Sheldon, I.W.C.E. Arends, A. Dijkman. *Catal. Today*, **57**, 157 (2000).
- [6] S.V. Ley, A. Madin. In *Comprehensive Organic Synthesis*, B.M. Trost, I. Fleming (Eds), Vol. 7, p. 251, Pergamon Press, Oxford (1991).
- [7] S.V. Ley, J. Norman, W.P. Griffith, S.P. Marsden. *Synthesis*, 639 (1994).
- [8] R.V. Stevens, K.T. Chapman, H.N. Waite. *J. Org. Chem.*, **45**, 2030 (1980).
- [9] A.R. Hajipour, S.E. Mallakpour, S. Khoee. *Synlett.*, 740 (2000).
- [10] R. DelRosso, A. Kaddouri, C. Mazzocchia, P. Gronchi, P. Cèntola. *Catal. Lett.*, **69**, 71 (2000).
- [11] M. Bagherzadeh, L. Tahsini, R. Latifi, A. Ellern, L.K. Woo. *Inorg. Chim. Acta*, **361**, 2019 (2008).
- [12] M. Bagherzadeh, M. Amini. *Inorg. Chem. Commun.*, **12**, 21 (2009).
- [13] T. Opstal, F. Verpoort. *Angew. Chem. Int. Ed.*, **42**, 2876 (2003).
- [14] N. Sathya, P. Muthusamy, N. Padmapriya, G. Rajaa, K. Deivasigamani, C. Jayabalakrishnan. *J. Coord. Chem.*, **62**, 3532 (2009).
- [15] H. Sigel, A. Sigel (Eds), *Vanadium and its Role in Life, Metal Ions in Biological Systems*, Vol. 31, Marcel Dekker, New York (1995).
- [16] J.O. Nriagu (Ed.), *Vanadium in the Environment*, Vol. 23, John Wiley & Sons, New York (1998).
- [17] A.A. Nejo, G.A. Kolawole, A.R. Opoku, C. Muller, J. Wolowska. *J. Coord. Chem.*, **62**, 3411 (2009).
- [18] D.C. Crans, J.J. Smee, E. Gaidamauskas, L. Yang. *Chem. Rev.*, **104**, 849 (2004).
- [19] A.S. Tracey, G.R. Willsky, E.S. Takeuchi. *Vanadium – Chemistry, Biochemistry, Pharmacology and Practical Applications*, CRC Press, Boca Raton, FL (2007).
- [20] D. Rehder. *Bioinorganic Vanadium Chemistry*, John Wiley & Sons, Chichester (2008).
- [21] T. Hirao. *Chem. Rev.*, **97**, 2707 (1997).
- [22] P.M. Reis, J.A.L. Silva, A.F. Palava, J.J.R. Fraústo da Silva. *J. Catal.*, **235**, 333 (2005).
- [23] M.S. Rigutto, H. van Bekkum. *J. Mol. Catal.*, **81**, 77 (1993).
- [24] C.U. Dinesh, R. Kumar, B. Pandey, P. Kumar. *J. Chem. Soc., Chem. Commun.*, 611 (1995).
- [25] S.K. Das, A. Kumar Jr, S. Nandrajog, A. Kumar. *Tetrahedron Lett.*, **36**, 7909 (1995).
- [26] G.B. Shul'pin, G.S. Mishra, L.S. Shul'pina, T.V. Strelkova, A.J.L. Pombeiro. *Catal. Commun.*, **8**, 1516 (2007).
- [27] H.M. Alvarez, J.L. de Andrade, N. Pereira Jr, E.M.F. Muri, A. Horn Jr, D.P. Barbosa, O.A.C. Antunes. *Catal. Commun.*, **8**, 1336 (2007).
- [28] S. Velusamy, T. Punniyamurthy. *Org. Lett.*, **6**, 217 (2004).
- [29] S. Bunce, R.J. Cross, L.J. Farrugia, S. Kunchandy, L.L. Meason, K.W. Muir, M. O'Donnell, R.D. Peacock, D. Stirling, S.J. Teat. *Polyhedron*, **17**, 4179 (1998).
- [30] S.K.S. Hazari, J. Kopf, D. Palit, S. Rakshit, D. Rehder. *Inorg. Chim. Acta*, **362**, 1343 (2009).
- [31] B. Khera, A.K. Sharma, N.K. Kaushik. *Polyhedron*, **2**, 1177 (1983).
- [32] M. Tümer, H. Köksal, S. Serin, M. Digrak. *Transition Met. Chem.*, **24**, 13 (1998).
- [33] W.J. Geary. *Coord. Chem. Rev.*, **7**, 81 (1971).
- [34] M. Tümer, C. Çelik, H. Köksal, S. Serin. *Transition Met. Chem.*, **24**, 525 (1999).
- [35] M. Tümer, H. Köksal, S. Serin. *Synth. React. Inorg. Met. Org. Chem.*, **26**, 1589 (1996).
- [36] M. Tümer, H. Köksal, S. Serin, S. Patat. *Synth. React. Met. Org. Chem.*, **27**, 59 (1997).
- [37] S.P. Maradur, S.B. Halligudi, G.S. Gokavi. *Catal. Lett.*, **96**, 165 (2004).
- [38] S.R. Reddy, S. Das, T. Punniyamurthy. *Tetrahedron Lett.*, **45**, 3561 (2004).