

This article was downloaded by:

On: 24 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Macromolecular Science, Part A

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713597274>

Novel Copolymers of Vinyl Acetate and Some Ring-Substituted 2-Phenyl-1,1-dicyanoethylenes

Gregory B. Kharas^a; Selena M. Russell^a; Vyvy Tran^a; Quenette L. Tolefree^a; Diana M. Tulewicz^a; Agnieszka Gora^a; Jasmina Bajgoric^a; Michael T. Balco^a; GERALYN A. DICKEY^a; George Kladis^a

^a Chemistry Department, DePaul University, Illinois, USA

To cite this Article Kharas, Gregory B. , Russell, Selena M. , Tran, Vyvy , Tolefree, Quenette L. , Tulewicz, Diana M. , Gora, Agnieszka , Bajgoric, Jasmina , Balco, Michael T. , Dickey, GERALYN A. and Kladis, George(2008) 'Novel Copolymers of Vinyl Acetate and Some Ring-Substituted 2-Phenyl-1,1-dicyanoethylenes', *Journal of Macromolecular Science, Part A*, 45: 1, 5 – 8

To link to this Article: DOI: 10.1080/10601320701681813

URL: <http://dx.doi.org/10.1080/10601320701681813>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Novel Copolymers of Vinyl Acetate and Some Ring-Substituted 2-Phenyl-1,1-dicyanoethylenes

GREGORY B. KHARAS, SELINA M. RUSSELL, VYVY TRAN, QUENETTE L. TOLEFREE, DIANA M. TULEWICZ, AGNIESZKA GORA, JASMINA BAJGORIC, MICHAEL T. BALCO, GERALYN A. DICKEY, and GEORGE KLADIS

Chemistry Department, DePaul University, Illinois, USA

Received and accepted July, 2007

Electrophilic trisubstituted ethylene monomers, some ring-substituted 2-phenyl-1,1-dicyanoethylenes, $\text{RC}_6\text{H}_4\text{CH}=\text{C}(\text{CN})_2$ (where R is 3- $\text{C}_6\text{H}_5\text{O}$, 4- $\text{C}_6\text{H}_5\text{O}$, 3- $\text{C}_6\text{H}_5\text{CH}_2\text{O}$, 4- $\text{C}_6\text{H}_5\text{CH}_2\text{O}$, 4- CH_3CO_2 , 4- CH_3CONH , 4- $(\text{C}_2\text{H}_5)_2\text{N}$) were synthesized by piperidine catalyzed Knoevenagel condensation of ring-substituted benzaldehydes and malononitrile, and characterized by CHN elemental analysis, IR, ^1H - and ^{13}C -NMR. Novel copolymers of the ethylenes and vinyl acetate were prepared at equimolar monomer feed composition by solution copolymerization in the presence of a radical initiator (ABCN) at 70°C. The composition of the copolymers was calculated from nitrogen analysis, and the structures were analyzed by IR, ^1H and ^{13}C -NMR, GPC, DSC, and TGA. High T_g of the copolymers, in comparison with that of polyvinyl acetate, indicates a substantial decrease in chain mobility of the copolymer due to the high dipolar character of the trisubstituted ethylene monomer unit. The gravimetric analysis indicated that the copolymers decompose in the 190–700°C range.

Keywords: trisubstituted ethylenes; radical copolymerization; vinyl acetate copolymers

1 Introduction

Trisubstituted ethylenes (TSE, $\text{CHR}^1=\text{CR}^2\text{R}^3$) continue attract attention of polymer chemists as reactive comonomers and as models for mechanistic studies. It was shown that electrophilic tri- and tetrasubstituted olefins are particularly useful in delineating the transition from radical chemistry to ionic chemistry (1). Previous studies showed that TSE containing substituents larger than fluorine have very low reactivity in radical homopolymerization due to polar and steric reasons. Although steric difficulties preclude homopolymerization of most tri- and tetrasubstituted olefins, their copolymerization with a monosubstituted alkene makes it possible to overcome these steric problems (2). Copolymerization of TSE having double bonds substituted with halo, cyano, and carbonyl groups and electron-rich monosubstituted ethylenes such as styrene, *N*-vinylcarbazole, and vinyl acetate (3–5) show a tendency toward the formation of alternating copolymers. Ring-unsubstituted 2-phenyl-1,1-dicyanoethylene was copolymerized with styrene (6), vinyl ethers (7), methyl

methacrylate (8), and *N*-vinyl-2-pyrrolidone (9). In relation to applications, piezoelectric activity was observed in copolymer of 1,1-dicyanoethylene (vinyledene cyanide) and vinyl acetate (10). Unlike fluoropolymers, this copolymer is amorphous with high T_g of 178°C and has alternating monomer unit structure. The copolymer has impedance similar to that of human body and has been suggested for medical applications as an ultrasonic transducer (11). When a high electric field is imposed to the copolymer film near its glass transition temperature, a thin fiber-like assembly about 10 nm thick appears on the surface (12). This behavior in electrical field (piezoelectrical and dielectrical) has been attributed to a strong dipole moment of nitrile groups and the presence of free volume which capable to abate electrostatic interactions between vinyl acetate dipoles and facilitating orientation of these dipoles in the direction of the applied field (13).

In continuation of our studies of the monomer structure-reactivity correlation in the radical copolymerization of ring-substituted 2-phenyl-1,1-dicyanoethylene monomers (14–16) we have prepared some ring-substituted 2-phenyl-1,1-dicyanoethylenes, $\text{RC}_6\text{H}_4\text{CH}=\text{C}(\text{CN})_2$ (where R is 3- $\text{C}_6\text{H}_5\text{O}$, 4- $\text{C}_6\text{H}_5\text{O}$, 3- $\text{C}_6\text{H}_5\text{CH}_2\text{O}$, 4- $\text{C}_6\text{H}_5\text{CH}_2\text{O}$, 4- CH_3CO_2 , 4- CH_3CONH , 4- $(\text{C}_2\text{H}_5)_2\text{N}$), and explore the feasibility of their copolymerization with vinyl acetate.

Address correspondence to: Gregory B. Kharas, Chemistry Department, DePaul University, IL 60614-3214, USA. Fax: 773-325-7421; E-mail: gkharas@depaul.edu

2 Experimental

2.1 General Procedures

Infrared spectra of the TSE monomers (NaCl plates) and polymers (KBr pellets) were determined with a Nicolet Avatar 360 FT-IR spectrometer. The melting points of the monomers and the glass transition temperatures (T_g) of the copolymers were measured with TA (Thermal Analysis, Inc.) Models 2010 and Q10 differential scanning calorimeters (DSC). The thermal scans were performed in 25 to 200°C range at a heating rate of 10°C/min. T_g was taken as a midpoint of a straight line between the inflection of the peak's onset and endpoint. The thermal stability of the copolymers was measured by thermogravimetric analyzers TA Models 2090 and Q50 from ambient temperature to 800°C at 20°C/min. The molecular weights of the polymers were determined relative to polystyrene standards in THF solutions with sample concentrations 0.8% (wt./vol.) by gel permeation chromatography (GPC) using a using a Altech 426 pump at an elution rate of 1.0 mL/min; TSK-GEL G4000H_{HR} column at 25°C, and Viscotek 302 and Viscotek UV 2501 detector. ¹H- and ¹³C-NMR spectra were obtained on 10–25% (w/v) monomer or polymer solutions in CDCl₃ at ambient temperature using a Bruker Avance 300 MHz spectrometer. Elemental analyses were performed by Quantitative Technologies Inc. (NJ).


2.2 Synthesis of Monomers

The TSE monomers were synthesized by Knoevenagel condensation (17) of some ring-substituted benzaldehydes with malononitrile, catalyzed by base, piperidine (Sch. 1).

3-C₆H₅O, 4-C₆H₅O, 3-C₆H₅CH₂O, 4-C₆H₅CH₂O, 4-CH₃CO₂, 4-CH₃CONH, 4-(C₂H₅)₂N-substituted benzaldehydes, malononitrile, and piperidine supplied from Aldrich Chemical Co., were used for monomer synthesis as received. The preparation procedure was essentially the same for all the monomers. In a typical synthesis, equimolar amounts of malononitrile and an appropriate ring-substituted benzaldehyde were mixed with a small amount of DMF in an Erlenmeyer flask. A few drops of piperidine were added with stirring. The crystalline product of the reaction was isolated by filtration and purified by crystallization from 2-propanol.

2.2.1 2-(3-Phenoxyphenyl)-1,1-dicyanoethylene

Yield: 79%; mp 67°C; ¹H-NMR δ 7.8–6.8 (9H, m, Ph-H), 7.8 (1H, s, C=CH); ¹³C-NMR δ 83 (>C=), 160 (HC=), 158,

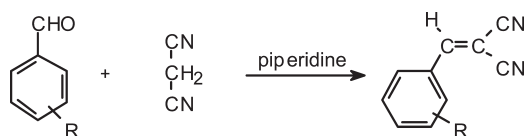

Sch. 1. Monomer synthesis (where R is 3-C₆H₅O, 4-C₆H₅O, 3-C₆H₅CH₂O, 4-C₆H₅CH₂O, 4-CH₃CO₂, 4-CH₃CONH, 4-(C₂H₅)₂N).

157, 133, 130, 128, 123, 118, 112 (Ph), 113 (CN); IR 3346, 3229, 3038, 2927 (s, CH), 2229 (m, CN), 1696, 1642, 1572 (m, Ar C=C), 1255, 1212 (s, C-O), 770, 693 (m, Ph); Anal. Calc. for C₁₆H₁₀N₂O: C, 78.04%, H, 4.09%, N, 11.38%; Found: C, 76.40; H, 4.15; N, 11.75.

2.2.2 2-(4-Phenoxyphenyl)-1,1-dicyanoethylene

Yield: 71%; mp 75°C; ¹H-NMR δ 7.9–6.8 (9H, m, Ph-H), 7.7 (1H, s, C=CH); ¹³C-NMR δ 77 (>C=), 160 (HC=), 164, 157, 133, 130, 123, 118, 112 (Ph), 113 (CN); IR 3029, 2927 (s, CH), 2215 (m, CN), 1606, 1555, 1500, 1487 (s, Ph C=C), 1254, 1193, 1165 (s, C-O), 864, 837 (p, Ph); Anal. Calc. for C₁₆H₁₀N₂O: C, 78.04%, H, 4.09%, N, 11.38%; Found: C, 77.14; H, 3.90; N, 11.77.

2.2.3 2-(3-Benzyloxyphenyl)-1,1-dicyanoethylene

Yield: 96%; mp 130°C; ¹H-NMR δ 7.8 (1H, s, =CH), 7.7–7.2 (9H, m, Ph-H), 5.2 (2H, s, OCH₂); ¹³C-NMR δ 160 (1H, s, CH=), 159, 137, 133, 130, 129, 128, 127, 118, 112 (Ph), 113 (CN), 83 (>C=), 70 (OCH₂); IR 2938 (C-H stretch), 2224 (s, CN), 1680, 1586 (s, C=C), 1273 (s, C-O), 780, 731 (Ph). Anal. Calc. for C₁₇H₁₂N₂O: C, 78.48%, H, 4.65%, N, 10.76%; Found: C, 77.44%, H, 4.10%, N, 10.28%.

2.2.4 2-(4-Benzyloxyphenyl)-1,1-dicyanoethylene

Yield 98%; mp 156°C; ¹H-NMR δ 7.9 (1H, s, =CH), 7.9–7.1 (9H, m, Ph-H), 5.2 (2H, s, OCH₂); ¹³C-NMR δ 160 (CH=), 164, 137, 134, 129, 128, 127, 115 (Ph), 113 (CN), 77 (>C=), 70 (OCH₂); IR 3032 (C-H stretch), 2223 (s, CN), 1599, 1567 (s, C=C), 1277 (s, C-O), 786, 778 (m, Ph). Anal. Calc. for C₁₇H₁₂N₂O: C, 78.48%, H, 4.65%, N, 10.76%; Found: C, 77.69%, H, 4.43%, N, 10.86%.

2.2.5 2-(4-Acetoxyphenyl)-1,1-dicyanoethylene


Yield 71%; mp 108°C; ¹H-NMR δ 7.9 (1H, s, =CH), 7.9–7.2 (4H, m, Ph-H), 2.3 (3H, s, CH₃); ¹³C-NMR δ 169 (C=O), 160 (CH=), 164, 134, 124, 122 (Ph), 113 (CN), 77 (>C=), 21 (CH₃); IR 3024 (C-H stretch), 2224 (s, CN), 1720 (s, C=O), 1597, 1562 (s, C=C), 1273 (s, C-O), 776, 758 (m, Ph). Anal. Calc. for C₁₂H₈N₂O₂: C, 67.92%, H, 3.80%, N, 13.20%; Found: C, 67.75%, H, 3.53%, N, 13.14%.

2.2.6 2-(4-Acetamidophenyl)-1,1-dicyanoethylene

Yield 50%; mp 238°C; ¹H-NMR δ 7.7 (1H, s, =CH), 7.9–7.3 (4H, m, Ph-H), 2.2 (3H, s, CH₃); 9.5 (1H, s, NH); ¹³C-NMR δ 169 (C=O), 160 (CH=), 145, 132, 126 (Ph), 114 (CN), 78 (>C=), 21 (CH₃); IR 3620 (b, NH), 3018 (C-H stretch), 2222 (s, CN), 1726 (s, C=O), 1596, 1561 (s, C=C), 1273 (s, C-O), 778, 762 (m, Ph). Anal. Calc. for C₁₂H₉N₃O: C, 68.24%, H, 4.29%, N, 19.89%; Found: C, 68.00%, H, 3.98%, N, 19.80%.

2.2.7 2-(4-Diethylaminophenyl)-1,1-dicyanoethylene

Yield 81%; mp 133°C; ¹H-NMR δ 7.7 (1H, s, =CH), 7.6–6.1 (4H, m, Ph-H), 3.5 (2H, q, CH₂), 1.2 (3H, s, CH₃); ¹³C-NMR δ 160 (CH=), 147, 132, 126, 111 (Ph), 113 (CN), 78 (>C=),

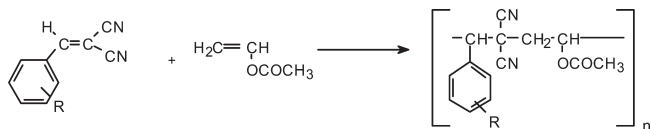

Sch. 2. Copolymer synthesis (where R is 3-C₆H₅O, 4-C₆H₅O, 3-C₆H₅CH₂O, 4-C₆H₅CH₂O, 4-CH₃CO₂, 4-CH₃CONH, 4-(C₂H₅)₂N).

44 (CH₂), 13 (CH₃); IR 3027 (C-H stretch), 2223 (s, CN), 1597, 1567 (s, C=C), 1271 (s, C-O), 776, 761 (m, Ph). Anal. Calc. for C₁₄H₁₅N₃: C, 74.64%, H, 6.71%, N, 18.65%; Found: C, 73.95%, H, 6.44%, N, 18.39%.

2.3 Copolymerization

Vinyl acetate and ethyl acetate (Aldrich) were used as received. 1,1'-Azobis(cyclohexanecarbonitrile) (ABCN) (Aldrich) was recrystallized twice from ethyl alcohol and then dried under reduced pressure at room temperature. Copolymers of the TSE monomers and vinyl acetate were prepared in 25-mL glass screw cap vials at TSE/VAC = 1/1 molar ratio of the monomer feed using 0.12 mol/L of ABCN at an overall monomer concentration 2.44 mol/L in 10 mL of ethyl acetate. The copolymerization was conducted at 70°C. After a predetermined time, the mixture was cooled to room temperature, and precipitated dropwise in petroleum ether. The crude copolymers were purified by reprecipitation from chloroform solution into an excess of petroleum ether. The composition of the copolymers was determined based on the nitrogen content.

3 Results and Discussion

3.1 Monomer Synthesis

The TSE monomers were synthesized by Knoevenagel condensation (17) of a ring-substituted benzaldehyde with an active hydrogen compound, malononitrile, catalyzed by a base, piperidine (Sch. 1). The condensation reaction

proceeded smoothly, yielding crystalline products, which were purified by conventional techniques.

3.2 Homopolymerization

An attempted homopolymerization of the TSE monomers in the presence of ABCN did not produce any polymer as indicated by the lack of a precipitate in methanol. Inability of the monomers to polymerize is associated with steric difficulties encountered in homopolymerization of 1,1- and 1,2-disubstituted ethylenes. Homopolymerization of VAC under conditions identical to those in the copolymerization experiments yielded 28.7% of poly(vinyl acetate), when polymerized for 30 minutes.

3.3 Copolymerization

Copolymerization (Sch. 2) of vinyl acetate and some ring-substituted 1,1-dicyanoethylenes resulted in formation of copolymers (Table 1) with weight-average molecular masses 1.5×10^3 to 2.9×10^3 daltons. According to elemental analysis, the copolymers have equimolar composition, which is indicative of high reactivity of the monomers in cross-propagation reactions.

3.4 Structure and Properties

A comparison of the spectra of the copolymers and polyvinyl acetate shows that the reaction between the TSE monomers and VAC is a copolymerization. All the IR spectra of the copolymers show overlapping bands in 3000–2800 cm⁻¹ region corresponding to C-H vibrations. The absorptions of the VAC units appear at 1747–1767 cm⁻¹ (carbonyl group), 1370–1375 cm⁻¹ (wagging CH₃), 1210–1270 cm⁻¹ (stretching COO), and 1010 and 1110 cm⁻¹ (stretching C-C-C). The bands for the TSE monomer unit are 2225–2235 cm⁻¹ (w, CN), 1580, 850–650 for the phenyl group. The broadening of the NMR signals in the spectra of the copolymers is apparently associated with

Table 1. Copolymerization of vinyl acetate (M₁) and ring-substituted 1,1-dicyanoethylenes, RC₆H₄CH=C(CN)₂ (M₂)

R	Yield, ^a wt.%	Nitrogen, wt.%	M ₂ in copolymer, mol%	M _w × 10 ⁻³ , D	T _g ^b , °C	TGA			
						Onset of decomp., °C	10% wt. loss, °C	50% wt. loss, °C	Residue wt.%
3-C ₆ H ₅ O	25	8.23	47.82	2.6	138	197	278	363	14
4-C ₆ H ₅ O	15	8.18	47.27	2.5	142	201	236	340	12
3-C ₆ H ₅ CH ₂ O	29	8.02	49.22	1.5	136	198	237	323	18
4-C ₆ H ₅ CH ₂ O	18	7.96	48.49	2.9	140	203	311	358	24
4-CH ₃ CO ₂	19	9.26	48.85	1.9	146	204	261	335	18
4-CH ₃ CONH	21	13.74	47.69	1.7	148	205	241	371	27
4-(C ₂ H ₅) ₂ N	17	13.22	48.23	1.7	137	206	233	304	12

^aPolymerization time was 8 h.

^bT_g transition was observed by DSC.

head-to-head structures, which formed through the attack of a VAC-ended radical on both sides of the TSE monomer unit (18). Thus, the ^1H -NMR spectrum of the unsubstituted TSE-VAC copolymer shows a broad peak in the 6.2–7.5 ppm region corresponding to the phenyl ring protons of TSE. A broad signal in the 5.7 ppm region is assigned to the VAC methine protons. The resonance signal at 2.8 ppm is assigned to the methine proton of TSE unit. The band at 1.6 ppm is assigned to methyl protons whereas the two shoulders at 1.2 and 0.9 are assigned to the methylene of VAC unit. The ^{13}C -NMR spectra of the copolymers also support the suggested skeletal structure of the copolymers. Thus, in the typical spectrum of the VAC-TSE copolymer the assignment of peaks as follows 170 ppm ($\text{C}=\text{O}$), 115–133 ppm (phenyl carbons), 160 ppm (phenyl carbons bonded to halogen), 121 ppm (CN) of TSE unit. The absorbance at 170 and 21 ppm may be assigned to the carbonyl and methyl of VAC. The absorptions at 45 and 74 ppm are assigned to the methylene and the methine signals carbon resonances respectively, of the VAC unit. IR and NMR data showed that these are true copolymers, composed of both TSE and VAC monomer units. The copolymers prepared in the present work are all soluble in methyl ethyl ketone, acetone, benzene, THF, DMF and CHCl_3 and insoluble cyclohexane, and in ethyl and petroleum ether. They are amorphous and show no crystalline DSC endotherm. Relatively high T_g of the copolymers (Table 1) in comparison with that of polyvinyl acetate ($T_g = 28\text{--}31^\circ\text{C}$) indicates decrease of chain mobility of the copolymer due to the high dipolar character of the TSE structural units.

Information on the degradation of the copolymers was obtained from thermogravimetric analysis. The TGA in nitrogen and air produce similar traces. The decomposition of the copolymers occurred in two steps, presumably acetic acid elimination in $197\text{--}380^\circ\text{C}$ range followed by a more slow decomposition of the formed residue at $380\text{--}800^\circ\text{C}$. Such two step degradation, acetic acid elimination followed by polyacetylene degradation is known for polyvinyl acetate (19). The decomposition products were not analyzed in this study, and the mechanism has yet to be investigated.

4 Conclusions

Novel trisubstituted ethylenes, ring-substituted 2-phenyl-1,1-dicyanoethylene were prepared via a base catalyzed condensation of appropriate substituted benzaldehyde and malononitrile. The copolymerization of the monomers with vinyl acetate results in equimolar alternating copolymers. The composition of the copolymers was calculated from nitrogen analysis and the structure was analyzed by IR, ^1H - and ^{13}C -NMR. High glass transition temperature of the copolymers in comparison with that of polyvinyl acetate indicates a substantial decrease in chain mobility of the copolymer due to the high dipolar character of the trisubstituted monomer unit. The

decomposition of the copolymers occurred in two steps, acetic acid elimination in $197\text{--}380^\circ\text{C}$ range followed by a more slow decomposition of the formed residue at $380\text{--}800^\circ\text{C}$.

5 Acknowledgments

We thank the National Science CCLI A & I program (Grant No. DUE0310624) for support in purchasing our Bruker NMR spectrometer. We are grateful to acknowledge that the project is partly supported by the Coatings Industry Education Foundation (CIEF), Chicago Society of Coating Technology and Office of Sponsored Programs and Research of DePaul University. S.M.R. was supported by a CIEF graduate fellowship.

6 References

- Hall, H.K. Jr. and Padias, A.B. (2004) *J. Polym. Sci. Part A: Polym. Chem.*, **42**, 2845–2858.
- Odian, G. *Principles of Polymerization*, 3rd Edn.; Wiley: New York, 1991.
- Hall, H.K. Jr. and Daly, R.C. (1975) *Macromolecules*, **8**, 22–31.
- Hall, H.K. Jr. and Ykman, P. (1977) *Macromolecules*, **10**, 464–469.
- Kharas, G.B. Trisubstituted ethylene copolymers. In *Polymeric Materials Encyclopedia*; Salamone, J.C. (ed.); CRC Press: Boca Raton, Vol. 11, 8405–8409, 1996.
- Kreisel, M., Garbatski, U. and Kohn, D.H. (1964) *J. Polym. Sci.*, **2(1;Pt A)**, 105–121.
- Kharas, G.B. and Ajbani, H. (1993) *J. Polym. Sci.*, **A31**, 2295–2303.
- Sayyah, S.M., El-Shafiey, Z.A., El-Sockary, M.A. and Kandil, U.F. (2002) *Int. J. Polym. Mat.*, **51(3)**, 225–242.
- Kharas, G.B. (1988) *J. Appl. Polym. Sci.*, **35**, 733–741, *ibid.*, 2173–2181.
- Koizumi, S., Tanado, K., Tanaka, Y., Shimidzu, T., Kutsumizu, S. and Yano, S. (1992) *Macromolecules*, **95**, 6563.
- Tasaka, S., Miyasato, K., Yoshikawa, M., Miyata, S. and Ko, M. (1984) *Ferroelectrics*, **57**, 267.
- Seto, T. and Nozoye, H. (1997) *Chem. Lett.*, 141–142.
- Poulsen, M., Ducharme, S., Sorokin, A., Reddy, S., Takacs, J., Wen, Y., Kim, J. and Adenwalla, S. (2005) *Ferroelectrics Letters*, **32(3–4)**, 91–97.
- Kharas, G.B., Smith, D.G., Karras, J.W., Maslanka, M., Mendelsohn, Y., Pintaric, A., Sklovsky, M., Wilder, A. and Watson, K. (2006) *J. Macromol. Sci.*, **43(1)**, 39–44.
- Kharas, G.B., Adibu, E., Brusek, A., Vigdor, W., Dorth, D., Hallis, L., Chipman, H., Kaiser, K. and Watson, K. (2007) *J. Macromol. Sci.*, **A44(7)**, 675–678.
- Kharas, G.B., Passe, L.B., Bishop, E., Dusinski, A., Farhadieh, P., Gatz, M., Klegerman, K., Vounatsos, A. and Watson, K. (2007) *J. Macromol. Sci.*, **A44(8)**, 779–782.
- Smith, M.B. and March, J. Addition to carbon-hetero multiple bonds. In *March's Advanced Organic Chemistry*; J. Wiley & Sons: New York, Ch. 16, 1225, 2001.
- Bednarski, R., Broun, D., Borberly, J. and Kelen, T. (1990) *Makromol. Chem.*, **191**, 773–779.
- Holland, B.J. and Hay, J.N. *Polymer*, 2002, **43**, 2207–2211.