

This article was downloaded by:

On: 24 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Macromolecular Science, Part A

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713597274>

Novel Copolymers of 4-Fluorostyrene. 7. Halogen Ring-Disubstituted 2-Phenyl-1,1-dicyanoethylenes

Gregory B. Kharas^a; Katherine T. Flynn^a; Benjamin L. Hill^a; Mustafa R. Ishaq^a; Darin A. Kopp^a; Brittany G. Koroll^a; Kristin M. Kupczyk^a; Danielle M. Schulte^a; Ubaldo Vera^a; Mark D. Aparece^a; Salima Atlas^b; Mustapha Raihane^b

^a Chemistry Department, DePaul University, Chicago, Illinois ^b Laboratory of Bioorganic and Macromolecular Chemistry, Chemistry Department, Faculty of Sciences and Techniques, Cadi Ayyad University, Marrakech, Morocco

Online publication date: 29 December 2010

To cite this Article Kharas, Gregory B. , Flynn, Katherine T. , Hill, Benjamin L. , Ishaq, Mustafa R. , Kopp, Darin A. , Koroll, Brittany G. , Kupczyk, Kristin M. , Schulte, Danielle M. , Vera, Ubaldo , Aparece, Mark D. , Atlas, Salima and Raihane, Mustapha(2011) 'Novel Copolymers of 4-Fluorostyrene. 7. Halogen Ring-Disubstituted 2-Phenyl-1,1-dicyanoethylenes', *Journal of Macromolecular Science, Part A*, 48: 2, 95 – 99

To link to this Article: DOI: 10.1080/10601325.2011.534716

URL: <http://dx.doi.org/10.1080/10601325.2011.534716>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Novel Copolymers of 4-Fluorostyrene. 7. Halogen Ring-Disubstituted 2-Phenyl-1,1-dicyanoethylenes

GREGORY B. KHARAS^{1,*}, KATHERINE T. FLYNN¹, BENJAMIN L. HILL¹, MUSTAFA R. ISHAQ¹, DARIN A. KOPP¹, BRITTANY G. KOROLL¹, KRISTIN M. KUPCZYK¹, DANIELLE M. SCHULTE¹, UBALDO VERA¹, MARK D. APARECE¹, SALIMA ATLAS², and MUSTAPHA RAIHANE²

¹Chemistry Department, DePaul University, Chicago, Illinois

²Laboratory of Bioorganic and Macromolecular Chemistry, Chemistry Department, Faculty of Sciences and Techniques, Cadi Ayyad University, Marrakech, Morocco

Received June 2010, Accepted July 2010

Novel copolymers of trisubstituted ethylene monomers, halogen ring-disubstituted 2-phenyl-1,1-dicyanoethylenes, $\text{RC}_6\text{H}_3\text{CH}=\text{C}(\text{CN})_2$ (where R is 2,3- Cl_2 , 2,4- Cl_2 , 2,6- Cl_2 , 3,4- Cl_2 , 3,5- Cl_2 , 2-Cl-4-F, 2-Cl-6-F, 3-Cl-4-F) and 4-fluorostyrene were prepared at equimolar monomer feed composition by solution copolymerization in the presence of a radical initiator (ABCN) at 70°C. The composition of the copolymers was calculated from nitrogen analysis, and the structures were analyzed by IR, ¹H and ¹³C-NMR. The order of relative reactivity ($1/r_1$) for the monomers is 2-Cl-4-F (2.42) > 3,4- Cl_2 (2.40) > 2,4- Cl_2 (1.97) > 2-Cl-6-F (1.86) > 3-Cl-4-F (1.68) > 2,3- Cl_2 (0.89) > 3,5- Cl_2 (0.70) > 2,6- Cl_2 (0.47). High T_g of the copolymers, in comparison with that of poly(4-fluorostyrene) indicates a substantial decrease in chain mobility of the copolymer due to the high dipolar character of the trisubstituted ethylene monomer unit. Softening of the copolymers started in 194–216°C range. Decomposition of the copolymers in nitrogen occurred in two steps, first in the 290–400°C range with residue, which then decomposed in 400–800°C range.

Keywords: Trisubstituted ethylenes, radical copolymerization, 4-fluorostyrene copolymers

1 Introduction

Trisubstituted ethylenes (TSE, $\text{CHR}^1 = \text{CR}^2\text{R}^3$) continue to attract attention of polymer chemists as reactive comonomers and models for mechanistic studies. It was shown that electrophilic tri- and tetrasubstituted olefins are particularly useful in delineating the transition from radical chemistry to ionic chemistry (1). Previous studies showed that TSE containing substituents larger than fluorine have very low reactivity in radical homopolymerization due to polar and steric reasons. Although steric difficulties preclude homopolymerization of most tri- and tetrasubstituted olefins, their copolymerization with a monosubstituted alkene makes it possible to overcome these steric problems (2). Copolymerization of TSE having double bonds substituted with halo, cyano, and carbonyl groups and electron-rich monosubstituted ethylenes such as styrene, *N*-vinylcarbazole, and vinyl acetate (3–5) show a tendency toward the formation of alternating copolymers.

Ring-unsubstituted 2-phenyl-1,1-dicyanoethylene was copolymerized with styrene (6), vinyl ethers (7), methyl methacrylate (8), and *N*-vinyl-2-pyrrolidone (9). In relation to applications, piezoelectric activity was observed in a copolymer of 1,1-dicyanoethylene (vinylidene cyanide) and vinyl acetate (10). Dielectric properties and α relaxation phenomena of two copolymers of vinylidene methyl cyanide with 4-fluorostyrene and 4-chlorostyrene have been studied (11). The values of dielectric increment $\Delta\epsilon$ have been calculated and compared to those of similar copolymers synthesized from vinylidene cyanide with various substituted styrenes. The low values of the increment were related to the steric effect of the bulky aromatic rings. The low values of the increment were related to the steric effect of the bulky aromatic rings.

Recently, we have described synthesis and characterization of copolymers of ring-unsubstituted 2-phenyl-1,1-dicyanoethylene (PDE) with 4-fluoro- and pentafluorostyrene (12), and alkyl ring-substituted PDE with 4-fluorostyrene (13). In continuation of our studies of the monomer structure-reactivity correlation in the radical copolymerization of electrophilic trisubstituted ethylene monomers, we have prepared copolymers of 4-fluorostyrene (4FST) with halogen ring-disubstituted 2-

*Address correspondence to: Gregory B. Kharas, Chemistry Department, Chicago, DePaul University, IL 60614-3214. Fax: 773-325-7421; E-mail: gkharas@depaul.edu

phenyl-1,1-dicyanoethylenes, $\text{RC}_6\text{H}_4\text{CH}=\text{C}(\text{CN})_2$ (where R is 2,3- Cl_2 , 2,4- Cl_2 , 2,6- Cl_2 , 3,4- Cl_2 , 3,5- Cl_2 , 2-Cl-4-F, 2-Cl-6-F, 3-Cl-4-F).

2 Experimental

2.1 General Procedures

Infrared spectra of the TSE monomers and polymers (KBr plates) were determined with a Nicolet Avatar 360 FT-IR spectrometer. The melting points of the monomers, the glass transition temperatures (T_g) of the copolymers were measured with a TA (Thermal Analysis, Inc.) Model Q10 differential scanning calorimeter (DSC). The thermal scans were performed in the 25 to 200°C range at a heating rate of 10°C/min. T_g was taken as a midpoint of a straight line between the inflection of the peak's onset and endpoint. The thermal stability of the copolymers was measured by a thermogravimetric analyzer TA Model Q50 from ambient temperature to 800°C at 20°C/min. The molecular weights of the polymers were determined relative to polystyrene standards in THF solutions with sample concentrations 0.8% (wt/vol) by gel permeation chromatography (GPC) using a Altech 426 pump at an elution rate of 1.0 mL/min, TSK-GEL G4000HHR column at 25°C, and Viscotek UV 2501 detector. ^1H - and ^{13}C -NMR spectra were obtained on 10–25% (w/v) monomer or polymer solutions in CDCl_3 at ambient temperature using a Bruker Avance 300 MHz spectrometer. Elemental analyses were performed by Quantitative Technologies Inc. (NJ).

2.2 Synthesis of Monomers

2,3- Cl_2 , 2,4- Cl_2 , 2,6- Cl_2 , 3,4- Cl_2 , 3,5- Cl_2 , 2-Cl-4-F, 2-Cl-6-F, 3-Cl-4-F-benzaldehydes, malononitrile, and piperidine supplied from Aldrich Chemical Co., were used for monomer synthesis as received. The preparation procedure was essentially the same for all the monomers. In a typical synthesis, equimolar amounts of malononitrile and an appropriate ring-substituted benzaldehyde were mixed with a small amount of DMF in an Erlenmeyer flask. A few drops of piperidine were added with stirring. The crystalline product of the reaction was isolated by filtration and purified by crystallization from 2-propanol. The details of the synthesis and characterization of 2,3- Cl_2 , 2,4- Cl_2 , 2,6- Cl_2 , 3,4- Cl_2 , 3,5- Cl_2 , 2-Cl-6-F, 3-Cl-4-F -substituted 2-phenyl-1,1-dicyanoethylenes were previously reported (14). 2-Cl-4-F, 3-Cl-4-F -substituted 2-phenyl-1,1-dicyanoethylenes were prepared and characterized for the first time.

2.2.1. 2-(2-chloro-4-fluorophenyl)-1,1-dicyanoethylene

Yield: 82%; mp 98°C; ^1H -NMR δ 7.9 (s, 1H, =CH), 7.5–7.2 (m, 3H, Ph); ^{13}C -NMR δ 161 (C-F), 151 (=CH), 135 (C-Cl), 134, 125, 114 (Ph), 113 (CN), 91 (=C); IR 3084, 3027 (m, CH), 2232 (m, CN), 1601, 1565 (m, Ph), 930, 911, 791

(s, Ph); Anal. Calc. for $\text{C}_{10}\text{H}_4\text{ClFN}_2$: C 58.13%, H 1.95%, N 13.56%; Found: C 57.96%, H 1.79%, N 13.49%.

2.2.2. 2-(3-chloro-4-fluorophenyl)-1,1-dicyanoethylene

Yield: 85%; mp 114°C; ^1H -NMR δ 7.9 (s, 1H, =CH), 7.6–7.1 (m, 3H, Ph); ^{13}C -NMR δ 160 (C-F), 152 (=CH), 135 (C-Cl), 135, 126, 115 (Ph), 112 (CN), 92 (=C); IR 3086, 3029 (m, CH), 2234 (m, CN), 1602, 1568 (m, Ph), 932, 913, 789 (s, Ph); Anal. Calc. for $\text{C}_{10}\text{H}_4\text{ClFN}_2$: C 58.13%, H 1.95%, N 13.56%; Found: C 57.75%, H 1.76%, N 13.52%.

2.3 Copolymerization

4-Fluorostyrene (4FST) and toluene (Aldrich) were used as received. 1,1'-Azobis(cyclohexanecarbonitrile) (ABCN) (Aldrich) was recrystallized twice from ethyl alcohol and then dried under reduced pressure at room temperature. Copolymers of the 4FST and the TSE monomers were prepared in 25-ml glass screw cap vials at 4FST/TSE = 1/1 (mol) the monomer feed using 0.12 mol/l of ABCN at an overall monomer concentration 2.44 mol/L in 10 ml of toluene. The copolymerization was conducted at 70°C. After a predetermined time the mixture was cooled to room temperature, and precipitated drop wise in methanol/petroleum ether mixture. The crude copolymers were purified by reprecipitation from chloroform solution into an excess of petroleum ether. The composition of the copolymers was determined based on the nitrogen content.


3 Results and Discussion

3.1 Monomer Synthesis


The TSE monomers were synthesized by Knoevenagel condensation (15) of a ring-disubstituted benzaldehyde with an active hydrogen compound, malononitrile, catalyzed by a base, piperidine (Sch. 1). The condensation reaction proceeded smoothly, yielding crystalline products, which were purified by conventional techniques

3.2 Homopolymerization

An attempted homopolymerization of the TSE monomers in the presence of ABCN did not produce any polymer as indicated by the lack of a precipitate in methanol. Inability of the monomers to polymerize is associated with steric

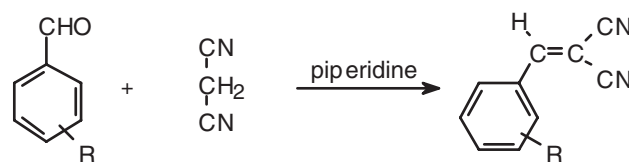

Sch. 1. Monomer synthesis (where R is 2,3- Cl_2 , 2,4- Cl_2 , 2,6- Cl_2 , 3,4- Cl_2 , 3,5- Cl_2 , 2-Cl-4-F, 2-Cl-6-F, 3-Cl-4-F).

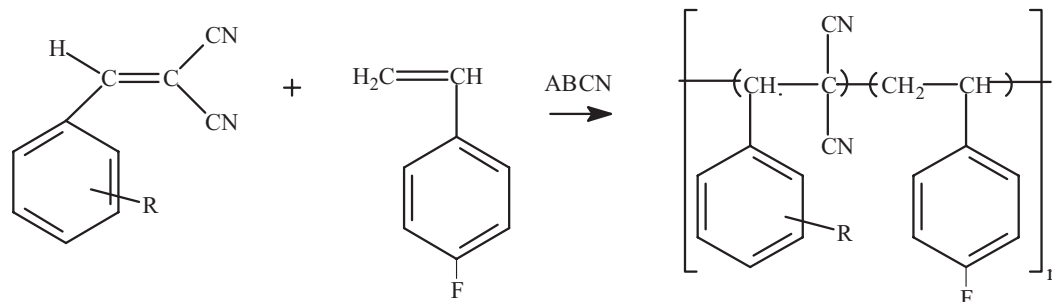

Sch. 2. Copolymer synthesis (where R is 2,3-Cl₂, 2,4-Cl₂, 2,6-Cl₂, 3,4-Cl₂, 3,5-Cl₂, 2-Cl-4-F, 2-Cl-6-F, 3-Cl-4-F).

difficulties encountered in homopolymerization of 1,1- and 1,2-disubstituted ethylenes. Homopolymerization of 4FST under conditions identical to those in the copolymerization experiments yielded 12.9% of poly(4-fluorostyrene), when polymerized for 30 min (12).

3.3 Copolymerization

Copolymerization (Sch. 2) of 4FST and the ring-substituted 1,1-dicyanoethylenes resulted in formation of copolymers (Table 1) with weight-average molecular masses 8 to 13 kD. According to elemental analysis, between 24.2 and 41.5 mol% of TSE monomer is present in the copolymers, which is indicative of high reactivity of the monomers in cross-propagation reactions.

In an attempt to qualitatively correlate the observed monomer reactivities, we considered copolymer composition data obtained at equimolar monomer feed. The relative reactivity of 4FST in copolymerization with these monomers can be estimated by assuming applicability of the copolymer composition equation (Eq. 1) of the terminal copolymerization model (2).

$$m_1/m_2 = [M_1](r_1[M_1] + [M_2])/[M_2]([M_1] + r_2[M_2]) \quad (1)$$

m_1 and m_2 are the mole fractions of 4FST and TSE monomer units in the copolymer, respectively; $[M_1]$ and $[M_2]$ are the concentrations of 4FST and TSE in the monomer feed, respectively. In the absence of the self-propagation of TSE monomers ($k_{22} = 0$, $r_2 = 0$) and at equimolar monomer feed ($[M_1]/[M_2] = 1$), Equation 1 yields:

$$r_1 = m_1/m_2 - 1 \quad (2)$$

or the equation for the relative reactivity of 4-fluorostyrene radical k_{12}/k_{11} with TSE monomers:

$$1/r_1 = 1/(m_1/m_2) - 1 \quad (3)$$

Consideration of monomer reactivities according to Equation 3 also involves the assumption of minimal copolymer compositional drift at equimolar monomer feed and given conversion. This non-rigorous kinetic treatment nevertheless allows estimation of the reactivity of a 4FST-ended polymer radical in reaction with electrophilic monomer. Thus the order of relative reactivity ($1/r_1$) and the tendency toward alternation of monomer units in the copolymer for the TSE monomers is 2-Cl-4-F (2.42) > 3,4-Cl₂(2.40) > 2,4-Cl₂(1.97) > 2-Cl-6-F (1.86) > 3-Cl-4-F (1.68) > 2,3-Cl₂ (0.89) > 3,5-Cl₂ (0.70) > 2,6-Cl₂ (0.47). More detailed information on the copolymer composition

Table 1. Copolymerization of 4-Fluorostyrene (M_1) and ring-substituted 1,1-dicyanoethylenes, $RC_6H_4CH=C(CN)_2$ (M_2)

R	Yield ^a ,		m_2 in pol., mol%	M_w , kD	T_g^b , °C	T_s^c , °C	TGA			
	wt%	N wt%					Onset of decomp., °C	10% Wt loss, °C	50% Wt loss, °C	Residue at 500°C, wt%
2,3-Cl ₂	38	6.31	32.0	9	180	200	286	314	356	12
2,4-Cl ₂	14	7.18	39.9	11	182	216	290	318	349	9
2,6-Cl ₂	20	5.01	24.2	8	196	196	292	318	355	7
3,4-Cl ₂	17	7.36	41.4	10	194	194	285	319	357	8
3,5-Cl ₂	10	5.76	29.1	10	194	194	299	312	347	10
2-Cl-4-F	17	7.92	41.5	8	189	201	301	314	352	9
2-Cl-6-F	14	7.64	39.4	13	187	198	297	314	349	12
3-Cl-4-F	23	7.52	38.6	9	182	197	298	312	356	10

^aPolymerization time was 24 h.

^b T_g – glass transition was observed by DSC.

^c T_s softening transition was observed by TMA.

at different monomer feed ratios would be necessary for the application of copolymerization models that would allow prediction of copolymer composition.

3.4 Structure and Spectral Properties

A comparison of the spectra of the monomers, copolymers and poly(4-fluorostyrene) shows, that the reaction between the TSE monomers and 4FST is a copolymerization. The structure of TSE-4FST copolymers was characterized by IR and NMR spectroscopy. IR spectra of the copolymers show overlapping bands in the 3125–2800 cm^{-1} region corresponding to C-H vibrations. The spectra of the copolymers show weak cyano group absorption of the TSE monomer unit at 2220–2236 cm^{-1} (2205–2230 cm^{-1} in monomers). Benzene rings of both monomers show ring stretching bands around 1600, 1500, and 1450 cm^{-1} , as well as a doublet 740, 690 cm^{-1} , associated with C-H out of plane deformations. These bands were found also in copolymers of 2-phenyl-1,1-dicyanoethylene with vinyl acetate (5) and *N*-vinyl-2-pyrrolidone (9).

^1H -NMR spectra of the 4FST-TSE copolymers show a broad double peak in a 5.8–8.0 ppm region corresponding to phenyl ring protons. The resonance at 3.2–4.6 ppm is assigned to 4FST backbone protons in the close proximity of in 4FST-TSE dyad or in 4FST centered TSE-4FST-TSE triads. The low and high field components of the 2.2–3.2 ppm peak is assigned to the overlapping resonances of the methine proton of the TSE monomer unit in head-to-tail and head-to-head structures (16). Backbone 4FST protons removed further from cyano groups give rise to the absorption in 1.8–2.3 ppm with a maximum at 2.2 ppm. The strong absorption in the 0.7–2.1 ppm range corresponds to 4FST backbone protons in 4FST-4FST diads. The ^{13}C -NMR spectra also support the suggested skeletal structure of the copolymers. Thus, the assignment of the peaks as follows: 125–148 (phenyl carbons), 112–116 ppm (CN), 55–65 ppm (methine carbons of TSE and 4FST, and methylene carbons of 4FST). The broad carbon resonances are due to presence of both head-to-tail and head-to-head dyads as discussed in more detailed assignment of ^1H and ^{13}C -NMR spectra of 2-phenyl-1,1-dicyanoethylene-styrene copolymers (16). The IR and NMR data showed that these are true copolymers, composed of 4FST and TSE monomer units.

The copolymers prepared in the present work are all soluble in methyl ethyl ketone, acetone, benzene, THF, DMF and CHCl_3 and insoluble cyclohexane. They are amorphous and show no crystalline DSC endotherm. Relatively high T_g of the copolymers (Table 1) in comparison with that of poly(4-fluorostyrene) ($T_g = 108^\circ\text{C}$) (12) indicates decrease of chain mobility of the copolymer due to the high dipolar character of the TSE structural units. TMA analysis indicated that softening of the copolymers starts in 194–216 $^\circ\text{C}$ range.

Information on the degradation of the copolymers was obtained from thermogravimetric analysis. The TGA in

nitrogen and air produce similar traces. The copolymers decomposed rapidly in one stage in the 290–400 $^\circ\text{C}$ range followed by a more slow decomposition of the formed residue at 400–800 $^\circ\text{C}$. The decomposition products were not analyzed in this study, and the mechanism has yet to be investigated.

4 Conclusions

Trisubstituted ethylenes, halogen ring-disubstituted 2-phenyl-1,1-dicyanoethylene were prepared via a base catalyzed condensation of appropriate substituted benzaldehyde and malononitrile. The copolymerization of the monomers with 4-fluorostyrene results in copolymers. The composition of the copolymers was calculated from nitrogen analysis and the structure was analyzed by IR, ^1H and ^{13}C -NMR. High glass transition temperature of the copolymers in comparison with that of poly(4-fluorostyrene) ($T_g = 108^\circ\text{C}$) indicates a substantial decrease in chain mobility of the copolymer due to the high dipolar character of the TSE monomer unit. TMA analysis indicated that softening of the copolymers starts in 194–216 $^\circ\text{C}$ range. The copolymers decomposed rapidly in one stage in the 290–400 $^\circ\text{C}$ range followed by a more slow decomposition of the formed residue at 400–800 $^\circ\text{C}$.

Acknowledgments

We thank the National Science Foundation Polymer Program (DMR-0710520) for support. We are grateful to acknowledge that the project is partly supported by the Coatings Industry Education Foundation (CIEF), Chicago Society of Coating Technology and Office of Sponsored Programs and Research of DePaul University. K.T.F. and B.L.H. were supported by CIEF graduate fellowship. We are grateful that the project is supported by the CNRST of Morocco for the framework of cooperation Morocco-USA in the field of Materials (n $^\circ$ 87/2007: Materials World Network).

References

- Hall, H.K., Jr. and Padias, A.B. (2004) *J. Polym. Sci. Part A: Polym. Chem.* 42, 2845–2858.
- Odian, G. *Principles of Polymerization*, 4th Ed.; Wiley: New York, 2004.
- Hall, H.K., Jr. and Daly, R.C. (1975) *Macromolecules*, 8, 22–31.
- Hall, H.K., Jr. and Ykman, P. (1977) *Macromolecules*, 10, 464–469.
- Kharas, G.B. Trisubstituted ethylene copolymers. In *Polymeric Materials Encyclopedia*, edited by Salamone, J.C., CRC Press: Boca Raton, Vol. 11, 8405–8409, 1996.
- Kreisel, M., Garbatski, U., and Kohn, D.H. (1964) *J. Polym. Sci.*, 2(1; Part A) 105–121.
- Kharas, G.B. and Ajbani, H. (1993) *J. Polym. Sci.*, A31, 2295–2303.

8. Sayyah, S.M., El-Shafiey, Z.A., El-Sockary, M.A., and Kandil, U.F. (2002) *Int. J. Polym. Mat.*, 51(3), 225–242.
9. Kharas, G.B. (1988) *J. Appl. Polym. Sci.*, 35: 733–741.
10. Koizumi, S., Tanado, K., Tanaka, Y., Shimidzu, T., Kutsumizu, S., and Yano, S. (1992) *Macromolecules*, 95, 6563.
11. Raihane, M., Montheard, J.P., and Boiteux, G. (2000) *Macromol. Chem. and Phy.* 201(17), 2365–2370.
12. Kharas, G.B., Hanawa, E., Hill, B.L., Atlas, S., and Raihane, M. (2009) *J. Macromol. Sci., Pure & Applied Chem.*, A46, 650–655.
13. Kharas, G.B., Hanawa, E., Hill, B.L., Flynn, K., Addante, A.N., Argueta, J.C., Boylan, G.A., Sisler, E., and Sbarboro, J. (2010) *J. Macromol. Sci., Pure & Applied Chem.*, A47(3) 197–201.
14. Kharas, G.B., Russell, S.M. Cisler, R., Capen, T.L., Chlupsa, E.A., DeBellis, L.A. Duke, J.T.A., Frazier, C.B., Gora, A., Kamenetsky, E., Kurani, A.S., Kuta, D.L., Madison, A.L., and Miramon, P. (2008) *J. Macromol. Sci., Pure & Applied Chem.*, A45(4) 261–264.
15. Smith, M.B., and March, J. (2001) Addition to Carbon-Hetero Multiple Bonds. In *March's Advanced Organic Chemistry*: J. Wiley & Sons: New York, Ch. 16, 1225.
16. Kharas, G.B., Murau, P.A., Watson, K., and Harwood, H.J. (1992) *Polym. Int.*, 28, 67–74.