

## Phase evolution in the Ti-Al-B and Ti-Al-C systems during combustion synthesis: Time resolved study by synchrotron radiation diffraction analysis

A. S. ROGACHEV

*Institute of Structural Macrokinetics and Materials Science RAS, Chernogolovka, Russia*

J.-C. GACHON

*LCSM UMR7555 Université Henri Poincaré, Nancy 1, France*

H. E. GRIGORYAN

*Institute of Structural Macrokinetics and Materials Science RAS, Chernogolovka, Russia*

D. VREL

*CNRS-LIMPH, Université Paris, Villetaneuse, France*

J. C. SCHUSTER

*Department of Physical Chemistry, Universitaet Wien, Wien, Austria*

N. V. SACHKOVA

*Institute of Structural Macrokinetics and Materials Science RAS, Chernogolovka, Russia*

Self-propagating high-temperature synthesis (SHS), also known as combustion synthesis, is a modern technique for producing refractory compounds and materials [1]. This method is based on the use of internal chemical reaction heat rather than external (furnace) heating for material synthesis and processing. Initial mixture consists of two or more powders, which are able to react exothermically with each other. Being locally initiated, the reaction becomes self-sustaining, heat produced in the reaction front igniting the nearest part of the mixture.

Ceramic-intermetallic composites, composed of ceramic grains (TiC, TiB<sub>2</sub>, etc.) and TiAl intermetallic binder, possess attractive properties for potential applications as cutting tools, aerospace materials, hard and refractory structural materials. As the enthalpies of reaction between Ti and C, B or Al are large, these materials can be produced through combustion synthesis (SHS) by means of heterogeneous reactions in the ternary mixtures of elemental powders. Formation mechanisms of the materials have been studied in the present work. Since the characteristic features of SHS are fast temperature variations and short duration of the product formation (usually from a few seconds to a few minutes), Time-Resolved Synchrotron Radiation Diffraction (TRSRD) is used for monitoring phase transformations. This method, firstly developed for investigation of SHS in the Ni-Al system [2], have been further improved in order to reach extremely short temporal resolution of 5 ms per diffraction pattern [3], or to combine it with thermal vision system [4].

Powders of Ti (~40 μm average size, 99.8% purity), C (carbon black, ~0.1 μm, 99% purity) and B (amorphous black, ~0.1 μm, 99% purity) were dry-mixed

and pressed into rectangular (20 × 10 × 5 mm) samples with a remaining porosity of roughly 40%. Two initial compositions were studied: 2Ti+Al+2B and 2Ti+Al+C. The samples were put in a specially designed chamber with an X-ray transparent window [4], under He atmosphere at normal pressure. Radiation, produced by one of L.U.R.E. (Orsay, France) synchrotron source, was monochromized and focused on the lateral surface of the sample. Radiation wavelength was chosen equal to 2.53 Å, intensity of the incident beam was ~10<sup>10</sup> photon per second. The sample surface exposed to synchrotron radiation (region of analysis), was a rectangle of 0.1 mm × 1.5 mm, with its long side parallel to the reaction front. Reaction was initiated locally by an electrically heated W wire. A gasless combustion front propagated along the sample with a velocity of 3 cm/s (Ti-Al-B) or 0.4 cm/s (Ti-Al-C), maximum averaged temperatures in the reaction zone were 2200 and 1960 K, respectively. Synchrotron ray diffraction patterns were recorded continuously (before, during and after reaction) by a curved linear detector which covered the range (theta) from 28 to 73°, divided into 512 or 1024 channels. Sequence of 1024 SRD patterns was stored without time interval on a PC during 40.96 s. Hence, every pattern represents information about sample current phase composition during an interval of 40 ms. The stored data files were further converted into bitmap images, where larger intensity of radiation correspond to darker areas. These images give general information about phase evolution during combustion synthesis of the materials.

TRSRD pattern of phase transformations in the Ti-Al-B system is shown in the Fig. 1. Lines of Ti and Al can be observed before reaction, amorphous boron does

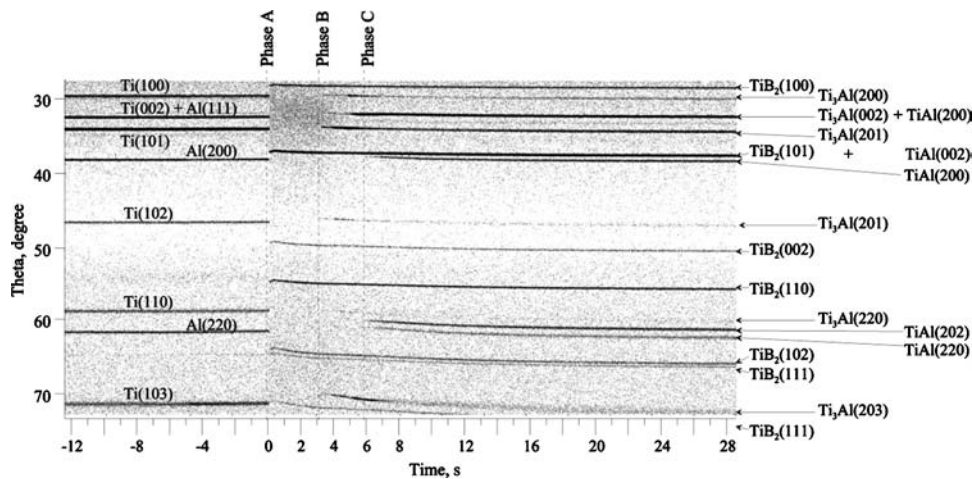


Figure 1 TRSRD pattern of phase transformations in the Ti-Al-B system.

not yield any diffraction peak. The diffraction pattern changes sharply when the combustion front crosses the region of analysis. This point of time is marked as 0 s on the SRD patterns. The only phase appearing immediately in the reaction front, is  $\text{TiB}_2$ , identified by six major peaks (Phase A in Fig. 1). Evidently, when  $\text{TiB}_2$  crystallizes, Al and the rest of Ti remain in the melt. When the temperature of the products goes down behind the combustion front, due to radiation, conduction and convection heat losses, two more crystal phases appear after  $\text{TiB}_2$ . Phase C, which crystallizes 6 s behind the combustion front, can be clearly recognized as  $\gamma$ -TiAl. Phase B, after cooling down, corresponds to  $\alpha_2$ - $\text{Ti}_3\text{Al}$  intermetallic compound. However,  $\text{Ti}_3\text{Al}$  maximum temperature (1473 K) is lower than  $\gamma$ -TiAl crystallization temperature from the Ti-Al melt ( $\sim 1723$  K). Therefore,  $\text{Ti}_3\text{Al}$  cannot precipitate before TiAl. Careful consideration of the Ti-Al phase diagram and TRSRD pattern (Fig. 1) allows us to conclude that B, which appears at 3.2 s behind the front, is  $\alpha$ -Ti solid solution. We may further assume that this phase chemical composition is close to that of Al saturated  $\text{Ti}_3\text{Al}$ . When temperature decreases, the high-temperature  $\alpha$ -Ti solid solution transforms into low-temperature  $\alpha_2$ - $\text{Ti}_3\text{Al}$ . Relatively intense lines at  $\sim 35^\circ$  and  $\sim 71^\circ$  belong to solid solution; broadening and diminution of

these lines at  $\sim 7$  s correspond to phase transformation from solid solution into ordered intermetallic  $\text{Ti}_3\text{Al}$ . Following this transformation, the mentioned two lines pass into the lines  $\text{Ti}_3\text{Al}(201)$  and  $\text{Ti}_3\text{Al}(203)$ , respectively.

Phase evolution in the Ti-Al-C system is shown in Fig. 2. Initial SRD patterns are similar to those shown in Fig. 1, since amorphous carbon does not produce any peak. The first phase appearing is TiC, probably non-stoichiometric (e.g.,  $\text{TiC}_x$  with  $x \sim 0.5$ – $0.7$ ). After 2.9 s behind TiC appearance, a second phase crystallizes (Phase B, Fig. 2). Phase B was recognized as  $\text{Ti}_3\text{AlC}_2$  [5] ( $a = 0.3076$  nm,  $c = 1.8543$  nm, isotypic with  $\text{Ti}_3\text{SiC}_2$ ). One minor line, which might belong to  $\text{Ti}_2\text{AlC}$ , is also observed. It is known from literature that  $\text{Ti}_3\text{AlC}_2$  was found at temperatures of  $1573 \text{ K} \leq T < 1633 \text{ K}$ . Therefore, this phase can appear in Ti-Al-C, when products cool down below 1633 K from the maximum combustion temperature 1960 K. It should be noted that direct synthesis of the  $\text{Ti}_3\text{SiC}_2$  in the combustion mode (by SHS) was reported earlier [6, 7], while authors donot know any previous publication about SHS production of the  $\text{Ti}_3\text{AlC}_2$ .

Microstructures of combustion products are presented in Fig. 3. Identification of phases was made using EPMA and EDS analyses. Products of the combustion

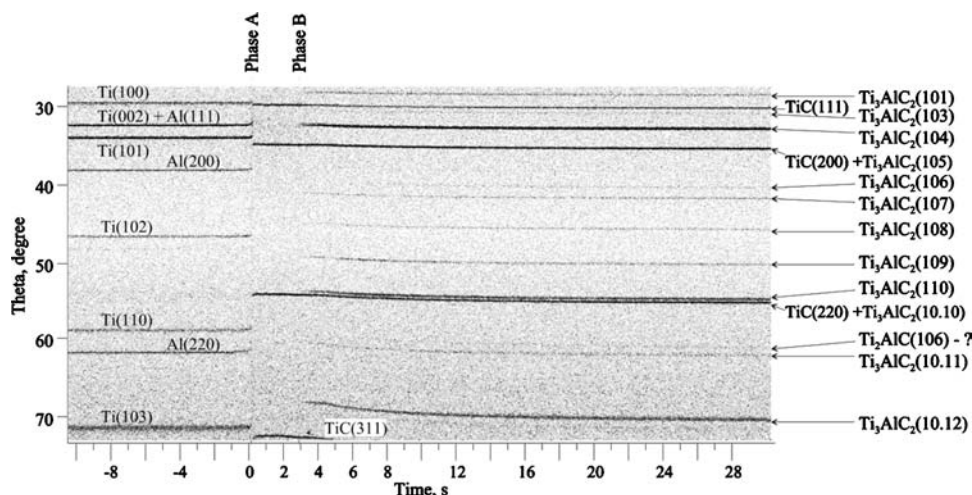


Figure 2 TRSRD pattern of phase transformations in the Ti-Al-C system.

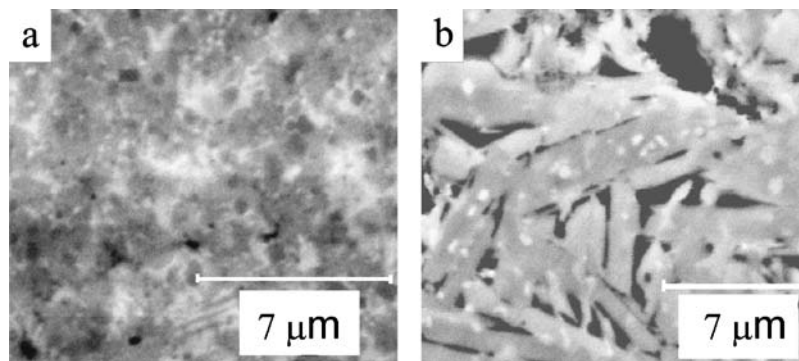


Figure 3 Microstructure of the products in Ti-Al-B (a) and Ti-Al-C (b) systems.

synthesis in the Ti-Al-B system (Fig. 3a) consist of fine rounded  $TiB_2$  grains (gray phase) and intermetallic binder (white phase). Ti-Al-C products contain  $TiC_x$  (light gray),  $Ti_3AlC_2$  (dark phase), and small inclusions (white), which are probably  $Ti_2AlC$ .

Thus, the results of TRSRD study show the following sequences of phase transformations in the Ti-Al-B and Ti-Al-C systems. Disappearance of initial phases and formation of the first products ( $TiC$  or  $TiB_2$ ) happen during a short time interval, at the most 40 ms (time resolution of the method). At this moment, temperature rises sharply up to its maximum value, which exceeds temperature ranges of existence of the other phases. Therefore, the first products of combustion reactions are refractory titanium carbide or diboride and melt. Then temperature decreases due to heat losses to surrounding medium, and other phases precipitate from the melt, according to phase diagram. This process takes a few seconds more, depending on the cooling rate. It is important to note that in the samples of moderate size, when cooling rate is fast enough, thermodynamic equilibrium between the first carbide/boride phase and other phases precipitated from the melt is not achieved. For example, equilibrium phases in the mixture  $2Ti+Al+2B$  are  $TiB$  and  $Al$ , however, fast SHS process allows to produce the material composed of  $TiB_2$  grains and intermetallic binder. This feature of the combustion synthesis method can be used for production of new materials with tailored phase constitution, microstructure and properties.

### Acknowledgment

This work is supported by INTAS grant No. 03-51-4103 and RFBR grant 04-03-32654.

### References

1. A. G. MERZHANOV, in "Combustion and Plasma Synthesis of High Temperature Materials," edited by Z. A. Munir and J. B. Holt (MCP Publishers, New York, 1990) p. 1.
2. V. V. BOLDYREV, V. V. ALEKSANDROV, M. A. KORCHAGIN, B. P. TOLOCHKO, S. N. GUSENKO, A. S. SOKOLOV, M. A. SHEROMOV and N. Z. LYAHKOV, *Doklady Akad. Nauk SSSR* **259** (1981) 1127.
3. M. SHARAFUTDINOV, V. ALEKSANDROV, O. EVDOKOV, D. NAUMOV, B. PIROGOV, E. PISMENSKAYA, A. ROGACHEV and B. TOLOCHKO, *J. Synchr. Rad.* **10** (2003) 384.
4. F. BERNARD, S. PARIS, D. VREL, M. GAILHANOU, J. C. GACHON and E. GAFFET, *Intern. J. Self-Propag. High-Temper. Synth.* **11** (2002) 181.
5. M. A. PIETZKA and J. C. SCHUSTER, *J. Phase Equilibria* **15** (1994) 392.
6. H. E. GRIGORYAN, A. S. ROGACHEV, V. I. PONOMAREV and E. A. LEVASHOV, *Intern. J. Self-Propag. High-Temper. Synth.* **7** (1998) 507.
7. D. P. RILEY, E. H. KISI, T. C. HANSEN and A. W. HEWAT, *J. Amer. Ceram. Soc.* **85** (2002) 2417.

Received 28 June

and accepted 31 August 2004