

# Mode I Field Intensity Factors of Infinitely Long Strip in Piezoelectric Media

Soon Man Kwon

Graduate Student, Department of Mechanical Engineering, Yonsei University

Kang Yong Lee\*

Department of Mechanical Engineering, Yonsei University

We consider the problem of determining the singular stresses and electric fields in a piezoelectric ceramic strip containing a Griffith crack under in-plane normal loading within the framework of linear piezoelectricity. The potential theory method and Fourier transforms are used to reduce the problem to the solution of dual integral equations, which are then expressed to a Fredholm integral equation of the second kind. Numerical values on the field intensity factors are obtained, and the influences of the electric fields for PZT-6B piezoelectric ceramic are discussed.

**Key Words** : Piezoelectric Medium, Field Intensity Factors, Potential Theory Method

## Nomenclature

$a$	: A half of crack length
$C_{11}, C_{13}, C_{33}, C_{44}$	: Elastic moduli measured in a constant electric field
$d_{11}, d_{33}$	: Dielectric permittivities measured at a constant strain
$D_x, D_z$	: Electric displacement vector
$e_{15}, e_{31}, e_{33}$	: Piezoelectric constants
$E_x, E_z$	: Electric field vector
$h$	: A half of thickness of the strip
$K^I$	: Field intensity factor
$\phi$	: Electric potential
$\psi$	: Potential function

## 1. Introduction

Because of its coupling characteristic between electric and mechanical deformation, piezoelectric materials have been widely used in transducers and sensors. Due to the intrinsic brittle property, however, the stress concentration caused by mechanical and/or electric load may induce the

initiation and propagation of crack under loading conditions. In order to predict the service lifetime of piezoelectric ceramic components, we must identify the damage and the fracture behavior of the materials. The increasing attention to the study of crack problems in piezoelectric materials in the last decade has led to a lot of significant works being published.

Of particular interest, Pak (1990) obtained the closed form solutions for an unbounded piezoelectric medium under anti-plane loading by employing a complex variable approach. Park and Sun (1995) obtained the closed form solutions for all modes of fracture for an infinite piezoelectric medium containing a center crack subjected to a combined mechanical and electrical loading. Shindo et al. (1996, 1997) obtained the solution for the infinite strip parallel or perpendicular to the crack under anti-plane loading using integral transform method. Recently, Kwon and Lee (2000) obtained the solution of piezoelectric rectangular media with a center crack under anti-plane shear loading.

In contrast to the success of the anti-plane (mode III) crack problem researches mentioned above, there are relatively few papers concerning in-plane (mode I) crack problem due to the

\* Corresponding Author,

E-mail : fracture@yonsei.ac.kr

TEL : +82-2-361-2813; FAX : +82-2-361-2813

Professor, Department of Mechanical Engineering,

Yonsei University Seoul 120-749, Korea.(Manuscript

Received February 3, 2000; Revised May 15, 2000)

complexity of analysis. The purpose of the present work is to conduct a systematic study of the in-plane crack problem of a transversely isotropic solid (class 6 mm or hexagonal) by using a potential theory and an integral transform method. In this paper, we consider the crack problem in a piezoelectric ceramic strip under in-plane normal loading. The numerical results for the field intensity factors are shown graphically for PZT-6B piezoelectric ceramic.

### 2. Potential Theory Method and Governing Equations

In a Cartesian coordinates  $(x, z)$ , poled with  $z$ -axis, the governing equations can be written as follows,

$$c_{11} \frac{\partial^2 u}{\partial x^2} + c_{44} \frac{\partial^2 u}{\partial z^2} + (c_{13} + c_{44}) \frac{\partial^2 w}{\partial x \partial z} + (e_{15} + e_{31}) \frac{\partial^2 \phi}{\partial x \partial z} = 0, \tag{1}$$

$$c_{44} \frac{\partial^2 w}{\partial x^2} + c_{33} \frac{\partial^2 w}{\partial z^2} + (c_{13} + c_{44}) \frac{\partial^2 u}{\partial x \partial z} + e_{15} \frac{\partial^2 \phi}{\partial x^2} + e_{33} \frac{\partial^2 \phi}{\partial z^2} = 0, \tag{2}$$

$$e_{15} \frac{\partial^2 w}{\partial x^2} + e_{33} \frac{\partial^2 w}{\partial z^2} + (e_{15} + c_{31}) \frac{\partial^2 u}{\partial x \partial z} - d_{11} \frac{\partial^2 \phi}{\partial x^2} - d_{33} \frac{\partial^2 \phi}{\partial z^2} = 0, \tag{3}$$

where  $u(x, z)$ ,  $w(x, z)$ ,  $\phi$ ,  $(c_{11}, c_{13}, c_{33}, c_{44})$ ,  $(d_{11}, d_{33})$  and  $(e_{15}, e_{31}, e_{33})$  are the displacement in  $x$ -direction, the displacement in  $z$ -direction, the electric potential, the elastic moduli measured in a constant electric field, the dielectric permittivities measured at a constant strain and the piezoelectric constants, respectively.

We introduce the following potential function which could transform Eqs. (1)-(3) into the familiar differential equations,

$$u = \frac{\partial \psi}{\partial x}, \quad w = k_1 \frac{\partial \psi}{\partial z}, \quad \phi = k_2 \frac{\partial \psi}{\partial z}, \tag{4}$$

where  $\psi(x, z)$  is the potential function introduced, and  $k_1$  and  $k_2$  are unknown constants. Putting Eq. (4) into Eqs. (1)-(3), we have the following equations,

$$c_{11} \frac{\partial^2 \psi}{\partial x^2} + [c_{44} + (c_{13} + c_{44}) k_1$$

$$+ (e_{15} + e_{31}) k_2] \frac{\partial^2 \psi}{\partial z^2} = 0, \tag{5}$$

$$[(c_{13} + c_{44}) + c_{44} k_1 + e_{15} k_2] \frac{\partial^2 \psi}{\partial x^2} + (c_{33} k_1 + e_{33} k_2) \frac{\partial^2 \psi}{\partial z^2} = 0, \tag{6}$$

$$[(e_{15} + e_{31}) + e_{15} k_1 - d_{11} k_2] \frac{\partial^2 \psi}{\partial x^2} + (e_{33} k_1 - d_{33} k_2) \frac{\partial^2 \psi}{\partial z^2} = 0, \tag{7}$$

The terms  $\partial^2 \psi / \partial x^2$  and  $\partial^2 \psi / \partial z^2$  are not identically equal to zero. Therefore, a non-trivial solution of Eqs. (5)-(7) is to exist only in the following case,

$$\frac{c_{44} + (c_{13} + c_{44}) k_1 + (e_{15} + e_{31}) k_2}{c_{11}} = \frac{c_{33} k_1 + e_{33} k_2}{c_{13} + c_{44} + c_{44} k_1 + e_{15} k_2} = \frac{e_{33} k_1 - d_{33} k_2}{e_{15} + e_{31} + e_{15} k_1 - d_{11} k_2} = \lambda \tag{8}$$

Eliminating  $k_1$  and  $k_2$  in Eq. (8), we obtain a cubic algebra equation of  $\lambda$ ,

$$A \lambda^3 + B \lambda^2 + C \lambda + D = 0, \tag{9}$$

where

$$A = e_{15}^2 + c_{44} d_{11}, \tag{10}$$

$$B = (2c_{13} e_{15}^2 - c_{44} e_{31}^2 + 2c_{13} e_{15} e_{31} - 2c_{11} e_{15} e_{33} + c_{13}^2 d_{11} + 2c_{13} c_{44} d_{11} - c_{11} c_{33} d_{11} - c_{11} c_{44} d_{33}) / c_{11}, \tag{11}$$

$$C = [c_{33} (e_{15} + e_{31})^2 - 2(c_{13} + c_{44}) (e_{15} + e_{31}) e_{33} + (2c_{44} e_{15} + c_{11} e_{33}) e_{33} + c_{33} c_{44} d_{11} - (c_{13}^2 + 2c_{13} c_{44} - c_{11} c_{33}) d_{33}] / c_{11}, \tag{12}$$

$$D = -(e_{33}^2 + c_{33} d_{33}) c_{44} / c_{11} \tag{13}$$

The three roots of Eq. (9) are denoted by  $\lambda_i$  ( $i = 1, 2, 3$ ) and  $\lambda_1$  is assumed to be a positive real number,  $\lambda_2$  and  $\lambda_3$  are to be either positive real numbers or a pair of conjugate complex roots with positive real parts.

Corresponding to three roots, there are three potential functions  $\psi_i$  ( $i = 1, 2, 3$ ) and each of them must satisfy the following equation,

$$\nabla_i^2 \psi_i = \frac{\partial^2 \psi_i}{\partial x^2} + \frac{\partial^2 \psi_i}{\partial z_i^2} = 0, \quad i = 1, 2, 3, \tag{14}$$

where

$$z_i = \frac{z}{\sqrt{\lambda_i}}. \tag{15}$$

### 3. Problem Statement and Method of Solution

Consider a piezoelectric medium in the form of an infinitely long strip containing a finite crack subjected to the combined in-plane mechanical and electric loads as shown in Fig. 1. A set of cartesian coordinates  $(x, z)$  is attached to the center of the crack. The piezoelectric ceramic strip poled with  $z$ -axis occupies the region  $(-\infty < x < \infty, -h \leq z \leq h)$  and is thick enough in the  $y$ -direction to allow a state of plane strain. The crack is situated along the  $-a \leq x \leq a, z=0$ . Because of the assumed symmetry in geometry and loading, it is sufficient to consider the problem for  $0 \leq x < \infty$  and  $z \geq 0$  only.

How to impose the electrical boundary conditions along the crack surfaces in piezoelectric fracture modelling is controversial. The impermeable boundary condition on the crack surface was widely used in the previous works. This condition shows that the electric displacement intensity factor depends on the electric load, and the energy release rate is always negative only in the presence of electric loading, irrespective of its sign. These contradict the available experimental observations (Park and Sun, 1995; Tobin and Pak, 1993).

In fact, cracks in piezoelectric media will be filled with vacuum or air. This requires that both the normal components of electric displacement and the tangential component of the electric field will be continuous across the crack faces.

Based on this concept, the boundary conditions are written in the forms,

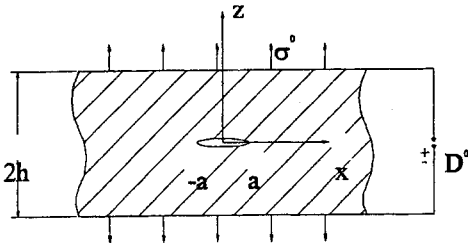


Fig. 1 Infinite piezoelectric strip with a crack subjected to the combined in-plane electric and mechanical loads

$$\sigma_z(x, h) = \sigma_z(x, -h) = \sigma_0, \tag{16}$$

$$D_z(x, h) = D_z(x, -h) = D_0, \tag{17}$$

$$\sigma_{xz}(x, 0) = 0, \tag{18}$$

$$\sigma_{xz}(x, h) = 0, \tag{19}$$

$$E_x(x, 0^+) = E_x(x, 0^-), \quad (0 \leq x < a), \tag{20a}$$

$$D_z(x, 0^+) = D_z(x, 0^-), \quad (0 \leq x < a), \tag{20b}$$

$$\phi(x, 0) = 0, \quad (0 < x < \infty), \tag{21}$$

$$\sigma_z(x, 0) = 0, \quad (0 \leq x < a), \tag{22}$$

$$w(x, 0) = 0, \quad (a < x < \infty). \tag{23}$$

By applying a Fourier transform to Eq. (14), we can find the displacements, electric fields, stresses and electric displacement components in the forms,

$$\begin{aligned} \phi_i(x, z_i) = & \frac{2}{\pi} \int_0^\infty \frac{1}{s} [A_i(s) \cosh(sz_i) \\ & + B_i(s) \sinh(sz_i)] \cos(sx) ds, \end{aligned} \tag{24}$$

$$\begin{aligned} u = & -\frac{2}{\pi} \int_0^\infty \sum_{i=1}^3 [A_i(s) \cosh(sz_i) \\ & + B_i(s) \sinh(sz_i)] \sin(sx) ds, \end{aligned} \tag{25}$$

$$\begin{aligned} w = & \frac{2}{\pi} \int_0^\infty \sum_{i=1}^3 \frac{k_{1i}}{\sqrt{\lambda_i}} [A_i(s) \sinh(sz_i) \\ & + B_i(s) \cosh(sz_i)] \cos(sx) ds + a_0 z, \end{aligned} \tag{26}$$

$$\begin{aligned} \phi = & \frac{2}{\pi} \int_0^\infty \sum_{i=1}^3 \frac{k_{2i}}{\sqrt{\lambda_i}} [A_i(s) \sinh(sz_i) \\ & + B_i(s) \cosh(sz_i)] \cos(sx) ds - b_0 z, \end{aligned} \tag{27}$$

$$\begin{aligned} E_x = & \frac{2}{\pi} \int_0^\infty s \sum_{i=1}^3 \frac{k_{2i}}{\sqrt{\lambda_i}} [A_i(s) \sinh(sz_i) \\ & + B_i(s) \cosh(sz_i)] \sin(sx) ds, \end{aligned} \tag{28}$$

$$\begin{aligned} \sigma_z = & \frac{2}{\pi} \int_0^\infty s \sum_{i=1}^3 \alpha_i [A_i(s) \cosh(sz_i) \\ & + B_i(s) \sinh(sz_i)] \cos(sx) ds + c_0, \end{aligned} \tag{29}$$

$$\begin{aligned} \sigma_{xz} = & -\frac{2}{\pi} \int_0^\infty s \sum_{j=1}^3 \beta_j [A_j(s) \sinh(sz_j) \\ & + B_j(s) \cosh(sz_j)] \sin(sx) ds, \end{aligned} \tag{30}$$

$$\begin{aligned} D_z = & \frac{2}{\pi} \int_0^\infty s \sum_{i=1}^3 \gamma_i [A_i(s) \cosh(sz_i) \\ & + B_i(s) \sinh(sz_i)] \cos(sx) ds + d_0, \end{aligned} \tag{31}$$

where

$$\alpha_i = \frac{c_{33}k_{1i} + e_{33}k_{2i}}{\lambda_i} - c_{13}, \tag{32}$$

$$\beta_i = \frac{c_{44}(1 + k_{1i}) + e_{15}k_{2i}}{\sqrt{\lambda_i}}, \tag{33}$$

$$\gamma_i = \frac{e_{33}k_{1i} - d_{33}k_{2i}}{\lambda_i} - e_{31}, \tag{34}$$

and  $A_i(s)$ ,  $B_i(s)$  ( $i=1, 2$ ) are the unknowns to be solved, and  $a_0, b_0, c_0 = c_{33}a_0 - e_{33}b_0$  and  $d_0 = e_{33}a_0 + d_{33}b_0$  are unknown constants, which will be determined from the far field loading conditions.

By applying the far field loading conditions (16)-(17), the relations between  $A_i(s)$  and  $B_i(s)$  as well as the constants  $a_0, b_0, c_0$  and  $d_0$  are evaluated as follows,

$$a_0 = \frac{d_{33}\sigma_0 + e_{33}D_0}{c_{33}d_{33} + e_{33}^2}, \quad b_0 = \frac{-e_{33}\sigma_0 + c_{33}D_0}{c_{33}d_{33} + e_{33}^2}, \tag{35}$$

$$c_0 = \sigma_0, \quad d_0 = D_0,$$

$$\alpha_1 \cosh(sh_1) A_1(s) + \alpha_2 \cosh(sh_2) A_2(s) + \alpha_3 \cosh(sh_3) A_3(s) = -\alpha_1 \sinh(sh_1) B_1(s) \tag{36}$$

$$-\alpha_2 \sinh(sh_2) B_2(s) - \alpha_3 \sinh(sh_3) B_3(s),$$

$$\gamma_1 \cosh(sh_1) A_1(s) + \gamma_2 \cosh(sh_2) A_2(s) + \gamma_3 \cosh(sh_3) A_3(s) = -\gamma_1 \sinh(sh_1) B_1(s) \tag{37}$$

$$-\gamma_2 \sinh(sh_2) B_2(s) - \gamma_3 \sinh(sh_3) B_3(s),$$

where

$$h_i = h/\sqrt{\lambda_i}, \quad i=1, 2, 3. \tag{38}$$

Also from Eqs. (18)-(21), we obtain,

$$\beta_1 B_1(s) + \beta_2 B_2(s) + \beta_3 B_3(s) = 0, \tag{39}$$

$$\beta_1 \sinh(sh_1) A_1(s) + \beta_2 \sinh(sh_2) A_2(s) + \beta_3 \sinh(sh_3) A_3(s) = -\beta_1 \cosh(sh_1) B_1(s) \tag{40}$$

$$-\beta_2 \cosh(sh_2) B_2(s) - \beta_3 \cosh(sh_3) B_3(s),$$

$$\frac{k_{21}}{\sqrt{\lambda_1}} B_1(s) + \frac{k_{22}}{\sqrt{\lambda_2}} B_2(s) + \frac{k_{23}}{\lambda_3} B_3(s) = 0. \tag{41}$$

It is convenient to use the following definition,

$$M(s) \equiv \frac{k_{11}}{\sqrt{\lambda_1}} B_1(s) + \frac{k_{12}}{\sqrt{\lambda_2}} B_2(s) + \frac{k_{13}}{\sqrt{\lambda_3}} B_3(s) \tag{42}$$

From Eqs. (39), (41) and (42), we can find  $B_i(s)$  in the forms,

$$B_1(s) = N_1 M(s), \quad B_2(s) = N_2 M(s),$$

$$B_3(s) = N_3 M(s), \tag{43}$$

where

$$N_1 = (-k_{22} - k_{13}k_{22} + k_{23} + k_{12}k_{23})\sqrt{\lambda_1}/\Delta, \tag{44}$$

$$N_2 = (k_{21} + k_{13}k_{21} - k_{23} - k_{11}k_{23})\sqrt{\lambda_2}/\Delta, \tag{45}$$

$$N_3 = (-k_{21} - k_{12}k_{21} + k_{22} + k_{11}k_{22})\sqrt{\lambda_3}/\Delta, \tag{46}$$

$$\Delta = k_{12}k_{21} - k_{13}k_{21} - k_{11}k_{22} + k_{13}k_{22} + k_{11}k_{23} - k_{12}k_{23}. \tag{47}$$

Therefore the unknowns  $A_i(s)$  ( $i=1, 2, 3$ ) can be determined in terms of  $M(s)$  from Eqs. (36)-(37) and (40).

Using the mixed boundary conditions, Eqs. (22) and (23), we obtain the following dual integral equations,

$$\int_0^\infty s f_i(s) M(s) \cos(sx) ds = -\frac{\pi}{2} c_0, \quad (0 \leq x < a), \tag{48}$$

$$\int_0^\infty M(s) \cos(sx) ds = 0, \quad (a < x < \infty), \tag{49}$$

where

$$f_i(s) = -\frac{\alpha_1 A_1(s) + \alpha_2 A_2(s) + \alpha_3 A_3(s)}{(\alpha_1 N_1 + \alpha_2 N_2 + \alpha_3 N_3) M(s)}. \tag{50}$$

To solve the dual integral equations, we define  $M(s)$  in the form,

$$M(s) = \int_0^a \xi \mathcal{O}(\xi) J_0(s\xi) d\xi, \tag{51}$$

where  $J_0(s\xi)$  is the zero-order Bessel function of the first kind.

Inserting Eq. (51) into Eqs. (48) and (49), we can find that the auxiliary function  $\mathcal{O}(\xi)$  is given by the following Fredholm integral equation of the second kind,

$$\Omega(\mathcal{E}) + \int_0^1 L(\mathcal{E}, H) \Omega(H) dH = \sqrt{\mathcal{E}}, \tag{52}$$

where

$$L(\mathcal{E}, H) = \sqrt{\mathcal{E}H} \int_0^\infty S [f_1(S/a) - 1] J_0(SH) J_0(SE) dS, \tag{53}$$

$$\begin{cases} S = sa, \quad \mathcal{E} = \frac{\xi}{a}, \quad H = \frac{\eta}{a}, \\ \Omega(\mathcal{E}) = -\frac{2}{\pi c_0} \sqrt{\mathcal{E}} \mathcal{O}(\xi), \\ \Omega(H) = -\frac{2}{\pi c_0} \sqrt{H} \mathcal{O}(\eta). \end{cases} \tag{54}$$

### 4. Field Intensity Factors

The mode I stress intensity factor,  $K^\sigma$  is defined and determined in the form,

$$K^\sigma \equiv \lim_{x \rightarrow a^+} \sqrt{2\pi(x-a)} \sigma_z(x, 0) = c_0 \sqrt{\pi a} \Omega(1). \tag{55}$$

Extending the traditional concept of stress intensity factor to other field variables (Pak, 1990) and considering four possible far field conditions, we have

$$K^f = C_f \sigma_0 \sqrt{\pi a} \Omega(1), \quad (f = \sigma, \epsilon, E, D), \tag{56}$$

where

$$C_\sigma = 1, \tag{57}$$

$$C_\epsilon = \frac{\frac{k_{11}N_1}{\lambda_1} + \frac{k_{12}N_2}{\lambda_2} + \frac{k_{13}N_3}{\lambda_3}}{\alpha_1 N_1 + \alpha_2 N_2 + \alpha_3 N_3}, \tag{58}$$

$$C_E = -\frac{\frac{k_{21}N_1}{\lambda_1} + \frac{k_{22}N_2}{\lambda_2} + \frac{k_{23}N_3}{\lambda_3}}{\alpha_1 N_1 + \alpha_2 N_2 + \alpha_3 N_3}, \tag{59}$$

$$C_D = \frac{\gamma_1 N_1 + \gamma_2 N_2 + \gamma_3 N_3}{\alpha_1 N_1 + \alpha_2 N_2 + \alpha_3 N_3}, \tag{60}$$

and  $K^\epsilon$ ,  $K^E$  and  $K^D$  are strain intensity, electric field intensity and electric displacement intensity factor, respectively.

From Eq. (56), it is noted that the uniform electric load has no influence on the field singularities under constant stress loading, and the electric displacement intensity factor depends on

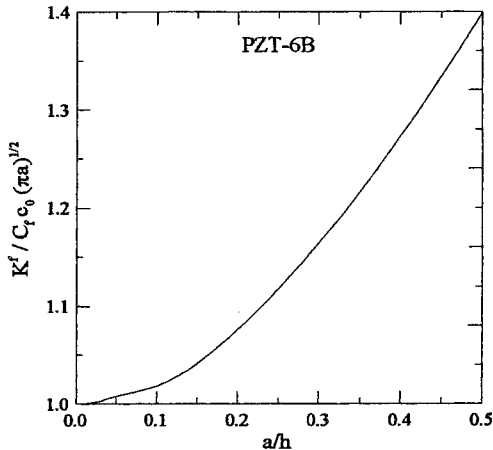


Fig. 2 Normalized field intensity factors  $K^f / C_f c_0 \sqrt{\pi a}$  vs.  $a/h$

the material constant  $C_D$  and the applied mechanical load  $\sigma_0$  but not on the applied electrical load. These are well agreed with the results of Gao and Fan (1999).

In case of  $h \rightarrow \infty$ , the field intensity factors for an infinite piezoelectric ceramic can be obtained in the form,

$$K^f = C_f c_0 \sqrt{\pi a}, \quad (f = \sigma, \epsilon, E, D), \tag{61}$$

These are also agreed with the results of Gao and Fan (1999).

To examine the effect of electromechanical interactions on the field intensity factors, equation (52) is computed numerically by Gaussian quadrature formula. We consider PZT-6B ceramic which material properties are as follows,

Elastic constants ( $10^{10}$  N/m<sup>2</sup>):

$$c_{11} = 16.8, \quad c_{33} = 16.3, \quad c_{44} = 2.71, \quad c_{13} = 6.0,$$

Piezoelectric constants (C/m<sup>2</sup>):

$$e_{15} = 4.6, \quad e_{31} = -0.9, \quad e_{33} = 7.1,$$

Dielectric permittivity ( $10^{-10}$  F/m):

$$d_{11} = 36, \quad d_{33} = 34.$$

Figure 2 displays the variation of the normalized field intensity factors,  $K^f / C_f c_0 \sqrt{\pi a}$ , against the  $a/h$  values. They increase with the increase of the  $a/h$  ratio.

### 5. Conclusions

The electroelastic crack problem in a transversely isotropic piezoelectric ceramic strip under in-plane normal loading was analyzed by the introduction of potential functions and the integral transform approach. The traditional concept of linear elastic fracture mechanics is extended to include the piezoelectric effects and the results are expressed in terms of the field intensity factors. Especially, the electric loadings have no influence on the field singularities under constant stress loading.

### Acknowledgements

The authors are grateful for the supports provided by the Brain Korea 21 project and a grant

from the Korea Science & Engineering Foundation (KOSEF) and Safety and Structural Integrity Research Center at the Sungkyunkwan University.

### References

- Gao, C. F. and Fan, W. X., 1999, "Exact Solutions for the Plane Problem in Piezoelectric Materials with an Elliptic or a Crack," *International Journal of Solids and Structures* Vol. 36, pp. 2527~2540.
- Kwon, S. M. and Lee, K. Y., 2000, "Analysis of Stress and Electric fields in a Rectangular Piezoelectric Body with a Center Crack Under Anti-Plane Shear Loading," *International Journal of Solids and Structures*, Vol. 37, pp. 4859~4869.
- Pak, Y. E. , 1990, "Crack Extension Force in a Piezoelectric Materials," *ASME Journal of Applied Mechanics*, Vol. 57, pp. 647~653.
- Park, S. B. and Sun, C. T., 1995, "Effect of Electric Field on Fracture of Piezoelectric Ceramics," *International Journal of Fracture*, Vol. 70, pp. 203~216.
- Shindo, Y., Narita, F. and Tanaka, K., 1996, "Electroelastic Intensification Near Anti-Plane Shear Crack in Orthotropic Piezoelectric Ceramic Strip," *Theoretical and Applied Fracture Mechanics*, Vol. 25, pp. 65~71.
- Shindo, Y., Tanaka, K. and Narita, F., 1997, "Singular Stress and Electric Fields of a Piezoelectric Ceramic Strip with a Finite Crack Under Longitudinal Shear," *Acta Mechanica*, Vol. 120, pp. 31~45.
- Tobin, A. G., Pak, Y. E., 1993, "Effect of electric field on fracture behavior of PZT ceramics." *Proc. SPIE, Smart Structures and Materials* 1916, pp. 78~86.