

Au-Tm (Gold-Thulium)

H. Okamoto

The Au-Tm phase diagram in [Massalski2] was redrawn from [1987Gsc]. This phase diagram was derived by thermodynamic modeling by assuming systematic changes in thermodynamic parameters of related phases in the gold-rare earth systems.

Figure 1 shows the Au-Tm phase diagram determined by [2002Sac] by means of x-ray powder diffraction, optical and scanning electron microscopy, electron probe microanalysis and differential thermal analysis. A new phase Au₁₀Tm₇ was found in this work.

Table 1 shows Au-Tm crystal structure data.

Table 1 Au-Tm crystal structure data

Phase	Composition, at.% Tm	Pearson symbol	Space group	Strukturbericht designation	Prototype
(Au)	0	<i>cF4</i>	<i>Fm</i> $\bar{3}$ <i>m</i>	<i>A1</i>	Cu
Au ₄ Tm	20	<i>tI10</i>	<i>I4/m</i>	<i>D1_a</i>	MoNi ₄
Au ₃ Tm	25	<i>oP8</i>	<i>Pmmn</i>	<i>D0_a</i>	β TiCu ₃
Au ₂ Tm	33.3	<i>tI6</i>	<i>I4/mmm</i>	<i>C11_b</i>	MoSi ₂
Au ₁₀ Tm ₇	41.1	<i>tI136</i>	<i>I4₁/acd</i>	...	Au ₁₀ Gd ₇
β AuTm	50	<i>cP2</i>	<i>Pm</i> $\bar{3}$ <i>m</i>	<i>B2</i>	CsCl
α AuTm	50	<i>oC8</i>	<i>Cmcm</i>	<i>B_f</i>	CrB
AuTm ₂	66.7	<i>oP12</i>	<i>Pnma</i>	<i>C23</i>	Co ₂ Si
(Tm)	100	<i>hP2</i>	<i>P6₃/mmc</i>	<i>A3</i>	Mg

References

- 1987Gsc:** K.A. Gschneidner Jr., F.W. Calderwood, H. Okamoto, and T.B. Massalski, The Au-Tm (Gold-Thulium) System, in *Phase Diagrams of Binary Gold Alloys.*, H. Okamoto and T.B. Massalski, Eds., ASM International, Metals Park OH, 1987, p 317-319
- 2002Sac:** A. Saccone, D. Macciò, S. Delfino, and R. Ferro, Alloying Behavior of the Rare Earth Metals with Gold: The Ho-Au, Er-Au, and Tm-Au Systems, *Intermetallics*, 2002, **10**(9), p 903-913

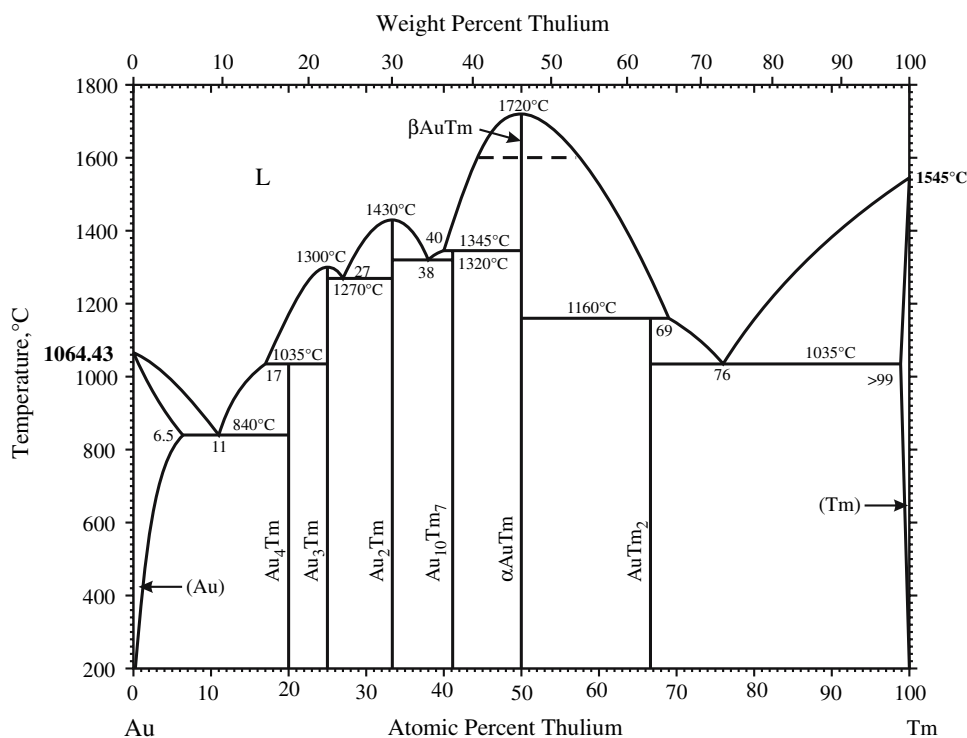


Fig. 1 Au-Tm phase diagram