

# The effects of gamma irradiation on non-isothermal crystallization kinetics and microhardness of the $\text{Li}_2\text{O}-\text{Al}_2\text{O}_3-\text{SiO}_2$ glass-ceramic

Omer Kaygili · Hulusi Yavuz

Received: 21 October 2009 / Accepted: 14 December 2009 / Published online: 5 January 2010  
© Akadémiai Kiadó, Budapest, Hungary 2010

**Abstract** The effects of gamma irradiation on crystallization kinetics and microhardness properties of the  $\text{Li}_2\text{O}-\text{Al}_2\text{O}_3-\text{SiO}_2$  (LAS) glass-ceramic sample have been investigated. The glass-ceramic was irradiated to  $\gamma$ -source  $^{60}\text{Co}$  of 0.7 MGy. The crystallization kinetics of the irradiated and non-irradiated samples were characterized using differential scanning calorimetry. The crystallization kinetics and microhardness properties of the glass-ceramic changed the gamma irradiation, and the high dose of gamma irradiation affects significantly the crystallization kinetics and microhardness properties of the  $\text{Li}_2\text{O}-\text{Al}_2\text{O}_3-\text{SiO}_2$  glass-ceramic sample.

**Keywords** Glass-ceramics · Crystallization kinetics ·  $\gamma$ -Irradiation effects · Microhardness

## Introduction

Glass-ceramics are fine-grained materials, which are formed using standard glass manufacturing methods. They are polycrystalline materials with crystalline size about 1  $\mu\text{m}$  and smaller than 1  $\mu\text{m}$  [1–4]. Lithium alumina-silicate (LAS) is one of the most common glass-ceramics and has extensively been used in cook wares, cook top panels, heat-resistant windows and telescope mirror blanks owing to its excellent properties such as the low, zero or even negative thermal expansion coefficient, as well as thermal and chemical durability and mechanical advantages such as high strength, hardness and resistance to wear [5–17] and

also these materials have high melting point and viscosity. The high melting point of glass-ceramic material is decreased with the addition of alkali oxides and earth-alkali oxides. These additives have been used in glass-ceramics for lower the melting temperatures for many years, such as  $\text{Li}_2\text{O}$ ,  $\text{Na}_2\text{O}$  and  $\text{K}_2\text{O}$  [5, 6, 18]. The aim of present study is to investigate the effects of gamma irradiation on non-isothermal crystallization kinetics, density and microhardness of the LAS glass-ceramic sample.

## Experimental

Glass-ceramic sample was prepared with 77.5%  $\text{SiO}_2$ , 21.2%  $\text{Li}_2\text{O}$  and 1.3%  $\text{Al}_2\text{O}_3$  (wt%) powder oxides whose purities are 99.5%. The powder mixture grinded for 3 hours was converted a pellet under 28.5 MPa pressure at 150 °C temperature. Then, this pellet has been melted in a platinum crucible in an electrical furnace for 2.5 h at 1300 °C temperature. The prepared glass-ceramic sample was irradiated to  $\gamma$ -source  $^{60}\text{Co}$  of 0.7 MGy at a dose rate of 2.50 kGy/h (Ankara Nuclear Research and Training Centre, Turkey).

The calorimetric measurements were performed by a TA Instruments DSC 2010 calorimeter. The crystallization temperatures of the glass-ceramic sample were determined from DSC measurements performed under heating rates of 10, 15, 20 and 25  $^{\circ}\text{C min}^{-1}$ .

The measuring process of density for the non-irradiated and irradiated glass-ceramic materials was calculated by Archimedes's method.

Vickers microhardness values of the non-irradiated and irradiated glass-ceramics were measured on MHT-10 microhardness tester equipment. The glass-ceramic samples were coated with Bakelite for measuring their micro-

O. Kaygili (✉) · H. Yavuz  
Department of Physics, Faculty of Arts and Science,  
Firat University, 23169 Elazig, Turkey  
e-mail: okaygili@firat.edu.tr

hardness, and then surfaces of the samples were polished with emery papers in wet ground.


## Results and discussion

DSC results of the non-irradiated and irradiated glass-ceramic samples are shown in Fig. 1. The crystallization kinetic parameters of the glass-ceramic sample were calculated with Avrami kinetics. The obtained parameters are given in Table 1. DSC curves of the sample give two peaks, as shown in Fig. 1 and as seen in Fig. 1, the second peaks of the glass-ceramic sample irradiated with gamma irradiation are the sharper and narrower than the peaks of the non-irradiated glass-ceramic sample.

The relation between reaction rate and crystallization peak temperature is defined by Arrhenius equation [19–21]

$$k = k_0 \exp(-E_a/RT_p), \quad (1)$$

where  $k$  is the reaction rate,  $k_0$  is the frequency factor,  $E_a$  is the activation energy,  $R$  is the gas constant and  $T_p$  is the

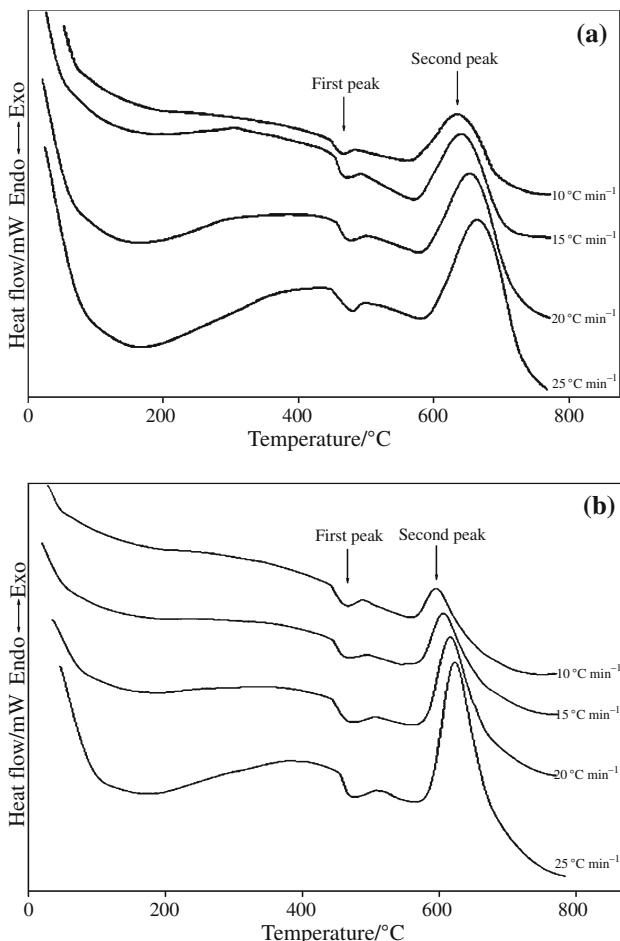

**Fig. 1** DSC results of the glass-ceramic sample. **a** Before irradiation and **b** after irradiation

crystallization peak temperature. Also, relation between heating rate and activation energy is defined by Kissinger's equation [22, 23].

$$\ln(\alpha/T_p^2) = -(E_a/RT_p) + \text{constant}. \quad (2)$$

Using Eq. 2, the activation energies were calculated from the slope of  $\ln(\alpha/T_p^2)$  versus  $1/T_p$  curves, as shown in Fig. 2. The activation energies for the first and second peaks were found to be 325.15 and 184.36 kJ mol<sup>-1</sup>, before irradiation, and 383.81 and 213.19 kJ mol<sup>-1</sup>, after irradiation, respectively.

As seen in Table 1, the crystallization peak temperature ( $T_p$ ) and reaction rate ( $k$ ) of the sample are dependent on the heating rate ( $\alpha$ ). The crystallization peak temperature ( $T_p$ ) and reaction rate ( $k$ ) of the sample increase linearly with the heating rate. The activation energy of the sample is increased with the gamma irradiation. The crystallization peak temperature, activation energy, reaction rate and frequency factor values of the sample increase with irradiation for the first peak. By way of exception, the crystallization peak temperature of the second peak of the glass-ceramic sample is decreased.

The Avrami exponents of the glass-ceramic materials can be computed by the modified Ozawa equation [24]

$$\ln[-\ln(1-x)]/\ln \alpha = -n, \quad (3)$$

where  $x$  is the volume fraction crystallized after any time  $t$ ,  $n$  is the dimensionless exponent depended on the mechanism of transformation known as the Avrami exponent and  $\alpha$  is the heating rate. Using Eq. 3, the Avrami exponents were calculated from the slope of the  $\ln[-\ln(1-x)]$  versus  $\ln \alpha$  curves, as shown in Fig. 3. The Avrami exponents of the non-irradiated and irradiated glass-ceramic samples were found to be 3.68, 2.18 and 1.97, 1.42, for the first and second DSC peaks, respectively. The Avrami exponent values of the glass-ceramic sample show that the crystallization mechanism changes from homogenous nucleation to two-dimension nucleation for the first peaks and changes from two-dimensional nucleation to surface nucleation for the second peaks, respectively [25–27]. It is obviously seen that the values of Avrami exponent ( $n$ ) of the sample were decreased with gamma irradiation. This result indicates that the gamma irradiation decreases the crystallization mechanism of the glass-ceramic sample.

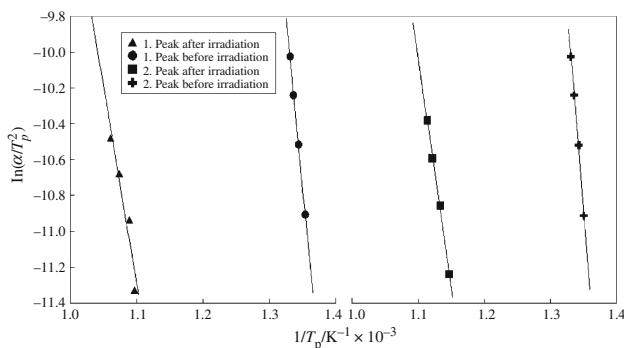
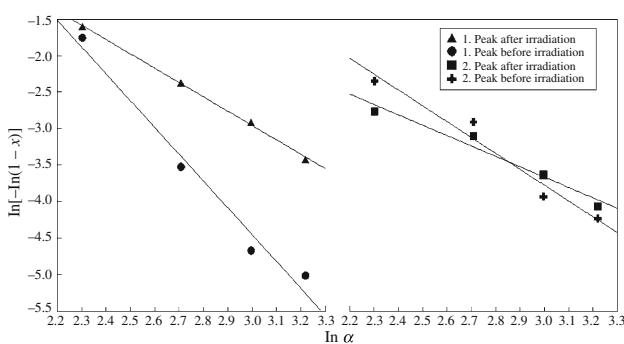
The densities of the non-irradiated and irradiated glass-ceramic materials can be calculated by Archimedes's method [28]

$$\rho = [a/(a-b)]\rho_l \quad (4)$$

where  $\rho$  is the density of the solid sample and  $\rho_l$  is the density of the immersion liquid. Water was used as immersion liquid and its density is 1 g cm<sup>-3</sup>. Additionally,  $a$  and  $b$  are weights of the sample in air and liquid, respectively. The

**Table 1** The crystallization kinetic values of the glass–ceramic sample for before and after gamma irradiation

$\alpha/C \text{ min}^{-1}$	Peak 1					Peak 2				
	$T_p/^\circ\text{C}$	$E_a/\text{kJ mol}^{-1}$	$k_0/\text{s}^{-1}$	$k/\text{s}^{-1}$	$n$	$T_p/^\circ\text{C}$	$E_a/\text{kJ mol}^{-1}$	$k_0/\text{s}^{-1}$	$k/\text{s}^{-1}$	$n$
Before irradiation										
10	465.22	325.15	$7.07 \times 10^{22}$	0.705	3.68	638.82	184.36	$1.08 \times 10^{10}$	0.298	2.18
15	470.79			1.048		645.33			0.354	
20	475.18			1.427		658.35			0.497	
25	477.83			1.716		669.80			0.663	
After irradiation										
10	467.49	383.81	$1.00 \times 10^{27}$	0.857	1.97	598.64	213.19	$2.03 \times 10^{12}$	0.342	1.42
15	471.65			1.214		608.93			0.483	
20	475.54			1.670		618.53			0.660	
25	478.29			2.099		624.59			0.801	

**Fig. 2** The plots of  $\ln(\alpha/T_p^2)$  versus  $1/T_p$  of the glass–ceramic sample for before and after gamma irradiation**Fig. 3** The plots of  $\ln[-\ln(1-x)]$  versus  $\ln \alpha$  of the glass–ceramic sample for before and after gamma irradiation

molar volume  $V_m$  can be determined by the following relation

$$V_m = \text{Molecular mass}/\text{Density}. \quad (5)$$

The measured values of density, molar volume and microhardness of the glass–ceramic samples are given in Table 2. The density and molar volume values of the

**Table 2** Values of density, molar volume and microhardness of the non-irradiated and irradiated glass–ceramic samples

Sample	$\rho/\text{kg m}^{-3}$	$V_m/\text{m}^3 \text{ mol}^{-1}$	Microhardness/GPa
Non-irradiated	2323	$23.33 \times 10^6$	8.297
Irradiated	2321	$23.33 \times 10^6$	10.797

irradiated sample were virtually unchanged in comparison with the non-irradiated sample, as shown in Table 2. Additionally, the microhardness of the irradiated sample is increased due to the rising of internal energy [29].

## Conclusions

In this study, the gamma irradiation effects on crystallization kinetics of the LAS glass–ceramic samples have been investigated using non-isothermal kinetics. Once the glass–ceramic sample was irradiated with gamma irradiation, its crystallization kinetic parameters included Avrami exponent ( $n$ ), reaction rate ( $k$ ), activation energy ( $E_a$ ) and frequency factor ( $k_0$ ) were changed. The microhardness of the sample increases with gamma irradiation. The density and molar volume values of the irradiated sample do not change in comparison with the non-irradiated sample.

**Acknowledgements** We are grateful to A.B. Selcuk for irradiating process of the glass–ceramic sample and F. Yakuphanoglu for critical reading and editing of the manuscript.

## References

- Šimon P, Jóna E, Pavlík V. Thermal properties of oxide glasses. Part III. Thermal stability of  $\text{Li}_2\text{O}\cdot 2\text{SiO}_2\cdot n\text{MeO}_2$  glasses ( $M = \text{Ti}, \text{Zr}$ ). *J Therm Anal Calorim*. 2008;94:421–5.

2. Liu H, Lu H, Chen D, Wang H, Xu H, Zhang R. Preparation and properties of glass-ceramics derived from blast-furnace slag by a ceramic-sintering process. *Ceram Int.* 2009;35:3181–4.
3. McMillan PW. Glass-ceramics. 2nd ed. London: Academic Press; 1979.
4. Strnad Z. Glass-ceramic materials. Amsterdam: Elsevier; 1986.
5. Guedes M, Ferro AC, Ferreira JMF. Nucleation and crystal growth in commercial LAS compositions. *J Eur Ceram Soc.* 2001;21: 1187–94.
6. Guo XZ, Yang H, Cao M. Nucleation and crystallization behavior of  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  system glass ceramic containing little fluorine and no-fluorine. *J Non-Cryst Solids.* 2005;351:2133–7.
7. Riello P, Canton P, Comelato N, Polizzi S, Verità M, Fagherazzi G, et al. Nucleation and crystallization behavior of glass-ceramic materials in the  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  system of interest for their transparency properties. *J Non-Cryst Solids.* 2001;288:127–39.
8. Arnault L, Gerland M, Rivière A. Microstructural study of two LAS-type glass-ceramics and their parent glass. *J Mater Sci.* 2000;35:2331–45.
9. Wurth R, Muñoz F, Müller M, Rüssel C. Crystal growth in a multicomponent lithia aluminosilicate glass. *Mater Chem Phys.* 2009;116:433–7.
10. Gutierrez OD, Osorio E, Paucar CG, Cogollo R, Hadad CZ. Synthesis and characterization of thermoluminescent glass-ceramics  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$ : $\text{CeO}_2$ . *J Lumin.* 2009;129:836–9.
11. Zhu S, Ma H, Calvez L, Zhang X, Lucas J, Adam JL, et al. Optical and mechanical properties of far infrared transmitting glass-ceramics. *J Non-Cryst Solids.* 2007;353:1298–301.
12. Zawrah MF, Hamzawy EMA. Effect of cristobalite formation on sinterability, microstructure and properties of glass/ceramic composites. *Ceram Int.* 2002;28:123–30.
13. Tick PA, Borelli NF, Reaney IM. The relationship between structure and transparency in glass-ceramic materials. *Opt Mater.* 2000;15:81–91.
14. Guo X, Yang H, Han C, Song F. Crystallization and microstructure of  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  glass containing complex nucleating agent. *Thermochim Acta.* 2006;444:201–5.
15. Vlase T, Păcurariu C, Lazău RI, Lazău I. Kinetic studies of the crystallization process of glass-ceramics based on basalt. *J Therm Anal Calorim.* 2007;88:625–9.
16. Hu AM, Liang KM, Wang G, Zhou F, Peng F. Effect of nucleating agents on the crystallization of  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  system glass. *J Therm Anal Calorim.* 2004;78:991–7.
17. Guo X, Zhang L, Yang H. Effects of Li replacement on the nucleation, crystallization and microstructure of  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  glass. *J Non-Cryst Solids.* 2008;354:4031–6.
18. Hu AM, Liang KM, Zhou F, Wang GL, Peng F. Phase transformations of  $\text{Li}_2\text{O}$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  glasses with  $\text{CeO}_2$  addition. *Ceram Int.* 2005;31:11–4.
19. Selçuk AB, Yavuz H. Gamma-irradiation effect on kinetic parameters of glass-ceramic materials. *Mater Lett.* 2003;57: 4382–7.
20. Păcurariu C, Lazău RI, Lazău I, Tiță D. Kinetics of non-isothermal crystallization of some glass-ceramics based on basalt. *J Therm Anal Calorim.* 2007;88:647–52.
21. Hu AM, Li M, Mao DL. Crystallization of spodumene-diopside in the LAS glass ceramics with  $\text{CaO}$  and  $\text{MgO}$  addition. *J Therm Anal Calorim.* 2007;90:185–9.
22. Kissinger HE. Reaction kinetics in differential thermal analysis. *Anal Chem.* 1957;29:1702–6.
23. Hu A, Li M, Mao D. Controlled crystallization of glass-ceramics with two nucleating agents. *Mater Charact.* 2009;60:1529–33.
24. Ozawa T. Kinetics of non-isothermal crystallization. *Polymer.* 1971;12:150–8.
25. Matusita K, Sakka S. Kinetic study of the crystallization of glass by differential scanning calorimetry. *Phys Chem Glasses.* 1979; 20:81–4.
26. Matusita K, Sakka S. Kinetic study of crystallization of glass by differential thermal analysis—criterion on application of Kissinger plot. *J Non-Cryst Solids.* 1980;28–29:741–6.
27. Sun T, Xiao H, Cheng Y, Liu H. Effects of MO (M–Ba, Mg, Ca) on the crystallization of  $\text{B}_2\text{O}_3$ – $\text{Al}_2\text{O}_3$ – $\text{SiO}_2$  glass-ceramics. *Ceram Int.* 2009;35:1051–5.
28. Sharma BI, Goswami M, Sengupta P, Shrinkande VK, Kale GB, Kothiyal GP. Study on some thermo-physical properties in  $\text{Li}_2\text{O}$ – $\text{ZnO}$ – $\text{SiO}_2$  glass-ceramics. *Mater Lett.* 2004;58:2423–8.
29. Ezz-Eldin FM. Radiation effects on some physical and thermal properties of  $\text{V}_2\text{O}_5$ – $\text{P}_2\text{O}_5$  glasses. *Nucl Instrum Methods B.* 1997;159:166–75.