

Table I. Physical Properties of Pillared Layered Oxides


layered precursor	basal <i>d</i> spacing, Å		surface area, m ² /g		cyclohexane adsorptn, ^a wt %	
	initial ^b	final ^c	initial	final	initial	final
titanates Na ₂ Ti ₃ O ₇	8.4	20	<5	280	<1	9
Metal titanate Cs _{0.7} (Ni _{10.35} Ti _{1.65})O ₄	8.4	22	<5	300	<1	10
magadiite	11.5	33	<20	530	<2	14
kenyaite	17.5	36	≤20	600	<5	21

^aAt 25 °C, 40 Torr. ^bDehydrated phase. ^cSwollen with octylammonium, pillared with silica.

Table II. Properties of Pillared Alkali Titanates with Varying *d* spacings

swelling agent	surface area, m ² /g	increase in <i>d</i> spacing, ^a Å	cyclohexane adsorptn, wt %
starting material Na ₂ Ti ₃ O ₇	<5	<1	<1
propylammonium	50	2-3	<3
hexylammonium	200	9	6
octylammonium	280	12	9
dodecylammonium	470	21	16

^aThe increase in *d* spacing is calculated by the formula $d_{001}(\text{pillared}) - d_{001}(\text{layered phase})$, where $d_{001}(\text{layered phase}) = 8.4$ Å.

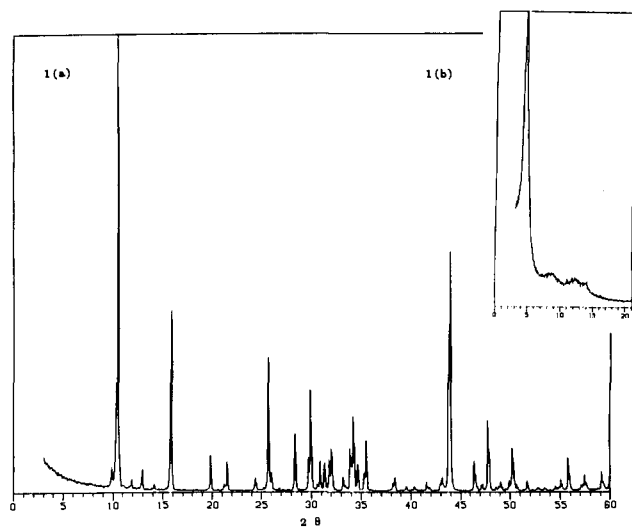**Figure 1.** X-ray diffraction pattern of sodium titanate (1a) and silica-pillared sodium titanate (1b).

$A_x[\text{MTi}]_2\text{O}_4$,¹² and layered silicates such as magadiite, Na₂Si₇O₁₅, and kenyaite, K₂Si₄O₂₉. Table I outlines the starting materials and relevant physical properties of the porous silica-pillared products.

Evidence for the creation of pillared, microporous products follows. First, X-ray diffraction patterns (Figure 1) of a dense, layered titanate, Na₂Ti₃O₇ (1a), and its silica-pillared product¹³ (1b) after calcination at 538 °C indicate a large increase in basal spacing (~12 Å). Secondly, this silica-pillared titanate, containing only 23 wt % silica, shows an increase in surface area from <5 m²/g in the starting Na₂Ti₃O₇ to 280 m²/g in the product. SEM photographs do not reveal significant amounts of amorphous silica external to the titanate crystallites. Also, a dense silica phase completely filling the interlayer region would not give rise to the observed high surface areas. Finally, this product adsorbs 9 wt % cyclohexane (Table I), characteristic of microporous solids such as zeolites.

This novel pillaring technique allows for tailoring of pore sizes as exemplified in Table II for a series of pillared titanates. As

(11) Anderson, S.; Wadsley, A. D. *Acta Crystallogr.* **1961**, *14*, 1245.

(12) Reid, A. F.; Mumme, W. G.; Wadsley, A. D. *Acta Crystallogr.* **1968**, *B24*, 1228. Groult, D.; Mercey, C.; Raveau, B. *J. Solid State Chem.* **1980**, *32*, 289.

(13) The X-ray diffraction pattern of the calcined silica-pillared product is very similar to that of its organoammonium precursor.

the alkyl chain length of the preswelling organic is increased, the observed *d* spacing, reflective of the pore size, also increases. Surface area and cyclohexane adsorption also increase with increasing interlayer separation. These examples illustrate preparation of stable pillared products with interlayer separations of 3–20 Å, determined by the size of the swelling agent. By careful choice of the organic preswelling agent, an even broader range of pore sizes are accessible. Thus, this new procedure not only allows for pillaring of diverse layer compositions but also permits the synthesis of materials with a wide range of pore sizes.

The ability to controllably modify chemical composition as well as pore size provides the flexibility to tailor catalysts for specialized end uses, and the catalytic potential of these materials is actively being explored.

NMR Determination of the Bond Lengths in C₆₀

C. S. Yannoni,* P. P. Bernier,[†] D. S. Bethune, G. Meijer,[‡] and J. R. Salem

IBM Research Division
Almaden Research Center
San Jose, California
Received February 7, 1991

Several years ago, the idea that 60 carbon atoms could form a molecule with icosahedral symmetry was conceived as a purely theoretical possibility.¹ Subsequently, mass spectrometric evidence indicated that microscopic quantities of this fascinating molecule could be produced in cluster beam experiments.² More recently, success in generating C₆₀ molecules in macroscopic amounts³ has stimulated intense interest and activity, and a number of spectroscopic studies of C₆₀ have confirmed that the molecular symmetry is indeed icosahedral (*I_h*).⁴ We have carried out solid-state ¹³C NMR experiments which showed that although C₆₀ reorients rapidly in the solid state at ambient temperatures, the motion can be slowed sufficiently by lowering the temperature that a measurement of the ¹³C chemical shift anisotropy can be made.⁵ The observed line shapes also indicate that the reorientational dynamics for C₆₀ is not uniform throughout the sample, which contained ~10% C₇₀.^{5,6}

Although the icosahedral symmetry of C₆₀ is now established with reasonable certainty, the detailed electronic and geometric structures of this molecule are still of considerable interest. Many

* Present address: GDPC-USTL, 34095 Montpellier, France.

[†] Present address: Department of Molecular and Laser Physics, Catholic University of Nijmegen, Toernooiveld, 6525 ED Nijmegen, The Netherlands.

(1) For this history, see: Kroto, H. W. *Science* **1988**, *242*, 1139.

(2) Heath, J. R. *Spectroscopy* **1990**, *5*, 36. Curl, R. F.; Smalley, R. E. *Science* **1988**, *242*, 1017.

(3) Krätschmer, W.; Lamb, L. D.; Fostiropoulos, K.; Huffman, D. R. *Nature* **1990**, *347*, 354.

(4) Johnson, R. D.; Meijer, G.; Bethune, D. S. *J. Am. Chem. Soc.* **1990**, *112*, 8983. Taylor, R.; Hare, J. P.; Abdul-Sada, A. K.; Kroto, H. W. *Chem. Commun.* **1990**, *20*, 1423. Krätschmer, W.; Fostiropoulos, K.; Huffman, D. R. *Chem. Phys. Lett.* **1990**, *170*, 167. Bethune, D. S.; Meijer, G.; Tang, W. C.; Rosen, H. J. *Chem. Phys. Lett.* **1990**, *174*, 219. Bethune, D. S.; Meijer, G.; Tang, W. C.; Rosen, H. J.; Golden, W. G.; Seki, H.; Brown, C. A.; DeVries, M. S. *Chem. Phys. Lett.* In press.

(5) Yannoni, C. S.; Johnson, R. D.; Meijer, G.; Bethune, D. S.; Salem, J. R. *J. Phys. Chem.* **1991**, *95*, 9.

(6) The same inhomogeneity in dynamics appears to hold in a sample of pure C₆₀; see: Tycko, R.; Haddon, R. C.; Dabbagh, G.; Glarum, S. H.; Douglass, D. C.; Mujser, A. M. *J. Phys. Chem.* **1991**, *95*, 518.

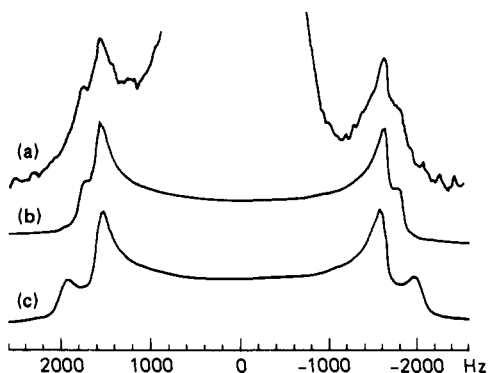


Figure 1. (a) Fourier transform of the ^{13}C signal obtained in a Carr–Purcell Meiboom–Gill sequence carried out on ^{13}C -enriched C_{60} at 77 K. The intense center line has been cropped for clarity (vide infra). The time domain signal was obtained by co-adding 60 000 transients with a 10-s delay between pulse sequences. (b) Simulation of two Pake doublets with carbon–carbon bond lengths of 1.45 and 1.40 Å; (c) as in (b), but with bond lengths of 1.451 and 1.345 Å.

electronic structure calculations have been carried out, giving predictions for the optical spectrum and geometry, and in particular the bond lengths, of C_{60} .⁷ To date, the most detailed geometric data have been provided by X-ray diffraction³ and by STM imaging.⁸ Both of these techniques indicate that the distance between molecular centers in the solid state is ~ 10 Å, but neither gives more detail because of rapid molecular reorientation.^{5,6} In the case of X-ray diffraction, static and/or dynamic disorder may contribute to the failure to determine the internal molecular structure.

In this communication we report a direct ^{13}C NMR measurement of two carbon–carbon bond lengths in C_{60} ⁹ using the Carr–Purcell sequence¹⁰ which has recently been quantified for measuring internuclear distances in orientationally disordered materials.¹¹

The bond lengths are obtained from a measurement of ^{13}C – ^{13}C magnetic dipolar coupling which depends on the inverse cube of the distance between nuclei.¹² Since the ^{13}C isotope is only 1.1% naturally abundant, it is necessary to enrich the sample in ^{13}C to observe this coupling. Samples of C_{60} enriched in ^{13}C were prepared by toluene extraction of soot generated by arc heating graphite in 100 Torr of He. The electrodes were fabricated by coring out graphite rods and packing them with ^{13}C -enriched amorphous carbon.¹³ Solution NMR indicated that the sample was enriched to $\sim 6\%$ ^{13}C . Mass spectrometry and solution NMR further showed that the sample consisted of C_{60} and C_{70} in a ratio of $\sim 6:1$.

To measure the ^{13}C – ^{13}C dipolar coupling, we have used the Carr–Purcell sequence¹⁰ to selectively remove broadening due to the chemical shift anisotropy while retaining the dipolar coupling.¹¹ The sequence, which consists of a single resonant $\pi/2$ pulse followed by a train of π pulses, produces a train of spin echoes.¹⁵ The amplitude of these echoes, captured in receiver windows between pulses, constitutes the transient NMR signal and is stored in a computer for coherent averaging.^{11,16} Dipolar coupling is

$$\Delta = 3\gamma^2\hbar(1 - D)/4\pi R_{\text{CC}}^3 \quad (1)$$

where R_{CC} is the intercarbon distance, γ is the ^{13}C gyromagnetic ratio, and D is the rf duty factor (the fraction of on-time for the 15 MHz radio frequency field).¹¹ Using the method outlined in ref 11, we measured a duty factor $D = 0.134$. The carbon–carbon bond lengths calculated from the splittings using (1) are 1.46 and 1.40 Å. These are upper limits since the effect of broadening due to nearby ^{13}C spins is to move the peaks together, thereby decreasing the splitting giving a bond length which is slightly greater than the actual value.¹⁶ Residual molecular motion could also reduce the dipolar splitting,¹⁷ again yielding bond lengths that would be too large. In the present case this effect can be neglected since observation of a fully developed chemical shift powder pattern with an overall width of ~ 3 kHz at 100 K⁵ suggests that at 77 K (the temperature used in these experiments) the molecule is static on the dipolar NMR time scale (~ 250 μs).

To assess the effect of spectral broadening due to nearby ^{13}C spins, we have made simulations using various bond lengths and compared them to the experimental spectrum in Figure 1a.¹⁶ From such comparisons the two bond lengths obtained are 1.45 ± 0.015 and 1.40 ± 0.015 Å. A simulation of the spectrum with use of these values is shown in Figure 1b. Although the two values of R_{CC} could be quite close given the estimated uncertainties, the difference in bond lengths must be at least 0.04 Å in order to give a splitting of the magnitude shown in Figure 1a. The simulation shown was made using twice as many 1.45 Å bonds, but the experimental signal-to-noise ratio is not high enough to determine the relative number of long and short bonds. The measured bond lengths are consistent with the values that have been calculated for the truncated icosahedral structure proposed for C_{60} .⁷ For the sake of completeness we also made a simulation, shown in Figure 1c, using bond lengths (1.451 and 1.345 Å) predicted for a truncated dodecahedron.¹⁹ It is clear that this simulation does not fit experiment so well, thus providing strong support for the truncated icosahedral form.

Carbon-13 enrichment increases the probability of finding clusters of more than two directly bonded ^{13}C atoms. Dipolar spectra from a cluster of three or four bonded ^{13}C atoms are complex, with many lines spread over a frequency range twice the observed doublet splittings.²⁰ Since no intensity was detected

(7) For a review of bond lengths calculated for C_{60} see: Feng, J.; Li, J.; Wang, A.; Zerner, M. C. *Int. J. Quantum Chem.* **1990**, *37*, 599.

(8) Wilson, R. J.; Meijer, G.; Bethune, D. S.; Johnson, R. D.; Chambliss, D. D.; DeVries, M. S.; Hunziker, H. H.; Wendt, H. R. *Nature* **1990**, *348*, 621. Wragg, J. L.; Chamberlain, J. E.; White, H. W.; Krätschmer, W.; Huffman, D. R. *Nature* **1990**, *348*, 623.

(9) A preliminary account of this work has been presented: Johnson, R. D.; Meijer, G.; Bethune, D. S.; Yannoni, C. S. Proceedings of the Materials Research Society, Symposium on Clusters and Cluster Assembled Materials, Special Session on Buckminsterfullerene, Boston, MA, November 29, 1990 (in press).

(10) Carr, H. Y.; Purcell, E. M. *Phys. Rev.* **1954**, *94*, 630.

(11) Engelsberg, M.; Yannoni, C. S. *J. Magn. Reson.* **1990**, *88*, 393.

(12) Pake, G. E. *J. Chem. Phys.* **1948**, *16*, 327.

(13) Amorphous carbon, 99 atom % ^{13}C , Cambridge Isotope Laboratories, Woburn, MA.

(14) Reference deleted in press.

(15) Hahn, E. L. *Phys. Rev.* **1950**, *80*, 580.

(16) Yannoni, C. S.; Kendrick, R. D. *J. Chem. Phys.* **1981**, *74*, 747.

Horne, D.; Kendrick, R. D.; Yannoni, C. S. *J. Magn. Reson.* **1983**, *52*, 299.

(17) Gutowsky, H. S.; Pake, G. E. *J. Chem. Phys.* **1950**, *18*, 162.

(18) Meiboom, S.; Gill, D. *Rev. Sci. Instrum.* **1958**, *29*, 688.

(19) Shibuya, T.-I.; Yoshitani, M. *Chem. Phys. Lett.* **1987**, *137*, 13.

(20) Andrew, E. R.; Bersohn, R. *J. Chem. Phys.* **1950**, *18*, 159.

Bersohn, R.; Gutowsky, H. S. *J. Chem. Phys.* **1954**, *22*, 651.

McIntyre, H. M.; Cobb, T. B.; Johnson, C. S. *Chem. Phys. Lett.* **1970**, *4*, 585.

Cobb, T. B.; Johnson, C. S. *J. Chem. Phys.* **1970**, *52*, 6224.

Eichhoff, Von. U.; Zachmann, H. G. *Kolloid-Z. Z. Polym.* **1970**, *241*, 928.

Nicol, A. T. *Magnetic Resonance in Colloid and Interface Science*; Fraissard, J. P., Resing, H. A., Eds.; D. Reidel Publishing Co.: Holland, 1980; p 207.

outside the peaks separated by 3596 Hz, isolated pairs of ^{13}C spins appear to predominate for our sample. This is consistent with estimates made assuming that atoms are randomly introduced into the molecules. In particular, for 6% enrichment, the probabilities for 2, 3, and 4 ^{13}C atom clusters are approximately in the ratio 100:10:1. We would also not expect the results to be affected significantly by C_{70} since (1) there is much less C_{70} present in the sample and (2) calculations indicate that it has seven different bond lengths.²¹

In conclusion, we have measured two carbon-carbon bond lengths in C_{60} : 1.45 ± 0.015 and 1.40 ± 0.015 Å. This result is consistent with the soccerball (truncated icosahedron) structure proposed for C_{60} . The observation of ^{13}C - ^{13}C dipolar coupling in enriched C_{60} suggests that it may be possible to explore the mechanism of fullerene assembly with multiple quantum cluster counting.²²

Acknowledgment. The authors enjoyed stimulating discussions with R. D. Johnson and H. C. Dorn. They are also grateful to R. D. Johnson for solution NMR measurements, M. S. DeVries for a mass spectrometric analysis, and R. D. Kendrick for skillful technical assistance. IBM France provided generous financial support for P.P.B. as an IBM Visiting Scientist.

(21) Rudzinski, J. M.; Slanina, Z. Togasi, M.; Osawa, E. *Therm. Acta* **1988**, *125*, 155.

(22) Baum, J.; Gleason, K. K.; Pines, A.; Garroway, A. N.; Reimer, J. A. *Phys. Rev. Lett.* **1986**, *56*, 1377.

The Infrared Spectrum of Silacyclopropenylidene

George Vacek, Brenda Thies Colegrove,[†] and Henry F. Schaefer, III*


Center for Computational Quantum Chemistry
University of Georgia, Athens, Georgia 30602

Received October 18, 1990

The laboratory synthesis and subsequent astronomical detection of cyclopropenylidene is a story that owes its success to the fruitful collaboration of experiment and theory. After two decades of theoretical¹⁻⁸ and experimental⁹⁻¹⁴ investigation, Reisenauer, Maier, Riemann, and Hoffmann¹⁵ identified cyclopropenylidene via matrix isolation. They were aided by the ab initio prediction of its vibrational frequencies and infrared intensities provided by Lee, Bunge, and Schaefer.¹⁶ Shortly thereafter cyclopropenylidene was observed in various interstellar sources,^{17,18} aided by the theoretically determined rotational constants. The silicon-substituted species, silacyclopropenylidene, is a likely candidate for

[†] Present address: Dow Chemical USA, Texas Division, Freeport, TX 77541.

- (1) Gleiter, R.; Hoffmann, R. *J. Am. Chem. Soc.* **1968**, *90*, 5457.
 (2) Lathan, W. H.; Radom, L.; Hariharan, P. c.; Hehre, W. J.; Pople, J. A. In *Topics in Current Chemistry*; Springer-Verlag: New York, 1973; Vol. 40.
 (3) Hehre, W. J.; Pople, J. A.; Lathan, W. A.; Radom, L.; Wasserman, E.; Wasserman, Z. R. *J. Am. Chem. Soc.* **1976**, *98*, 4378.
 (4) Lee, C. K.; Li, W. K. *J. Mol. Struct.* **1977**, *38*, 253.
 (5) Kollmar, H. *J. Am. Chem. Soc.* **1978**, *100*, 2660.
 (6) Baird, N. C.; Taylor, K. F. *J. Am. Chem. Soc.* **1978**, *100*, 1333.
 (7) Shepard, R.; Banerjee, A.; Simons, J. *J. Am. Chem. Soc.* **1979**, *101*, 6174.
 (8) Schoeller, W. W. *Tetrahedron Lett.* **1980**, *21*, 1509.
 (9) Jones, W. M.; Stowe, M. E. *Tetrahedron Lett.* **1964**, 3459.
 (10) Jones, W. M.; Denham, J. M. *J. Am. Chem. Soc.* **1964**, *86*, 944.
 (11) Breslow, R.; Altman, L. J. *J. Am. Chem. Soc.* **1966**, *88*, 504.
 (12) McGregor, S. D.; Jones, W. M. *J. Am. Chem. Soc.* **1968**, *90*, 123.
 (13) Jones, M. W.; Stowe, M. E.; Wells, E. E.; Lester, E. W. *J. Am. Chem. Soc.* **1968**, *90*, 1849.
 (14) Yoshida, Z. *Pure Appl. Chem.* **1982**, *54*, 1059.
 (15) Reisenauer, H. P.; Maier, G.; Riemann, A.; Hoffmann, R. W. *Angew. Chem., Int. Ed. Engl.* **1984**, *23*, 641.
 (16) Lee, T. J.; Bunge, A.; Schaefer, H. F. *J. Am. Chem. Soc.* **1985**, *107*, 137.
 (17) Matthews, H. E.; Irvine, W. M. *Astrophys. J.* **1985**, *298*, L61.
 (18) Thaddeus, P.; Vrtilik, J. M.; Gottlieb, C. A. *Astrophys. J.* **1985**, *299*, L63.



investigation since in recent years there has been significant success in finding silicon analogues of organic molecules.¹⁹

One might expect the silicon molecule to be more stable than the hydrocarbon due to silicon's propensity for the divalent state.²⁰ On the other hand, three-membered rings containing a silicon atom are significantly more strained than the analogous hydrocarbon rings.²¹ There have been two previous theoretical reports on the SiC_2H_2 molecular system. Frenking, Remington, and Schaefer²² thoroughly surveyed the singlet potential energy surface, locating 15 different isomers. Of these, silacyclopropenylidene was the lowest energy structure. They reported the infrared spectrum at the DZP SCF level of theory. Su, Amos, and Handy²³ found 16 different triplet isomers of SiC_2H_2 , but they concluded that the lowest triplet isomer lies 47 kcal/mol above singlet silacyclopropenylidene. Experimentally, both $\text{Si}^{+}(^2\text{P})$ and $\text{Si}(^3\text{P})$ have been observed to react with acetylene, yielding stable products.^{24,25} Thus far, there is no evidence for a singlet species, although the data suggest that singlet silacyclopropenylidene would be the most stable neutral species. Because there has as yet been no observation of the SiC_2H_2 global minimum singlet silacyclopropenylidene despite these indications that it might be a synthesizable species, we have employed ab initio molecular orbital techniques²⁶ to predict its molecular properties at much higher levels of theory than have been previously reported.

In this study, we have used two different basis sets (DZP and TZ2P) and several theoretical methods: self-consistent field (SCF), single and double excitation configuration interaction (CISD) and singles and doubles coupled cluster (CCSD). (Studies at the TZ2P CCSD level, however, were slightly beyond our current facilities.) The DZP basis set consisted of a standard Huzinaga-Dunning-Hay²⁷⁻²⁹ contracted double- ζ basis set supplemented with a set of polarization functions on each atom, i.e., $\text{Si}(11s7p1d/6s4p1d)$, $\text{C}(9s5p1d/4s2p1d)$, and $\text{H}(4s1p/2s1p)$. The polarization function orbital exponents were $\alpha_d(\text{Si}) = 0.50$, $\alpha_d(\text{C}) = 0.75$, and $\alpha_p(\text{H}) = 0.75$. For the TZ2P basis set on silicon we used McLean and Chandler's³⁰ 6s5p contraction of Huzinaga's 12s9p primitive Gaussian set augmented by two sets of six Cartesian d-like functions with orbital exponents $\alpha_d(\text{Si}) = 1.0$, 0.25. For carbon and hydrogen we used a standard Huzinaga-Dunning-Hay triple- ζ basis set and two sets of polarization functions, each with $\alpha_d(\text{C}) = 1.50$ and 0.375 and $\alpha_p(\text{H}) = 1.50$ and 0.375, i.e., $\text{C}(10s6p2d/5s3p2d)$ and $\text{H}(4s2p/3s2p)$. The TZ2P CISD wave functions included 120 787 configuration state functions (CSFs) for the C_{2v} equilibrium geometry, and up to

(19) Apeloig, Y. In *The Chemistry of Organic Silicon Compounds*; Patai, S., Rappoport, Z., Eds.; John Wiley & Sons Ltd.: New York, 1989; Part 1, p 57 ff.

(20) Colegrove, B. T.; Schaefer, H. F. *J. Phys. Chem.* **1990**, *94*, 5593.

(21) (a) Boatz, J. A.; Gordon, M. S. *J. Phys. Chem.* **1989**, *93*, 3025. (b) Grev, R. S.; Schaefer, H. F. *J. Am. Chem. Soc.* **1987**, *109*, 6569.

(22) Frenking, G.; Remington, R. B.; Schaefer, H. F. *J. Am. Chem. Soc.* **1986**, *108*, 2169.

(23) Su, M.-D.; Amos, R. D.; Handy, N. C. *J. Am. Chem. Soc.* **1990**, *112*, 1499.

(24) Bohme, D. K.; Wlodek, S.; Fox, A. In *Rate Coefficients in Astrochemistry*; Mollat, T. J., Williams, D. A., Eds.; Astrophysics Space Science Library; Kluwer Academic Publishers: Boston, 1988.

(25) Basu, S. C.; Husain, D. *J. Photochem. Photobiol.* **1988**, *A42*, 1.

(26) All investigations were performed by using the PSI suite of computer programs, distributed by PSITECH, Inc., Watskinsville, GA.

(27) Huzinaga, S. *J. Chem. Phys.* **1965**, *42*, 1293.

(28) Dunning, T. H. *J. Chem. Phys.* **1970**, *53*, 2823.

(29) Dunning, T. H.; Hay, P. H. In *Modern Theoretical Chemistry*; Schaefer, H. F., Ed.; Plenum Press: New York, 1977; Vol. 3, p 1 ff.

(30) McLean, A. D.; Chandler, G. S. *J. Chem. Phys.* **1980**, *72*, 5639.