

Now, V_z can be defined in terms of θ when the layer normal is parallel to \mathbf{B}_0 as

$$V_z = \cos \theta_{\text{para}} \quad (\text{A-11})$$

and substituting eq A-11 into eq A-10

$$\theta_{\text{para}} = \cos^{-1} \sqrt{\frac{1 - \cos^2 \rho}{1 + \tan^2 20^\circ}} \quad (\text{A-12})$$

rewriting eq A-12 using the relationship $\sin^2 \rho + \cos^2 \rho = 1$

$$\theta_{\text{para}} = \cos^{-1} \sqrt{\frac{\sin^2 \rho}{1 + \tan^2 20^\circ}} \quad (\text{A-13})$$

or, in terms of θ_{perp} ,

$$\theta_{\text{perp}} = \cos^{-1} \sqrt{\frac{\sin^2 \rho}{1 + \tan^2 70^\circ}} \quad (\text{A-14})$$

Equation A-13 can be rewritten as

$$\cos^2 \theta_{\text{para}} = \frac{\sin^2 \rho}{1 + \tan^2 20^\circ} \quad (\text{A-15})$$

or

$$\rho = \sin^{-1} \sqrt{\cos^2(\theta_{\text{para}})(1 + \tan^2 20^\circ)} \quad (\text{A-16})$$

and eq A-14 can be rewritten as

$$\cos^2 \theta_{\text{perp}} = \frac{\sin^2 \rho}{1 + \tan^2 70^\circ} \quad (\text{A-17})$$

or

$$\rho = \sin^{-1} \sqrt{\cos^2(\theta_{\text{perp}})(1 + \tan^2 70^\circ)} \quad (\text{A-18})$$

and therefore

$$\cos \theta_{\text{perp}} / \cos \theta_{\text{para}} = \tan 20^\circ \quad (\text{A-19})$$

Well-Defined Redox-Active Polymers and Block Copolymers Prepared by Living Ring-Opening Metathesis Polymerization

D. Albagli, G. Bazan, M. S. Wrighton,* and R. R. Schrock*

Contribution from the Department of Chemistry, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139. Received June 13, 1991.

Revised Manuscript Received January 30, 1992

Abstract: $\text{Mo}(\text{CH-}i\text{-Bu})(\text{NAr})(\text{O-}i\text{-Bu})_2$ (**1a**) in THf/0.1 M [*n*-Bu₄N]AsF₆ is not oxidized at potentials up to 1.0 V and undergoes a reversible, one electron reduction at -2.16 V vs SCE at a Pt electrode. An analogous initiator containing a ferrocenylmethylidene ligand (**1b**) can be synthesized by treating **1a** with vinylferrocene. Redox-active derivatives of norbornene, containing ferrocene (**2**) or phenothiazine (**3**), were prepared and polymerized by **1a** or **1b** to give living block copolymers containing the ring-opened norbornene derivatives. The living polymer was cleaved from the metal in a Wittig-like reaction with pivaldehyde, trimethylsilylbenzaldehyde, or octamethylferrocenecarboxaldehyde. Polydispersities for the longer block copolymers containing up to ~80 monomer units were found to be as low as 1.05 by GPC. In one case the polydispersity of a homopolymer made from the ferrocene-containing monomer was determined by FD-mass spectroscopy to be 1.06. DSC studies suggest that microphase formation occurs in the block copolymers, even in the case of relatively low molecular weight materials. Solution voltammetric studies of homo and block copolymers showed that the redox centers were electrochemically independent and that all centers exchanged electrons with the electrode. Neutral polymers became insoluble upon oxidation to a polycation, yielding an adsorbed polymer layer on the electrode that could then be cathodically stripped. This oxidative deposition process depended on the electrolyte and the polymer molecular weight but also could be controlled by the size of a nonelectroactive block in the block copolymers. Problems resulting from precipitation of the redox polymers could be circumvented by employing normal pulse voltammetry. Polymers containing redox centers in both end groups as well as in the polymer chain itself have been prepared and their nature confirmed in electrochemical studies.

Introduction

Studies of electroactive polymers attached to the surface of electrodes have focused primarily on electrochemical characteristics, and modification of electrodes with such polymers in order to achieve "molecular electronic" functions, such as pH-dependent charge trapping and chemical sensing,¹ has been successful to some degree. Ideally, however, one would like to be able to control the primary structure and the morphology of a polymer attached to an electrode to a degree that would maximize the desired electrochemical properties. The primary structure of an electroactive polymer, and ultimately its morphology (lamellae, rods, or spheres), could be controlled if living polymerization techniques could be employed.² Under such circumstances (no chain transfer

or termination) the nature of the functionality at each end of the polymer as well as the nature and length of blocks (containing a given monomer) in the polymer chain could be specified. However, traditional living anionic polymerization methods³ probably cannot be employed routinely, since relatively sensitive, redox-active groups would be destroyed. Cationic⁴ or group transfer methods⁵ might be more suitable than anionic methods but again some desirable functionalities may not be tolerated. Living ring opening metathesis polymerization (ROMP) of nor-

(2) (a) Odian, G. *Principles of Polymerization*; Wiley: New York, NY, 1981. (b) Rempp, P.; Merrill, E. *Polymer Synthesis*; Huethig & Wepf: Heidelberg, 1986. (c) Gold, L. *J. Chem. Phys.* **1958**, *28*, 91. (d) Flory, P. *J. Am. Chem. Soc.* **1940**, *62*, 1561. (e) Szwarc, M. *Nature* **1956**, *178*, 1168.

(3) Szwarc, M. *Carbanions, Living Polymers, and Electron Transfer Processes*; Wiley: New York, 1968.

(4) Miyamoto, M.; Sawamoto, M.; Higashimura, T. *Macromolecules* **1984**, *17*, 265.

(5) Sogah, D. Y.; Webster, O. W. *Macromolecules* **1986**, *19*, 1775.

(1) (a) Smith, D. K.; Tender, L. M.; Lane, G. A.; Licht, S.; Wrighton, M. S. *J. Am. Chem. Soc.* **1989**, *111*, 1099. (b) Shu, C.-F.; Wrighton, M. S. *J. Phys. Chem.* **1988**, *92*, 5221.


bornenes and norbornadienes^{6,7} appears more promising since functionalized derivatives are relatively easy to synthesize in wide variety by Diels–Alder reactions and since well-characterized ROMP catalysts have been developed that will tolerate many functionalities.^{7,8} In this paper we report the synthesis and characterization of electroactive polymers and block copolymers made using living ROMP that demonstrate the potential utility of this approach.

Results and Discussion

Initiators, Monomers, and Capping Groups. Scheme I illustrates the method of preparing block copolymers that we report here where the norbornene substituted with two X groups represents the electroactive monomer. Normally norbornene is added first to initiator **1a** in THF. The polymerization of norbornene is complete within minutes. The monomer containing the electroactive group or groups is then added to the living polynorbornene. After that monomer has been consumed (minutes) an aldehyde is added in order to cap the polymer in a Wittig-like reaction. This technique is similar to that reported recently elsewhere for the synthesis of other functionalized homopolymers and block copolymers.^{7,8} Typically less than 30 min are required to prepare the relatively short polymers reported here.

Before attempting to synthesize any polymer from monomers that contain redox-active groups we checked to be certain that the metal catalyst is electrochemically suitable in the potential range of interest. A cyclic voltammogram of Mo(CH-*t*-Bu)(NAr)(O-*t*-Bu)₂ (**1a**) is shown in Figure 1a. The molybdenum complex is not oxidized in THF/0.1 M [*n*-Bu₄N]AsF₆ at potentials up to 1 V vs SCE, but it is reduced at -2.16 V at a Pt disk in a one-electron reversible process. A plot of E vs log[(*i*_{lim} - *i*)/*i*] yields a line of slope $RT/nF = 59$ mV, with $n = 1$, indicative of a reversible redox couple.⁹ Since **1a** is electrochemically inactive over a 3-V range, it should be stable toward reduction or oxidation by most redox-active groups that we might choose to incorporate into a monomer.

An initiator that contains a redox-active group can be prepared by adding 1 equiv of vinylferrocene to **1a** as shown in eq 1.



Polymers prepared with **1b** as the initiator will have one ferrocene as a unique redox-active end group. **1b** can be isolated as a bright red crystalline solid in 50–60% yield. A significant byproduct is [Mo(μ -NAr)(O-*t*-Bu)₂]₂,¹⁰ which is believed to be the product of coupling of methylene complexes. **1b** itself is relatively stable toward bimolecular decomposition. The proton and carbon NMR spectra of **1b** are characteristic of one rotameric form of an alkylidene complex of this general type ($\delta H_{\alpha} = 11.90$, $\delta C_{\alpha} = 274$, $J_{CH_{\alpha}} = 127$), presumably the more stable *syn* form in which the ferrocenyl substituent points toward the imido ligand. Rotamers have been observed in many circumstances¹¹ and appear to interconvert in systems of this type with $\Delta G^{\ddagger} = 16$ –18 kcal mol⁻¹.

Cyclic voltammograms of **1b** in THF and in CH₂Cl₂ are shown in Figure 1b. No reduction wave is observed out to -2.40 V vs SCE, consistent with the ferrocenyl substituent being a stronger electron donor than a *tert*-butyl group, thereby making the metal center more difficult to reduce. In THF a ferrocene-like oxidation wave is observed, but two overlapping ferrocene-like oxidation waves are observed in dichloromethane using a 500 μ m Pt disk electrode. At present we have no explanation. One possible explanation for two waves is the presence of two different con-

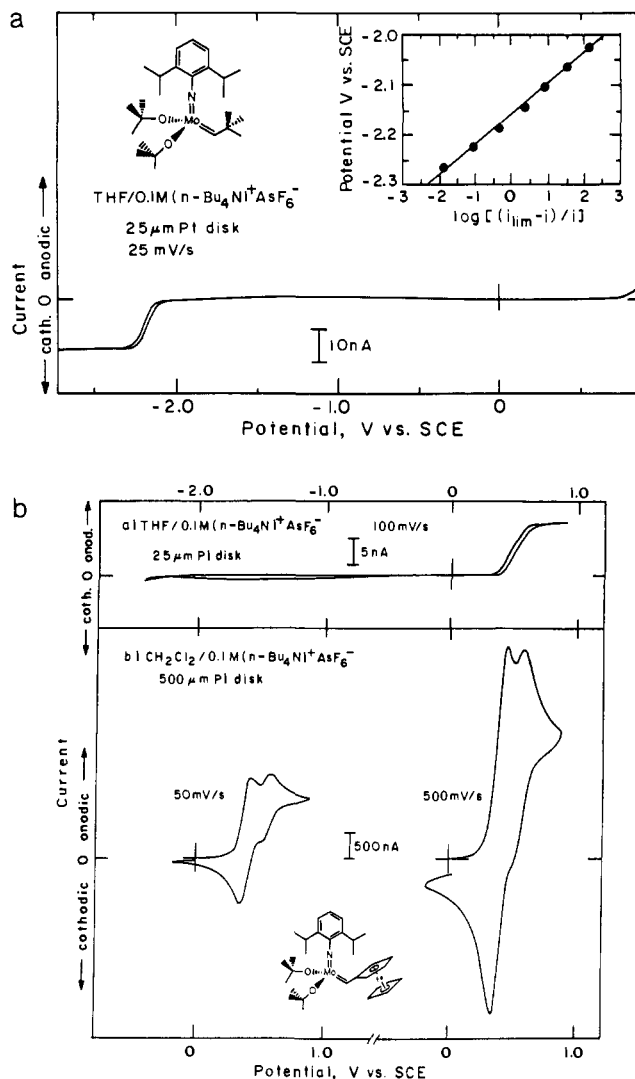


Figure 1. Cyclic voltammetry of (a) **1a** in THF/0.1 M [*n*-Bu₄N]AsF₆ at 25 mV s⁻¹ at a 25 μ m Pt disk electrode and (b) **1b** in CH₂Cl₂/0.1 M [*n*-Bu₄N]AsF₆ at 50 and 500 mV s⁻¹ at a 500 μ m Pt disk electrode.

formers in dichloromethane with different redox potentials.^{12,13} (Electrochemically-induced structural changes that yield isomers with different redox potentials have been observed for organometallic complexes¹⁴ and hindered olefins.¹⁵) Although decomposition of **1b** has not yet been ruled out completely, different synthetic samples and recrystallized samples all yield the same result, and polymers prepared with **1b** as the initiator produce polymers with the expected stoichiometry (see below).

Initial tests to determine whether a functional group can be tolerated by **1a** consisted of polymerizing norbornene (NBE) in the presence of 30–50 equiv of a molecule containing that functional group. Norbornene polymerization was unaffected by either ferrocene or phenothiazine. In contrast, benzoquinone reacted with **1a** and/or living polynorbornene made with **1a** as the initiator and therefore cannot be considered as a potential redox group. Alkylidene complexes of this type react with the carbonyl group in aldehydes and ketones in a Wittig-like reaction,⁷ and the instability of the alkylidene complexes to benzoquinone therefore is not surprising.

Ferrocene was incorporated into the norbornene skeleton as shown in eq 2. The acid group was employed in order to facilitate

(6) Grubbs, R. H.; Tumas, W. *Science* **1989**, *243*, 907.
 (7) Schrock, R. R. *Acc. Chem. Res.* **1990**, *23*, 158.
 (8) (a) Bazan, G. C.; Schrock, R. R.; Cho, H.-N.; Gibson, V. C. *Macromolecules* **1991**, *24*, 4495. (b) Bazan, G. C.; Oskam, J. H.; Cho, H.-N.; Park, L. Y.; Schrock, R. R. *J. Am. Chem. Soc.* **1991**, *113*, 6899.
 (9) Bard, A. J.; Faulkner, L. R. *Electrochemical Methods*; Wiley: New York, 1980, Chapter 5.
 (10) Robbins, J.; Schrock, R. R. *Organometallics* **1991**, *10*, 2902.
 (11) Schrock, R. R.; Crowe, W. E.; Bazan, G. C.; DiMare, M.; O'Regan, M. B.; Schofield, M. H. *Organometallics* **1991**, *10*, 1832.

(12) Evans, D. H.; O'Connell, K. M. *Electroanalytical Chem.* **1986**, *14*, 113.
 (13) Bond, A. M.; Oldham, K. B. *J. Phys. Chem.* **1983**, *87*, 2492.
 (14) Wimmer, F. L.; Snow, M. R.; Bond, A. M. *Inorg. Chem.* **1986**, *14*, 113.
 (15) Evans, D. H.; Busch, R. W. *J. Am. Chem. Soc.* **1982**, *104*, 5057.


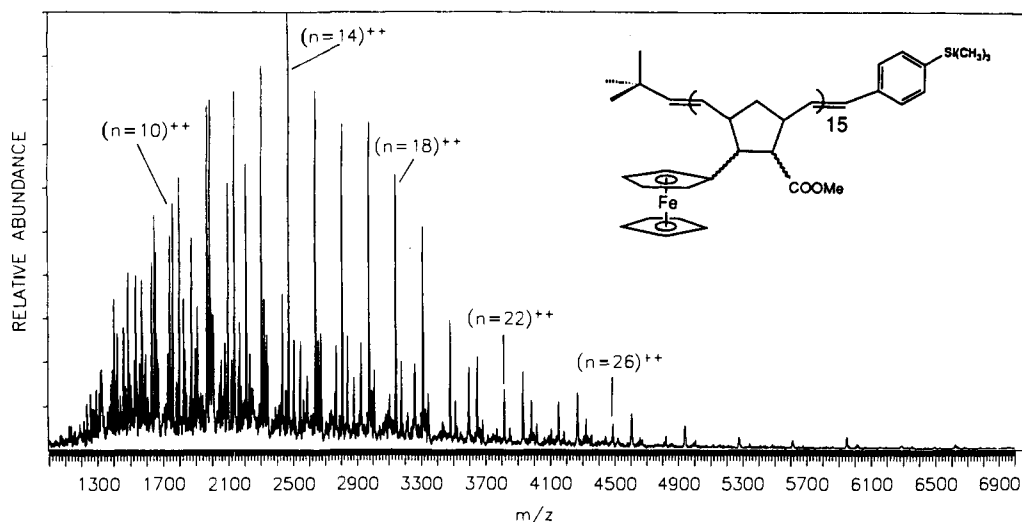


Figure 2. The doubly-charged manifold of peaks in the field desorption mass spectrum of 2_{15} .

the Diels–Alder reaction and was later turned into a carbomethoxy group, which is not expected to interfere with polymerizations that employ Mo catalysts of the type described here.^{7,8} The ferrocenyl and carbomethoxy substituents are *trans*, but two isomers (presumably *endo/exo*) were observed. The phenothiazine redox group was introduced as shown in eq 3. This straightforward preparation

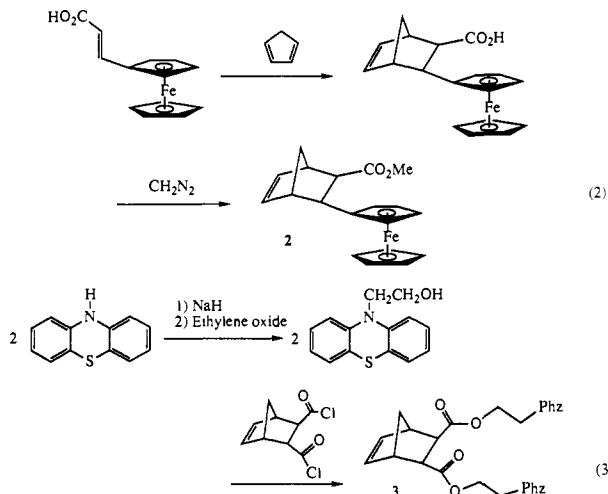


could be scaled up readily to give gram quantities of *trans*-2,3-(10'-(2'-ethyl)phenothiazine)dicarboxylatonorbornene (**3**) in good yield. The redox potential of **2** was found to be +0.380 V vs SCE in dichloromethane, and that of **3**, which has one redox wave in which two electrons are transferred (one from each phenothiazine), was found to be +0.750 V vs SCE in dichloromethane (Figure 7). The ester groups increase the polarity of both **2** and **3**, aiding the solubility of polymers made from them in electrolyte media.

In this paper three aldehydes have been employed in the capping reaction (Scheme I). Pivaldehyde and trimethylsilylbenzaldehyde have been used as ¹H NMR probes for end group analysis, while octamethylferrocenecarboxaldehyde has been employed as a means of introducing a redox-active end group. The polyalkylated ferrocene provides a distinct redox probe, since its redox potential is ~0.8 V negative of the ferrocene unit or units in the monomer or in the initiator.

Synthesis of Ferrocene-Containing Homopolymers and Block Copolymers. Monomer **2** is polymerized quantitatively employing **1a** as the initiator. The polymer was cleaved from the metal with *p*-trimethylsilylbenzaldehyde and purified by precipitation from nonpolar solvents such as hexane, pentane, or petroleum ether. This polymer will be designated 2_x where *x* is the number of equivalents of **2** added to **1a**. GPC analysis shows that the resulting molecular weights are within the narrow range expected

Scheme I. Initiation, Propagation, and Capping Reactions Involved in Preparing Block Copolymers

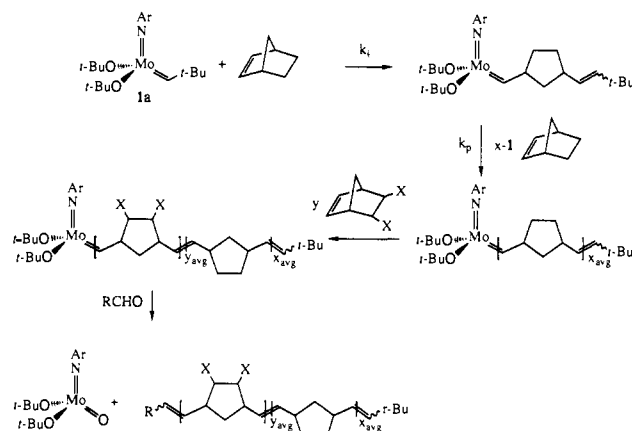

for polymers prepared by living systems (Table I). The GPC trace of 2_{15} and 2_{30} each consisted of a single peak with a polydispersity of 1.13, a relatively low value considering the few equivalents of monomer that were employed. ¹H and ¹³C NMR spectra of 2_{15} and 2_{30} are broad and complex, as expected for polymers that contain a mixture of *cis/trans* olefinic linkages, *endo/exo*, and head-to-tail isomers.¹⁶ Integration of the TMS group in the cap versus the *tert*-butyl group in the initiator and the olefinic protons in the backbone yields the result expected from quantitative polymerization and capping in which the most abundant chain has a length equal to the number of equivalents of monomer added. Similar NMR studies of other homopolymers and block copolymers discussed later also were entirely consistent with their formulation. The ratio of the rate constant for propagation versus that for initiation (k_p/k_i ; Scheme I) can be measured by NMR techniques under conditions where some, but not all, initiator is consumed, assuming that both initiation and propagation are first order in catalyst and monomer and that the rates of the second and subsequent insertion steps are all the same.¹⁷ The k_p/k_i for **2** was found to be ~10, approximately the same (~12) as that found for norbornene.

A more direct measure of the polydispersity in one case was obtained by field desorption mass spectroscopy (FD-MS).¹⁸

(16) Ivin, K. J. *Olefin Metathesis*; Academic Press: London, 1983.

(17) Bazan, G.; Khosravi, E.; Schrock, R. R.; Feast, W. J.; Gibson, V. C.; O'Regan, M. B.; Thomas, J. K.; Davis, W. M. *J. Am. Chem. Soc.* **1990**, *112*, 8378.

(18) (a) Saito, J.; Waki, H.; Teramae, N.; Tanaka, S. *Prog. Org. Coatings* **1988**, *15*, 311. (b) Lattimer, R. P.; Schuttner, H.-R. *Anal. Chem.* **1989**, *61*, 1201A.

Table I. Characterization of Redox-Active Polymers and Block Copolymers

polymer ^a	PDI ^b	M _n ^c	MW (theory) ^d	T _g ^e
2 ₁₅	1.13	5090	5183	143
2 ₃₀	1.13	9030	10226	150
(NBE) ₁₅ 2 ₁₅ ^f	1.05	10460	6688	60, 123
(NBE) ₆₀ 2 ₁₅ ^f	1.07	16190	10925	43, 107
3 ₁₅	1.20	8360	9632	88
3 ₃₀ ^g	1.10	14750	19187	88
3 ₃₀ (NBE) ₅₀	1.12	26740	23832	45, 91
3 ₁₀ (NBE) ₇₀	1.08	35860	13059	50, 80
Fc-3 ₅ ^h	1.22	2700	3420	81
Fc-3 ₅ -FcMe ₈ ⁱ	1.22	2700	3668	81

^a Polymers were prepared with **1a** as the initiator and capped by addition of pivaldehyde, unless otherwise noted. ^b Polydispersity was determined by gel permeation chromatography in dichloromethane versus polystyrene standards. For **2**₁₅ the PDI measured by FD-MS (see text and Figure 2) was 1.06. ^c M_n = weight average molecular weight as determined by GPC vs polystyrene standards. ^d Theoretical molecular weight calculated on the basis of stoichiometry. ^e Determined by DSC (scan rate 20 °C/min). ^f The end group is CH(*p*-C₆H₄SiMe₃). ^g The end group is *p*-(*N,N*-dimethylamino)phenylmethylene. ^h Fc = ferrocenylmethylene that was introduced using **1b** as the initiator. ⁱ FeMe₈ = octamethylferrocenylmethylene that was introduced in the capping reaction as the aldehyde.

Figure 2 shows the doubly-charged manifold of peaks obtained for **2**₁₅ ranging from *n* = 8 to *n* = 26. Singly- and triply-charged peak manifolds were obtained at different values of emitter current. In two manifolds the most abundant chain length was *n* = 14; it was *n* = 15 in the third. These data were used to calculate a polydispersity of 1.06. This value is similar to that obtained by GPC. The accuracy of a PDI measured by FD-MS is limited to some degree by the tendency for the lower molecular weight polymers to produce higher intensity peaks, i.e., the composition of the desorbed material will not match the decomposition of the sample exactly. In fact, complete spectra of **2**₃₀ could not be obtained by FD-MS under the same conditions used to obtain spectra of **2**₁₅.

Block copolymers containing NBE and **2** capped by *tert*-butylmethylene (from **1a**) and *p*-trimethylsilylbenzylidene can be prepared straightforwardly (Table I). Although in these cases norbornene was added first to **1a**, the similarity in the values of *k_p/k_t* for NBE and **2** suggests that the block copolymers that are formed by adding **2** first would be identical to those obtained by adding NBE first. The polydispersities of these block copolymers are slightly lower than those of the homopolymers, consistent with the longer chain lengths.

Differential scanning calorimetry (DSC) traces of **2_n** homopolymers and (NBE)_{*n*}**2_m** block copolymers are shown in Figure 3; glass transition temperatures can be found in Table I. It is evident that the (NBE)_{*n*} and **2_m** blocks separate into microphases in the block copolymers, even though the chains are relatively short. For the **2_n** homopolymers, *T_g* increases with molecular weight, as one would expect, since glass transition temperatures generally do not stop increasing until the molecular weight surpasses ~ 10000.¹⁹ In the block copolymers the *T_g* ascribed to the **2_m** phase is comparatively low (123 and 107°), probably because of the relatively small ratio of domain volume to interphase region for these small blocks. Since the lower *T_g* block is linked to the higher *T_g* block, the motion in the polynorbornene block increases the free volume of the **2_m** phase, and cooperativity of chain movements is mediated by the chain in the region between the two phases.²⁰ As the relative block size of (NBE)_{*n*} to **2_m** increases, the magnitude of this effect increases (*T_g* **2** = 123 °C for (NBE)₁₅**2**₁₅ and 107 °C for (NBE)₆₀**2**₁₅). Conversely, the lower *T_g* in block copolymers is higher than that in polynorbornene (~45 °C), presumably because the higher *T_g* domains for **2_x** can dampen chain motions

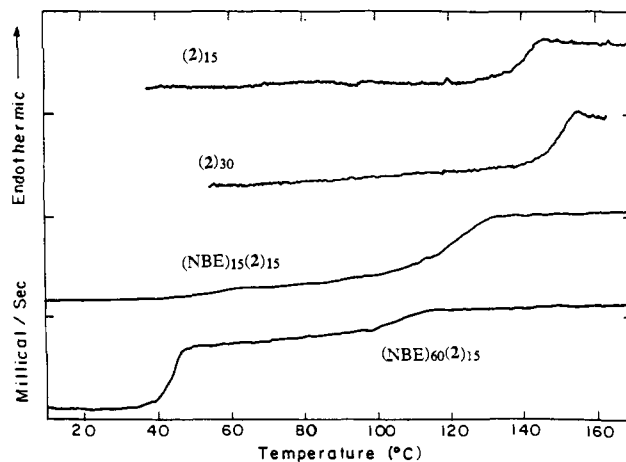


Figure 3. DSC traces of the **2_n** polymers and (NBE)_{*n*}**2_m** block copolymers (scan rate 20 °C/min). Samples were annealed first above the transition temperature for 10 min, and all measurements were repeated several times in order to check reproducibility.

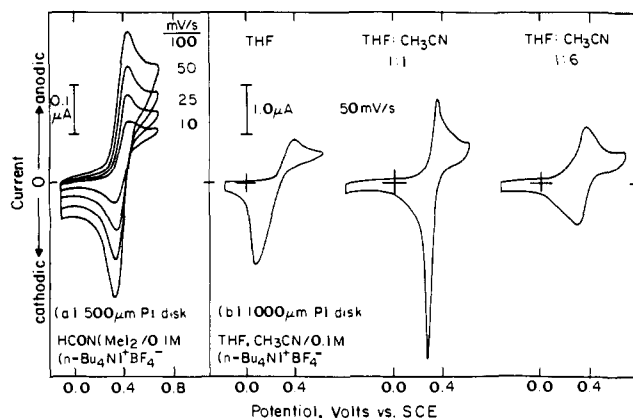


Figure 4. Solvent dependence of the cyclic voltammograms of **2**₁₅: (a) DMF/0.1 M [*n*-Bu₄N]BF₄ and (b) THF, 1:1 THF/CH₃CN and 1:6 THF/CH₃CN. (The supporting electrolyte was 0.1 M [*n*-Bu₄N]BF₄.)

in the region nearby.^{2a} As the (NBE)_{*n*} block size increases *T_g*-(NBE) is observed at lower temperatures, consistent with the idea that high *T_g* domains should have less influence as the high *T_g* monomer becomes a smaller fraction of the polymer composition, i.e., *T_g*(NBE) = 60 °C for (NBE)₁₅**2**₁₅ and 43 °C for (NBE)₆₀**2**₁₅.

The electrochemistry of **2_n** and (NBE)_{*n*}**2_m** were studied in solution and confined to the electrode surface. The surface-confined electrochemistry will be presented elsewhere. The solution electrochemical behavior of such redox polymers is marked by changes in solubility, which are governed by the amount of charge in the ferrocene units. Reduced (neutral) polymers containing **2** are soluble in benzene, THF, dichloromethane, and dimethylformamide but insoluble in hexane, ethanol, acetonitrile, and water. In the oxidized state, the polymer is still somewhat soluble in dimethylformamide, but it is insoluble in THF and dichloromethane, and it is only slightly soluble in acetonitrile.

The effects of the solubility properties of **2**₁₅ in DMF, THF, and CH₃CN are illustrated in Figure 4. As shown in Figure 4a, in DMF the CV is not much different from that expected for a soluble molecule that has a reversible redox couple, except that the peak cathodic current is ~30% larger than the peak anodic current. In the other solvents the change in solubility with the change in oxidation state is more pronounced. For example, in THF oxidation of **2_n** results in precipitation of the polymer onto the electrode surface, as has been observed in other circumstances.^{21,22} During the reverse scan, the polymer redissolves as

(19) Elias, H.-G. *Macromolecules*; Plenum: New York, 1984; Chapter 10.

(20) Morêse-Sêquêla, B.; St.-Jacques, M.; Renaud, J. M.; Prud'homme, J. *Macromolecules* 1980, 13, 100.

(21) Flanagan, J. B.; Margel, S.; Bard, A. J.; Anson, F. C. *J. Am. Chem. Soc.* 1978, 100, 4248.

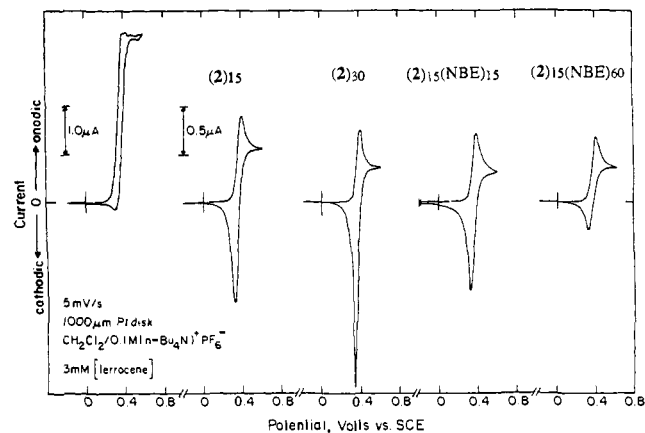


Figure 5. Comparison of the cyclic voltammograms of ferrocene, 2_{15} , 2_{30} , $2_{15}(\text{NBE})_{15}$, and $2_{15}(\text{NBE})_{60}$ in $\text{CH}_2\text{Cl}_2/0.1 \text{ M } [n\text{-Bu}_4\text{N}]\text{PF}_6$. The concentration of ferrocene centers is the same (3.0 mM) in each case.

it is reduced. Adding CH_3CN to the THF electrolyte medium changes the CV of 2_{15} to that shown in Figure 4b. In nearly pure acetonitrile the cathodic stripping peak disappears, and the wave becomes similar to what is observed in DMF, i.e., both neutral and oxidized 2_{15} are more soluble in a solvent that consists primarily of acetonitrile versus THF.

The solubility properties of a redox polymer also depend on polymer composition. Diluting the number of charged sites per chain lowers the charge-to-mass ratio and results in a polymer whose solubility is less affected by the state of charge, as in a block copolymer with a redox-active block and a nonredox-active block. In Figure 5, the cyclic voltammograms of the polymers containing 2 are shown along with that of ferrocene. The current for the polymer is diminished because of the smaller rate of diffusion. The 2_n polymers become insoluble in dichloromethane upon oxidation, resulting in a cathodic stripping wave of the adsorbed polymer. As one would expect the cathodic stripping current is much greater for 2_{30} than 2_{15} .

The hydrodynamic radius of a species determines its diffusion rate.²³ The hydrodynamic radius, sweep rate, and electrode area together determine the nature of the current-voltage curve. The information contained in the relationship among the parameters is expressed by the dimensionless number p ²⁴ (eq 4) where r is a characteristic length of the electrode, v is the sweep rate, D is the diffusion coefficient, and the other symbols have their usual meaning. The value of n needs to be considered carefully; for these multiredox center polymers $n = 1$ is appropriate. This point will be discussed later. For $p > 13$ a cyclic voltammogram limited by semiinfinite linear diffusion is obtained, and for $p < 1$ a steady-state curve with radial diffusion is obtained.²⁴ In the case of ferrocene $p = 4.5$, so intermediate behavior that approaches the steady-state response is observed, as expected. For polymers, D is much smaller. (Values of D can be estimated from a relation that has been verified by experiment between D and the molecular weight;²³ see the following section.) Estimated values give $p > 15$, so cyclic voltammograms of the polymers are expected to be characterized by linear diffusion with a diffusional tail that decays at $t^{-1/2}$. Instead, we find that the current peaks and then decays to a steady value that is smaller than expected. The smaller steady-state current is attributable to an equilibrium between oxidized polymers precipitated on the electrode and those in the diffusional boundary layer. The charge transport rate through the precipitated polymer apparently limits the current associated with oxidation of the species in solution.

$$p = (nF/RT)^{1/2}(r^2v/D)^{1/2} \quad (4)$$

(22) (a) Merz, A.; Bard, A. J. *J. Am. Chem. Soc.* **1978**, *100*, 3222. (b) Smith, T. W.; Kuder, J. E.; Wychik, D. J. *J. Polym. Sci.* **1976**, *14*, 2433. (23) Tanford, C. *The Physical Chemistry of Macromolecules*; Wiley: New York, 1961.

(24) Aoki, K.; Akimoto, K.; Tokuda, K.; Matsuda, H.; Osteryoung, J. J. *Electroanal. Chem.* **1984**, *171*, 219.

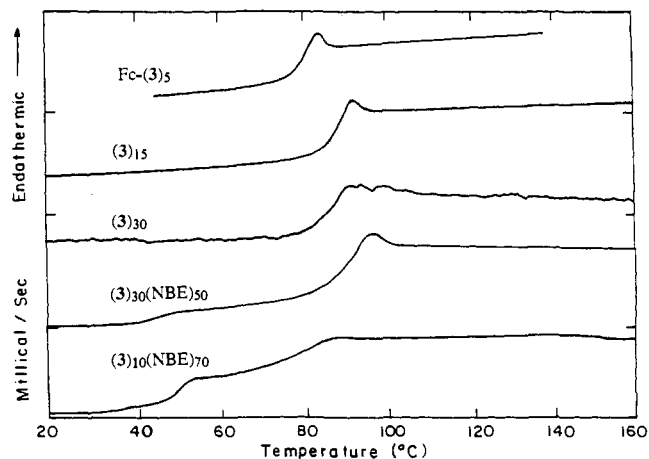


Figure 6. DSC traces of the 3_n polymers and $3_n(\text{NBE})_m$ block copolymers (scan rate was $20 \text{ }^\circ\text{C}/\text{min}$). The samples were annealed first above the transition temperature for 10 min, and all measurements were repeated several times in order to check reproducibility.

Adding a block of $(\text{NBE})_n$ to 2_m decreases the amount of material that deposits on the electrode upon oxidation. For $(\text{NBE})_{60}2_{15}$ the ratio of cathodic to anodic peak current is 1 at all sweep rates, notably the slower sweep rates ($5\text{--}500 \text{ mV s}^{-1}$). This is the ratio observed for ferrocene and is the value expected for a reversible couple without adsorption.⁹ The 2_n homopolymers are $\sim 50\%$ by weight ferrocene, whereas $(\text{NBE})_{60}2_{15}$, which does not precipitate when oxidized, is 25% by weight ferrocene. In the block copolymers, the charged sites are not evenly distributed along the chain, but are located solely within one block, and thus retain the same local structure as the homopolymers and develop the same charge density in that block when oxidized. However, the solubilizing (nonredox-active) block changes the oxidized block/solvent interaction in a manner that keeps the polymer in solution.

Homopolymers and Block Copolymers That Contain Phenothiazine. A series of homopolymers and block copolymers made from 3 and NBE are shown in Table I. The $3_n(\text{NBE})_m$ block copolymers were made by adding 3 to $1a$ first, followed by NBE. The ratio of k_p/k_i can be determined for 3 as described earlier; here $k_p/k_i = 5$ for addition of 3 to $1a$. The lower value for k_p/k_i for 3 probably results from the relatively bulky nature of 3 , i.e., the *tert*-butyl group in the initiator is actually sterically smaller than the alkylidene substituent in the growing polymer chain. PDI values could not be confirmed by FD-MS for any of these polymers. It should be noted that even the smallest, 3_{15} , is nearly twice the average molecule weight of the polymer that was successfully characterized by FD-MS, 2_{15} . Despite the fact that these polymers have relatively easily ionized redox groups, desorption of the polymer in the electric field must be slower than decomposition.

DSC analyses of polymers containing 3 are shown in Figure 6; glass transition temperatures are listed in Table I. The blocks in $3_n(\text{NBE})_m$ also microphase separate. In the block copolymers the main change is the $\sim 10 \text{ }^\circ\text{C}$ decrease in $T_g(3)$ as the length of the $(\text{NBE})_m$ block increases, as found in the case of the $(\text{NBE})_n2_m$ polymers discussed earlier. The glass transition of the 3_n blocks shows a distinct endothermic peak, which increases in magnitude the more slowly the sample is cooled through the glass transition region. Slowly annealing the sample allows it time to approach a lower energy state. Consequently more heat is required to initiate segmental motion, at which point there is an exothermic relaxation to an amorphous state.²⁵

The electrochemistry in dichloromethane of a set of 3_n polymers, $3_n(\text{NBE})_m$ block copolymers, and 3 itself was studied in solutions matched in phenothiazine concentration. The sweep rate dependence as moderate rates is shown in Figure 7. The CV of 3 is characteristic of a reversible, Nernstian redox couple with

(25) Burfield, D. R.; Lim, K.-L. *Macromolecules* **1983**, *16*, 1170.

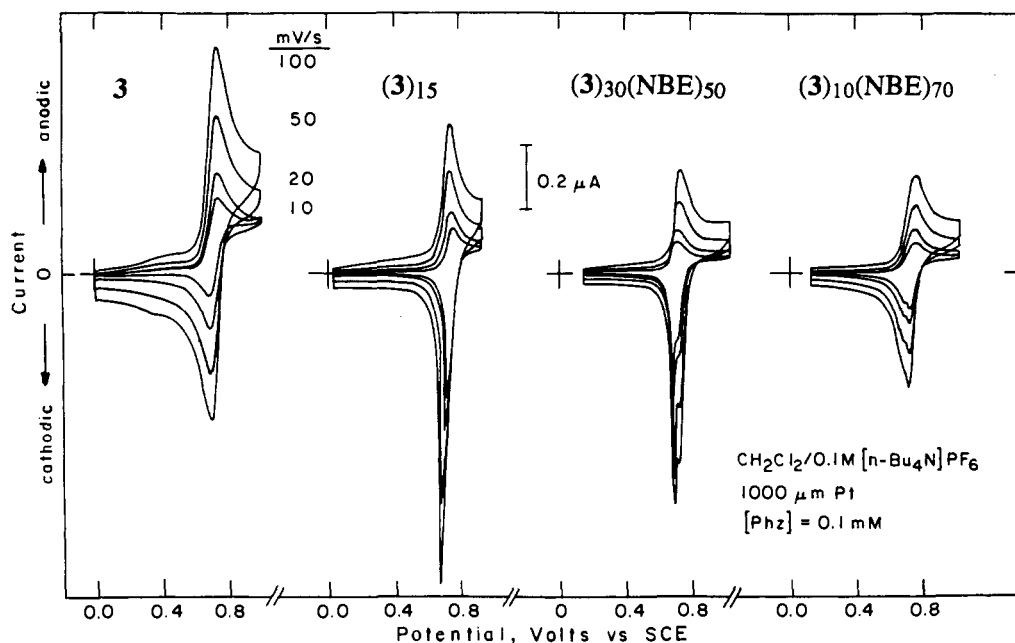


Figure 7. Scan rate dependence of the 3, 3₁₅, 3₃₀(NBE)₅₀, and 3₁₀(NBE)₇₀ in CH₂Cl₂/0.1 M [n-Bu₄N]PF₆. The concentration of phenothiazine centers is the same for all solutions (0.2 mM).

a potential $E' = 0.75$ V vs SCE. The CVs of the homopolymers made from 3, as in the case of homopolymers made from 2, are marked by a reductive stripping wave due to precipitation of the oxidized material onto the electrode, while the anodic wave maintains the characteristics for linear diffusion of the electroactive species. The peak potential is independent of sweep rate, and the peak current scales linearly with the square root of the sweep rate up to 500 mV s^{-1} . Note that although 3 contains 2 equiv of phenothiazine, there is a single redox wave and the peak separation ($\Delta E_p = 65 \text{ mV}$) is consistent with a value for $n = 1$ (59 mV), not $n = 2$ (29.5 mV). Similarly, cyclic voltammograms of the polymers have only one anodic wave, with no shoulders, and yet contain >20 phenothiazine units. It has been demonstrated for molecules with two identical redox sites,²⁶ and with ~1200 identical redox sites,²⁷ that reversible oxidation and reduction by 2 or 1200 electrons with a current-potential waveshape characteristic of a one-electron process occurs if the redox sites behave independently of one another. It is the magnitude of the wave that scales with the number of electrons and the diffusion coefficient. Because of oxidative deposition of the 3_n polymers in dichloromethane, the peak-to-peak separation cannot be used as a criterion of whether the polymers have a one-electron voltammetric waveshape.⁹

Problems with adsorption and precipitation of redox polymers can be overcome by employing normal pulse voltammetry (NPV). In NPV the applied potential is alternatively stepped between the initial potential at the foot of the wave, and a potential that increases with each pulse through the potential region of interest.²⁸ The duration of each pulse is short (57 ms) in order to minimize precipitation of oxidized material. Since the potential then returns to the initial potential any material that might have deposited is stripped away, and the initial conditions of the experiment recreated for the next pulse. The current is sampled over the last 17 ms of each potential pulse, i.e., transient currents such as double-layer charging have decayed and the majority of the signal measured is faradaic current. NPV is a form of sampled-current voltammetry, and for reversible couples provides information about the formal potential, the concentration profile, diffusion coefficients

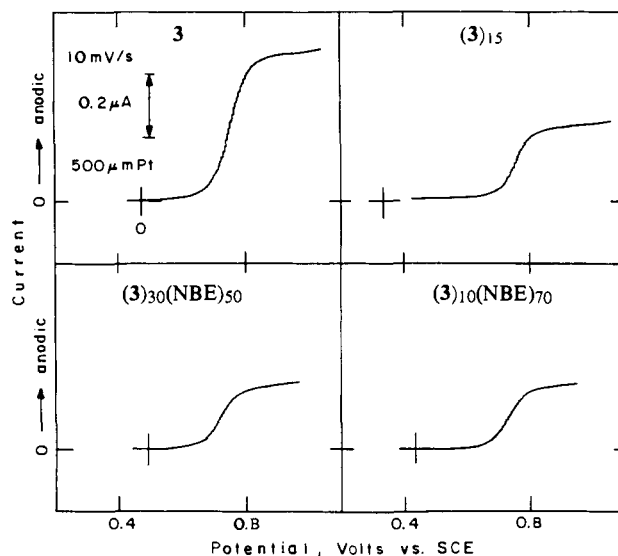


Figure 8. Normal pulse voltammograms of 3, 3₁₅, 3₃₀(NBE)₅₀, and 3₁₀(NBE)₇₀ in CH₂Cl₂/0.1 M [n-Bu₄N]PF₆. The current was sampled over the last 17 ms of a 57 ms pulse (sweep rate 10 mV s^{-1} ; drop time 1 s).

Table II. Data from Normal Pulse Voltammetric Oxidation

species	i_{lim}^a	$E_{1/2}^b$	slope ^c	D_{NPV}^d	D_{ss}^e	D_{cv}^f
3	0.44	750	-61	9.4	11.0	25.0
3 ₁₅	0.21	740	-62	2.6	3.4	12.0
3 ₃₀ (NBE) ₅₀	0.16	740	-58	1.3	2.1	4.4
3 ₁₀ (NBE) ₇₀	0.19	750	-61	1.9	2.8	4.6

^a mA. ^b mV vs SCE. ^c Slope of the plot E vs $\log [(i_{lim} - i)/i]$ in mV. ^d Calculated from eq 9 in units of $\text{cm}^2 \text{ s}^{-1} \times 10^6$. ^e Calculated from eq 8. ^f Calculated from eq 7.

and number of electrons in the process.

Normal pulse voltammograms of 3 and 3_n are shown in Figure 8. Data from the curves, the limiting current, i_{lim} , half-wave potential, $E_{1/2}$, slope of the plot E vs $\log [(i_{lim} - i)/i]$, and the diffusion coefficient, D_{NPV} , are given in Table II. In the plot of the Heyrovsky-Ilkovic equation (eq 4) the slope is $2.3RT/nF$, and n represents the number of electrons characterizing the waveshape. For $n = 1$, the slope is 59 mV. The slopes determined for all

(26) Ammar, F.; Savéant, J. M. *J. Electroanal. Chem.* **1973**, *47*, 115.

(27) Saji, T.; Paseh, N. F.; Webber, S. E.; Bard, A. J. *J. Phys. Chem.* **1978**, *82*, 1101.

(28) (a) Parry, E. P.; Osteryoung, R. A. *Anal. Chem.* **1965**, *37*, 1635. (b) Osteryoung, J. G.; Schreiner, M. M. *CRC Crit. Rev. Anal. Chem.* **1988**, *19*, S1.

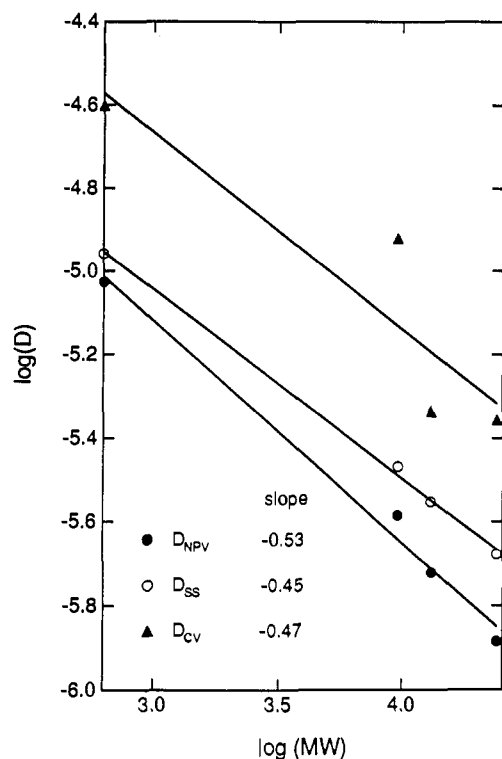


Figure 9. Log-log plot of the diffusion coefficient vs the molecular weight of a series of phenothiazine polymers and a least-squares fit of the data. The diffusion coefficients were obtained experimentally by cyclic voltammetry, steady-state cyclic voltammetry, and normal pulse voltammetry.

samples containing **3** agree quite well with this value. Thus the multiple redox sites behave independently, and the polymer passes its electrons in a wave characteristic of a one-electron process. That the polymer passes all of its electrons per redox unit will be shown in the next section using polymers with a redox-active end group.

The diffusion coefficient for a randomly coiled, spherical polymer has been shown to be related to the molecular weight²³ as shown in eq 5 for both biological and synthetic materials. This relation can be reexpressed as shown in eq 6 where $\log(C)$ arises from the proportionality constant in eq 5. A log-log plot of the

$$D \propto MW^{-0.55} \quad (5)$$

$$\log(D) = -0.55 \log(MW) + \log(C) \quad (6)$$

diffusion coefficient and molecular weight should yield a line with slope -0.55 . Values for D calculated in three ways are included in Table II. D_{CV} was determined from the cyclic voltammetric sweep rate dependence. The slope of the plot $i_{p,a}$ vs $v^{1/2}$ is given by eq 7 where A is the electrode area and C is the concentration of phenothiazine units, and $n = 1$. D_{SS} was determined from the steady-state current, i_{SS} , in voltammetric sweeps at a $25 \mu\text{m}$ Pt disk electrode from the relation²⁹ shown in eq 8 where r is the electrode radius and the other symbols are defined as usual. D_{NPV} was obtained from the limiting current (i_{lim} ; eq 9) in a normal pulse voltammogram from the simplification of the i - V relation for the limiting current, which is just the Cottrell equation³⁰ where t is the time at which the current is sampled after a potential pulse.

$$\text{slope} = (2.69 \times 10^5) n^{3/2} A C D^{1/2} \quad (7)$$

$$i_{SS} = 4nFrDC \quad (8)$$

$$i_{lim} = nFAC(D/\pi t)^{1/2} \quad (9)$$

Equation 6 is plotted in Figure 9 for the three sets of diffusion coefficients. The slopes agree well with the theoretical value of

(29) Saito, Y. *Rev. Polarogr.* **1968**, *15*, 178.

(30) Delahay, P. *New Instrumental Methods in Electrochemistry*; Interscience Publishers: New York, NY, 1954; p 57.

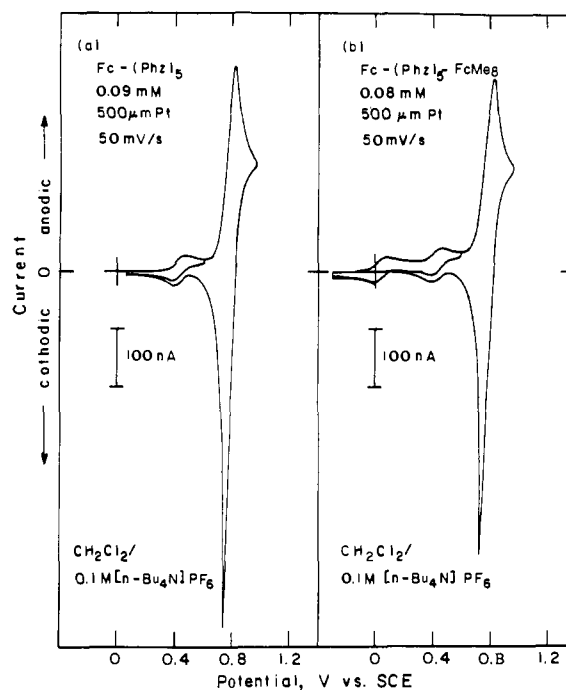


Figure 10. Cyclic voltammograms of Fc-**3**, and Fc-**3**-FcMe₃ in CH₂Cl₂/0.1 M [n-Bu₄N]AsF₆ at a 500 μm Pt disk electrode. In the first cycle the potential sweep was reversed at +0.50 V; in the second cycle it was reversed at +1.00 V.

-0.55 . The data derived from NPV are probably the most reliable. Normal pulse measurements minimize transient currents, since the electrode potential is constant during the measurement. The reproducibility of the measurement manifests itself with each successive pulse in the voltammogram. Because measurements of i_{lim} can be highly accurate, NPV is a good method for determining molecular properties such as diffusion coefficients. With the potential sweep techniques employed here there is the possibility of surface adsorption or precipitation during the sweep, changing the observed current and thus the diffusion coefficient from its true value. The good agreement with the theoretical power relationship, $MW^{-0.55}$ (eq 5), supports the assumption that the polymers assume a randomly coiled spherical conformation in solution.

Polymers Containing Redox-Active End Groups. When **1b** is employed as an initiator, polymers are formed that have a ferrocenylmethylene cap at one end of the chain. Using octamethylferrocenecarboxaldehyde to terminate the reaction yields polymers capped with an octamethylferrocenylmethylene group at the other end. In this way two distinct redox tags can be incorporated. Small polymers were made to more clearly illustrate the redox properties of these materials. The ferrocenylmethylidene complex, **1b**, was found to react more readily with norbornene than **1a** does, i.e., the value of k_p/k_i for polymerization of **3** was found to be 2 for **1b** (versus ~ 10 for **1a**; see earlier). The results of GPC and DSC analyses are given in Table I. The PDI value is very low, if one considers how short the chain is. T_g is lower (by only 7 °C) than the limiting T_g value observed for the larger **3_n** polymers. The presence of one or two ferrocenyl groups should limit the decrease in T_g , since they comprise a significant fraction of the chain.

Cyclic voltammograms of ferrocene-capped polymers of **3** are shown in Figure 10. The redox waves for the end groups have the characteristics of one-electron, reversible, solution couples; the peak potential is independent of scan rate, the peak current is linearly proportional to the square root of the scan rate, and the ratio of peak anodic current to peak cathodic current is roughly one. For Fc-**3**-FcMe₃, a comparison of the peak currents in each wave indicates the ratio of the Fc group in the initiator to the FcMe₃ group in the terminating cap is ~ 1.06 . Oxidation and reduction of each does not affect the solubility of the polymer,

Table III. Data from Normal Pulse Voltammetric Oxidation of Polymers with Redox-Active End Groups

component	Fc-3 ₅			Fc-3 ₅ -FcMe ₈		
	<i>i</i> _{lim} ^a (nA)	<i>E</i> _{1/2} ^a (mV)	slope ^b (mV)	<i>i</i> _{lim}	<i>E</i> _{1/2}	slope
FcMe ₈				9.5	5	-72
Fc	12	410	-70	10.3	380	-86
phenothiazine	122	750	-56	101.2	750	-58
diff coeff (cm ² s ⁻¹)						
<i>D</i> _{obs} ^c		6.7 × 10 ⁻⁶			5.2 × 10 ⁻⁶	
<i>D</i> _{calc} ^d		4.8 × 10 ⁻⁶			4.7 × 10 ⁻⁶	

^aVs SCE. ^bSlope of the plot E vs $\log[(i_{lim} - i)/i]$. ^cCalculated using i_{lim} from Fc wave. ^dCalculated from the relation $D_1 = D_2(MW_1/MW_2)^{0.55}$ using ferrocene for the comparison; $m_w = 186$, $D = 2.4 \times 10^{-5}$ (Kadish, K. M.; Ding, J. Q.; Malinski, T. *Anal. Chem.* **1984**, *56*, 1741).

since solubility is controlled by the larger phenothiazine block. The phenothiazine reduction wave is a spike, indicating that the oxidized material deposits on the electrode. Because of the small size of these polymers precipitation is less pronounced, but it still occurs for polymers that on average consist of five phenothiazine monomer units and have a molecular weight of ~ 3400 . Comparison of the peak currents for the phenothiazine and each of the ferrocene waves yields a ratio of $\sim 12:1$; the expected ratio is 10:1. The higher than expected ratio may not be significant, as the phenothiazine couple is not a simple reversible process because of absorption of the oxidized polymer.

The normal pulse voltammogram of Fc-3₅-FcMe₈ is shown in Figure 11. Values of the limiting currents, half-wave potentials, slopes of the plots E vs $\log[(i_{lim} - i)/i]$, and diffusion coefficients are given in Table III. The ratio of the components in these redox polymers is more clearly defined in NPV since adsorption and precipitation effects are minimized. At each potential where a pulse is applied the diffusion limited current is proportional to the number of redox sites per polymer that can be oxidized at that potential. At +0.25 V only FcMe₈ can be oxidized, at +0.55 V, FcMe₈ and Fc can be oxidized, and at +0.90 V, FcMe₈, Fc, and 3 are all oxidized. From the diffusion limited currents at these potentials the ratio of the components are determined to be 0.92:1.0:9.6. Similarly, for Fc-3₅ the ratio determined was 1.0:10.2.

The initiator **1b** provides a unique redox-active end group which is an absolute internal standard. The NPV results show that the average number of monomer units of **3** in the polymer is equal to the stoichiometry of reagents in the polymerization reaction. Moreover, NPV shows that all redox centers in the polymer exchange electrons with the electrode.

Conclusions

It has been established that ring opening metathesis polymerization with Mo alkylidene initiators of the type Mo(CHR')(NAR)(OR)₂ can be used to make polymers and block polymers that contain redox-active centers with redox potentials between -2.1 and ~ 1 V vs SCE. The primary structure of the polymer (block identity, block size, block order, and end-capping groups) are all controlled as well as is possible in a polymerization process. These redox-active polymers undergo oxidative deposition, but deposition can be moderated by adding nonredox-active blocks to the polymer. On the basis of these studies, we expect that these and related molybdenum initiators can be used to produce other well-defined multifunctional polymers, in particular those with blocks containing redox-active groups with potentials that increase or decrease uniformly in one direction along the chain.

Experimental Section

General Procedures. All chemicals used were reagent grade. Tetrahydrofuran was freshly distilled from CaH₂ or Na benzophenone ketyl under dinitrogen immediately prior to use. Pyridine was stored over 4 Å molecular sieves. Benzene was stirred with concentrated H₂SO₄, decanted, and distilled under N₂. Anhydrous diethyl ether and the solvents used in chromatography were used as received. Silica gel (230–400 mesh) was used in chromatography. *N*-Nitroso-*N*-methyl urea, stabilized with 10 wt% CH₃CO₂H, was generously provided by Professor S. Ma-

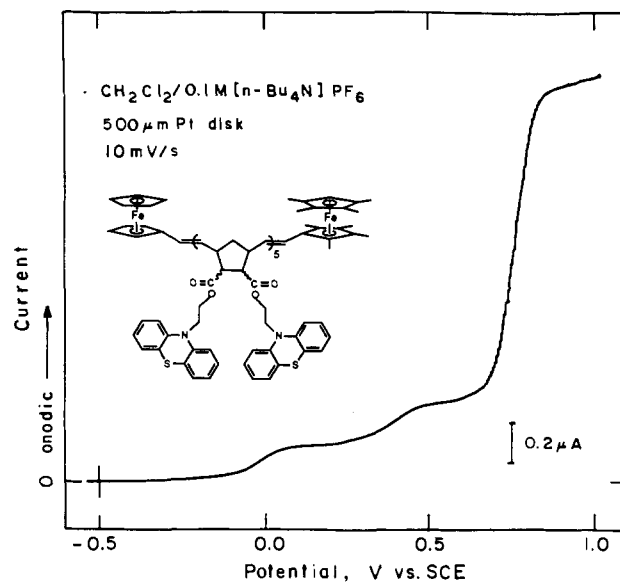


Figure 11. Normal pulse voltammogram of Fc-3₅-FcMe₈ in CH₂Cl₂/0.1 M [n-Bu₄N]PF₆. The current was sampled for the last 17 ms of a 57-ms pulse (sweep rate 10 mV s⁻¹; drop time 1 s).

samune. Ethylene oxide, dicyclopentadiene, pyrrolidine, norbornene, pivaldehyde, ferrocenecarboxaldehyde, *p*-(dimethylamino)benzaldehyde, and 10-methylphenothiazine were obtained from commercial sources. Norbornene was distilled from molten sodium, pivaldehyde was distilled from molecular sieves under dinitrogen, ferrocenecarboxaldehyde, 1-pyrenecarboxaldehyde, and 10-methylphenothiazine were recrystallized from ethanol, and *p*-(dimethylamino)benzaldehyde was passed through a 5-cm column of activated alumina. Octamethylferrocenecarboxaldehyde,³¹ *p*-(trimethylsilyl)benzaldehyde,³² Mo(CH-*t*-Bu)(NAR)(O-*t*-Bu)₂³³ (Ar = 2,6-C₆H₃-*i*-Pr₂), and β -ferrocenylacrylic acid³⁴ were prepared as described in the literature.

Polymers were synthesized under dinitrogen in a Vacuum Atmospheres drybox. The Mo catalyst (5–10 mg) was dissolved in 1 mL of THF. Monomer was dissolved in THF, and the solution was injected into the well-stirred catalyst solution. After an appropriate reaction time, either a second monomer was added, or the living polymer was terminated by adding 3–5 equiv of an aldehyde. When a series of related polymers was made the solution of the living polymer was split at the latest possible point. The polymers were purified by precipitating them twice in hexane, collecting by centrifugation, and drying in vacuo. They were characterized by gel permeation chromatography (GPC) in dichloromethane (0.1–0.3 w/v%) using Shodex KF 802.5, 803, 804, 805, 800P columns, a Knauer differential refractometer, and a Spectroflow 757 absorbance detector.

Differential scanning calorimetry (DSC) and NMR studies were done on commercial instruments. Field desorption mass spectrometry (FD-MS) was done on a JEOL HX110/HX110 instrument by Dr. Catherine Costello.

Electrochemical experiments were done using conventional three-electrode cells under Ar or N₂. In the case of Mo alkylidene compounds, electrochemical experiments were done in a drybox in cells which had been heated to 110 °C under 10⁻⁶ Torr vacuum. Cyclic voltammetric experiments were performed using a Pine Instruments RDE 4 bipotentiostat modified for low current sensitivity. Normal pulse voltammetry was done using a PAR 174 polarographic analyzer. Traces were recorded on a Kipp and Zonen BD 91 X-Y recorder. The working electrode was a Pt disk made by sealing Pt wire in soft glass. The Pt disk electrodes were polished with 3 μ and 1 μ diamond paste (Buehler) to a mirror-like finish before use. The counter electrode was a large piece of Pt gauze. The Ag quasi-reference electrode was prepared by dipping a Ag wire in concentrated HNO₃, rinsing with water and methanol, and drying. The reference potential was calibrated with ferrocene (0.380 V vs SCE, 5 mM in CH₃CN/0.1 M [n-Bu₄N]PF₆) and converted to V vs SCE. [n-Bu₄N]AsF₆ was prepared by combining equimolar aqueous solutions of [n-Bu₄N]Br and LiAsF₆. After 2 h at 4 °C, the solid was collected by

(31) Zou, C.-F.; Wrighton, M. S. *J. Am. Chem. Soc.* **1990**, *21*, 7578.

(32) Wilbur, D. S.; Svita, Z. V. *J. Label. Compds. Radiopharm.* **1984**, *21*, 415.

(33) Schrock, R. R.; Murdzek, J. S.; Bazan, G. C.; Robbins, J.; DiMare, M.; O'Regan, M. *J. Am. Chem. Soc.* **1990**, *112*, 3875.

(34) Osgerby, J. M.; Pauson, P. L. *J. Chem. Soc.* **1958**, 650.

filtration, recrystallized from aqueous acetone and water, dried at 110 °C for 48 h, and then stored in a drybox: mp 244 °C (lit.³⁵ 245 °C). $[n\text{-Bu}_4\text{N}]\text{PF}_6$ was recrystallized from 95% ethanol and $[n\text{-Bu}_4\text{N}]\text{BF}_4$ from aqueous acetone.

trans-3-Ferrocenyl-5-norbornene-2-carboxylic Acid. The procedure was adapted from the literature.³⁶ β -Ferrocenylacrylic acid (1.6 g, 6.2 mmol) and *p*-hydroquinone (25 mg, 0.2 mmol) were added under a stream of argon to 25 mL of benzene in a flask fitted with a condenser and gas inlet, glass stoppers, and a stir bar. Cyclopentadiene was added to the stirred refluxing solution in 1-mL (15 mmol) portions five times a day over seven days. The progress of the reaction was monitored by proton NMR. The reaction solution was cooled to room temperature, transferred to a separatory funnel, and washed three times with 10% NaHCO_3 . The orange aqueous solution was neutralized with 10% HCl , and the resulting precipitate was extracted with diethyl ether until the aqueous phase was colorless. The ether extracts were dried with MgSO_4 , filtered, and evaporated to give the orange product in 80% and 94% yields (two runs). Two diastereomers were present in a 2:3 ratio in each case: $^1\text{H NMR}$ (CDCl_3) δ 1.48 (m, 1), 1.66 (m, 0.6), 1.82 (m, 0.4), 2.32 (m, 0.4), 2.75–2.90 (m, 2.2), 3.10 (m, 0.4), 3.23 (m, 0.6), 3.49 (m, 0.4), 4.08 (m, 9), 5.94 (m, 0.4), 6.08 (m, 0.6), 6.26 (m, 0.4), 6.39 (m, 0.6).

trans-(exo,endo)-2-Carbomethoxy-(endo,exo)-3-ferrocenyl-5-norbornene (2). Diazomethane (generated from *N*-nitroso-*N*-methyl urea) in diethyl ether was added to a stirred ethereal solution of *trans*-3-ferrocenyl-5-norbornene-2-carboxylic acid. The progress of the reaction was followed by TLC. The ether was removed by rotary evaporation, and the resulting yellow solid was purified by flash chromatography (1:19 ethyl acetate/hexane). The diastereomers were separable by TLC (1:19 ethyl acetate/hexane) and identified on the basis of their ^1H and ^{13}C NMR spectra as *exo*-2-carbomethoxy-*endo*-3-ferrocenyl-5-norbornene and *endo*-2-carbomethoxy-*exo*-3-ferrocenyl-5-norbornene. Polymerizations were done using the mixture of diastereomers: $^1\text{H NMR}$ of *exo*, *endo* mixture (C_6D_6) δ 1.42 (m, 1), 2.01 (m, 1), 2.36 (m, 1), 2.67 (m, 1), 2.91 (ni, 1), 3.44 (s, 3), 3.62 (m, 1), 3.71 (m, 1), 3.92 (m, 2), 3.94 (m, 1), 4.06 (s, 5), 5.81 (m, 1), 6.00 (m, 1); *endo*, *exo* mixture δ 1.36 (m, 1), 1.51 (m, 1), 2.61 (m, 1), 2.80 (m, 1), 3.05 (m, 1), 3.11 (m, 1), 3.38 (s, 3), 3.96 (m, 4), 4.06 (s, 5), 6.04 (m, 1), 6.26 (m, 1); $^{13}\text{C NMR}$ (C_6D_6) *exo*, *endo* mixture δ 43.96, 47.89, 49.04, 49.68, 50.90, 51.52, 66.92, 67.64, 67.74, 68.75, 90.67, 136.22, 136.63, 176.02; *endo*, *exo* mixture δ 43.16, 46.42, 47.56, 51.02, 51.21, 51.66, 67.34, 67.83, 67.89, 69.01, 92.15, 133.77, 138.84, 174.36. Anal. Calcd for $\text{C}_{19}\text{H}_{20}\text{FeO}_2$: C, 67.88; H, 6.00; Fe, 16.61; Found: C, 68.34; H, 6.12; Fe, 16.51.

10-(2-Hydroxyethyl)phenothiazine. Phenothiazine (recrystallized from xylene, 4.95 g, 25 mmol) was dissolved in 20 mL of THF, and the solution was added to a NaH dispersion (1.0 g of a 60% oil dispersion) in 80 mL of THF. The mixture was refluxed for 2 h and cooled to 0 °C, and ethylene oxide (2.4 mL, 50 mmol) was added via cannula. After stirring the mixture for 3 h at 0 °C, it was transferred to a separatory funnel containing saturated aqueous NH_4Cl . The product was extracted with dichloromethane, and the extract was washed twice with water and dried over MgSO_4 . The mixture was filtered, and the filtrate was concentrated by rotary evaporation. Kugelrohr vacuum distillation (168–175 °C/0.15 mmHg) yielded 5.0 g (83%) of product: $^1\text{H NMR}$ (CDCl_3) δ 2.00 (m, 1), 3.89 (t, 2), 4.10 (t, 2), 6.89–6.99 (m, 4), 7.14–7.21 (m, 4).

Bis(10-(2-ethyl)phenothiazinyl)-trans-5-norbornene-2,3-dicarboxylate (3). A 250-mL, three-necked flask was assembled hot with a stopper, gas inlet, septum, and stir bar and cooled under Ar. Via cannula, 60 mL of THF and then a 20-mL THF solution of 10-(2-hydroxyethyl)phenothiazine (5.35 g, 22 mmol) and pyridine (1.83 mL, 22 mmol) were added to the flask. *trans*-5-Norbornene-2,3-dicarbonyl chloride (1.56 mL, 10 mmol) was added dropwise via syringe to the stirred solution. After 9 h, the THF was removed by rotary evaporation, and the residue was taken up in chloroform and water. The phases were separated, the organic phase was washed with water, and the aqueous phases were extracted the chloroform. The combined organic solutions were dried over MgSO_4 and concentrated to a light green, viscous gum. The crude product was chromatographed with a graded elution solvent, from 3:7 to 3:1 ethyl acetate/hexane (EA/Hex). The fractions containing the product were combined, and the solvents were removed by rotary evaporation. The resulting white solid was recrystallized from EtOH/ CHCl_3 to give 3.03 g (48%) of product: R_f (3:7 EA/Hex) 0.39; (1:1 EA/Hex) 0.56; (7:3 EA/Hex) 0.82; mp 121 °C; $^1\text{H NMR}$ (CDCl_3) δ 1.33 (m, 1), 1.44 (m, 1), 2.64 (m, 1), 3.04 (m, 1), 3.17 (m, 1), 3.32 (m, 1), 4.07 (t, 2), 4.14 (t, 2), 4.33 (t, 2), 4.41 (t, 2), 5.85 (m, 1), 6.14 (m, 1), 6.90 (m,

8), 7.12 (m, 8); $^{13}\text{C NMR}$ (CDCl_3) δ 45.8, 46.0, 47.1, 47.4, 47.6, 47.9, 61.0, 61.3, 115.3, 115.4, 122.9, 125.3, 125.4, 127.4, 127.6, 135.0, 137.6, 144.7, 173.2, 174.3. Anal. Calcd for $\text{C}_{37}\text{H}_{32}\text{N}_2\text{O}_4$: C, 70.23; H, 5.10; N, 4.43; S, 10.13; Found: C, 70.22; H, 5.12; N, 4.42; S, 10.24.

Mo(CHFc)(NAr)(O-*t*-Bu)₂ (1b; Fc = Ferrocenyl). Vinyl ferrocene (65 mg, 0.31 mmol) and **1a** (150 mg, 0.31 mmol) were placed together as solids, and the minimum amount of toluene (~1–2 mL) needed to dissolve the two was added. The solution color changed from dark orange to bright red as a light red solid precipitated out of solution. The mixture was stirred for 48 h after which the solvents were removed in vacuo. The red residue was extracted with pentane (1–2 mL), and the extracts were filtered through Celite. Recrystallization from a minimum amount of pentane at –40 °C gave the product as bright red needles in two crops (82 mg, 43%): $^1\text{H NMR}$ δ 11.90 (s, 1, H_a), 7.05 (m, 3, Ar-N-2,6- $\text{C}_6\text{H}_3(\text{CHMe}_2)_2$), 4.21 (dd, 2, $\text{C}_\alpha\text{C}_5\text{H}_4\text{Fe}$), 4.09 (s, 5, $\text{C}_5\text{H}_3\text{Fe}$), 4.00 (sept, 2, N-2,6- $\text{C}_6\text{H}_3(\text{CHMe}_2)_2$), 3.97 (dd, 2, $\text{C}_\alpha\text{C}_5\text{H}_4\text{Fe}$), 1.35 (s, 18, OCMe_3), 1.08 (d, 12, N-2,6- $\text{C}_6\text{H}_3(\text{CHMe}_2)_2$); $^{13}\text{C NMR}$ δ 2.74 (C_α , $J_{\text{CH}} = 127$), 155.5 (C_{ipso}), 146.3 (C_α), 127.2 (C_β), 123.1 (C_m), 95.1 (C_β), 77.2 (OCMe_3), 69.3 ($\text{C}_\alpha\text{C}_\beta(\text{CH}_2)_4\text{Fe}$), 69.3 ($\text{C}_5\text{H}_3\text{Fe}$), 68.2 ($(\text{C}_\alpha\text{C}_\beta(\text{CH}_2)_4\text{Fe})$), 32.0 (OCMe_3), 28.4 (CHMe_2), 27.8 (CHMe_2). Anal. Calcd for $\text{MoC}_{31}\text{H}_{45}\text{FeNO}_2$: C, 60.50; H, 7.37; N, 2.28. Found: C, 60.28; H, 7.44; N, 2.07.

Preparation of Polymers. Representative preparations of several polymers are described here. Other preparations were analogous. The extent of conversion of capping reactions with the various aldehydes was followed by monitoring the loss of the alkylidene proton resonance at ~11.6 ppm. See Table I for characterization data.

2₁₅. A solution of **2** (103 mg, 3.1×10^{-4} mol) in THF (1 mL) was added quickly to a rapidly stirred solution of **1a** (10 mg, 2.05×10^{-5} mol) in THF (1.0 mL). After 15–20 min the reaction was quenched with an excess of pivaldehyde (20 μL). After 30 min the polymer was precipitated by pouring the reaction mixture into 200 mL of hexane, isolated by centrifugation, and dried in vacuo for several hours: yield 95 mg (92%) of a light orange powder. The $^1\text{H NMR}$ spectrum shows an olefinic proton resonance for *trans* double bonds in the backbone at ~4.1 ppm and a *cis* olefinic proton resonance at ~3.7 ppm in a ratio of approximately 2:1: $^{13}\text{C NMR}$ (CDCl_3) δ 174.6, 175.0, 129–134 (olefinic region), 91.8, 89.9, 70, 68.4, 67.2, 66.7, 65.1, 55.1, 51.8, 51.4, 47.5, 45.5, 41, 39, 29.8.

(3)₁₅. A solution of **3** (128 mg, 3.05×10^{-4} mol) in THF (1 mL) was added quickly to a rapidly stirred solution of **1a** (10 mg, 2.05×10^{-5} mol) in THF (1 mL). After 15 min the reaction was quenched with an excess of pivaldehyde (20 μL) and the polymer was isolated as described above as a cream-colored powder (120 mg, 94%): $^1\text{H NMR}$ (CDCl_3) δ 7.02 (b, 8), 6.78 (b, 8), 5.19 (b, 2), 4.22 (b, 4), 3.93 (b, 4), 3.2–2.4 (b, 4), 1.66 (b, 1), 1.34 (b, 1), 0.94 and 0.91 and 0.89 (s, 0.9); $^{13}\text{C NMR}$ (CDCl_3) δ 173.2, 172.5, 144.5, 133.5, 132.3, 130.8, 129.9, 127.6, 125, 123, 115, 60.5, 52.3, 51.2, 46, 44.5, 39.0, 32.6, 29.5.

(NBE)₆₀(2)₁₅. A solution of norbornene (115.8 mg, 1.23×10^{-3} mol) in THF (1.0 mL) was added quickly to a well-stirred solution of **1a** (10 mg, 2.05×10^{-5} mol) in THF (1.0 mL). After 5 min a solution of **2** (103.4 mg, 3.08×10^{-4} mol) in THF (1 mL) was added quickly to the reaction. After 10 min *p*-trimethylsilylbenzaldehyde (20 μL , 1.1×10^{-4} mol) was added. After 10 min the reaction mixture was added slowly to 100 mL of stirred hexane, and the light yellow precipitate was collected by centrifugation, reprecipitated in hexane, and dried under vacuum to give 195 mg (90%) of the product as a yellow powder. Proton and carbon NMR spectra were a superposition of those for the homopolymers in the expected ratio. The ratio of trimethylsilyl to *tert*-butyl end groups was 1:1.

Fc-(3)₅-FcMe₉. **3** (127 mg, 2.0×10^{-4} mol) was dissolved in 900 μL of C_6D_6 and added quickly to a solution of **1b** (25 mg, 4.1×10^{-5} mol) in C_6D_6 (900 μL). After 15–20 min the resulting solution was split into $3 \times 600 \mu\text{L}$ portions, the first was immediately quenched by addition of 15 μL of pivaldehyde and served as a standard for the polymerization of **3**. Octamethylferrocenecarboxaldehyde (11 mg, 3.3×10^{-5} mol) in C_6D_6 (100 μL) was added to another portion. To the last portion a solution of 2-(triethoxysilyl)-5-norbornene (7 mg, 2.7×10^{-5} mol, 2 equiv relative to concentration of propagating alkylidene) in C_6D_6 (200 μL) was added under vigorous stirring, stirred for an additional 10 minutes and finally quenched with octamethylferrocenecarboxaldehyde (11 mg, 3.3×10^{-5} mol) in C_6D_6 (100 μL). The oligomers were purified in the usual fashion.

Acknowledgment. R.R.S. thanks the National Science Foundation (DMR 87-19217) and Nippon-Zeon for support. G.B. thanks NSERC for a postdoctoral fellowship. M.S.W. and R.R.S. also thank the Office of Naval Research, and M.S.W. thanks the Defense Advanced Research Projects Agency for partial support of this research.

(35) Compton, S.; Wang, H. H.; Williams, J. M. *Inorg. Synth.* 1986, 24, 138.

(36) Nicolas, L.; Beugelmans-Verrier, M.; Guilhem, J. *Tetrahedron* 1981, 37, 3847.