


Communication

**Room Temperature Ionic Liquids from 20 Natural Amino Acids**

Kenta Fukumoto, Masahiro Yoshizawa, and Hiroyuki Ohno

*J. Am. Chem. Soc.*, **2005**, 127 (8), 2398-2399 • DOI: 10.1021/ja043451i • Publication Date (Web): 03 February 2005

Downloaded from <http://pubs.acs.org> on March 24, 2009

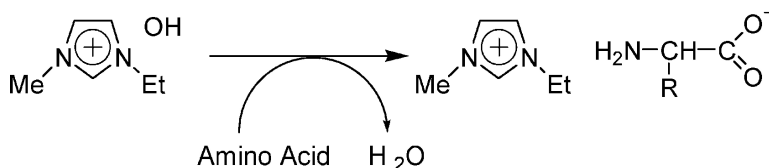

**More About This Article**

Additional resources and features associated with this article are available within the HTML version:

- Supporting Information
- Links to the 47 articles that cite this article, as of the time of this article download
- Access to high resolution figures
- Links to articles and content related to this article
- Copyright permission to reproduce figures and/or text from this article

[View the Full Text HTML](#)

## Room Temperature Ionic Liquids from 20 Natural Amino Acids

Kenta Fukumoto, Masahiro Yoshizawa, and Hiroyuki Ohno\*


Department of Biotechnology, Tokyo University of Agriculture and Technology, Koganei, Tokyo 184-8588, Japan

Received October 29, 2004; E-mail: ohnoh@cc.tuat.ac.jp

Room temperature ionic liquids (RTILs)<sup>1</sup> are attracting considerable attention as reaction solvents,<sup>2</sup> extraction solvents,<sup>3</sup> and electrolyte materials<sup>4</sup> as a result of their remarkable properties, including a negligibly small vapor pressure, high thermal stability, and high ionic conductivity. RTILs are now expected to be designer liquids with controllable physical and chemical properties or even specific functions.<sup>3a,4b,5</sup> Although there have been extensive studies of RTILs, relations between their structure and physicochemical properties have not yet been summarized.<sup>6</sup> RTILs have mostly been designed using a series of cationic derivatives<sup>4,9</sup> due to their convenient chemical modification, but there is much less information about the effect of anion structure. We have been developing novel task-specific RTILs by focusing on the amino acids because such RTILs can behave as anions with various characteristics. With this approach, we can analyze the effects of anion structure on the properties of the corresponding salts. Moreover, various functional groups on amino acids should be valuable for designing RTILs for a wide range of tasks. Here, we describe novel RTILs that are prepared by coupling the imidazolium cation with 20 different natural amino acids.

The common way of preparing RTILs is by the anion exchange of halide salts with metal salts. However, this method seems to be unsuitable for preparing pure and various RTILs due to contamination of halide salts and the limited variety of commercially available metal salts. Furthermore, because amino acids coordinate transition metal ions, pure amino acid RTILs cannot be obtained using the conventional method with metal salts.<sup>7</sup> Thus, we used a different method that involves preparing imidazolium hydroxide to neutralize a series of amino acids.<sup>8</sup>

Among several onium cations that we tested, 1-ethyl-3-methylimidazolium cation exhibited an excellent ability to form RTILs with amino acids. All of the resulting amino acid ionic liquids we obtained were transparent, nearly colorless liquids at room temperature (Figure 1). The structure of these amino acid ionic liquids was confirmed using <sup>1</sup>H NMR (JEOL  $\alpha$ -500) and elemental analysis (see Supporting Information). Although these amino acid ionic liquids were insoluble in ethers, as are typical ionic liquids, they were miscible with various organic solvents, such as methanol, acetonitrile, and chloroform. Some RTILs prepared from amino acids containing two carboxyl groups, such as [emim][Glu] and [emim][Asp], were insoluble in chloroform. This miscibility, which has never been found in native amino acids, may allow amino acids to be used in many new applications. The miscibility of RTILs with organic solvents was dependent upon the side-chain structure of the corresponding amino acid anion. In addition, we found that these amino acid ionic liquids dissolved amino acids; for example, at least 2 wt % of L-valine dissolved in [emim][Val] at 25 °C. Studies have shown that RTILs have a strong hydrogen bonding ability that is useful for dissolving biomaterials, such as DNA, cellulose,<sup>9</sup> and other carbohydrates.<sup>10</sup> Thus, in various fields, such as industrial chemistry and pharmaceutical chemistry, these amino acid ionic liquids should provide a variety of applications, such as

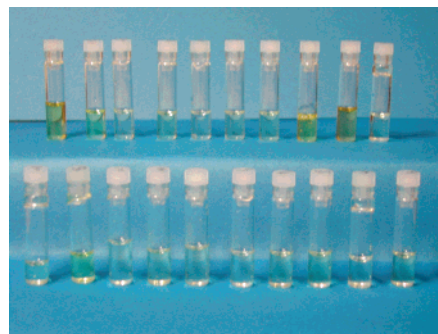

**Figure 1.** Prepared amino acid ionic liquids. Upper side (left to right): [emim][Leu], [emim][Lys], [emim][Met], [emim][Phe], [emim][Pro], [emim][Ser], [emim][Thr], [emim][Trp], [emim][Tyr], and [emim][Val]. Lower side (left to right): [emim][Ala], [emim][Arg], [emim][Asn], [emim][Asp], [emim][Cys], [emim][Gln], [emim][Glu], [emim][Gly], [emim][His], and [emim][Ile].


intermediates for peptide syntheses,<sup>11</sup> chiral solvents,<sup>12</sup> functional materials, and biodegradable ionic liquids.<sup>13</sup>

Differential scanning calorimetric measurements showed that these amino acid ionic liquids had no melting point, but a glass transition temperature ( $T_g$ ) ranging from  $-65$  to  $6$  °C (Table 1). Also, thermal gravimetric analysis revealed that, except for the decomposition of [emim][Cys] at  $173$  °C, all liquids were stable at temperatures of at least  $200$  °C. The  $T_g$  of these amino acid ionic liquids depended on the side-chain structure of the amino acid. [emim][Ala], [emim][Val], [emim][Leu], and [emim][Ile] had  $T_g$  values lower than those of other liquids. An increase of the alkyl side-chain length coincided with a gradual increase of  $T_g$ , probably due to an increase of the van der Waals force between alkyl side chains. By comparing the salt pair of [emim][Asn] and [emim][Gln] with the salt pair of [emim][Asp] and [emim][Glu], we found the alkyl chain length to have the dominant influence on  $T_g$ , regardless of the functional group. On the other hand, RTILs with a carboxyl and an amide group had a  $T_g$  higher than that of other amino acid ionic liquids. In particular, [emim][Asp] and [emim][Glu] had the highest  $T_g$  values at  $5$  and  $6$  °C, respectively. As a comparison of amino acid ionic liquids with different functional side groups, the  $T_g$  values of these three salts have the following sequence:  $-47$  °C ([emim][Lys]) <  $-12$  °C ([emim][Gln]) <  $+6$  °C ([emim][Glu]). Thus, the  $T_g$  of [emim][Glu] is  $50$  °C higher than that of [emim][Lys] although Lys has a longer hydrocarbon side chain. On the other hand, [emim][Met] showed unique characteristics. It has relatively low  $T_g$ , due to its thioether unit. Introduction of ether units into substituents of the onium cation is known to lower the  $T_g$  of the corresponding RTILs.<sup>14</sup> A similar effect can be expected in [emim][Met] to lower its  $T_g$ .

Starting from [emim][Ala], we explored the effects of substituents on the  $T_g$  of the corresponding salts. When we added a hydroxyl group ([emim][Ser]),  $T_g$  increased by  $8$  °C, whereas introduction of carboxylate ([emim][Asp]) increased  $T_g$  by  $62$  °C. Although these values are not universal, they can act as a guide to the functional

**Table 1.** Thermal Properties and Ionic Conductivity of 20 Kinds of Amino Acid Ionic Liquids

salt	$T_g$ (°C)	$\sigma_i$ (S/cm) at 25 °C	salt	$T_g$ (°C)	$\sigma_i$ (S/cm) at 25 °C
[emim][Gly]	-65	$5.7 \times 10^{-4}$	[emim][Trp]	-31	$9.1 \times 10^{-9}$
[emim][Ala]	-57	$6.4 \times 10^{-4}$	[emim][His]	-24	$1.0 \times 10^{-7}$
[emim][Met]	-57	$2.4 \times 10^{-4}$	[emim][Tyr]	-23	$4.0 \times 10^{-8}$
[emim][Val]	-52	$8.8 \times 10^{-5}$	[emim][Cys]	-19	$3.5 \times 10^{-5}$
[emim][Ile]	-52	$6.9 \times 10^{-5}$	[emim][Arg]	-18	$9.0 \times 10^{-7}$
[emim][Leu]	-51	$8.1 \times 10^{-5}$	[emim][Asn]	-16	$1.1 \times 10^{-6}$
[emim][Ser]	-49	$6.5 \times 10^{-4}$	[emim][Gln]	-12	$1.7 \times 10^{-7}$
[emim][Lys]	-47	$7.8 \times 10^{-5}$	[emim][Asp]	5	$1.7 \times 10^{-9}$
[emim][Thr]	-40	$1.0 \times 10^{-4}$	[emim][Glu]	6	$5.0 \times 10^{-7}$
[emim][Phe]	-36	$6.0 \times 10^{-5}$	[emim][Pro]	-48	$1.6 \times 10^{-4}$

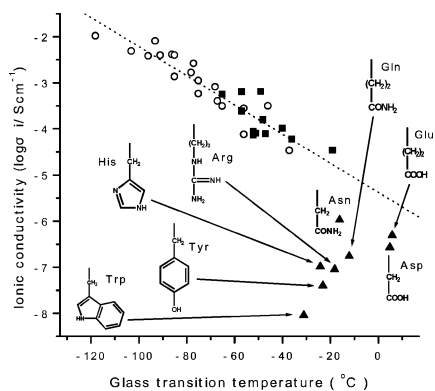**Figure 2.** Relation between ionic conductivity (25 °C) and glass transition temperature ( $T_g$ ) of amino acid ionic liquids (▲ and ■, amino acid ionic liquids; O, imidazolium-type ionic liquids prepared by the neutralization in our laboratory).

groups of uninspected RTILs. For [emim][Phe],  $T_g$  is  $-36$  °C, which is 21 °C higher than that of [emim][Ala] due to the stacking interaction of the phenyl groups. Introduction of a hydroxyl group to this Phe anion increased  $T_g$  as in the previous case (see [emim]-[Tyr] in Table 1;  $T_g = -23$  °C). Therefore, these substituents are a kind of “ $T_g$  indicator” for uninspected RTILs containing functional groups.

The ionic conductivity of these amino acid ionic liquids ranges from  $10^{-9}$  to  $10^{-4}$  S/cm at 25 °C. Figure 2 shows the relation between the ionic conductivity at 25 °C and  $T_g$  for these liquids. In this figure, the open circles (O) are data for imidazolium-type ionic liquids prepared in our previous studies.<sup>6</sup> The ionic conductivity of previously synthesized RTILs is closely related to their  $T_g$ . This strong correlation indicates that the ionic conductivity of a given number of carrier ions is governed mainly by their mobility. In this study, the major amino acid ionic liquids followed a linear relationship between  $T_g$  and ionic conductivity (Figure 2, ■). However, the correlation is not so strong for other amino acid ionic liquids (Figure 2, ▲); moreover, the ionic conductivities are less than those for major amino acids of the same  $T_g$ . In particular, the relatively low ionic conductivities of amino acid ionic liquids, such as [emim][His] and [emim][Glu], may be due to hydrogen bonding or some other ion interaction that is expected through their side chains.

In summary, we synthesized new ionic liquids from a series of amino acids. The amino acid ionic liquids were miscible with organic solvents and could dissolve native amino acids. From the trends found in this study, one can estimate the glass transition temperature, the ionic conductivity, and the miscibility with organic solvents based on the structure of the side chains on the component ions. These findings should be useful for designing suitable ionic liquids for specific applications.

**Acknowledgment.** This research has been supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Culture, Sports, Science and Technology, Japan (No. 14205136), and the 21st Century COE program of “Future Nano-Materials” in Tokyo University of Agriculture & Technology.

**Supporting Information Available:** The details of the characterization of compounds. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## References

- (1) Wilkes, J. S.; Zaworotko, M. J. *J. Chem. Soc., Chem. Commun.* **1992**, 965–967.
- (2) (a) Welton, T. *Chem. Rev.* **1999**, 99, 2071–2083. (b) Wasserscheid, P.; Welton, T. *Ionic Liquids in Synthesis*; Wiley-VCH: Weinheim, Germany, 2003.
- (3) (a) Visser, A. E.; Swatoski, R. P.; Reichert, W. M.; Mayton, R.; Sheff, S.; Wierzbicki, A.; Davis, J. H., Jr.; Rogers, R. D. *Chem. Commun.* **2001**, 135–136. (b) Huddleston, J. G.; Rogers, R. D. *Chem. Commun.* **1998**, 16, 1765–1766.
- (4) (a) Bonhôte, P.; Dias, A.-P.; Papageorgiou, N.; Kalyanasundaram, K.; Grätzel, M. *Inorg. Chem.* **1996**, 35, 1168–1178. (b) Yoshizawa, M.; Narita, A.; Ohno, H. *Aust. J. Chem.* **2004**, 57, 139–144.
- (5) (a) Bates, E. D.; Mayton, R. D.; Ntai, I.; Davis, J. H., Jr. *J. Am. Chem. Soc.* **2002**, 124, 926–927. (b) Yoshizawa, M.; Ogihara, W.; Ohno, H. *Electrochem. Solid-State Lett.* **2001**, 4, E25–E27. (c) Yoshizawa, M.; Hirao, M.; Akita, K. I.; Ohno, H. *J. Mater. Chem.* **2001**, 11, 1057–1062.
- (6) (a) Ohno, H.; Yoshizawa, M. *Solid State Ionics* **2002**, 154–155, 303–309. (b) Hirao, M.; Sugimoto, H.; Ohno, H. *J. Electrochem. Soc.* **2000**, 147, 4168–4172.
- (7) Vidugiris, G.-J. A.; Razumas, V. J.; Drungiliene, A. A.; Kulys, J. *J. Bioelectrochem. Bioenerg.* **1988**, 19, 513–520.
- (8) General procedure for amino acid ionic liquids. 1-Ethyl-3-methylimidazolium hydroxide ([emim][OH]) aqueous solution was prepared from 1-ethyl-3-methylimidazolium bromide using anion exchange resin (AMBERLITE IRA400CL (Aldrich) or AMBERLITE IRA400OH (SULPELCO)). An [emim][OH] aqueous solution was added dropwise to a slightly excess equimolar amino acid aqueous solution. The mixture was stirred under cooling for 12 h. Then water was evaporated at 40–50 °C. To this reaction mixture were added 90 mL of acetonitrile and 10 mL of methanol, and it was stirred vigorously. The mixture was then filtered to remove excess amino acid. Filtrate was evaporated to remove solvents. The product was dried in vacuo for 2 days at 80 °C. Structure of the resulting amino acid ionic liquid was confirmed by <sup>1</sup>H NMR spectroscopy (JEOL  $\alpha$ -500) and elemental analysis. The water content of most amino acid ionic liquids, determined with a Karl Fischer moisture titrator (MKS-210; Kyoto Electronics Co.), was less than 0.2 wt %. Those of salts composed of Glu and Asp were around 0.4 wt %.
- (9) Swatoski, R. P.; Spear, S. K.; Holbrey, J. D.; Rogers, R. D. *J. Am. Chem. Soc.* **2002**, 124, 4974–4975.
- (10) Forsyth, S. A.; MacFarlane, D. R.; Thomson, R. J.; von Itzstein, M. *Chem. Commun.* **2002**, 7, 714–715.
- (11) Vallette, H.; Ferron, L.; Coquerel, G.; Gaumont, A.-C.; Plaquevent, J.-C. *Tetrahedron Lett.* **2004**, 45, 1617–1619.
- (12) (a) Wasserscheid, P.; Bosmann, A.; Bolm, C. *Chem. Commun.* **2002**, 3, 2000–2001. (b) Bao, W.; Wang, Z.; Li, Y. *J. Org. Chem.* **2003**, 68, 591–593.
- (13) Gathergood, N.; Garcia, M. T.; Scammells, P. J. *Green Chem.* **2004**, 6, 166–175.
- (14) Branco, L. C.; Rosa, J. N.; Ramos, J. J. M.; Afonso, C. A. M. *Chem.—Eur. J.* **2002**, 8, 3671–3677.

JA043451I