


Communication

## New Polyethylene Macroinitiators and Their Subsequent Grafting by Atom Transfer Radical Polymerization

Yanika Schneider, Jason D. Azoulay, Robert C. Coffin, and Guillermo C. Bazan

*J. Am. Chem. Soc.*, **2008**, 130 (32), 10464-10465 • DOI: 10.1021/ja803006d • Publication Date (Web): 19 July 2008

Downloaded from <http://pubs.acs.org> on February 8, 2009

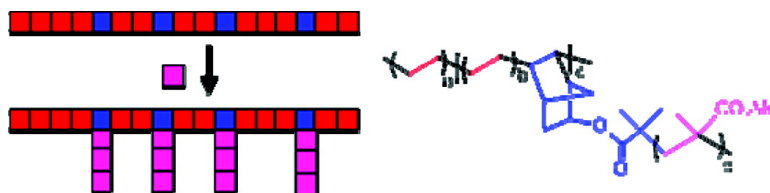

### More About This Article

Additional resources and features associated with this article are available within the HTML version:

- Supporting Information
- Access to high resolution figures
- Links to articles and content related to this article
- Copyright permission to reproduce figures and/or text from this article

[View the Full Text HTML](#)

## New Polyethylene Macroinitiators and Their Subsequent Grafting by Atom Transfer Radical Polymerization

Yanika Schneider, Jason D. Azoulay, Robert C. Coffin, and Guillermo C. Bazan\*

Department of Chemistry and Biochemistry, Department of Materials, Center for Polymers and Organic Solids, University of California, Santa Barbara, California 93106

Received April 23, 2008; E-mail: bazan@chem.ucsb.edu


There has been a long-standing interest in the synthesis of block or graft copolymers containing ethylene and a suitable functional comonomer that can serve as blend compatibilizers between polyolefins and polar commodity plastics.<sup>1</sup> The ultimate goal is a polymer alloy that combines desirable properties of the individual materials.<sup>2</sup> Early transition metal catalysts are highly oxophilic, making it difficult to copolymerize polar monomers without loss in activity.<sup>3</sup> Late transition metal complexes are more tolerant of functional groups but typically produce branched materials that therefore have low moduli.<sup>4,5</sup> At present, commercial production of functionalized polyolefins is dominated by high-pressure, high-temperature radical processes that offer little control over the polymer architecture.<sup>6</sup>

Efforts in response to these challenges have appeared in the literature.<sup>7</sup> In one example, a metallocene catalyst was used to copolymerize ethylene and 10-undecen-1-ol, protected with triethylaluminum, producing a material with an  $M_n$  (number average molecular weight) of 36K and a PDI (polydispersity index) of 3.<sup>8</sup> The alcohol groups were converted into ATRP (atom transfer radical polymerization) initiators, and in a second step, acrylates and methacrylates were polymerized from the polyethylene (PE) backbone. A more recent report demonstrated that a Pd diimine catalyst can incorporate an ATRP initiator directly by chain walking ethylene polymerization, yielding functionalized PE.<sup>9</sup> However, because the resulting material is hyperbranched, it is anticipated to be a poor compatibilizer for linear PE.<sup>10</sup>


Previously, we reported the quasi-living copolymerization of ethylene and functionalized norbornenes using nickel  $\alpha$ -iminocarboxamidato complexes.<sup>11</sup> In this communication, we demonstrate how this catalytic system can be utilized to directly copolymerize ethylene and an ATRP initiator to produce a PE macroinitiator, with excellent control over polymer architecture, via the sequence of steps in Scheme 1. As shown in the first step, [*N*-(2,6-diisopropylphenyl)-2-(2,6-diisopropylphenylimino)isobutanamidato]-Ni( $\eta^1$ -CH<sub>2</sub>Ph)(PMe<sub>3</sub>) (**1**) and Ni(COD)<sub>2</sub> (bis(1,5-cyclooctadiene)-nickel) (**2**), as the coactivator, are used to copolymerize ethylene with 5-norbornen-2-yl-2'-bromo-2'-methyl propanoate (**3**). The isobutyl variant was chosen because increased bulk adjacent to the imine leads to faster initiation and weaker interactions with polar groups.<sup>12</sup> Compound **3**, which provides the functionality for initiating the ATRP reactions in the second step of Scheme 1, is easily prepared from 5-norbornen-2-ol and bromoisobutryl bromide. Initial efforts showed that, while **1** is inert, **2** immediately yields a metallic precipitate in the presence of **3**. A modified procedure was thus developed, where the 1/2 mixture is exposed to ethylene for a time  $t_1$ , after which **3** is added via a prepressurized addition funnel, and the polymerization is allowed to proceed for another period of time,  $t_2$ .

A series of polymerization reactions were performed to test the strategy in Scheme 1, at an ethylene pressure ( $P_{C_2H_4}$ ) of 100 psi and 20 °C, using a solution of **1** and **2** (0.24 and 0.6 mM, respectively) in toluene, followed by the addition of **3** (0.06 M) at  $t_1$ . The  $M_n$  increases linearly with  $t_2$  (from 2 to 22 min) when  $t_1$  is kept constant at 3 min. This dependence, illustrated by the plot in Figure 1, confirms that the polymerization takes place in a controlled manner. Table 1 provides additional information about reaction

**Scheme 1.** Synthesis of PE Macroinitiator and Its Grafting by ATRP<sup>a</sup>

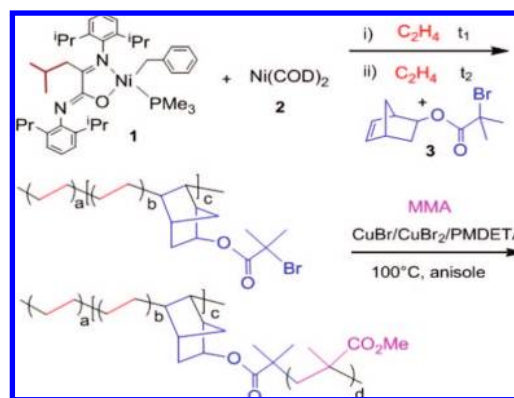

<sup>a</sup> PMDETA is *N,N,N',N',N''*-pentamethyldiethylenetriamine.

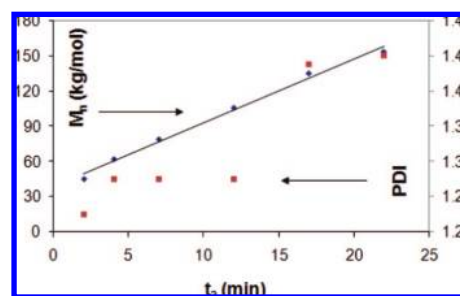

**Figure 1.** Plot of PE macroinitiator  $M_n$  and PDI vs time ( $t_1 = 3$  min).

conditions, along with compositional analysis of the products. As shown in entry 1, when  $t_2$  is 2 min, a polymer with an  $M_n$  of 45K and a PDI of 1.3 is produced. This material has a melting point ( $T_m$ ) of 126 °C, a degree of crystallinity ( $X_c$ ) of 43%, and ~14 units of **3** per chain (0.9 mol %), as determined by <sup>1</sup>H NMR spectroscopy (Supporting Information). Entries 1–3 reveal that there is little variation in the mol % of **3** as a function of  $t_2$ . Increasing the reaction temperature from 20 to 29 °C nearly doubles  $M_n$  and increases the overall activity 3-fold (entry 1 vs 4). Decreasing the temperature to 16 °C yields a polymer with an  $M_n$  of 30K and a substantial decrease in activity. Comparison of entries 1 and 6–8 demonstrates the influence of  $P_{C_2H_4}$  on the incorporation of **3**. At  $P_{C_2H_4} = 400$  psi, the iminer content is below the detection limit of <sup>1</sup>H NMR spectroscopy, and the  $T_m$  is the highest (132 °C). Changing  $P_{C_2H_4}$  from 100 to 200 psi yields a decrease in incorporation from 0.9% to 0.4%. At 50 psi (entry 8), the activity decreases by 50% (relative to entry 1) and the **3** content increases to 2.2%. The structure of the final product can also be tailored by changing the concentration of **3** added at  $t_1$ , as illustrated by entries 9 and 10. When [**3**] is doubled, the average number of initiators per chain increases from 14 to 27; similarly, when [**3**] is halved, there are

**Table 1.** Polymerization Conditions and Resulting Macroinitiators


entry	$t_1$	$t_2$	[3]	$T^a$	$P^b$	$A^c$	mol % $\mathbf{3}^d$	$M_n^e$	$T_m^f$
1	3	2	0.06	20	100	360	0.9	45	126
2	3	4	0.06	20	100	370	1.1	62	125
3	3	22	0.06	20	100	330	0.9	154	128
4	3	2	0.06	29	100	960	0.9	80	125
5	3	2	0.06	16	100	200	1.2	30	126
6	3	2	0.06	20	400	390	<0.01	48	132
7	3	2	0.06	20	200	350	0.4	46	127
8	3	2	0.06	20	50	180	2.2	45	123
9	3	2	0.12	20	100	300	1.7	43	125
10	3	2	0.03	20	100	360	0.4	46	127
11	1	4	0.06	20	100	220	2.8	42	115

<sup>a</sup> Temperature (°C). <sup>b</sup> Pressure (psi). <sup>c</sup> Activity (kg/mol·h). <sup>d</sup> % inimer determined by <sup>1</sup>H NMR spectroscopy. <sup>e</sup>  $M_n$  (kg/mol) determined by GPC. <sup>f</sup> Melting point (°C) determined by DSC. All PDIs are between 1.2 and 1.4.

**Table 2.** Optimization of Grafting Conditions

entry	equiv MMA	volume (mL)	time (h)	$M_n$	PDI	mol % PMMA <sup>a</sup>	$T_m^b$	$X_c^b$
1	200	5	1	58	1.3	26	126	16
2	200	5	3	62	1.3	40	126	12
3	400	5	3	75	1.7	60	126	7
4	100	5	3	54	1.2	2	127	25
5	200	6	3	58	1.3	25	127	14
6	200	3	3	-	-	-	-	-

<sup>a</sup> Determined by <sup>1</sup>H NMR spectroscopy; <sup>b</sup> Melting point (°C) and degree of crystallinity ( $X_c$ ) determined by DSC. ATRP performed at 100 °C on 50 mg of macroinitiator: [3]/[MMA]/[Cu<sup>I</sup>Br]/[Cu<sup>II</sup>Br<sub>2</sub>]/[PMDETA] = 1:200:1:0.05:2.

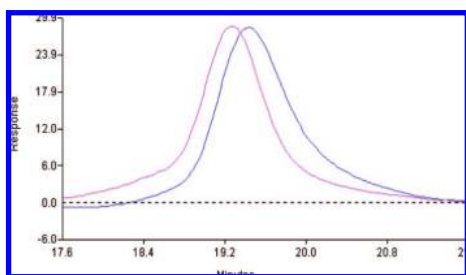**Figure 2.** GPC traces of PE macroinitiator (entry 1, Table 1) and PE-graft-PMMA (entry 1, Table 2) in *o*-dichlorobenzene at 135 °C.

only 6 initiators per chain. Finally, when  $t_1$  is reduced to 1 min, and the total polymerization time is the same as that in entry 1 (5 min), the inimer content increases from 0.9% to 2.8%. This material has the lowest  $T_m$  (115 °C) and  $X_c$  (17%). Note that despite variations in pressure, temperature, and [3], one obtains products with low PDIs (between 1.2 and 1.4); this is a remarkable feature considering that **2** is unstable toward **3**.

A series of ATRP reactions were performed as shown in the second step of Scheme 1 by using literature methodologies.<sup>8,13</sup> Typically, 50 mg of macroinitiator (from entry 1, Table 1) were treated with methyl methacrylate (MMA) and a solution of a copper salt in anisole at 100 °C, such that the ratio of reactants was [3]/[MMA]/[Cu<sup>I</sup>Br]/[Cu<sup>II</sup>Br<sub>2</sub>]/[PMDETA] = 1:200:1:0.05:2. The results are summarized in Table 2. After an hour of reaction,  $M_n$  increases from 45K to 58K, as illustrated in Figure 2. While the  $T_m$  of this material is 126 °C, similar to the starting macroinitiator, the  $X_c$  decreases from 43% to 16%. Comparison of entries 1 and 2 reveals that products have low PDIs and increased PMMA content at longer reaction times, indicating a good degree of control over the grafting process. There is also a decrease in  $X_c$ , from 16% to 12%, while the  $T_m$  remains constant. Although the change in  $M_n$

between 1 and 3 h is small, this has been previously observed in other PE-graft-PMMA systems<sup>8</sup> and can be attributed to a propensity to form micellar structures in solution, which alters the hydrodynamic volume and yields inaccurate molecular weight measurements. PMMA side chains were hydrolyzed using sodium methoxide in methanol.<sup>8</sup> GPC analysis confirms that the  $M_n$  of the detached chains increases from 8600 (entry 1) to 13,800 (entry 2), while the PDIs remain at  $\sim$ 1.2.

When [MMA] is doubled, the PMMA content increases from 40% to 60% and the  $M_n$  rises to 70K (entry 3), although at the cost of an increase in PDI. Similarly, when [MMA] is halved, the reaction yields only 2 mol % of PMMA after 3 h (entry 4). Comparison of entry 2 to entries 5 and 6 reveals the importance of maintaining a proper volume such that the macroinitiator remains in solution and unwanted side reactions do not occur. When the total volume is increased from 5 to 6 mL, the PMMA content shifts from 40% to 25%. However, when the volume is reduced to 3 mL, an insoluble gel is obtained. Successful grafting experiments were also performed using HMTETA in place of PMDETA (Supporting Information).

In conclusion, the method in Scheme 1 provides access to PE-graft-PMMA with excellent control over the structural properties of the macroinitiator and the resulting graft copolymers. A key element is the initiation in the absence of **3**, which decomposes Ni(COD)<sub>2</sub>. Once the active species is generated, the copolymerization of ethylene and **3** proceeds in a controlled fashion. Furthermore, it is noteworthy that the final graft material is semicrystalline, which argues favorably for its use as a blend compatibilizer for linear PE.

**Acknowledgment.** The authors are grateful to Mitsubishi Chemical Center for Advanced Materials (MC-CAM) and to the DOE (DE-FG02-98ER14910) for financial support.

**Supporting Information Available:** General experimental and characterization procedures. This is available free of charge via the Internet at <http://pubs.acs.org>.

## References

- (1) (a) Schellekens, M.; Klumperman, B. *J. Macromol. Sci., Polym. Rev.* **2000**, *40* (2), 167–192. (b) Kobori, Y.; Akiba, I.; Akiyama, S. *Polymer* **2000**, *41*, 5971–5975. (c) Hadjichristidis, N.; Pispas, S. *Block Copolymers*; Wiley-Interscience: Hoboken, NJ, 2003.
- (2) (a) Yanjarappa, M. J.; Sivaram, S. *Prog. Polym. Sci.* **2002**, *27*, 1347–1398. (b) Cheng, J. Y.; Mayes, A. M.; Ross, C. A. *Nat. Mater.* **2004**, *3*, 823–828. (c) Dong, J.-Y.; Hu, Y. *Coord. Chem. Rev.* **2006**, *250*, 47–65.
- (3) Gibson, V. C.; Spitzmesser, S. K. *Chem. Rev.* **2003**, *103*, 283–315.
- (4) (a) Ittel, S. D.; Johnson, L. K.; Brookhart, M. *Chem. Rev.* **2000**, *100*, 1169–1203. (b) Michalak, A.; Ziegler, T. *Top. Organomet. Chem.* **2005**, *12*, 145–186.
- (5) There are exceptions in the literature, including: (a) Yonkin, T.; Connor, E.; Henderson, J.; Friedrich, S.; Grubbs, R.; Bansleben, D. *Science* **2000**, *28*, 460. (b) Nelana, S. M.; Darkwa, J.; Guzei, I. A.; Mapolie, S. F. *J. Organomet. Chem.* **2004**, *689*, 1835–1842.
- (6) Chung, T. C. *Prog. Polym. Sci.* **2002**, *27*, 39–85.
- (7) (a) Liu, S.; Sen, A. *Macromolecules* **2001**, *34*, 1529–1532. (b) Cao, C.; Zou, J.; Dong, J.-Y.; Hu, Y.; Chung, T. C. *J. Polym. Sci., Part A: Polym. Chem.* **2005**, *43*, 429–437.
- (8) Inoue, Y.; Matsugi, T.; Kashiwa, N.; Matyjaszewski, K. *Macromolecules* **2004**, *37*, 3651–3658.
- (9) Zhang, K.; Wang, J.; Subramanian, R.; Ye, Z.; Lu, J.; Yu, Q. *Macromol. Rapid Commun.* **2007**, *28*, 2185–2191.
- (10) LDPE is only miscible with HDPE if it has less than 30 branchers per carbon. Reference 9 reports approximately 90 branchers. Fan, Z.; Williams, M.; Choi, P. *Polymer* **2002**, *43*, 1492–1502.
- (11) (a) Diamanti, S. J.; Ghosh, P.; Shimizu, F.; Bazan, G. C. *Macromolecules* **2003**, *36*, 9731–9735. (b) Diamanti, S.; Khanna, V.; Hotta, A.; Yamakawa, D.; Shimizu, F.; Kramer, E.; Fredrickson, G.; Bazan, G. *J. Am. Chem. Soc.* **2004**, *126*, 10528.
- (12) Azoulay, J.; Iligaki, K.; Wu, G.; Bazan, G. *Organometallics* **2008**, *27*, 2273–2280.
- (13) (a) Kaneyoshi, H.; Inoue, Y.; Matyjaszewski, K. *Macromolecules* **2005**, *38*, 5425–5435. (b) Yamamoto, K.; Miwa, Y.; Tanaka, H.; Sakaguchi, M.; Shimada, S. *J. Polym. Sci., Part A: Polym. Chem.* **2002**, *40*, 3350–3359.

JA803006D