

Chiral manganese and iron complexes of binaphthyl Schiff bases: syntheses, crystal structures and asymmetric epoxidation of alkenes

Ming-Chuan Cheng,^a Michael Chi-Wang Chan,^a Shie-Ming Peng,^b Kung-Kai Cheung^a and Chi-Ming Che^{*,a}

^a Department of Chemistry, The University of Hong Kong, Pokfulam Road, Hong Kong

^b Department of Chemistry, National Taiwan University, Taipei, Taiwan

The chiral binaphthyl Schiff-base manganese complexes [MnL(X)] [$H_2L = 2,2'$ -bis(3- R^1 -5- R^2 -2-hydroxybenzylideneimino)-1,1'-binaphthyl; $R^1 = R^2 = Cl$, $X = O_2CMe$ **1**; $R^1 = Et$, $R^2 = NO_2$, $X = O_2CMe$ **2**; $R^1 = R^2 = Cl$, $X = acac$ (acetylacetonate) **3**] and an iron analogue [FeL(acac)] **4** ($R^1 = R^2 = Cl$) have been prepared. The crystal structures of the racemic forms of **3**·CH₂Cl₂ and **4**·2H₂O exhibit non-planar *cis*- β configurations with dihedral angles of 85.5 and 72.1° respectively between the two naphthalene rings. Complexes (*R*)-**1** to **3** are active catalysts for the asymmetric epoxidation of alkenes by PhIO. The oxidation of *cis*- β -methylstyrene by (*R*)-**2** in toluene at -20 °C gave an enantiomeric excess of 76%.


The search for chiral complexes which can catalyse asymmetric oxidation has continued to attract considerable interest.¹ Recent results in asymmetric epoxidation of unfunctionalised alkenes have been achieved by Jacobsen and Katsuki² using chiral Schiff-base manganese complexes based on optically active 1,2-diamines. However, the binaphthyl moiety, which has been effectively deployed in other asymmetric catalysis reactions,³ has rarely been incorporated into the Schiff base for mediating asymmetric oxidation. We recently reported that the *in situ* Mn(O₂CMe)₃ + (*S*)-H₂L systems [$H_2L = 2,2'$ -bis(3- R^1 -5- R^2 -2-hydroxybenzylideneimino)-1,1'-binaphthyl, $R^1 = Cl$, H or alkyl; $R^2 = Cl$, NO₂ or Me] are effective catalysts for asymmetric epoxidation of alkenes by PhIO.⁴ Nevertheless, there are few examples of complexes containing the binaphthyl Schiff-base ligand⁵ and to our knowledge the only published crystal structure is the copper(II) complex where $R^1 = R^2 = Cl$.⁴ We now report the successful synthesis of monomeric chiral manganese(III) and iron(III) binaphthyl Schiff-base complexes, and asymmetric catalysis results which show improved enantioselectivity. Crystal structures of complexes in racemic forms have been determined.

Experimental

Full instrumentation details and preparation of the chiral and racemic forms of the Schiff base have been given.⁴ The compounds Mn^{III}(O₂CMe)₃·2H₂O (Aldrich) and [Fe^{III}(acac)₃] (acac = acetylacetonate) (Strem) were dried *in vacuo* before use; [Mn^{III}(acac)₃] was prepared according to the literature method.⁶ Iodosylbenzene was prepared by hydrolysis of iodobenzene diacetate (Aldrich) in NaOH solution. Solvents for catalytic epoxidation were purified according to standard procedures.⁷ All alkene substrates used for catalytic epoxidation were from Aldrich and Fluka and purified either by vacuum distillation or by passing through activated alumina. *cis*- β -Methylstyrene was prepared by hydrogenation of 1-phenylprop-1-yne (Aldrich) using Lindler catalyst.⁸ Racemic styrene oxide was obtained from Fluka and distilled before use; (*R*)-(-) styrene oxide from Aldrich was used without further purification. All other epoxides required for determination of product yield and enantiomeric excess (e.e.) were independently prepared from the corresponding alkene and *m*-chloroperoxybenzoic acid in dichloromethane.⁹

Syntheses

[Mn^{III}L¹(O₂CMe)] **1**. A mixture of H₂L¹ (0.5 g, 0.8 mmol)

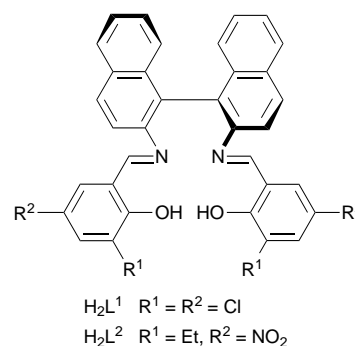

and Mn(O₂CMe)₃·2H₂O (0.21 g, 0.8 mmol) in acetonitrile (30 cm³) was heated at 60 °C for 30 min. The solvent was removed *in vacuo*. The residue was dissolved in dichloromethane (10 cm³) and then filtered. Addition of *n*-hexane yielded a green solid. Chiral complexes were prepared by the same method using optically active ligands. Yield 0.44 g, 74% (Found: C, 58.1; H, 3.1; N, 3.8. C₃₆H₂₁Cl₄MnN₂O₄ requires C, 58.25; H, 2.85; N, 3.8%; $\lambda_{max}(CH_3CN)/nm$ 222 (ϵ 87820), 274 (51740), 317 (19590) and 391 (14180 dm³ mol⁻¹ cm⁻¹); $\tilde{\nu}(KBr)/cm^{-1}$ 1602 (C=N) and 1421 (O₂CMe); *m/z* 683 (*M* - O₂CMe).

[Mn^{III}L²(O₂CMe)] **2**. The procedure was the same as for complex **1** using Mn(O₂CMe)₃·2H₂O (0.21 g, 0.8 mmol) and H₂L² (0.5 g, 0.8 mmol). Chiral complexes were prepared using optically active ligands. Yield 0.49 g, 81% (Found: C, 66.7; H, 4.5; N, 7.7. C₄₀H₃₁MnN₄O₃ requires C, 66.85; H, 4.45; N, 7.8%; $\lambda_{max}(CH_3CN)/nm$ 242 (ϵ 80560), 274 (54620), 317 (19590), 386 (14190 dm³ mol⁻¹ cm⁻¹); $\tilde{\nu}(KBr)/cm^{-1}$ 1593 (C=N), 1420 (O₂CMe) and 1315 (NO₂).

[Mn^{III}L¹(acac)] **3**. A mixture of H₂L¹ (0.3 g, 0.5 mmol) and [Mn(acac)₃] (0.18 g, 0.5 mmol) in acetonitrile (30 cm³) was refluxed for 4 h. The solution was evaporated to dryness and then dissolved in dichloromethane. Upon addition of *n*-hexane a green solid was obtained. Chiral complexes were prepared by the same method using optically active ligands. Yield 0.33 g, 85% (Found: C, 59.6; H, 3.5; N, 3.7. C₃₉H₂₅Cl₄MnN₂O₄ requires C, 59.9; H, 3.2; N, 3.6%; $\lambda_{max}(CH_2Cl_2)/nm$ 220 (ϵ 104870), 273 (74720), 320 (26490) and 389 (15860 dm³ mol⁻¹ cm⁻¹); $\tilde{\nu}(KBr)/cm^{-1}$ 1602 (C=N) and 1418 (acac); *m/z* 683 (*M* - acac).

[Fe^{III}L¹(acac)] **4**. A mixture of H₂L¹ (0.5 g, 0.8 mmol) and [Fe(acac)₃] (0.28 g, 0.8 mmol) in acetonitrile (30 cm³) was

refluxed for 6 h. The resultant solution was filtered and concentrated, and dark red crystals were obtained upon standing for 1 d. Yield 0.52 g, 83% (Found: C, 59.7; H, 3.4; N, 3.6. $C_{39}H_{25}Cl_4FeN_2O_4$ requires C, 59.8; H, 3.2; N, 3.6%); $\lambda_{\max}(\text{CH}_2\text{Cl}_2)/\text{nm}$ 269 (ϵ 75760), 360 (14960) and 445 (9020 $\text{dm}^3 \text{mol}^{-1} \text{cm}^{-1}$); $\tilde{\nu}(\text{KBr})/\text{cm}^{-1}$ 1604 (C=N) and 1424 (acac); m/z 684 ($M - \text{acac}$).

X-Ray crystallography

Crystal data for complexes **3**· CH_2Cl_2 and **4**· $2\text{H}_2\text{O}$ are collected in Table 1. For **3**· CH_2Cl_2 a green crystal of dimensions $0.25 \times 0.50 \times 0.50$ mm was used for data collection at 25°C on a Enraf-Nonius diffractometer (graphite-monochromatized Cu radiation, $\lambda = 1.5406 \text{ \AA}$) using θ - 2θ scans. Intensity data ($2\theta_{\max} = 130^\circ$; $h -16$ to 16 , $k 0$ to 21 , $l 0$ to 18 ; three standard reflections measured every 3600 s showed 2% decay) were corrected for decay and for Lorentz-polarisation effects and an empirical absorption correction was made. 6513 Unique reflections were obtained from a total of 6613 measured reflections; 3592 reflections with $I > 2\sigma(I)$ were used in the structural analysis. The structure was solved by Patterson and Fourier methods¹⁰ and subsequent refinement by full-matrix least squares was performed using the software package NRCVAX.¹¹ All 53 non-H atoms were refined anisotropically. Convergence for 476 variable parameters by least-squares refinement was reached at $R = 0.077$ and $R' = 0.087$ with a goodness of fit of 2.17, $(\Delta/\sigma)_{\max} = 0.01$. The final Fourier-difference map was featureless, with residual extrema of 0.89 and -0.67 e \AA^{-3} respectively.

For complex **4**· $2\text{H}_2\text{O}$ a purple-brown crystal of dimensions $0.20 \times 0.15 \times 0.35$ mm was used for data collection at 25°C on a Enraf-Nonius diffractometer (graphite-monochromatized Mo-K α radiation, $\lambda = 0.7107 \text{ \AA}$) using ω - 2θ scans. Intensity data ($2\theta_{\max} = 44^\circ$; $h 0$ to 12 , $k -18$ to 18 , $l -21$ to 21 ; three standard reflections measured every 300 showed decay of 7.95%) were corrected for decay and for Lorentz-polarisation effects and an empirical absorption correction was made. 9397 Unique reflections were obtained from a total of 9972 measured reflections; 5494 reflections with $I > 3\sigma(I)$ were used in the structural analysis. The structure was solved by direct methods (SIR 92¹²), expanded by the Fourier method and refined by full-matrix least squares using the software package TEXSAN.¹³ Two formula units constitute a crystallographic asymmetric unit. All 100 non-H atoms, including the oxygen atoms of the four water molecules, were refined anisotropically. Hydrogen atoms of the water molecules were not located. Convergence for 937 variable parameters by least-squares refinement was reached at $R = 0.045$ and $R' = 0.050$ with a goodness of fit of 2.07, $(\Delta/\sigma)_{\max} = 0.04$. The final Fourier-difference map was featureless, with residual extrema of 0.80 and -0.45 e \AA^{-3} respectively.

CCDC reference number 186/632.

Alkene oxidation

All catalytic oxidation reactions were carried out at room temperature under an argon atmosphere unless specified. In a typical run the alkene (100 mg), catalyst (5 mg) and PhIO (50 mg) were stirred in the appropriate solvent (5 cm^3) until all PhIO had dissolved. The epoxide product and iodobenzene formed were quantified by GC using the internal standard method and the epoxide yield for the PhIO epoxidation was based on the amount of iodobenzene formed.

Results and Discussion

Previous studies by Meunier and co-workers⁵ demonstrated that Schiff bases can readily form complexes with transition-metal ions in alcohol. Despite this, we found that the catalytically inactive $[\text{Mn}^{\text{III}}_2\text{L}_2(\text{OME})_2]$ dimer was afforded by

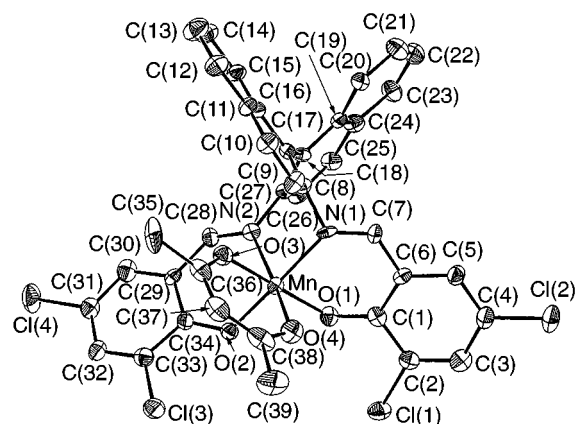


Fig. 1 Perspective view of one enantiomer of complex **3**· CH_2Cl_2 (30% probability ellipsoids, solvent molecule omitted)

refluxing the binaphthyl Schiff base with $\text{Mn}(\text{O}_2\text{CMe})_3$ in methanol.⁴

Subsequently, by using acetonitrile as solvent and hence removing the methoxide ions, we have been able to prepare monomeric binaphthyl Schiff-base complexes. Hence treatment of $\text{Mn}(\text{O}_2\text{CMe})_3$ with H_2L^1 and H_2L^2 in acetonitrile yielded $[\text{Mn}^{\text{III}}\text{L}^1(\text{O}_2\text{CMe})]$ **1** and $[\text{Mn}^{\text{III}}\text{L}^2(\text{O}_2\text{CMe})]$ **2** as dark green solids respectively. In solution, complexes **1** and **2** are stable for 2 h at room temperature, but slow decomposition is observed over longer periods. By comparison, reaction of $[\text{Mn}(\text{acac})_3]$ and $[\text{Fe}(\text{acac})_3]$ with H_2L^1 in acetonitrile afforded $[\text{Mn}^{\text{III}}\text{L}^1(\text{acac})]$ **3** and $[\text{Fe}^{\text{III}}\text{L}^1(\text{acac})]$ **4** respectively, which are stable in solution for over 24 h. This difference may be attributed to the strained nature of the four-membered ring formed between the metal ion and the bidentate acetato group in **1** and **2**, while by analogy a six-membered ring is present in **3** and **4**. The UV/VIS spectra of **1** and **3** are comparable indicating that the complexes are structurally related.

Crystal structures of binaphthyl Schiff-base complexes

The different chiral modes of ligation by the tetradentate ligand in an octahedral complex are shown in Fig. 3. The remaining sites are *cis*, while α and β denotes *trans*- and *cis*-aryloxo groups respectively; Δ chirality at the metal atom arises from co-ordination by an (*R*)-ligand, and the Λ form is generated upon complexation by an (*S*)-ligand.

Molecular structures of the racemic complexes **3**· CH_2Cl_2 and **4**· $2\text{H}_2\text{O}$ have been established by X-ray crystallography. The geometry around the manganese atom in **3**· CH_2Cl_2 (Fig. 1) is octahedral with the Schiff-base ligand bound to the metal centre in a *cis*- β configuration. The acac ligand occupies the remaining co-ordination sites with Mn–O(3) and Mn–O(4) distances of 1.915(7) and 2.124(7) \AA respectively. The dihedral angle of $85.5(3)^\circ$ between the two naphthalene rings is similar to those of $75.5(1)^\circ$ and $87.59(5)^\circ$ in $[\text{Cu}^{\text{II}}\text{L}^1]$ ⁴ and 2,2'-bis(pyridine-2-carboxamido)-1,1'-binaphthyl.¹⁴ As expected, the (*S*)-binaphthyl Schiff-base ligand induces a chiral centre (Λ) at the manganese atom while the (*R*) form affords Δ chirality at the metal. Complex **4**· $2\text{H}_2\text{O}$ (Fig. 2) is isostructural to **3**· CH_2Cl_2 hence the corresponding dihedral angle of $72.1(1)^\circ$ is comparable. All metal–ligand bond lengths are slightly longer due to the greater radius of the iron(III) ion.

Catalytic epoxidation of alkenes using PhIO

We have previously demonstrated that the *in situ* $\text{Mn}^{\text{III}} + (\text{S})\text{-H}_2\text{L}$ system can catalyse asymmetric epoxidation of alkenes using PhIO with moderate e.e.⁴ However, there are potential problems associated with *in situ* catalysis: complexation is not well defined and may be incomplete, greater than one active species may be present and the choice of solvents is limited to

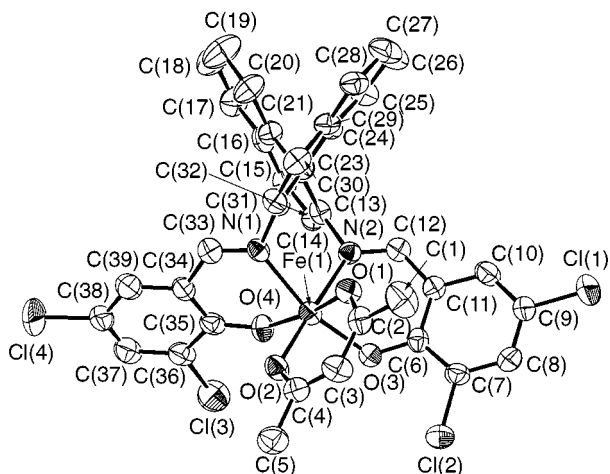


Fig. 2 Perspective view of one enantiomer of complex **4**·2H₂O [Molecule A, 40% probability ellipsoids, solvent molecules omitted, C(22) is obscured by C(30)]

those which can solubilise the reactants. We therefore investigated the catalytic reactivity of the isolated chiral Schiff-base manganese complexes using an analogous procedure and found that they are also active towards asymmetric alkene epoxidation by PhIO. The reactivity of (*R*)-**1** and (*R*)-**2** and their respective yields and e.e. for the epoxidation of styrene are very similar to those for the corresponding *in situ* systems under identical conditions, which implies that the catalytic cycle of the latter proceeds by generating the monomeric species isolated in this work.

For the present study attention was focused on complex (*R*)-**2** since the *in situ* system bearing the same ethyl/nitro substituents

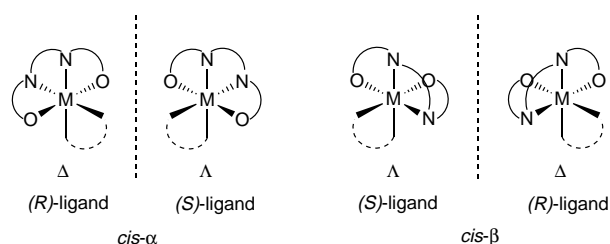


Fig. 3 Chiral centres in binaphthyl Schiff-base complexes

gave the highest e.e. of 58% and *cis*:*trans* ratio of 10:1 for the epoxidation of *cis*- β -methylstyrene.⁴ Results are summarised in Table 4: significantly, the enantioselectivity is enhanced by using a low-polarity solvent, e.g. benzene and toluene and at lower temperatures. This also suppresses the *cis*/*trans* isomerisation of *cis*-disubstituted alkenes. The effect of solvents upon e.e. has recently been observed for epoxidation catalysts based on ruthenium porphyrins.¹⁵ Hence the epoxidation of *cis*- β -methylstyrene in toluene gave e.e. of 63% at 25 °C and 76% at -20 °C. A *cis*:*trans* ratio of 14:1 was obtained at 25 °C, while only a trace amount of the *trans* product was afforded at -20 °C. Lowering the reaction temperature to -20 °C did not affect the yield markedly, although at -60 °C virtually no epoxidation reaction was observed.

The acac derivative (*R*)-**3** is also active towards the epoxidation of alkenes, although slightly lower yields and e.e. were detected compared to (*R*)-**1**. For example, an e.e./yield of 43%/72% for (*R*)-**3** and 54%/80% for (*R*)-**1** were obtained using *cis*- β -methylstyrene. The active species for the epoxidation reaction may be an oxo-intermediate,² or a PhIO adduct in accordance with the study by Hill and co-workers¹⁶ on the Mn(tpp) system (H₂tpp = 5,10,15,20-tetraphenylporphyrin) and work by Valentine and co-workers.¹⁷ Nevertheless, since there is no direct evidence for the formation of such species and their

Table 1 Crystal data for complexes **3**·CH₂Cl₂ and **4**·2H₂O

	3 ·CH ₂ Cl ₂	4 ·2H ₂ O
Formula	C ₃₈ H ₂₅ Cl ₄ MnN ₂ O ₄ ·CH ₂ Cl ₂	C ₃₈ H ₂₅ Cl ₄ FeN ₂ O ₄ ·2H ₂ O
<i>M</i>	867.32	819.33
Crystal system	Monoclinic	Triclinic
Space group	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> $\bar{1}$ (no. 2)
<i>a</i> /Å	13.974(6)	11.664(2)
<i>b</i> /Å	18.036(8)	17.550(4)
<i>c</i> /Å	15.5367(17)	20.876(4)
α /°		66.00(2)
β /°	100.193(24)	80.09(1)
γ /°		84.87(2)
<i>U</i> /Å ³	3854.1(24)	3503(1)
<i>Z</i>	4	4
<i>D</i> _c /g cm ⁻³	1.495	1.415
μ /cm ⁻¹	70.9	7.17
<i>F</i> (000)	1760	1676
<i>R</i> , <i>R</i> '	0.077, 0.087	0.045, 0.050

$$R = \frac{\sum |F_o| - |F_c|}{\sum |F_o|}, R' = \frac{[\sum w|F_o| - |F_c|]^2 / \sum w|F_o|^2}{}.$$

Table 2 Selected bond distances (Å) and angles(°) for complex **3**·CH₂Cl₂

Mn–O(1)	1.896(7)	Mn–N(2)	2.277(7)
Mn–O(2)	1.887(6)	N(1)–C(7)	1.276(12)
Mn–O(3)	1.915(7)	N(1)–C(8)	1.444(12)
Mn–O(4)	2.124(7)	N(2)–C(27)	1.447(12)
Mn–N(1)	2.056(8)	N(2)–C(28)	1.275(12)
O(1)–Mn–O(2)	90.9(3)	O(2)–Mn–N(2)	86.9(3)
O(1)–Mn–O(3)	178.2(3)	O(3)–Mn–O(4)	87.5(3)
O(1)–Mn–O(4)	91.0(3)	O(3)–Mn–N(1)	92.0(3)
O(1)–Mn–N(1)	87.0(3)	O(3)–Mn–N(2)	84.9(3)
O(1)–Mn–N(2)	96.5(3)	O(4)–Mn–N(1)	93.3(3)
O(2)–Mn–O(3)	90.3(3)	O(4)–Mn–N(2)	172.3(3)
O(2)–Mn–O(4)	94.7(3)	N(1)–Mn–N(2)	85.5(3)
O(2)–Mn–N(1)	171.8(3)		

Table 3 Selected bond distances (Å) and angles (°) for molecule A of complex **4**·2H₂O; parameters for molecule B in square brackets

Fe(1)–O(1)	2.015(4) [2.017(5)]	Fe(1)–N(2)	2.149(5) [2.144(5)]
Fe(1)–O(2)	2.001(4) [1.993(5)]	N(1)–C(32)	1.442(7) [1.442(7)]
Fe(1)–O(3)	1.941(4) [1.947(4)]	N(1)–C(33)	1.278(7) [1.277(7)]
Fe(1)–O(4)	1.918(4) [1.912(4)]	N(2)–C(11)	1.276(7) [1.276(7)]
Fe(1)–N(1)	2.166(5) [2.170(5)]	N(2)–C(13)	1.442(7) [1.446(8)]
O(1)–Fe(1)–O(2)	86.5(2) [86.9(2)]	O(2)–Fe(1)–N(2)	175.8(2) [174.4(2)]
O(1)–Fe(1)–O(3)	88.2(2) [88.6(2)]	O(3)–Fe(1)–O(4)	103.1(2) [101.8(2)]
O(1)–Fe(1)–O(4)	168.3(2) [169.4(2)]	O(3)–Fe(1)–N(1)	165.2(2) [165.6(2)]
O(1)–Fe(1)–N(1)	84.3(2) [85.5(2)]	O(3)–Fe(1)–N(2)	84.2(2) [84.0(2)]
O(1)–Fe(1)–N(2)	89.3(2) [88.4(2)]	O(4)–Fe(1)–N(1)	85.2(2) [84.8(2)]
O(2)–Fe(1)–O(3)	95.7(2) [98.8(2)]	O(4)–Fe(1)–N(2)	94.5(2) [94.6(2)]
O(2)–Fe(1)–O(4)	89.6(2) [89.5(2)]	N(1)–Fe(1)–N(2)	82.9(2) [82.7(2)]
O(2)–Fe(1)–N(1)	96.6(2) [94.0(2)]		

Table 4 Alkene epoxidation catalysed by complex (*R*)-**2** using PhIO

Substrate	Product	e.e. ^a (%)			
		Benzene		Toluene	
		25 °C ^b	25 °C ^b	0 °C ^c	-20 °C ^d
Styrene	Styrene oxide ^{e,f}	38 (82)	34 (68)	42 (62)	46 (68)
4-Chlorostyrene	4-Chlorostyrene oxide ^{e,g}	38 (91)	36 (65)	43 (63)	46 (64)
<i>cis</i> - β -Methylstyrene	<i>cis</i> - β -Methylstyrene oxide ^h	64 (70)	63 (59)	71 (67)	76 (63)

^a Based on amount of PhI formed; yields (%) in parentheses. ^b Reaction for 0.5–1 h. ^c Reaction for 1–1.5 h. ^d Reaction for 3 h. ^e *R* configuration. ^f Benzaldehyde (2%) was detected after each run. ^g 4-Chlorobenzaldehyde (trace, except toluene, 25 °C: 4%) was detected after each run. ^h 1*R*, 2*S* Configuration. *trans*- β -Methylstyrene oxide (benzene: 6%; toluene, 25 °C: 7%; 0 °C and -20 °C: trace) was detected after each run.

isolation has so far been unsuccessful, the active species in this system remains a point of contention.

Unlike the manganese(III) catalysts, epoxidation of alkenes was not observed using the iron(III) complex (*R*)-**4**. Addition of PhIO to a solution of (*R*)-**4** led to rapid decomposition of the metal species.

Conclusion

New monomeric chiral binaphthyl Schiff-base complexes of manganese and iron have been prepared using acetonitrile as solvent. The manganese(III) derivatives (*R*)-**1** to **3** mediate the catalytic asymmetric epoxidation of alkenes by PhIO and the highest e.e. in this system so far has been achieved at -20 °C in low-polarity toluene. In contrast to the planar structures observed for Jacobsen-type catalysts,¹⁸ the crystal structures of the racemic complexes **3**·CH₂Cl₂ and **4**·2H₂O depict non-planar molecules. This fundamental difference may be responsible for the higher e.e. obtained by Jacobsen, since in our system the environment for metal-alkene interaction is evidently more open, and this may ultimately lead to different reaction patterns.

Acknowledgements

We acknowledge support from The University of Hong Kong and the Hong Kong Research Grants Council.

References

- 1 T. Katsuki and K. B. Sharpless, *J. Am. Chem. Soc.*, 1980, **102**, 5974; M. G. Finn and K. B. Sharpless, *Asymmetric Synthesis*, ed. J. D. Morrison, Academic Press, New York, 1985, vol. 5, p. 247; H. C. Kolb, M. S. Van Nieuwenhze and K. B. Sharpless, *Chem. Rev.*, 1995, **94**, 2483 and refs. therein.
- 2 E. N. Jacobsen, *Catalytic Asymmetric Synthesis*, ed. I. Ojima, VCH, New York, 1993, p. 159; T. Katsuki, *Coord. Chem. Rev.*, 1995, **140**, 189.

- 3 C. Rosini, L. Franzini, A. Raffaelli and P. Salvadori, *Synthesis*, 1992, 504; R. Noyori, *Chem. Soc. Rev.*, 1989, **18**, 187; R. Noyori and H. Takaya, *Acc. Chem. Res.*, 1990, **23**, 345 and refs. therein.
- 4 C. W. Ho, W. C. Cheng, M. C. Cheng, S. M. Peng, K. F. Cheng and C. M. Che, *J. Chem. Soc., Dalton Trans.*, 1996, 405.
- 5 K. Bernardo, S. Lippard, A. Robert, G. Commenges, F. Dahan and B. Meunier, *Inorg. Chem.*, 1996, **35**, 387.
- 6 M. N. Bhattacharjee, M. K. Chaudhuri and D. T. Khathing, *J. Chem. Soc., Dalton Trans.*, 1982, 669.
- 7 D. D. Perrin, W. L. F. Armarego and D. R. Perrin, *Purification of Laboratory Chemicals*, 2nd, edn., Pergamon, Oxford, 1980.
- 8 H. Lindler and R. Dubuis, *Org. Synth.*, 1973, *Coll. Vol. V*, 880.
- 9 L. F. Fieser and M. Fieser, *Reagents for Organic Synthesis*, Wiley, New York, 1967, vol. 1, p. 137.
- 10 PATTY and DIRDIF 92, P. T. Beurskens, G. Admiraal, G. Beurskens, W. P. Bosman, S. Garcia-Granda, R. O. Gould, J. M. M. Smits and C. Smykalla, The DIRDIF program system, Technical Report of the Crystallography Laboratory, University of Nijmegen, 1992.
- 11 NRCVAX, E. J. Cabe, Y. Le Page, J. P. Charland, F. L. Lee and P. S. White, *J. Appl. Crystallogr.*, 1989, **22**, 384.
- 12 SIR 92, A. Altomare, M. Cascarano, C. Giacovazzo, A. Guagliardi, M. C. Burla, G. Polidori and M. Camalli, *J. Appl. Crystallogr.*, 1994, **27**, 435.
- 13 TEXSAN, Crystal Structure Analysis Package, Molecular Corporation, Houston, TX, 1985 and 1992.
- 14 J. H. Lin, C. M. Che, T. F. Lai, C. K. Poon and Y. X. Cui, *J. Chem. Soc., Chem. Commun.*, 1991, 468.
- 15 Z. Gross, S. Ini, M. Kapon and S. Cohen, *Tetrahedron Lett.*, 1996, **37**, 7325.
- 16 J. A. Smegal, B. C. Schardt and C. L. Hill, *J. Am. Chem. Soc.*, 1983, **105**, 3510; J. A. Smegal and C. L. Hill, *J. Am. Chem. Soc.*, 1983, **105**, 3515.
- 17 R. B. Van Atta, C. C. Franklin and J. S. Valentine, *Inorg. Chem.*, 1984, **23**, 4121.
- 18 W. Zhang, J. L. Loebach, S. R. Wilson and E. N. Jacobsen, *J. Am. Chem. Soc.*, 1990, **112**, 2801; P. J. Pospisil, D. H. Carsten and E. N. Jacobsen, *Chem. Eur. J.*, 1996, **2**, 974.

Received 30th January 1997; Paper 7/00712D