

Structure and photochemical properties of ruthenium complexes having dimethyl-substituted DPPZ or TPPHZ as a ligand †

Nobuko Komatsuzaki, Ryuzi Katoh, Yuichiro Himeda, Hideki Sugihara, Hironori Arakawa and Kazuyuki Kasuga*

National Institute of Materials and Chemical Research, 1-1 Higashi, Tsukuba, Ibaraki 305-8565, Japan. E-mail: kasuga@nimc.go.jp

Received 6th July 2000, Accepted 9th August 2000

Published on the Web 23rd August 2000

Novel ruthenium complexes having 4,7-dimethyl-substituted DPPZ or TPPHZ as a ligand have been synthesized: the methyl groups on the ligands exert a shielding effect on the phenazine nitrogens which prevents solvent-quenching.

The ruthenium complexes having DPPZ (dipyrido[3,2-*a*:2',3'-*c*]-phenazine)¹ or TPPHZ (tetrapyrro[3,2-*a*:2',3'-*c*:3'',2''-*h*:2''',3'''-*j*]phenazine)² as a ligand have been of much interest because of their unique emission properties arising from extended aromatic structures incorporating a phenazine moiety. In particular, the most remarkable feature is the high sensitivity towards their environment.^{3,4,5} In highly polar protic solvents such as water and MeOH, the emission intensities, *i.e.* the emission lifetimes of the complexes, decrease considerably due to the deactivation of the excited state by hydrogen bonding or proton transfer to the phenazine nitrogens. By contrast, in hydrophobic media rather strong emissions are observed.⁶ This makes the complexes potentially useful as luminescence probes for DNA^{5,7} and micelles.⁴ However, this unique character also limits the utility of the complexes as a photo-sensitizer.

We were interested in controlling the solvent-dependence of the emission properties of the complexes. For this purpose, we newly synthesized ruthenium complexes having 4,7-dimethyl-substituted DPPZ (dmDPPZ) or TPPHZ (dmTPPHZ) as a ligand (**1b**, **2b** and **3b**), expecting that the hydrophobic methyl groups on the new ligands would shield the phenazine nitrogens from the environment, and thereby effectively preventing the solvent-quenching (Fig. 1). ‡

For the synthesis of the complexes **1b–3b**, § [Ru(bpy)₂L]²⁺ (L = 4,7-dimethyl-1,10-phenanthroline-5,6-dione) was prepared at first from Ru(bpy)₂Cl₂ and L, which was obtained by oxidation of 4,7-dimethyl-1,10-phenanthroline according to the reported method.⁸ Condensation^{5,9} of [Ru(bpy)₂L]²⁺ with the appropriate 1,2-diaminobenzene derivatives yielded **1b** and **2b** in only modest yields (30–40%), which may be caused by steric hindrance of the methyl groups.

The crystal structure of **1b** clearly shows the close vicinity of the methyl groups to the phenazine nitrogens (Fig. 2). ¶ The average bond distances and angles of **1b** are comparable to typical values for similar ruthenium polypyridine complexes.¹⁰ Two methyl carbon atoms and the DPPZ framework lie on an essentially perfect plane. The two dmDPPZ ligands are packed in a head-to-tail fashion as observed in the crystal structure of [Ru(OH₂)(DPPZ)(tpy)]²⁺ (tpy = terpyridine),¹¹ although their planes are not superposed on each other owing to the presence of the methyl groups.

Table 1 summarizes the electrochemical data of **1a,b–3a,b** as well as those of DPPZ and dmDPPZ. All the oxidation and reduction potentials of the complexes **1b–3b** are shifted to more negative values by the introduction of the methyl groups. This tendency is consistent with the previous observations in

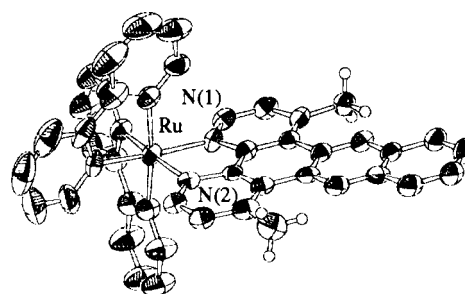
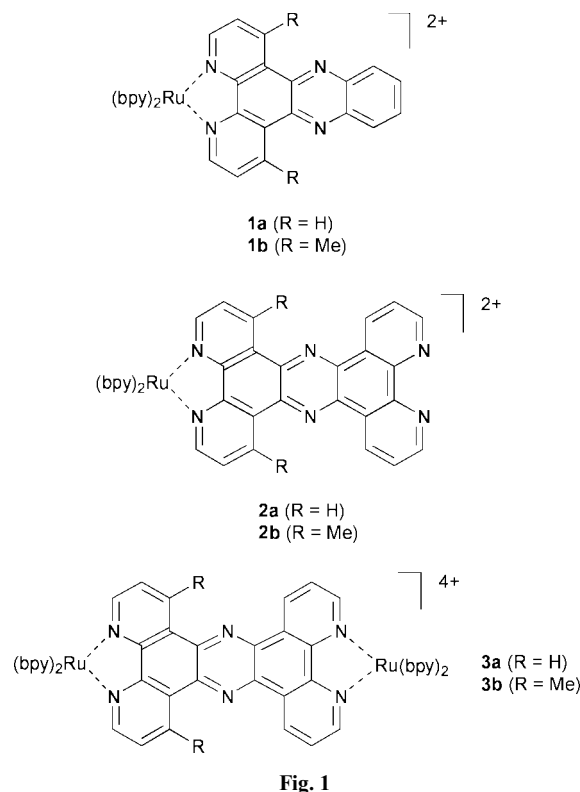


Fig. 2 The ORTEP¹⁶ view of **1b**. Hydrogen atoms and anions are omitted for clarity. Selected bond lengths (Å) and angle (°): Ru–N(1) 2.050(7), Ru–N(2) 2.049(7); N(1)–Ru–N(2) 78.6(3).

the ruthenium complexes having dimethyl-substituted 2,2'-bipyridine or 1,10-phenanthroline derivatives as ligands.^{12,13}

The photochemical properties of **1a,b–3a,b** in MeCN and MeOH are summarized in Table 2. As almost no solvent-dependence was observed in the absorption spectra for all of the complexes, only the data in MeCN are depicted in the table. The peak positions and intensities of the MLCT absorption bands of the complexes are not changed markedly by the introduction of the methyl groups. The emission maxima

† Electronic supplementary information (ESI) available: unit cell of **1b**. See <http://www.rsc.org/suppdata/dt/b0/b005428n/>

Table 1 Electrochemical data ($E_{1/2}/V$ vs. Fc/Fc^+)^a

| Compound | Oxidation | Reduction | | |
|-----------|-----------|--------------|--------------|--------------|
| | | 1 | 2 | 3 |
| DPPZ | | -1.62 | | |
| dmDPPZ | | -1.76 | | |
| 1a | +0.91 | -1.36 | -1.79 | -2.00 |
| 1b | +0.85 | -1.48 | -1.80 | -2.03 |
| 2a | +0.91 | -1.26 | ^b | ^b |
| 2b | +0.89 | ^b | ^b | ^b |
| 3a | +0.92 | -1.19 | ^b | ^b |
| 3b | +0.89 | -1.25 | ^b | ^b |

^a The cyclic voltammetry was conducted with glassy C, Pt and Ag/Ag⁺ as working, counter and reference electrodes, respectively, under a N₂ atmosphere. The concentration was kept at 1 mM in DMF (DPPZ, dmDPPZ) or MeCN (**1a,b-3a,b**) with 0.1 M TBAP. Scan rate = 100 mV s⁻¹. ^b These values were not determined due to broad or irreversible peaks.

Table 2 Photochemical data

| | Absorption ^a in MeCN λ_{max}/nm ($\epsilon/10^4$ M ⁻¹ cm ⁻¹) | Emission ^b | | | |
|-----------|--|-----------------------|-----------|--------------------|-----------|
| | | in MeCN | | in MeOH | |
| | | λ_{max}/nm | τ/ns | λ_{max}/nm | τ/ns |
| 1a | 450 (1.8) | 625 | 740 | 619 | 30 |
| 1b | 450 (1.7) | 625 | 1160 | 619 | 820 |
| 2a | 450 (2.1) | 620 | 930 | 619 | 580 |
| 2b | 451 (2.2) | 624 | 1100 | 623 | 920 |
| 3a | 444 (3.5) | 680 | 90 | 671 | 30 |
| 3b | 445 (3.6) | 682 | 180 | 678 | 100 |

^a MLCT absorptions were measured in MeCN at room temperature.

^b Emission spectra excited at 450 nm were recorded at room temperature and corrected for spectral response by calibrating the fluorimeter with a standard lamp. The concentrations of all measured samples were 1.0×10^{-5} M.

of **1b-3b** are almost the same or slightly red-shifted as compared with those of **1a-3a** respectively. These observations indicate that the methyl substitution on the ligands does not alter the relative energies of the excited states of the complexes appreciably.¹³

The effect of the methyl groups on the emission lifetimes of the complexes is obvious. Even in MeCN, **1b-3b** exhibit increased lifetimes, as observed for the ruthenium complexes with 4,7- or 5,6-dimethyl-1,10-phenanthroline as ligands.^{12,14} In MeOH, the presence of the methyl groups effects emission lifetimes more profoundly. The lifetime of **1b** is 27 times longer than that of **1a**, while **2b** and **3b** show moderate increase (2–3 times). This result can be interpreted by the difference in the steric environments around the phenazine nitrogens between DPPZ and TPPHZ. As pointed out already,⁵ the phenazine nitrogen atoms of the DPPZ ligand are more exposed to the outer environment than those of TPPHZ, in which the space around the phenazine nitrogens is inherently sterically crowded. This makes the solvent-interaction of the phenazine nitrogens more difficult for TPPHZ than for DPPZ and results in the relatively longer emission lifetime of **2a** in MeOH compared to that of **1a**.

In the cases of **3a** and **3b**, the emissions are considerably red-shifted and the lifetimes are rather short regardless of solvent as already reported for **3a**.¹⁵ These facts suggest that the solvent-interaction may not be the main factor for the deactivation of the excited states in **3a** and **3b**. Consequently, the shielding

effect of the methyl groups on the phenazine nitrogens is more profound in **1b** than in **2b** and **3b**. A similar increase in the emission lifetime was observed for **1b** in MeCN containing 10% water (**1a**: $\tau = 35$ ns, **1b**: $\tau = 835$ ns), although the emission of **1b** was quenched in 100% water.

Thus, we have succeeded in controlling the solvent-dependence of the emission properties of the ruthenium complexes having the DPPZ or TPPHZ ligand by the introduction of methyl groups on the ligands. The present results may increase the utility of these complexes as a photo-sensitizer and also contribute to the further understanding of the photochemical properties of the complexes.

Notes and references

‡ Barton and Hartshorn have already reported on the photochemical properties of the ruthenium complexes with derivatives of the DPPZ ligand and discussed the effect of peripheral substitution.⁹

§ Selected data for [Ru(bpy)₂L][ClO₄]₂ (L = 4,7-dimethyl-1,10-phenanthroline-5,6-dione): Anal. Found: C, 46.80; H, 3.13; N, 9.48%. Calcd for C₃₄H₂₆N₈Cl₂O₁₀Ru·H₂O: C, 47.01; H, 3.25; N, 9.68%. ES-MS: 750 [M - ClO₄]⁺. For **1b**: Anal. Found: C, 51.33; H, 3.37; N, 11.66%. Calcd for C₄₀H₃₀N₈Cl₂O₈Ru·H₂O: C, 51.07; H, 3.43; N, 11.91%. ES-MS: 822 [M - ClO₄]⁺. For **2b**: Anal. Found: C, 51.04; H, 3.15; N, 13.10%. Calcd for C₄₆H₃₂N₁₀Cl₂O₈Ru·3H₂O: C, 51.21; H, 3.55; N, 12.98%. ES-MS: 924 [M - ClO₄]⁺. For **3b**: Anal. Found: C, 47.85; H, 2.91; N, 11.60%. Calcd for C₆₆H₄₈N₁₄Cl₄O₁₆Ru₂·H₂O: C, 47.89; H, 3.04; N, 11.85%. ES-MS: 1537 [M - ClO₄]⁺. The new ligand L was characterized by ¹H-NMR and used in the next reaction without further purification due to its instability.

¶ Crystal data for C₄₀H₃₀N₈O₈Cl₂Ru **1b**: $M = 922.70$, Triclinic, $a = 15.799(8)$, $b = 15.86(1)$, $c = 17.17(1)$ Å, $\alpha = 89.17(3)$, $\beta = 89.64(4)$, $\gamma = 76.57(5)^\circ$, $V = 4183(4)$ Å³, $T = 223$ K, space group $P\bar{1}$, $Z = 4$, $D_c = 1.47$ g cm⁻³, $\mu(\text{Mo-K}) = 5.63$ cm⁻¹, $R = 0.074$ and $R_w = 0.093$ for 9199 unique reflections with $I > 3\sigma(I)$. CCDC reference number 186/2134. See <http://www.rsc.org/suppdata/dt/b0/b005428n/> for crystallographic files in .cif format.

- J. E. Dickeson and L. A. Summers, *Aust. J. Chem.*, 1970, **23**, 1023.
- J. Bolger, A. Gourdon, E. Ishow and J.-P. Launay, *J. Chem. Soc., Chem. Commun.*, 1995, 1799.
- E. Amouyal, A. Homs, J.-C. Chambron and J.-P. Sauvage, *J. Chem. Soc., Dalton Trans.*, 1990, 1841; J.-C. Chambron, J.-P. Sauvage, E. Amouyal and P. Koffi, *Nouv. J. Chim.*, 1985, **9**, 527.
- J.-C. Chambron and J.-P. Sauvage, *Chem. Phys. Lett.*, 1991, **182**, 603.
- J. Bolger, A. Gourdon, E. Ishow and J.-P. Launay, *Inorg. Chem.*, 1996, **35**, 2937.
- E. J. Olson, D. Hu, A. Hörmann, A. M. Jonkman, M. R. Arkin, E. D. A. Stemp, J. K. Barton and P. F. Barbara, *J. Am. Chem. Soc.*, 1997, **119**, 11458; R. B. Nair, B. M. Cullun and C. J. Murphy, *Inorg. Chem.*, 1997, **36**, 962.
- A. E. Friedman, J.-C. Chambron, J.-P. Sauvage, N. J. Turro and J. K. Barton, *J. Am. Chem. Soc.*, 1990, **112**, 4960. See also references cited in ref. 6.
- M. Yamada, Y. Tanaka, Y. Yoshimoto, S. Kuroda and I. Shima, *Bull. Chem. Soc. Jpn.*, 1992, **65**, 1006.
- R. M. Hartshorn and J. K. Barton, *J. Am. Chem. Soc.*, 1992, **114**, 5919.
- D. Paul and D. S. Jones, *J. Chem. Soc., Chem. Commun.*, 1979, 849.
- N. Gupta, N. Grover, G. A. Neyhart, W. Liang, P. Singh and H. H. Thorp, *Angew. Chem., Int. Ed. Engl.*, 1992, **31**, 1048.
- C.-T. Lin, W. Böttcher, M. Chou, C. Creutz and N. Sutin, *J. Am. Chem. Soc.*, 1976, **98**, 6536.
- P. A. Mabrouk and M. S. Wrighton, *Inorg. Chem.*, 1986, **25**, 526.
- P. C. Alford, M. J. Cook, A. P. Lewis, G. S. McAuliffe, V. Skarda, A. J. Thomson, J. L. Glasper and D. J. Robbins, *J. Chem. Soc., Perkin Trans. 2*, 1985, 705.
- C. Chiorboli, C. A. Bignozzi, F. Scandola, E. Ishow, A. Gourdon and J.-P. Launay, *Inorg. Chem.*, 1999, **38**, 2402; S. Campagna, S. Serroni, S. Bodige and F. M. MacDonnell, *Inorg. Chem.*, 1999, **38**, 692.
- C. K. Johnson, ORTEP, Report ORNL-5138, Oak Ridge National Laboratory, Oak Ridge, TN, 1976.