

This article was downloaded by:

On: 26 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713926090>

X-Ray Investigation of Discotic Mesophases of Alkylthio Substituted Triphenylenes

E. F. Gramsbergen^a; H. J. Hoving^a; W. H. De Jeu^a; K. Praefcke^b; B. Kohne^b

^a Solid State Physics Laboratory, University of Groningen, The Netherlands ^b Institute of Organic Chemistry, Technische Universität Berlin, Germany

To cite this Article Gramsbergen, E. F. , Hoving, H. J. , De Jeu, W. H. , Praefcke, K. and Kohne, B.(1986) 'X-Ray Investigation of Discotic Mesophases of Alkylthio Substituted Triphenylenes', *Liquid Crystals*, 1: 4, 397 – 400

To link to this Article: DOI: 10.1080/02678298608086671

URL: <http://dx.doi.org/10.1080/02678298608086671>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

PRELIMINARY COMMUNICATIONS

X-ray investigation of discotic mesophases of alkylthio substituted triphenylenes

by E. F. GRAMSBERGEN, H. J. HOVING and W. H. de JEU†
Solid State Physics Laboratory, University of Groningen, Melkweg 1,
9751 EP Groningen, The Netherlands


K. PRAEFCKE and B. KOHNE
Institute of Organic Chemistry, C3, Technische Universität Berlin,
Strasse des 17. Juni 135, D-1000 Berlin 12, F.R. Germany

(Received 7 March 1986; accepted 15 June 1986)

Power samples of three alkylthio substituted triphenylenes have been investigated by X-ray diffraction. All have a hexagonal columnar D_{hd} phase. In one compound, a phase transition $D_{ho} \leftrightarrow D_{hd}$ is found, in which the hexagonal lattice of columns remains unaffected by the order-disorder transition within the columns.

It has been recognized for a number of years [1] that disc-like molecules can exhibit thermotropic mesophases. Apart from the fluid nematic phase [2], all of these so-called discotic phases are columnar phases with the molecules stacked in columns that can slide more or less easily along each other, while the order within each column can be either solid- or liquid-like [3]. We have investigated the structural behaviour of a series of alkylthio substituted triphenylenes [4] which have been synthesized recently. All have a hexagonal columnar D_{hd} phase, while one of the compounds also shows a $D_{ho} \leftrightarrow D_{hd}$ phase transition. In addition a diffuse reflection characteristic of the liquid-like aliphatic regions is observed for the higher homologues.

The general formulae of the compounds studied is

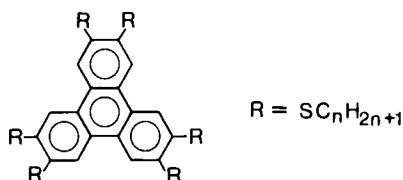

with $n = 6, 8$ and 10 [4]. The triphenylene core has already proved to be fruitful for building discotic molecules which exhibit mesomorphic behaviour, with end groups R such as $O-C_nH_{2n+1}$ (HET series) [5, 6], $OCO-C_nH_{2n+1}$ (HAT series) [6], $OCO\emptyset-OC_nH_{2n+1}$ [2, 7] and $OCO\emptyset-C_nH_{2n+1}$ [3]. The transition temperatures of the alkylthio substituted triphenylenes are listed in table 1. The compounds were studied

† Also: The Open University, P.O. Box 2960, 6401 DL Heerlen, The Netherlands.

by X-ray scattering of powder samples in a glass capillary of 0.3 mm diameter, with a high-temperature Guinier camera using monochromatic Cu/K $_{\alpha 1}$ radiation.

The various columnar phases as determined from the X-ray diffraction pattern are listed in table 1. All three compounds have a D $_{hd}$ phase (hexagonal lattice of liquid-like columns), as inferred by the presence of only one low-angle Bragg peak. The uniaxial symmetry of the phase is confirmed by the observation of homeotropic textures with optical microscopy. The hexyl compound ($n = 6$) shows a second mesophase at a lower temperature, which is essentially a D $_{ho}$ phase (hexagonal lattice of ordered columns). There are, however, a number of weak Bragg reflections that indicate some degree of coupling between the columns. In this sense the phase is rather a crystal than a liquid crystal, albeit with an extreme anisotropy. An analogous situation is that of smectic B phases of rod-like molecules, in which a weak coupling between the solid-like layers can exist. At the D $_{ho} \leftrightarrow$ D $_{hd}$ phase transition, neither the position nor the intensity of the low-angle diffraction peak shows an observable change. This indicates that the hexagonal lattice of columns can be considered to be a constant background for this phase transition. In fact, even in the crystalline phase this lattice of columns is still present with the same lattice spacing. This is a unique feature, and offers one of the purest known examples of melting/condensation of one-dimensional stacks of molecules. It is only the weak coupling between the columns that prevents this phase transition from being effectively one-dimensional. As is well known, general considerations of statistical mechanics imply that phase transitions are impossible in strictly one-dimensional systems [8].

Table 1. Phases of the alkylthio substituted triphenylenes. K = crystalline, D = discotic, I = isotropic liquid, h = hexagonal lattice of columns, o = ordered (solid) columns, d = disordered (liquid) columns. The transition temperatures are in °C.

Alkyl carbon number n	Phases						
	K		D $_{ho}$		D $_{hd}$		I
6	x	62	x	70	x	93	x
8	x	55			x	87	x
10	x	67			x	70	x

It is tempting to compare the observed D $_{ho}$ phase with the D $_{ho}$ phase found in the HET series, because the molecules of both series are sterically very similar. In the HET series, the columns were found to be helicoidal with a pitch equal to 13 Å [6]. This structure was also shown to be energetically favourable in a theoretical study [12]. The X-ray pattern of such a structure consists of two diffuse sheets perpendicular to the column axis; these are smeared out over a large angle region in a powder sample. In practice, this can hardly be separated from the background and other contributions. In consequence X-ray data on oriented samples are required to solve this problem.

The distance between neighbouring columns shown in table 2 varies with increasing alkyl chain length from 21.2 Å to 24.8 Å, which is approximately halfway between the diameter of the rigid core including the sulphur atoms (~ 14 Å), and the diameter of the molecule with elongated alkyl chains (~ 26 Å to 30 Å). This implies a large degree of penetration of the alkyl chains into the aliphatic regions of neighbouring columns, and/or a high degree of orientational disorder for the alkyl chains.

At higher Bragg angles, two diffuse reflections occur in the D $_{hd}$ phase: one at 3.6 Å and the other at 4.6 Å (cf. table 2). The first one is only present in the hexyl ($n = 6$)

and octyl ($n = 8$) compounds. It is caused by the stacking of the molecular cores in the columns. The width of the reflection, which is determined by the correlation lengths, ξ_{\parallel} and ξ_{\perp} , parallel and perpendicular to the column axis, is of the order of $(30 \text{ \AA})^{-1}$ full width at half maximum. The location of the reflection along the column axis makes ξ_{\parallel} dominant in determining the width in a powder sample. If ξ_{\perp} is assumed to be equal to the core radius it gives a contribution of only a few per cent. Hence we conclude that the in-column correlation length ξ_{\parallel} is of the order of 30 \AA or about 10 molecules. The intermolecular spacing of 3.6 \AA is close to those found in other triphenylene derivatives [6, 9, 10]. The absence of this reflection in the decyl ($n = C_{10}$) compound is probably due to preferential orientation of the columns along the capillary axis.

Table 2. Bragg spacing d_B of the observed reflections; ‡ diffuse, () very weak.

n	Phase	Hexagonal lattice spacing $(2/\sqrt{3}) d_B/\text{\AA}$	Order within the columns $d_B/\text{\AA}$
6	D_{ho}	21.2	3.61†
	D_{hd}	21.2	3.6‡
8	D_{hd}	23.4	3.6‡ 4.6‡
10	D_{hd}	24.8	4.6‡

† Additional weak reflections: 3.54; 4.50; 4.59; 4.91; 5.24; (5.71); (6.22); (6.72); (9.36).

The second high-angle reflection (4.6 \AA) is present in the octyl ($n = 8$) and decyl ($n = 10$) compounds. It is much weaker and broader than the first. A similar diffuse reflection is found in many triphenylene derivatives [6, 9–11], and has been identified with the liquid-like order of the alkyl chains [6]. In the hexyl ($n = 6$) compound the alkyl chains are probably just too short for this reflection to gain sufficient intensity. In this context it is interesting to note that the D_{ho} phase of this compound shows a number of weak Bragg reflections around 4.6 \AA with the clearest one at 4.50 \AA . We could speculate about a possible relation with the 4.6 \AA diffuse reflection in the other compounds. Then the question arises as to how the order of the alkyl chains is related to the long-range periodicity, which must be described in terms of coupling between the columns. Attempts to identify all the (very weak) reflections in the D_{ho} phase with a specific lattice have failed. A large unit cell is clearly needed to describe the coupling between the columns adequately. To solve the remaining problems experiments on oriented samples are needed.

This work forms part of the research program of the 'Stichting voor Fundamenteel Onderzoek der Materie' (Foundation for Fundamental Research on Matter, FOM) and was made possible by financial support from the 'Nederlandse Organisatie voor Zuiver Wetenschappelijk Onderzoek' (Netherlands Organization for the Advancement of Pure Research, ZWO). One of us (K. P.) acknowledges financial support by the Deutsche Forschungsgemeinschaft (Pr 116/8–1–3), the Fonds der Chemischen Industrie, Frankfurt/Main, and the Technische Universität Berlin (Kanzler and PA1), Germany. This publication is Part XXXII on liquid crystalline and Part LXXII on organic sulphur compounds, respectively. Part XXXI as well as Part LXXI: SPIELBERG, N., LUZ, Z., POUPKO, R., PRAEFCKE, K., KOHNE, B., PICKARDT, J., and HORN, K., 1986, *Z. Naturf. (a)*, **41** (submitted).

References

- [1] CHANDRASEKHAR, S., SADASHIVA, B. K., and SURESH, K. A., 1977, *Pramana*, **9**, 471.
- [2] TINH, NGUYEN HUU, DESTRADE, C., and GASPAROUX, H., 1979, *Physics Lett. A*, **72**, 251.
- [3] LEVELUT, A. M., 1983, *J. Chim. phys.*, **80**, 149.
- [4] KOHNE, B., POULES, W., and PRAEFCKE, K., 1984, *Chem. Zeit.*, **108**, 113.
- [5] BILLARD, J., DUBOIS, J. C., TINH, NGUYEN HUU, and ZANN, A., 1978, *Nouv. J. Chim.*, **2**, 535.
- [6] LEVELUT, A. M., 1979, *J. Phys. Lett., Paris*, **40**, L-81.
- [7] LEVELUT, A. M., HARDOUIN, F., GASPAROUX, H., DESTRADE, C., and TINH, NGUYEN HUU, 1981, *J. Phys., Paris*, **42**, 147.
- [8] See, for example, LANDAU, L. D., and LIFSHITZ, E. M., 1968, *Statistical Physics*, 2nd edition (Pergamon Press).
- [9] DESTRADE, C., TINH, NGUYEN HUU, MALTHÊTE, J., and LEVELUT, A. M., 1983, *J. Phys., Paris*, **44**, 597.
- [10] SAFINYA, C. R., LIANG, K. S., VARADAY, W. A., CLARK, N. A., and ANDERSSON, G., 1984, *Phys. Rev. Lett.*, **53**, 1172.
- [11] LEVELUT, A. M., OSWALD, P., GHANEM, A., and MALTHÊTE, J., 1984, *J. Phys., Paris*, **45**, 745.
- [12] COTRAIT, M., MARSAU, P., PESQUES, M., and VOLPILHAC, V., 1982, *J. Phys., Paris.*, **43**, 355.