

This article was downloaded by:

On: 26 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



## Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713926090>

### X-ray study of the sharpness of the smectic A layer structure

E. F. Gramsbergen<sup>ab</sup>, W. H. De Jeu<sup>cd</sup>

<sup>a</sup> Solid State Physics Laboratory, Groningen, The Netherlands <sup>b</sup> Laboratory for Physical Chemistry, University of Amsterdam, Amsterdam, WS, The Netherlands <sup>c</sup> FOM-Institute for Atomic and Molecular Physics, Amsterdam, SJ, The Netherlands <sup>d</sup> The Open University, Heerlen, DL, The Netherlands

**To cite this Article** Gramsbergen, E. F. and De Jeu, W. H.(1989) 'X-ray study of the sharpness of the smectic A layer structure', *Liquid Crystals*, 4: 4, 449 – 455

**To link to this Article:** DOI: 10.1080/02678298908035492

**URL:** <http://dx.doi.org/10.1080/02678298908035492>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

## X-ray study of the sharpness of the smectic A layer structure

by E. F. GRAMSBERGEN†‡ and W. H. DE JEU§||

† Solid State Physics Laboratory, Melkweg 1, 9718 EP Groningen,  
The Netherlands

§ FOM-Institute for Atomic and Molecular Physics, Kruislaan 407,  
1098 SJ Amsterdam, The Netherlands

(Received 26 November 1985; accepted 2 October 1988)

The intensity ratio of the second order to the first order Bragg reflection resulting from smectic A layering is reported for two compounds. In one case this ratio is small ( $\sim 10^{-3}$ ), which is of the same order as commonly reported. The second compound shows an intensity ratio which is two orders of magnitude higher. In the latter case, the spatial distribution function of the molecular centres of gravity cannot be taken as sinusoidal.

### 1. Introduction

In smectic A ( $S_A$ ) liquid crystals, elongated molecules have their centres, on average, arranged in liquid-like layers that are perpendicular to the preferred direction of the long molecular axes. The layering of the smectic phase is reflected by the X-ray pattern, which, in most cases, is characterized by a clear first order diffraction peak and a very weak second order peak [1-4]. The loss of second order intensity can be attributed to important short range disorder, which makes the density wave describing the layering nearly sinusoidal. This observation is basic for McMillans description of the smectic A-nematic phase transition in terms of a single order parameter,  $\tau_1$ , which is the first harmonic in a Fourier expansion of the density wave [5]. Exceptions are bilayer ( $S_{A2}$ ) phases which are not considered here.

We report the measurement of the intensity  $I_{002}$  of the second order (quasi) Bragg reflection relative to the first order one  $I_{001}$ , for the compounds 4,4'-di-n-heptylazoxybenzene (*A*) and 4-n-butyloxybenzylidene-4'-aminopropiophenone (*B*). Structural formulas and phase transition temperatures are given in table 1. Compound *A* has a 20 K wide  $S_A$  temperature interval ending in a second order  $S_A$ -N phase transition at 53.5°C [6]. The 002-reflection is very weak as usual. Compound *B* [7] has a 56 K wide  $S_A$  interval between a smectic B [8] and a nematic phase; the  $S_A$ -N transition is first order. The ratio  $I_{002}/I_{001}$  is over one 100 times higher than for compound *A*. The results are interpreted in terms of the ratio of the order parameters  $\tau_2/\tau_1$ , where



$$\tau_k = \int_{-d/2}^{d/2} f(z) \cos(2\pi kz/d) dz; \quad (1)$$

here  $f(z)$  is the spatial distribution function of the molecular centres of gravity and  $d$  is the layer thickness. The first harmonic  $\tau_1$ , usually referred to as the order

‡ Present address: Laboratory for Physical Chemistry, University of Amsterdam, Nieuwe Achtergracht 127, 1018 WS Amsterdam, The Netherlands.

|| Also: The Open University, P.O. Box 2960, 6401 DL Heerlen, The Netherlands.

Table 1. Structural formulas and transition temperatures of the compounds investigated.

Compound formula	Phases (temperatures in °C)
A 	K 34 S <sub>A</sub> 53.5 N 70.4 I
B 	K 79 S <sub>B</sub> 87 S <sub>A</sub> 143 N 146 I

parameter  $\tau$ , is a measure of the *strength* of the smectic layering, to be distinguished from the *sharpness* of the layering. The latter quantity indicates the deviation of  $f(z)$  from a sinusoidal shape into a more peaked one, and reflects itself in a non-zero ratio  $\tau_2/\tau_1$ . In the extreme case of an ideal solid,  $f(z)$  is an array of delta functions and  $\tau_2/\tau_1 = 1$ . The relation between the order parameters and the scattering intensity is given by

$$\frac{I_{002}}{I_{001}} = \frac{1}{2} \left| \frac{S(2q_0)}{S(q_0)} \frac{\tau_2}{\tau_1} \right|^2, \quad (2)$$

where  $S(q)$  is the molecular structure factor and  $q_0 = 2\pi/d$  is the position of the first order Bragg reflection. The factor  $\frac{1}{2}$  is the Lorentz factor resulting from mosaic spread in the sample. Once  $S(q)$  is known from molecular models,  $\tau_2/\tau_1$  can be calculated.

## 2. Experimental

The measurements were performed at the Risø National Laboratory (Roskilde, Denmark) with a triple axis spectrometer. X-rays are obtained from a rotating copper anode operating at 50 kV and 180 mA. After a beam defining slit an Si(111) monochromator single crystal selects the  $\text{CuK}_\alpha$  doublet ( $\lambda = 1.54 \text{ \AA}$ ). A second slit placed just before the sample oven eliminates the  $K_{\alpha 2}$  component. The sample oven is placed on a rotation stage and the angle of rotation is denoted by  $\omega$ . The detector arm can be turned through an angle  $2\theta$  relative to the direct beam. When the spectrometer is tuned to a Bragg reflection,  $\theta = \theta_B$ . The analyser is another Si(111) single crystal, placed behind a set of slits for further reduction of the background scattering. The analyser and monochromator crystals are placed such that they reflect in opposite directions (non-dispersive mode). The resolution obtained with this set-up is approximately  $0.003^\circ$  FWHM in  $\theta$ , with the angles of interest between  $1.5$  and  $4^\circ$ . The liquid crystal is held in a sample holder with Be windows; the cell thickness is between  $1.6$  and  $2.5$  mm and the lateral dimensions are  $13 \times 13$  mm. The cell is placed in a two-stage oven which achieves a temperature stabilization better than  $0.05^\circ\text{C}$ . Built-in permanent magnets provide a field of  $0.4$  T for alignment of the director in the sample.

The small intensity of the 002 reflection requires elimination of possible multiple scattering. Because the mosaicity of the samples can be of the same order of magnitude as the 001 Bragg angle, it is possible that X-rays are diffracted by two successive 001 scattering processes. The emerging X-rays then coincide either with the direct beam or with the 002-diffracted radiation. In principle, the effect of multiple scattering could be eliminated by measuring at various cell thicknesses and extrapolating to zero thickness. Practical considerations, such as the limited amount of material and the

large beam intensity needed for thin samples, led us to another approach, based on the rocking curves of the 001 and 002 peaks [4]. By analysing the shape of the 002 rocking curve with the mosaicity known from the 001 curve, multiple scattering from intrinsic 002 scattering can be separated.

### 3. Results and discussion

Each compound was investigated at three temperatures. In the  $(\theta, 2\theta)$  scans (sample rotation  $\omega = \theta$ , analyser arm rotation  $2\theta$ ), first and second order Bragg reflections were observed with widths close to the experimental resolution of  $0.003^\circ$  FWHM. The first order reflection occurred at a Bragg angle  $\theta_0$  of respectively  $1.53^\circ$  for compound *A* and  $2.00^\circ$  for *B*. Corresponding repeat distances are listed in table 2 and found to be close to the length of a stretched molecule as obtained from space-filling models ( $29.5 \text{ \AA}$  for *A*,  $22.1 \text{ \AA}$  for *B*). The rocking curves of the 001 reflections are shown in figure 1. Mosaicities are typically a few degrees (see also table 2). For compound *A*, the rocking curves of the 002 reflection are significantly different in shape from the 001 rocking curves, as can be seen in figure 2 (*a*). The difference is attributed to multiple scattering. Separate contributions of intrinsic 002 and multiple 001 scattering to the signal are also indicated in the figure, with their relative proportions determined by a least-square fit to the experimental data. The slight asymmetry present in the mosaicity (001 rocking curve) is strongly enhanced in the theoretical multiple scattering curve. Multiple scattering amounts to approximately half of the second order signal at high temperatures, and 17 per cent at  $35^\circ\text{C}$  because of the smaller mosaicity of the sample at this temperature. For compound *B*, multiple scattering resulted in only a minor contribution to the second order intensity (see figure 2 (*b*) and table 2). Rocking curves of the 002 Bragg peak were therefore only measured at the two lower temperatures.

Table 2. Layer thickness  $d$ , mosaicity  $M$  (FWHM of 001), intensity ratio  $I_{002}/I_{001}$  with and without correction for multiple scattering, and the order parameter ratio  $\tau_2/\tau_1$  for compounds *A* and *B* at different temperatures. The errors in  $\tau_2/\tau_1$  are due mainly to uncertainties in the calculated structure factors.

Compound	$T/^\circ\text{C}$	$d/\text{\AA}$	$M/\text{deg}$	$I_{002}/I_{001} \times 10^4$		$\tau_2/\tau_1$
				Measured	Corrected	
<i>A</i>	35	28.76	1.4	2.95	2.45	0.092
	45	28.76	2.2	2.62	1.50	0.072
	50	28.74	2.2	1.31	0.63	0.047
<i>B</i>	90	22.11	4.2	584	566	0.49
	110	22.10	4.5	372	361	0.39
	130	21.99	4.6	95	92	0.20

In the calculation of the structure factor  $S(q)$ , the molecules are assumed to be in their most stretched configuration, with bond angles and lengths taken from space-filling models. Taking the origin in the middle of a smectic layer, the imaginary part of  $S(q)$  cancels due to the random updown distribution of the molecules in the smectic A phase. The electrons are treated as point charges located on the atomic nuclei; electrons of hydrogen atoms are located on their neighbouring carbon atoms. These simplifications have very little influence on  $S(q)$  as long as  $2\pi/q$  is large compared to the interatomic distances. Careful evaluation of  $S(q)$  requires inclusion of the effect




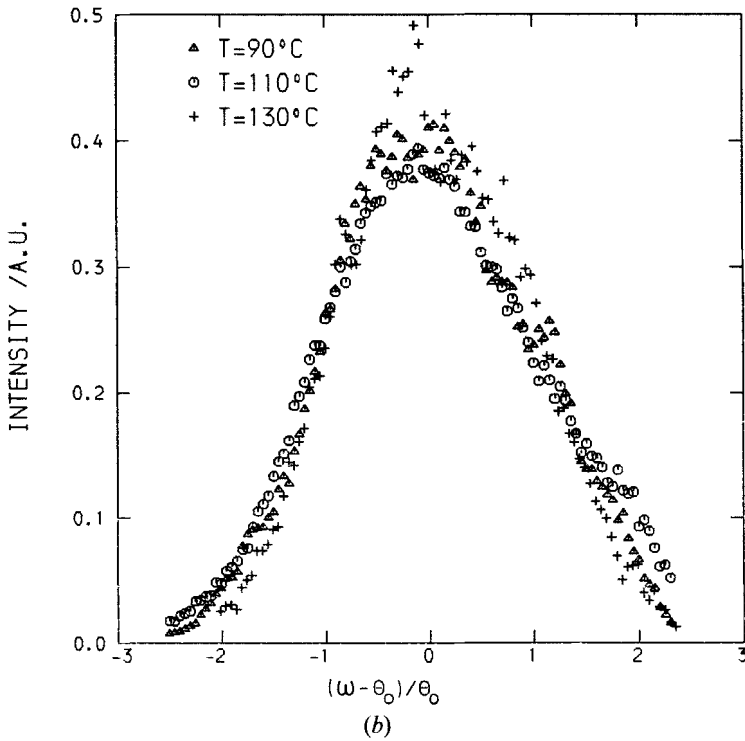


Figure 1. Rocking curve of the first order Bragg reflection at different temperatures; (a) compound A, (b) compound B.

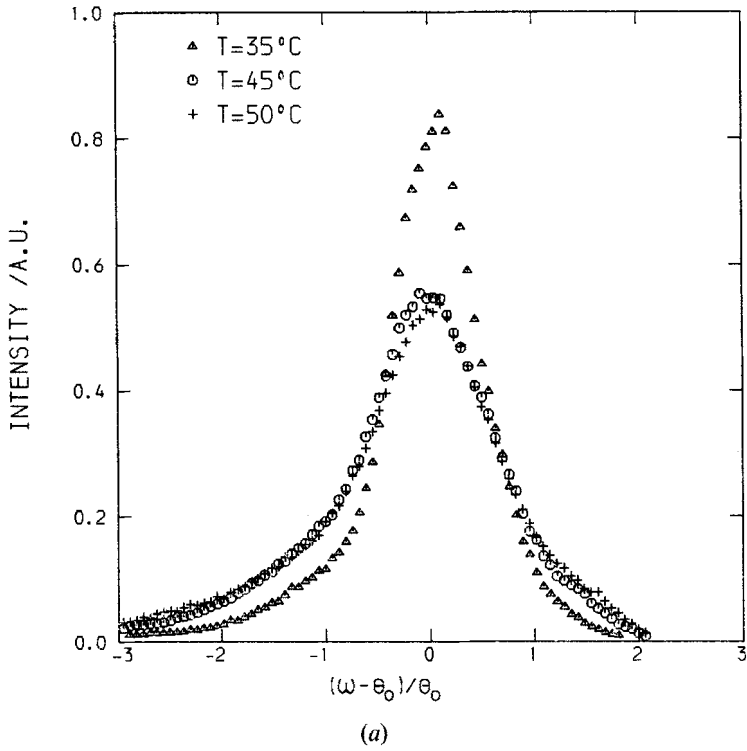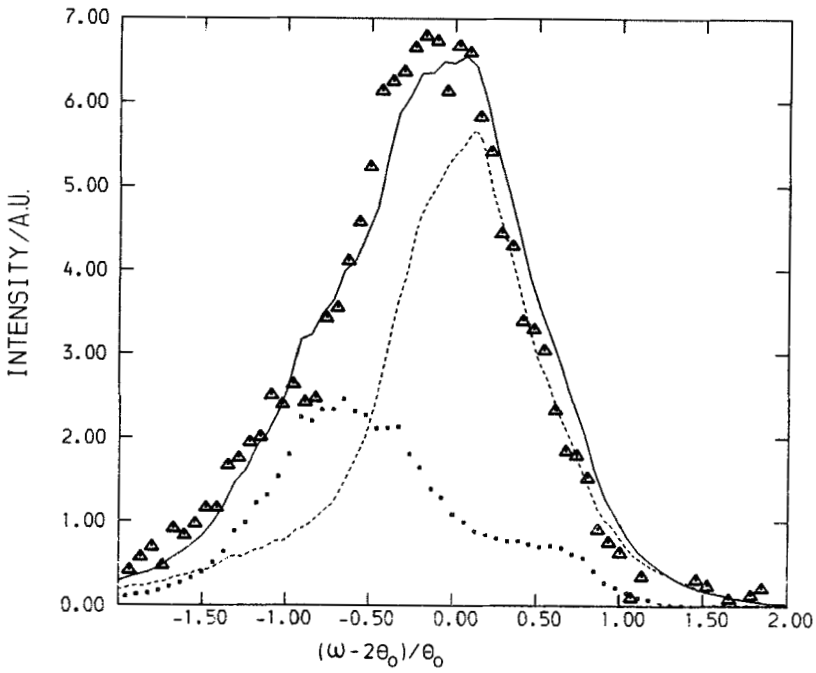

(a)

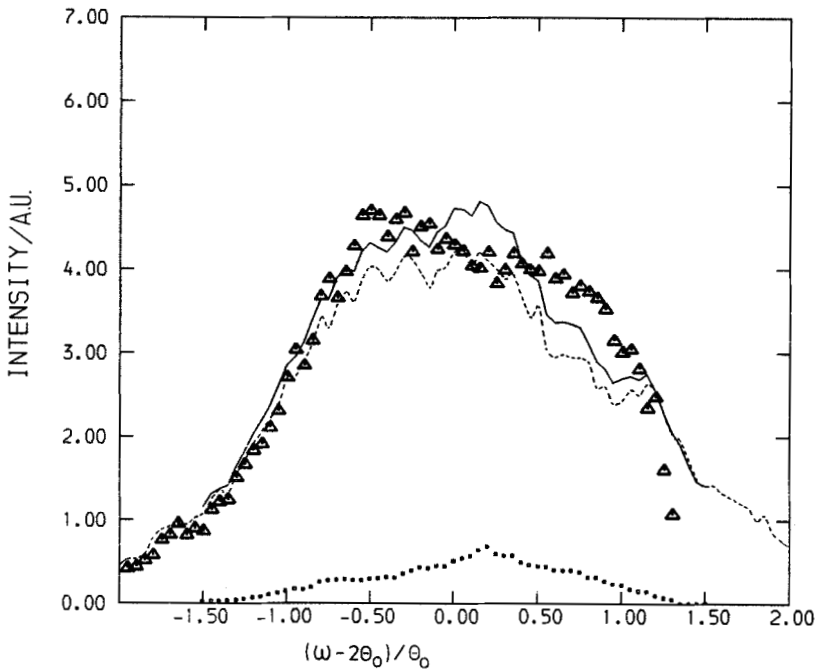

(b)

Figure 2. Rocking curves of the second order Bragg reflections; (a) compound *A* at 35°C, (b) compound *B* at 90°C. Solid lines: least-square fit made up of contributions from intrinsic 002 scattering (broken lines) and multiple 001 scattering (dotted lines).

of orientational disorder [9], since the orientational order parameter is known to be not yet saturated in the  $S_A$  phase. Approximating the orientational distribution function by a gaussian of the appropriate width to obtain an order parameter between 0.7 and 0.8 [2, 10], we find  $S(2q_0)/S(q_0) = -0.24 \pm 0.06$  for compound *A* and  $S(2q_0)/S(q_0) = -0.69 \pm 0.06$  for compound *B*. The resulting values of  $\tau_2/\tau_1$  are listed in table 2. Although part of the difference in the second order intensity between the two compounds is due to the structure factor, there is still almost an order of magnitude difference in the ratio of order parameters  $\tau_2/\tau_1$ .

From our observations it follows that the weak 002 reflection usually observed in smectic A phases is mainly due to multiple scattering. This is also true for compound *A* in this work, and similar cases have been reported [3, 4]. Though few data have been carefully analysed, compound *B* seems to be the first exception to this behaviour, with  $\tau_2/\tau_1$  an order of magnitude higher. This anomalous smectic order could also be at the origin of the absence of texture changes at the  $S_A S_B$  phase transition, which lead the original authors to the (now known to be incorrect) conclusion of two  $S_A$  phases [7]. It suggests that the  $S_A$  ordering in this case might be of an unusual kind, although it is still classical in the sense that there are no X-ray reflections or diffuse spots corresponding to  $d \approx 2l$  ( $l$  is the molecular length). In-plane correlations via the terminal  $-\text{CO}-\text{C}_2\text{H}_5$  moiety might play a role. Any mechanism, however, which leads to an anomaly in  $I_{002}/I_{001}$ , is likely to lead to anomalies in other properties as well. In this context, it is worth noting that the  $S_A$ -N phase transition in compound *B* is first order with a transition heat  $\sim 0.4$  kJ/mol [7], whereas most  $S_A$ -N transitions, including that of compound *A*, are second order. Powder photographs of the next higher homologue of *A*, which has a first order  $S_A$ -N transition [6], however, show the usual weak 002 reflection. Thus there seems to be no straightforward connection between the value of  $\tau_2/\tau_1$  and the order of the transition.

We conclude that in compound *B* the ratio of order parameters  $\tau_2/\tau_1$  has an exceptionally high value. It is clear that the usual concept of a sinusoidal distribution function to describe the smectic density wave [5] cannot be applied in such a case. This observation could well be relevant to many more smectics where this point has not been investigated experimentally.

The authors wish to thank Drs. J. Als-Nielsen, J. Bohr and K. Mortenson (Risø) for their help and hospitality. The excellent conditions provided by the Risø National Laboratory are gratefully acknowledged. This work forms part of the research program of the 'Stichting voor Fundamenteel Onderzoek der Materie' (Foundation for Fundamental Research on Matter, FOM) and was made possible by financial support from the 'Nederlandse Organisatie voor Wetenschappelijk Onderzoek' (Netherlands Organization for the Advancement of Research, NWO).

### References

- [1] ALS-NIELSEN, J., LITSTER, J. D., BIRGENAU, R. J., KAPLAN, M., and SAFINYA, C. R., 1980, *Ordering in Strongly Fluctuating Condensed Matter Systems*, edited by T. Riste (Plenum), p. 57.
- [2] LEADBETTER, A. J., 1979, *The Molecular Physics of Liquid Crystals*, edited by G. R. Luckhurst and G. W. Gray (Academic Press), Chap. 13.
- [3] OCKO, B. M., KORTAN, A. R., BIRGENAU, R. J., and GOODYBY, J. W., 1984, *J. Phys., Paris*, **45**, 113.
- [4] (a) STAMATOFF, J., CLADIS, P. E., GUILLON, D., CROSS, M. C., BILASH, T., and FINN, P., 1980, *Phys. Rev. Lett.*, **44**, 1509. (b) CLADIS, P. E., STAMATOFF, J., GUILLON, D., CROSS, M. C., BILASH, T., and FINN, P., 1980, *Advances in Liquid Crystal Research and Applications*, edited by Lajos Bata (Pergamon Press), p. 81.

- [5] McMILLAN, W. L., 1971, *Phys. Rev. A*, **4**, 133.
- [6] GRAMSBERGEN, E. F., and DE JEU, W. H., 1988, *J. chem. Soc. Faraday Trans. II*, **84**, 1015.
- [7] ARORA, S. L., TAYLOR, T. R., and FERGASON, J. L., 1970, *Liquid Crystals and Ordered Fluids*, edited by J. F. Johnson and R. S. Porter (Plenum), p. 321.
- [8] BUDAI, J., and PINDAK, R. (private communication).
- [9] PAPE, E. H., SCHRÖDER, K., and ZUGENMAIER, P., 1987, *Molec. Crystals liq. Crystals Lett.*, **4**, 165.
- [10] LEADBETTER, A. J., and WRIGHTON, P. G., 1979, *J. Phys., Paris, Colloque*, **40**, C-234.