

This article was downloaded by:

On: 26 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



## Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713926090>

### Response times and voltages for PDLC light shutters

Bao-Gang Wu<sup>ab</sup>; John H. Erdmann<sup>a</sup>; J. William Doane<sup>a</sup>

<sup>a</sup> Department of Physics, Liquid Crystal Institute and, Kent State University, Kent, Ohio, U.S.A. <sup>b</sup> Polytronix, Inc., Richardson, Texas, U.S.A.

**To cite this Article** Wu, Bao-Gang , Erdmann, John H. and Doane, J. William(1989) 'Response times and voltages for PDLC light shutters', *Liquid Crystals*, 5: 5, 1453 – 1465

**To link to this Article:** DOI: 10.1080/02678298908027783

**URL:** <http://dx.doi.org/10.1080/02678298908027783>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

## Response times and voltages for PDLC light shutters

by BAO-GANG WU†, JOHN H. ERDMANN and J. WILLIAM DOANE

Liquid Crystal Institute and Department of Physics, Kent State University, Kent, Ohio 44242, U.S.A.

The response times and operating voltages of light shutters formed from polymer dispersed liquid crystals (PDLCs) have been studied experimentally and the results compared with calculations based on non-spherically shaped nematic droplet models. The experiments were performed on light shutters with elongated and uniformly aligned droplets where the relaxation time and voltage response were measured. It is shown that the droplet shape can be a dominant factor, particularly for the relaxation time, and the data are compared with equations derived in terms of the aspect ratio of the droplet  $l = a/b$ , where  $a$  and  $b$  are the lengths of the semi-major and semi-minor axes, respectively, of the elongated droplet. It is further demonstrated that the electric field inside the droplet can be considerably smaller than the applied field, due to the conductivity and dielectric properties of the polymer and liquid crystal materials. These data are used to obtain values for the ratio of the conductivities of the polymer binder and liquid crystal droplet, as well as the anisotropy of the conductivity in the liquid crystal.

### 1. Introduction

Polymer dispersed liquid crystals (PDLCs) are a new type of light shutter which have been explored in recent years [1-4] and are beginning to find applications in switchable windows, displays, colour projectors and other devices [5]. These materials consist of submicrometre size nematic droplets dispersed in a polymer matrix, and their optical response is based on the electrically controlled light scattering properties of the droplets. An applied electric field aligns the nematic droplets to yield a transparent or non-scattering state. Surface interactions at the droplet wall and the droplet shape return the droplets to their original orientation in the absence of the field to yield a scattering or opaque state. A competition between the applied field and the elastic and viscous torques of the liquid crystal govern the response times and switching voltages of the light shutters.

A typical light shutter prepared with droplets about  $1.0 \mu\text{m}$  in diameter requires a switching field of approximately  $1.0 \text{ V} \mu\text{m}^{-1}$  and has a response of about 100 ms upon removal of the voltage. There can, however, be large departures from this. For example, a film prepared from epoxy polymers can sometimes have a response time of near 1.0 s. Stretching the film or applying a shear stress to the glass substrates elongates the droplets and shortens the response time to  $< 1.0 \text{ ms}$  without a substantial increase in the voltage threshold required to switch the film. Reducing the size of the droplets can have the same effect. The type of polymer binder can also affect the voltage response. For example, a light shutter prepared from poly(methyl methacrylate) (PMMA) can have a switching voltage of 200 V, whereas an identical shutter with identical droplet sizes and shapes prepared from an epoxy polymers can have a switching voltage of 20 V.

† Present address: Polytronix, Inc., P.O. Box 833024, Richardson, Texas 75083, U.S.A.

Here we report an experimental and theoretical study to explain and quantify some of these features in PDLC light shutters. In this study particular emphasis is placed upon the effects of droplet shape on the shutter response. In droplets with a particular type of nematic director configuration, namely the bipolar configuration [5], droplet shape can be a significant factor. Experiments have been designed in which the droplets are elongated and aligned by shearing the glass substrates of the shutter. The optical response characteristics were then measured using laser light, and were compared with model calculations. Models of two different droplet shapes with small and with large radii of curvature are compared with measurement of the response time with reasonable success, and the results are instructive. The voltage response is more difficult to model as it is found that the conductivity and dielectric properties of the polymer and liquid crystal play a strong role. Again, some preliminary models are presented with reasonable fits to experiment. These studies indicate that the ratio of conductivities of the polymer and liquid crystal is significant in the switching voltage.

We believe this work to be only the beginning in understanding the electro-optic response of PDLC films. Significant future experimentation and theory are required to understand this subject.

## 2. Model calculations

Under static conditions the director configuration inside a droplet is, in part, understood under conditions where the droplet is large ( $> 1.0 \mu\text{m}$  in diameter) and strong anchoring conditions apply. For spherical droplets, computer simulations have been found to predict reasonably well those configurations observed by optical microscopy [6–9]. Recently we have obtained computer simulations of director configurations which result under the conditions of an applied field and also for droplets which have the shape of an ellipsoid of revolution [10]. Figure 1 shows such a computer simulation of the bipolar configuration, which is one case that results from tangential wall alignment and the most common configuration that we have observed in PDLC materials. Because of the tangential anchoring at the polymer surface,

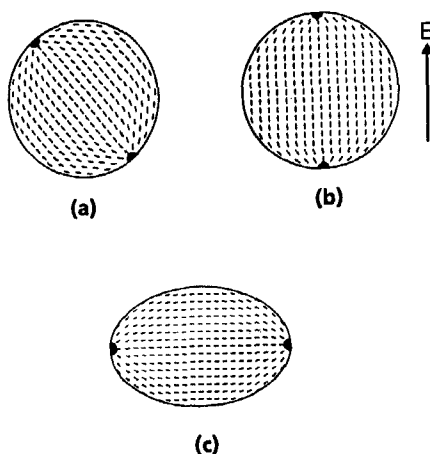


Figure 1. The bipolar configuration obtained from tangential anchoring (a) in the absence of a field, (b) in the presence of a strong electric field, and (c) in an elongated cavity. Three dimensional patterns can be obtained by rotation of these figures about the symmetry axis.

application of an electric field aligns the bipolar axis but appears to have minimal effect on the bipolar configuration of the droplet, as illustrated by the computer simulation in figure 1(b). For a perfectly spherical polymer cavity, little elastic distortion is required to align a bipolar droplet by an electric field to preserve the tangential anchoring at the cavity wall. In fact, the question arises of how a spherical bipolar droplet would reorient to its original orientation upon removal of an applied field. A possible answer is that in practice the droplets in PDLC materials are never perfectly spherical. The polymer binder is often a soft material and the droplet cavities easily become elongated or flattened during the fabrication of the shutter or during the phase separation process. Differences between the thermal expansivities of the polymer and glass or plastic cell substrate can also shape the droplets.

It is possible to model and calculate the effect of droplet shape on the response time of a PDLC light shutter with bipolar configured droplets. This is done by recognizing that the deformation free energy density inside the droplet is governed by the radius of curvature of the cavity. In a droplet which is slightly elongated in shape the bipolar axis will prefer to orient along the long axis of the cavity (see figure 1(c)) where both splay and bend deformations are minimized. At the equator of the elongated bipolar droplet, near the wall, the elastic deformation is pure bend and the free energy density is  $K_{33}/2R^2$ , where  $K_{33}$  is the bend constant and  $R$  is the radius of curvature at the equator.

We generalize this concept to model the free energy density,  $F_d$ , of a nematic droplet in an elongated cavity, by using the expression  $F_d = (K/2)q^2$ , where  $q$  is the radius of curvature at the cavity wall indicated by the position vector,  $\mathbf{r}$ , in figure 2(a) and  $K$  is an effective deformation constant. Ignoring the details of the director configuration, we assign a droplet director,  $\mathbf{n}$ , shown in figure 2(a), which can reorient in the elongated cavity. In analogy to the bipolar droplet, the droplet director has its preferred orientation in the direction of the long axis of the cavity in the absence of a field. This simplified model assumes that we can approximate the dynamics of a droplet as one in which the droplet director reorients upon the onset or removal of a field with little variation in the effective value of  $K$ . The elastic restoring torque,  $\Gamma_d$ , per unit volume is given as

$$\Gamma_d = dF_d/d\lambda, \tag{1}$$

where the functional form of  $\Gamma_d$  depends upon the shape of the droplet and  $\lambda$ , the angle between the applied electric field,  $\mathbf{E}$ , and the droplet director,  $\mathbf{n}$ , as shown in figure 2(a). Later we apply equation (1) to two specific droplet shapes, which exhibit a small and large radii of curvature.

The electrostatic free energy density inside the droplet due to an applied field is given by

$$F_e = -\frac{\epsilon_{\perp} E^2}{2} - \frac{\Delta\epsilon (\mathbf{n} \cdot \mathbf{E})^2}{2}, \tag{2}$$

where  $\Delta\epsilon = \epsilon_{\parallel} - \epsilon_{\perp}$  is the anisotropy in the dielectric constant. Application of the electric field serves to rotate  $\mathbf{n}$  to its equilibrium orientation  $\mathbf{N}$ . The orientation of  $\mathbf{N}$  approaches the direction of  $\mathbf{E}$  as the field strength is increased, provided  $\Delta\epsilon$  is positive. Assuming a uniform field in the droplet, the electric torque on the droplet director,  $\Gamma_e$ , per unit volume is given by

$$\Gamma_e = \frac{dF_e}{d\lambda} = \frac{\Delta\epsilon}{2} (E)^2 \sin 2\lambda. \tag{3}$$

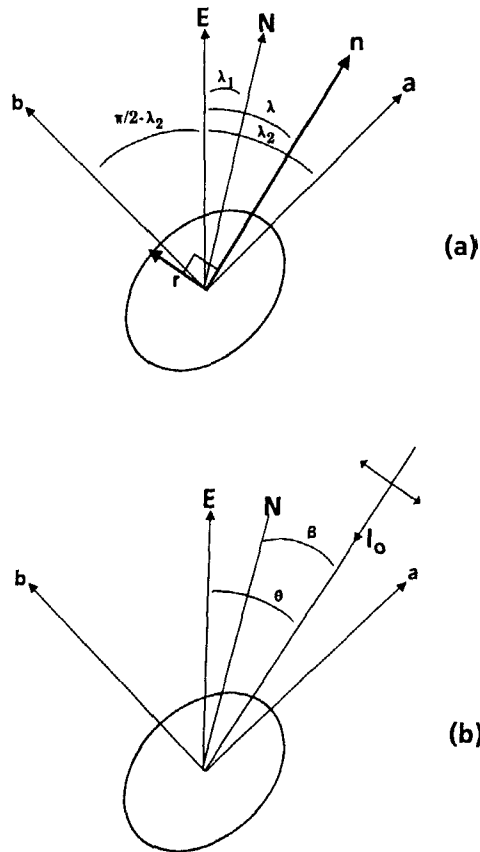


Figure 2. (a) Illustration of the droplet director,  $\mathbf{n}$ , arbitrarily oriented in an elongated cavity where  $\mathbf{r}$  is the position vector (perpendicular to the director) indicating the point on the wall where the radius of curvature is of interest. The vector  $\mathbf{N}$  is the equilibrium orientation of the director in an electric field,  $\mathbf{E}$ , of arbitrary strength. Directions  $\mathbf{a}$  and  $\mathbf{b}$  are the orientation of the major and minor axes of the elongated droplet. (b) Illustration of an incident polarized light of intensity,  $I_0$ , at an angle  $\beta$  from the ON state droplet director,  $\mathbf{N}$ , and angle  $\theta$  from the direction of the electric field  $\mathbf{E}$ .

A difficult problem is to relate the field inside the droplet to the applied field  $V/d_0$ , where  $V$  is the voltage applied to the transparent conducting electrodes of a light shutter with a PDLC film thickness of  $d_0$ . An exact calculation is beyond the scope of this paper, but simple and crude approximations are possible. To account for the effects of the boundary between the polymer and the nematic droplet, we assume an isolated spherical droplet in a polymer which is in a uniform electric field. Application of electrostatic boundary conditions in a one droplet approximation yields the field,  $E_2$ , inside the droplet as [11]

$$\begin{aligned}
 E_2 &= E_1 \frac{3\epsilon_1}{2\epsilon_1 + \epsilon_2} \\
 &\underset{(\omega \rightarrow 0)}{=} 3E_1 \left( \frac{\sigma_2}{\sigma_1} + 2 \right)^{-1},
 \end{aligned} \tag{4}$$

where  $E_1$  is the field in the polymer and  $\epsilon_1$  and  $\epsilon_2$  the dielectric constants of the polymer and liquid crystal, respectively. We take  $\epsilon_i$  to be complex where  $\epsilon_i = \epsilon'_i + j\sigma_i/\omega$  and  $\sigma_i$  is the conductivity,  $\omega$  is the angular frequency and  $\epsilon'_i$  is the real part of the susceptibility. In the zero frequency (D.C.) limit, the ratio of the conductivities can govern the magnitude of the field inside the droplet. The value of  $\sigma_2$  is known to be anisotropic [12]. We account for this anisotropy by

$$\sigma_2 = \sigma_{\parallel}\sigma_{\perp}(\sigma_{\parallel}\sin^2\lambda + \sigma_{\perp}\cos^2\lambda)^{-1}, \quad (5)$$

where  $\sigma_{\parallel}$  and  $\sigma_{\perp}$  are the conductivities parallel and perpendicular, respectively, to the droplet director. Equation (5) assumes uniform director orientation within the droplet. In our experiments D.C. pulses were applied and so we are interested in the field within the droplet after the D.C. voltage has been applied for a sufficient length of time for the droplet director to achieve its equilibrium orientation,  $\mathbf{N}$ , at an angle  $\lambda_1$  as defined in figure 2(a).

A viscous torque,  $\Gamma_v$ , opposes reorientation of the droplet director. In the absence of flow in a nematic material, this torque can be expressed by

$$\Gamma_v = \gamma_1 \frac{d\lambda}{dt}, \quad (6)$$

where  $\gamma_1$  is the rotational viscosity coefficient.

We now consider elongated droplets of two different shapes.

### 2.1. Model A (small radius of curvature)

In this model we consider an elongated droplet where the radius of curvature at the droplet edge is

$$\rho = a [\cos^2(\lambda_2 - \lambda) + l^2 \sin^2(\lambda_2 - \lambda)]^{-1/2}, \quad (7)$$

where  $a$  and  $b$  are the lengths of the semi-major and semi-minor axes, respectively,  $l = a/b$  is the aspect ratio of the droplet, and  $\lambda_2$  is the orientation of the long axis of the droplet and is defined in figure 2(a). Applying equation (1), the elastic torque,  $\Gamma_d$ , per unit volume becomes

$$\Gamma_d = \frac{dF_d}{d\lambda} = -\frac{K(l^2 - 1)}{2a^2} \sin 2(\lambda_2 - \lambda). \quad (8)$$

#### 2.1.1. Field response

We balance the elastic and field torques to determine the equilibrium orientation  $\mathbf{N}$  is the presence of a voltage applied to a shaped droplet. Setting  $\Gamma_e + \Gamma_d = 0$ ,

$$\lambda_1 = \frac{1}{2} \arctan\left(\frac{\sin 2\lambda_2}{A + \cos 2\lambda_2}\right), \quad (9)$$

where  $A = \Delta\epsilon \alpha^2 E^2 / K(l^2 - 1)$ . An interesting condition results at  $\lambda_2 = \pi/2$ , where there is a critical voltage

$$V_c = \frac{d_0}{3a} \left(\frac{\sigma_2}{\sigma_1} + 2\right) \left(\frac{K(l^2 - 1)}{\Delta\epsilon}\right)^{1/2}. \quad (10)$$

This can be regarded as the shape contribution to the switching voltage of a normal PDLC shutter. This may, in fact, be the dominant contribution for a PDLC shutter

as illustrated by applying equation (10) to a shutter prepared from epoxy materials wherein the normal process of fabricating the cell droplets may become slightly deformed, say  $l = 1.1$ . A shutter made from epoxy materials commonly has a switching voltage of  $V_c \approx 30$  V for  $d_0 = 25 \mu\text{m}$  and  $a = 1.0 \mu\text{m}$ , where cyanobiphenyl liquid crystals are used with  $\Delta\epsilon = 14\epsilon_0$  and  $K \approx 1 \times 10^{-11}$  N. Application of equation (10) yields  $\sigma_2/\sigma_1 \approx 25$ , which is not unreasonable in view of the fact that Chidichimo *et al.* [13] have reported experimental evidence for dramatic reductions in the switching voltage as the conductivity of the polymer,  $\sigma_1$ , is increased. We have therefore ignored contributions other than the shape, such as changes in the director configuration or other factors toward estimating the voltage response of the shutter.

### 2.1.2. Relaxation time

When the electric field is removed, the orientation of the droplet director returns from an angle of  $\lambda_1$  to  $\lambda_2$ . To calculate the relaxation time we balance the elastic and viscous torques ( $\Gamma_d + \Gamma_v = 0$ ), ignoring the inertial term, to obtain

$$\lambda = \lambda_2 - \arctan \left\{ \tan(\lambda_2 - \lambda_1) \exp \left[ - \left( \frac{K(l^2 - 1)t}{\gamma_1 a^2} \right) \right] \right\}. \quad (11)$$

The time constant for the relaxation time is therefore

$$\tau_{\text{off}} = \frac{\gamma_1 a^2}{K(l^2 - 1)}. \quad (12)$$

The effect of shaping on the relaxation time is seen to be appreciable, as estimated by taking  $\gamma_1 = 4 \times 10^{-2} \text{ kg m}^{-1} \text{ s}^{-1}$  and the previous values for the other parameters. A slightly shaped droplet of  $l = 1.1$  yields  $\tau_{\text{off}} \approx 20$  ms. This is comparable with that observed in weakly stretched films. The small value of  $l$  illustrates the large effect droplet shape can have on the relaxation time. It is noted that equation (12) accounts only for the droplet shape. In the case of a spherical droplet,  $l = 1$ , the relaxation time is undefined since surface interactions and configuration changes were ignored.

### 2.1.3. Response time

The response time upon application of the electric field is calculated by balancing all of the torques;  $\Gamma_e + \Gamma_d + \Gamma_v = 0$  which yields

$$\lambda = \arctan \left[ \frac{1}{\tan \lambda_1} \left( \frac{1 + \tan^2 \lambda_1}{1 - m \exp(-t/\tau_{\text{on}})} - 1 \right) \right], \quad (13)$$

with  $\lambda_1$  given by equation (9),

$$m = \frac{\tan \lambda_1 \tan \lambda_2 - \tan^2 \lambda_1}{\tan \lambda_1 \tan \lambda_2 + 1} \quad (14)$$

and

$$\tau_{\text{on}}^{-1} = \frac{1}{\gamma_1} \left( \Delta\epsilon E^2 + \frac{K(l^2 - 1)}{a^2} \frac{1 - \tan^2 \lambda_2}{1 + \tan^2 \lambda_2} \right) \left( \frac{1 + \tan^2 \lambda_1}{1 - \tan^2 \lambda_1} \right). \quad (15)$$

For  $\lambda_2 \approx \pi/2$  and  $\lambda_1 \approx 0$

$$\tau_{\text{on}}^{-1} = \left[ \frac{1}{\gamma_1} \left( \Delta\epsilon E^2 + \frac{K(l^2 - 1)}{a^2} \right) \right] \quad (16)$$

and for large voltages  $\tau_{\text{on}} = \gamma_1/\Delta\epsilon E^2$ .

2.2. Model B (large radius of curvature)

In order to investigate further the effect of droplet shape, we have selected another model, an ellipse, which provides a larger radius of curvature following

$$\varrho = \frac{a}{l^2} \left( \frac{l^4 + \tan^2(\lambda_2 - \lambda)}{l^2 + \tan^2(\lambda_2 - \lambda)} \right)^{3/2} \tag{17}$$

The aspect ratio of the ellipse is made by a cross-sectional cut in the plane of the largest and smallest axes of the spheroid. The restoring torque,  $\Gamma_d$ , is

$$\begin{aligned} \Gamma_d &= \frac{dF_d}{d\lambda} \\ &= - \frac{3Kl^6(l^2 - 1) \tan(\lambda_2 - \lambda)[l^2 + \tan^2(\lambda_2 - \lambda)]^2}{a^2 \cos^2(\lambda_2 - \lambda)[l^4 + \tan^2(\lambda_2 - \lambda)]^4} \end{aligned} \tag{18}$$

Note that for  $l = 1$ , a spherical droplet, there is no restoring torque and  $a = r_{\text{droplet}}$ . Also, for  $\lambda_2 = \lambda$  the elastic deformation energy is minimized.

2.2.1. Voltage response

Upon application of an electric field,  $\mathbf{n}$  moves away from the OFF state position. For small fields  $\lambda_1 = \lambda_2$  and for very large fields  $\lambda_1 \rightarrow 0$ . After equilibrium is established in the ON state ( $\lambda = \lambda_1$ ), there is a static balance between the electric and the elastic deformation torques with the resulting expression

$$\begin{aligned} V &= \frac{d_0 l^3 [(\sigma_{\parallel}/\sigma_1) + 2]}{a \cos(\lambda_2 - \lambda_1)} \frac{l^2 + \tan^2(\lambda_2 - \lambda_1)}{[l^4 + \tan^2(\lambda_2 - \lambda_1)]^2} \left[ \frac{3\epsilon_0 \sin 2\lambda_1}{2K(l^2 - 1) \tan(\lambda_2 - \lambda_1)} \right. \\ &\quad \left. \times \left( \Delta\epsilon - \frac{2(\epsilon_{\perp} + \Delta\epsilon \cos^2 \lambda_1)(\sigma_{\parallel}/\sigma_1)[(\sigma_{\parallel}/\sigma_{\perp}) - 1]}{[(\sigma_{\parallel}/\sigma_1) + 2][(\sigma_{\parallel}/\sigma_{\perp}) \sin^2 \lambda_1 + \cos^2 \lambda_1]} \right) \right]^{-1/2}, \end{aligned} \tag{19}$$

where  $\sigma_1$  is the conductivity of the polymer binder.

2.2.2. Relaxation time

In this case a balance of the viscous and electric torques results in the expression

$$\begin{aligned} t &= \tau \left\{ \ln x + \frac{l^2}{2} \frac{u}{u+1} \frac{1}{ux^2+1} + \left( \frac{l^{12}}{2} - \frac{v^4}{2u^2} + \frac{v^4}{u^3} - \frac{2v^3}{u^3} - \frac{1}{2} \right) \ln(ux^2 + 1) \right. \\ &\quad \left. - \frac{v^4}{2u^2} x^2 + l^{12} [\ln(1 - x^2)^{1/2}] \right\} \Bigg|_{x=\cos(\lambda_2-\lambda_1)}^{x=\cos(\lambda_2-\lambda)}, \end{aligned} \tag{20}$$

where

$$\tau = \frac{\gamma_1 a^2}{3Kl^6(l^2 - 1)}, \tag{21}$$

$u = l^2 - 1$  and  $v = l^4 - 1$ . Unlike model A, this model does not yield a simple expression for the relaxation time.

3. Experiment and results

3.1. Sample preparation and apparatus

The PDLC samples used in this experiment were prepared by phase separation methods using PMMA mixed with the nematic material E7 (EM Chemicals) in a ratio



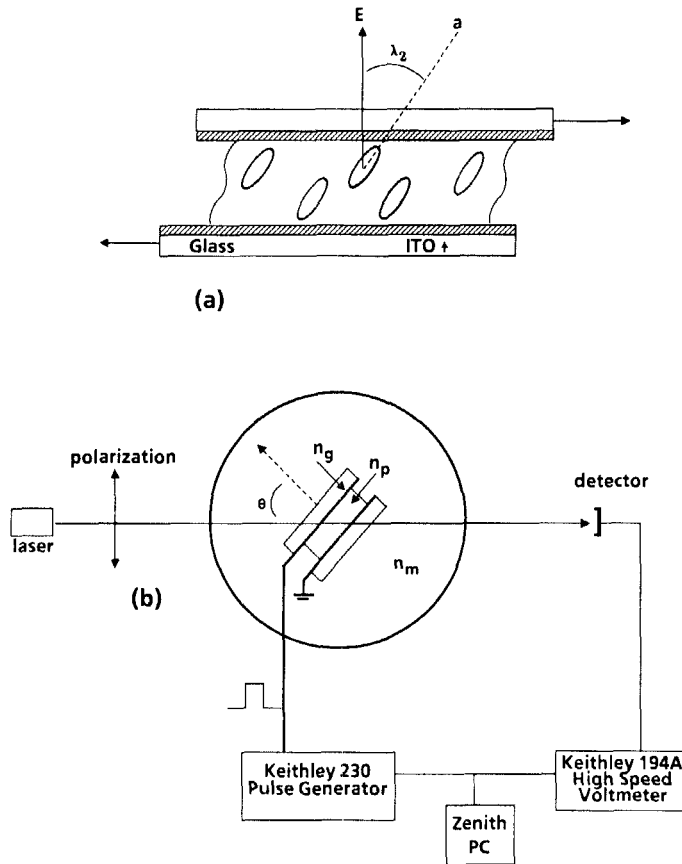


Figure 3. Illustration of (a) PDLC sample with aligned and shaped droplets obtained by shearing and (b) experimental configuration where the collection angle of the detector is  $\leq 2^\circ$ . The refractive index of the glass substrate,  $n_g$ , is approximately matched to that of the fluid in the cylindrical vial,  $n_m$ . ITO, indium-tin oxide.

of 1 : 2 by weight. Acetone was used as a solvent to form a homogeneous mixture and the sample was prepared on a hot plate. A relatively long cooling time was needed to obtain droplets about  $1.0 \mu\text{m}$  in size. The index match resulting from these materials is quite good. Samples of elongated droplets were first prepared between glass substrates with  $17.5 \mu\text{m}$  spacers and with transparent conductive coatings, then warmed to temperatures near the melting point of the polymer and the substrates slightly sheared as illustrated in figure 3 (a). It was often observed that there were regions of the sample where droplet alignment was more uniform than in others, but uniformly aligned samples were possible.

Polarized laser light is incident on the sample at an angle  $\theta$  defined in figures 3 (b) and 2 (b). A D.C. voltage pulse 2 ms in duration was applied to the indium-tin oxide electrode of the sample and the transmitted light collected in a small collection cone angle of  $< 2^\circ$ . The sample was placed in a cylindrical container with a fluid index matched to the glass to avoid Fresnel corrections. Since the refractive index of the polymer,  $n_p$ , is a close match to the index,  $n_l$ , of the liquid crystal, the angle of maximum transmission allowed us to monitor the orientation of  $\mathbf{n}$ ,  $\mathbf{N}$  and  $\mathbf{a}$  [14] (see figure 2). Since the collection angle of the detector is small, the measured transmitted

light intensity  $I$  is related to the total scattering cross-section of the nematic droplets,  $\sigma$ , by the expression  $I_0 \exp(-\sigma \alpha d)$ , where  $\alpha$  is the number density of the scatterers,  $d$  is the distance the light traverses the sample,  $d_0/\cos \theta$ , and  $I_0$  is the incident intensity [15, 16].

Figure 4 shows the relative transmitted light intensity as a function of the angle of incidence,  $\theta$ , in the presence and absence of a large saturating voltage applied to the cell. The peak at  $66^\circ$  establishes the orientation of  $\mathbf{a}$  in the sample and the angle  $\lambda_2$ . A single peak in the transmitted intensity at  $66^\circ$  indicates that the refractive index of the polymer,  $n_p$ , is closely matched to  $n_\perp$  of the nematic droplet [14]. The breadth of the peak at  $\theta = 66^\circ$  reflects the distribution in the droplet directors in their equilibrium orientation in the absence of the field. In the presence of the aligning field, the broader peak is due to a broader distribution of droplet directors caused by a non-uniformity in droplet shapes and sizes. The peak at  $29^\circ$  gives the direction of  $\mathbf{N}$  and the angle  $\lambda_1$ . Small variations in  $l$  and  $a$  distribute the value of  $\lambda_1$  and hence broaden the peak.

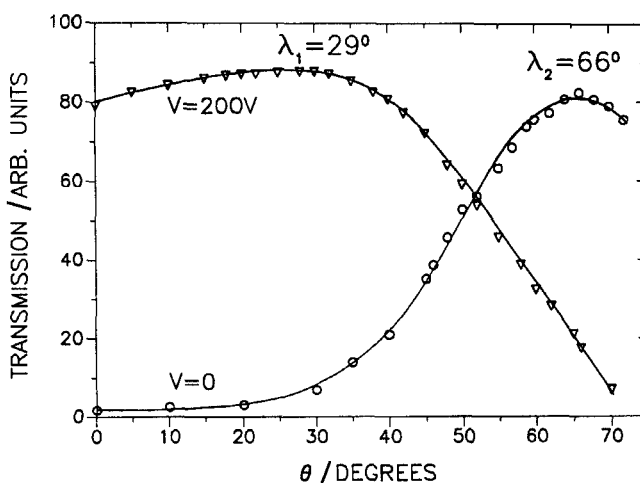


Figure 4. Plot of the relative transmitted intensity versus the angle of incidence for a sheared sample of PMMA-E7 (1:2) with no voltage and with a saturating voltage of 200 V applied to the sample cell.

### 3.2. Relaxation of the droplet director

Figure 5 shows typical traces of light transmission resulting from a D.C. pulse 2.0 ms in duration. Representative transmission responses are shown for selected angles,  $\theta$ , of incident polarized light. The peak in the transmitted intensity following the leading edge of the applied D.C. pulse results when the orientation of the droplet director is parallel to incident beam (index matched orientation) as the nematic droplets respond to the applied field. Following the removal of the D.C. voltage, the transmitted intensity again passes through a maximum as the droplet director relaxes to its equilibrium orientation. The time associated with this second maxima allows us to determine the orientation of  $\mathbf{n}$ , given by the angle  $\lambda$ , as a function of time.

The droplet director angle  $\lambda(t)$  is plotted in figure 6 for the relaxing PMMA-E7 sample following the removal of the D.C. pulse. The full curve in the plot is calculated from equation (20) for the ellipsoidally shaped droplet (model B) using parameters

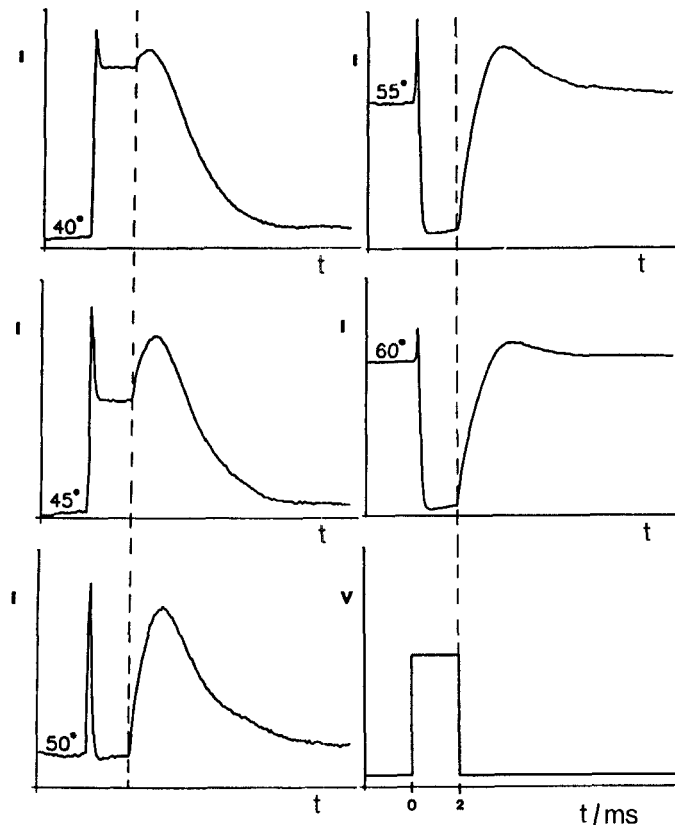


Figure 5. Recordings of the relative transmitted polarized light intensity through a PMMA-E7 sample cell during and following an applied 200 V D.C. 2 ms pulse at selected angles of incidence,  $\theta$ .

listed in the caption of figure 6. For comparison, the broken curve is the best fit to equation (11) of model A. In each case the fitting parameter is the value of  $l$  which is  $l = 1.19$  for model A and  $l = 1.625$  for model B. It is seen that the ellipsoidally shaped droplet gives a slightly better fit. It appears that there is a large discrepancy in values for the aspect ratio of the droplets between models A and B; however, this can be reconciled by considering the dependence of the radius of curvature of the two models on the aspect ratio. A close inspection of equations (7) and (17) reveals that the shape of model A can be approximated as an ellipse with an aspect ratio of  $l^2$ , in which case  $(1.19)^2 = 1.42$  is closer to the value obtained for  $l$  of model B. A comparison of the two models is illustrated in figure 6.

### 3.3. Voltage response

In figure 7 we have plotted the measured values of  $\lambda_1$  versus the applied voltage for the PMMA-E7 sample. The solid curve is the best fit from model B, where we have used the value of  $l$  from the relaxation time measurement. In this case the fit is sensitive to the electronic properties of the polymer and the liquid crystal; the fitting parameters are ratios of the conductivities  $\sigma_{\parallel}/\sigma_{\perp}$  and  $\sigma_{\parallel}/\sigma_1$ . The full curve shows the best fit to equation (19) of model B, with  $\sigma_{\parallel}/\sigma_1 = 21.0 \pm 0.5$  and

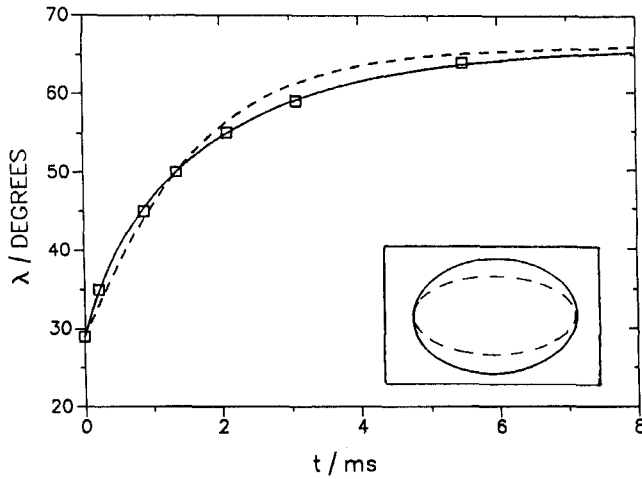


Figure 6. Relaxation of the droplet director,  $\mathbf{n}$ , in terms of the angle  $\lambda$  versus time for the sample of PMMA with E7. The full curve is a fit to equation (20) model B using the parameters  $\lambda_1 = 29^\circ$ ,  $\lambda_2 = 66^\circ$ ,  $a = 0.5 \mu\text{m}$ , and  $\gamma_1 = 4 \times 10^{-2} \text{kg m}^{-1} \text{s}^{-1}$ . The broken curve is a fit to equation (11) of model A with the same values for  $\lambda_1$ ,  $\lambda_2$ ,  $\gamma_1$  and  $a$ . The fitting parameter in both cases is the aspect ratio  $l$ . Model A is best fit with  $l = 1.19$  and for model B  $l = 1.625$ . The fits indicate that not only the aspect ratio but also the shape of the elongated droplet is significant. The inset shows an ellipse with an aspect ratio of  $l$  for the full curve. This is the figure that would result from the radius of curvature described in equation (17) for model B. The broken-curve is an ellipse with an aspect of  $l^2$ . This is approximately what would result for the shape of model A with the same length for the major axis of model B.

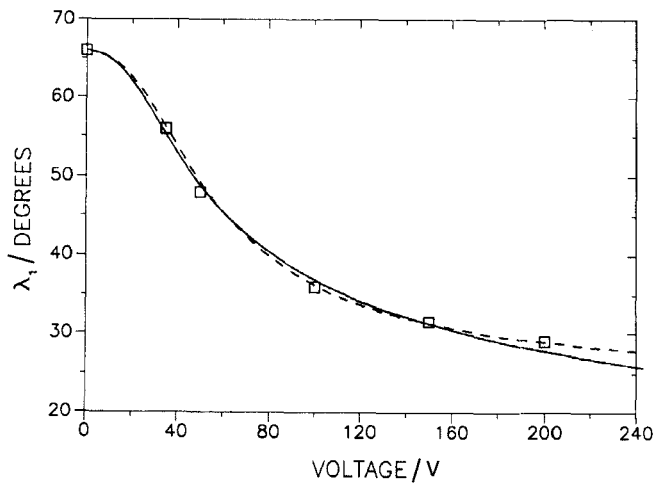


Figure 7. Measured values of  $\lambda_1$  versus applied voltage for the PMMA-E7 sample. The full curve represents the best fit of equation (19) of model B and the broken curve is the best fit with the same electric field correction as equation (19) but with the smaller radius of curvature from model A. The full curve was fitted with the values  $\sigma_{\parallel}/\sigma_{\perp} = 1.420$  and  $\sigma_{\parallel}/\sigma_1 = 21.0$ . The broken curve was fitted with  $\sigma_{\parallel}/\sigma_{\perp} = 1.510$  and  $\sigma_{\parallel}/\sigma_1 = 18.0$ . The aspect ratios used are those from figure 6 and other parameters include:  $d_0 = 17.5 \mu\text{m}$ ,  $a = 0.5 \mu\text{m}$ ,  $\Delta\epsilon = 13.8\epsilon_0$ ,  $\epsilon_{\parallel} = 19.0\epsilon_0$ ,  $K = 1.71 \times 10^{-11} \text{N}$  and  $\lambda_2 = 66^\circ$ .

$\sigma_{\parallel}/\sigma_{\perp} = 1.420 \pm 0.005$ . The broken curve is the best fit using the radius of curvature described in model A, equation (7) where the best fit parameters are  $\sigma_{\parallel}/\sigma_1 = 18.0 \pm 0.5$  and  $\sigma_{\parallel}/\sigma_{\perp} = 1.510 \pm 0.005$ .

#### 4. Discussion and conclusions

Experiments have been presented to study the effect of droplet shape on the relaxation time and voltage response of a PDLC light shutter. Models, although admittedly crude, have been presented to quantify the effects of droplet shape on these response characteristics and explain the experimental results. In the case of the relaxation time, the results indicate that the droplet shape can be a dominant feature. Aspect ratios no larger than  $l = 1.1$  have a significant influence on the relaxation time. This would suggest that droplet shaping, which naturally results from the preparation of PDLC films (without intentional shearing), could be a principal mechanism for relaxation in some, or possibly most, displays, and that the simple equations of model A, (see equations (10), (12) and (16)) may give reasonable estimates for the response of PDLC shutters. In the comparison of the two different droplet shapes, the elliptically shaped droplet model B gave the best fit to the data. This appears to be in agreement with our photographs from scanning electron microscopy of sheared samples (not shown here) which appear to be of an elliptical shape and have aspect ratios of about 1.5–2.0.

The voltage response has been found to be more difficult to understand in that the electric field inside the droplet is substantially reduced from the field  $V/d_0$  applied to the shutter. In the model presented here this reduction is explained in terms of the conductivity ratio between the polymer and liquid crystal,  $\sigma_{\parallel}/\sigma_1$ , which had values of approximately 20 for the system studied. This value appears to be small but may be reasonable since the polymer is heavily plasticized with dissolved liquid crystal material and is very soft. The conductivity ratio may, therefore, not be too small. Published result in other thermoplastics have determined that as much as 50 per cent of the liquid crystal remains dissolved while the remainder is phase separated into droplets [14].

We have found that the anisotropy in the conductivity of the liquid crystal was essential to fit Figure 7. The measured ratio of  $\sigma_{\parallel}/\sigma_{\perp} = 1.4$  is in reasonable agreement with that reported in the literature [12].

The model of an isolated spherical droplet used to calculate the internal electric field may be too simplified. It could be that an elongated droplet is also required in this model calculation. The effect of an elongated droplet tilted with respect to the field would be to change not only the magnitude of the internal field but also its direction. Such calculations are in progress. More experiments on different values of  $l$  are intended and it is clear that more-refined theoretical models are necessary. In general, the applied voltage needed to turn the shutter on is proportional to the factor  $(\sigma_2/\sigma_1 + 2)$ , whereas the turn-on time will be proportional to the square of this factor. Future experiments to obtain independent measurements of  $\sigma_{\parallel}/\sigma_1$  and  $\sigma_2(\lambda)$  are under way, as are electro-optic experiments where this ratio is varied to study its effect on the response times and voltages.

The most significant result of this study is that by shaping the droplets we have been able to shorten the relaxation time with little increase in the switching voltage. In recent work with shaped droplets in epoxy materials we have achieved relaxation times of about 5 ms with a switching field of  $1 \text{ V } \mu\text{m}^{-1}$ .

The authors are indebted to Professor M. H. Hawton of Lakehead University for her valuable comments on the dielectric properties of materials, and for discussions with the PDLC groups at General Motors Research Center and Hughes Research Laboratories. The research was supported, in part, by DARPA-ONR Contract No. N00014-86-K-0772.

### References

- [1] CRAIGHEAD, H. G., CHENG, J., and HACKWOOD, S., 1982, *Appl. Phys. Lett.*, **40**, 22.
- [2] DOANE, J. W., VAZ, N. A., WU, B.-G., and ŽUMER, S., 1986, *Appl. Phys. Lett.*, **48**, 269.
- [3] DRZAIĆ, P. S., 1986, *J. appl. Phys.*, **60**, 2142.
- [4] VAZ, N. A., SMITH, G. W., and MONTGOMERY, G. P., JR., 1987, *Molec. Crystals liq. Crystals*, **146**, 1; 1987, *Ibid.*, **146**, 17.
- [5] DOANE, J. W., GOLEMME, A., WEST, J. L., WHITEHEAD, J. B., JR., and WU, B.-G., 1988, *Molec. Crystals liq. Crystals*, **165**, 511.
- [6] DUBOIS-VIOLETTE, E., and PARODI, O., 1969, *J. Phys., Paris C*, **4**, 57.
- [7] VOLOVIK, G. E., and LAURENTOVICH, O. D., 1983, *Zh. eksp. teor. Fiz.* **85**, 1997 [1983, *Soviet Phys. JETP*, **58**, 1159].
- [8] WILLIAMS, R. D., 1986, *J. Phys. Math. Gen.*, **19**, 3211.
- [9] DRZAIĆ, P. S., 1988, *Molec. Crystals liq. Crystals*, **154**, 289.
- [10] GOLEMME, A., ŽUMER, S., and DOANE, J. W., 1988, *Phys. Rev. A*, **37**, 559.
- [11] JACKSON, J. D., 1975, *Classical Electrodynamics*, 2nd edition (Wiley), p. 151.
- [12] SPROKEL, G. J., 1973, *Molec. Crystals liq. Crystals*, **22**, 249.
- [13] CHIDICHIMO, G., GOLEMME, A., ARABIA, G., and DOANE, J. W., 1989, *Liq. Crystals*, **5**, 1443.
- [14] WU, B.-G., WEST, J., ŽUMER, S., and DOANE, J. W., 1987, *J. appl. Phys.*, **62**, 3925.
- [15] ŽUMER, S., and DOANE, J. W., 1986, *Phys. Rev. A*, **34**, 3373.
- [16] ŽUMER, S., 1988, *Phys. Rev. A*, **37**, 4006.