

This article was downloaded by:

On: 16 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Liquid Crystals Today

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713681230>

Just thin nematic films...

Oleg D. Lavrentovich^a

^a Liquid Crystal Institute, Kent State University, Kent, Ohio, USA

To cite this Article Lavrentovich, Oleg D.(1992) 'Just thin nematic films...', *Liquid Crystals Today*, 2: 3, 4 – 5

To link to this Article: DOI: 10.1080/13583149208628605

URL: <http://dx.doi.org/10.1080/13583149208628605>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Just thin nematic films. . .

by Oleg D Lavrentovich, *Liquid Crystal Institute, Kent State University, Kent, Ohio 44242, USA*

The photographs shown on these two pages represent the polarizing-microscopy textures of nematic films. No external fields, no temperature gradients — just thin films of a standard nematic liquid crystal 5CB. However the textures reveal many striking features.

Firstly, they show the existence of different periodic domain patterns. The ability to form periodic spatial structures either because of specific molecular interactions (cholesterics, smectics, blue phases) or under the influence of electric or magnetic fields is one of the most important and well-known properties of liquid crystals. In the present case, however, one deals with a translationally symmetric phase with no external field.




Secondly, the textures contain defect points (boojums) with enormously high topological charges, or strengths. They manifest themselves as nuclei with numerous black brushes. General rules of polarizing microscopy tell us that the director \mathbf{n} should undergo a $\pi/2$ rotation between each pair of successive brushes [1]. The presence of 12 brushes indicates that defect contains as many as $12\pi/2$ turns! It is quite amazing, because the greater the number of turns the greater the elastic energy. Thus only defects with the lowest possible number of turns, such as disclinations with total π -rotation or boojums with 2π -rotation, are supposed to exist.

Thirdly, the pairs of boojums turn out to be connected by strings that appear in textures as four or three parallel black brushes. All deformations induced by the defect pair are stretched out into this string of constant width, across which the director field undergoes rotation through an angle 2π . It is noteworthy that the constant thickness of the string means that the attractive force between boojums does not depend on the separation, as in the case of quarks [2]. The strings can appear also as isolated loops or form sophisticated cellular patterns.

Despite the absence of external fields or temperature gradients, these strange structures are not present without a reason. The cause lies in the very nature of the film preparation that is different from conventional methods of putting a liquid crystal between two rigid plates. The samples used for microphotography are nematic films with a free surface placed onto an isotropic liquid substrate, such as polyethylglycol, glycerin, or water. The thinnest films ($\leq 0.5 \mu\text{m}$) show up different periodic textures [3]. The films of intermediate thickness (1-20 μm) manifest strings, defects with large strengths as well as nucleation of defect pairs [2,4]. Finally, the textures of thick films are similar to those of conventional cells: periodical structures, high-strength defects, and strings do not appear.

There are two crucial features of the liquid crystalline films that make their properties unique. First, the polar tilt angles of the director at two surfaces need not necessarily coincide since the two ambient media are different. Thus the film is hybrid aligned. Secondly, because of the isotropic nature of the ambient media, the molecular interactions do not fix the azimuthal orientation. Thus the boundary conditions degenerate in the film plane and the director can rotate on the film surface without anchoring energy losses.

With non-zero vertical curvature and zero azimuthal anchoring, how can the system gain energy? Surprisingly, the total energy of

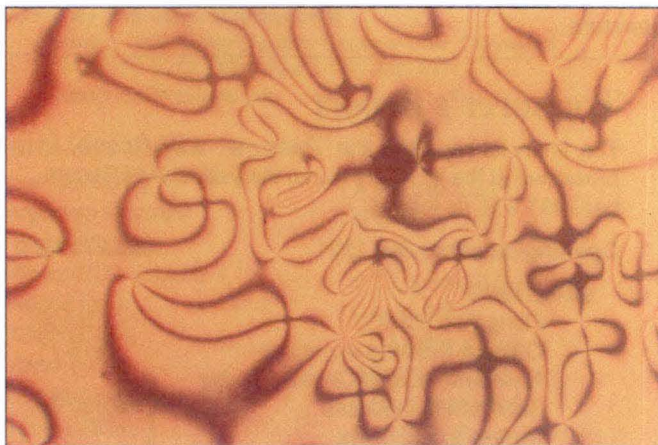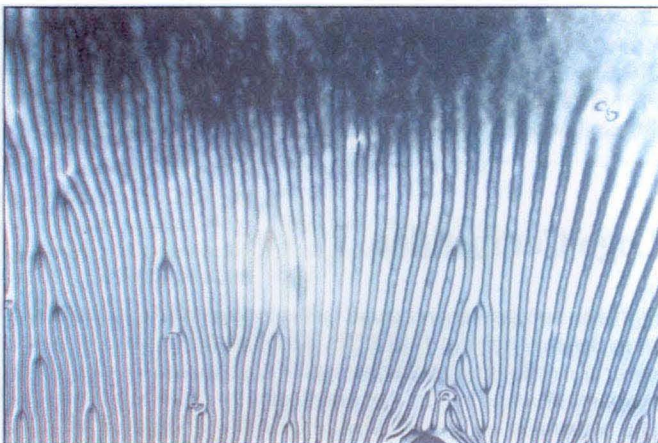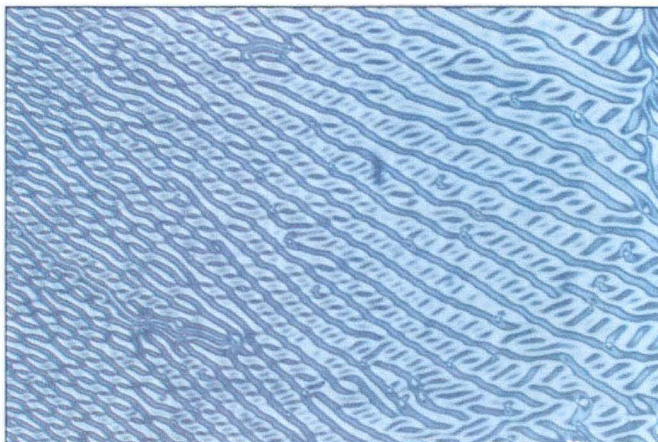

distortions can be reduced if additional deformations arise in the film plane. To demonstrate this, let us imagine surface Σ that is perpendicular to \mathbf{n} , **Fig 1**. Deformations of Σ are characterized by principal radii of curvature R_1 and R_2 . R_1 and R_2 are algebraic lengths, whose signs depend on the orientation chosen on the normal to Σ . They define the mean curvature $(1/R_1 + 1/R_2)$ and the Gaussian curvature $1/R_1 R_2$ of Σ . The mean and Gaussian curvatures can be expressed in terms of derivatives on \mathbf{n} [1]: $1/R_1 + 1/R_2 = -\text{div} \mathbf{n}$ and $1/R_1 R_2 = 1/2 \text{div}(\mathbf{n} \text{div} \mathbf{n} + \mathbf{n} \times \text{rot} \mathbf{n})$. The corre-

sponding contributions to the elastic energy density are splay $\frac{1}{2}K_{11}\text{div}^2\mathbf{n}$ and saddle-splay $K_{24}\text{div}(\mathbf{n}\text{div}\mathbf{n} + \mathbf{n} \times \text{rot}\mathbf{n})$ terms respectively.

The difference in the polar anchoring fixes the non-zero value of one of the principal radii of curvature, say R_1 . The hybrid-aligned film that is uniform in the horizontal plane (a,b) is characterised by one radius of curvature; as a result, the splay term is equal to $K_{11}/2R_1^2$ and the saddle-splay term is zero. In the states with horizontal deformations (c,d) both radii are finite. The splay contribution $\frac{1}{2}K_{11}(1/R_1 + 1/R_2)^2$ decreases when R_1 and R_2 are of opposite signs (so-called splay cancelling mechanism [5]). Moreover, with finite R_2 the saddle-splay term becomes non zero and reduces the total energy when K_{24}/R_1R_2 is negative. It does not mean that the Gaussian curvature of the energetically preferred states should always be negative: the saddle-splay constant K_{24} can be either positive or negative, in contrast to standard elastic moduli such as K_{11} . Thus the positive K_{24} will favour the deformation with $1/R_1R_2 < 0$, $K_{24} < 0$ will favour $1/R_1R_2 > 0$. Despite the evident importance and long history of the saddle-splay problem in nematics, up to now there are only a few tentative experimental estimations of K_{24} [6,7].

Qualitative consideration suggests that the deformed states can be energetically preferable to the expected "uniform" hybrid aligned film because of non-zero Gaussian curvature and zero azimuthal anchoring. Furthermore, these states can provide a number of independent methods for determination of the saddle-splay elastic constant K_{24} . For example, K_{24} defines the thickness threshold for periodic domain patterns [3] and domain behaviour under the action of external field [8] or thickness changes [9] can allow the measurements of K_{24} . Another approach is based on the peculiarities of strings which can be viewed as two π -substrings with opposite signs of Gaussian curvature [7].

Liquid crystalline films placed on an isotropic substrate reveal many other interesting properties, connected for example, with their polar structure and corresponding flexoelectric or thermochemical effects. We believe that the beauty and sometimes unexpected behaviour of these definitely "soft-matter" objects deserves detailed study.




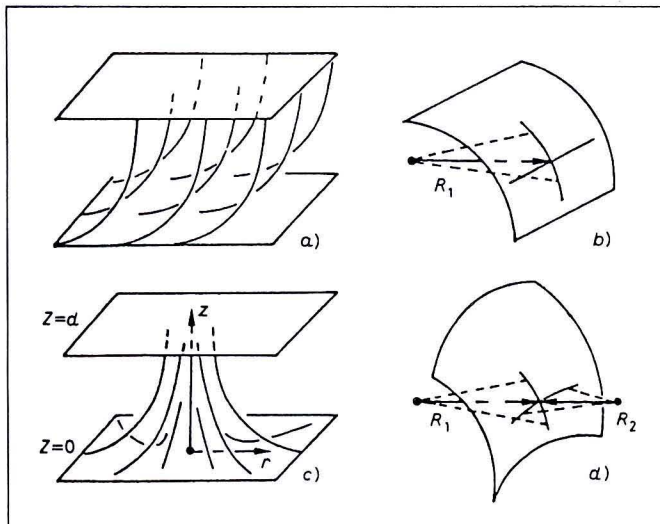


Fig 1. Director field (a,c) and corresponding surface Σ (b,d) for uniform and deformed states of a hybrid aligned film.

Acknowledgements: The main part of this research was done at the Institute of Physics, Academy of Sciences, Kiev, Ukraine in collaboration with Yu A Nastishin (L'viv State University) and V M Pergamenschchik and S S Rizhkov (Institute of Physics, Kiev). The support of Laboratoire de Physique des Solides, Orsay, France and DARPA National Center for Integrated Photonic Technology (NCIPT) Contract No. MDA792-90-C-0037 is gratefully acknowledged.

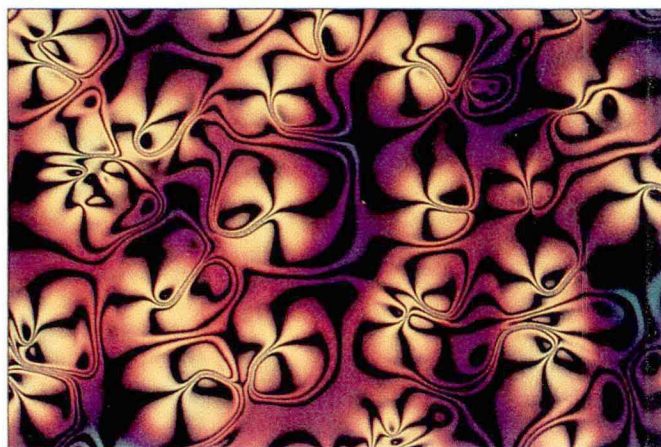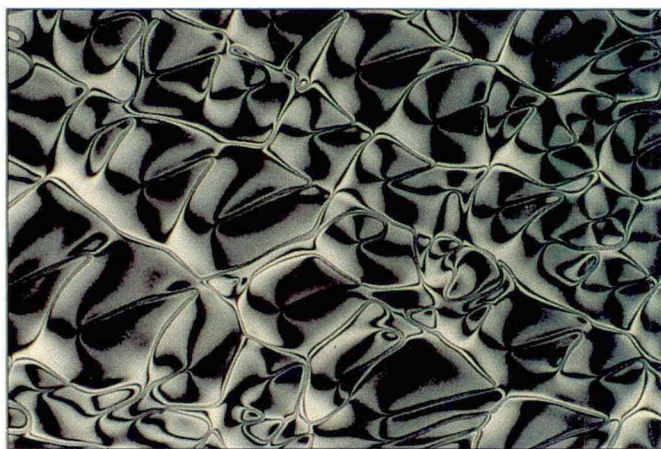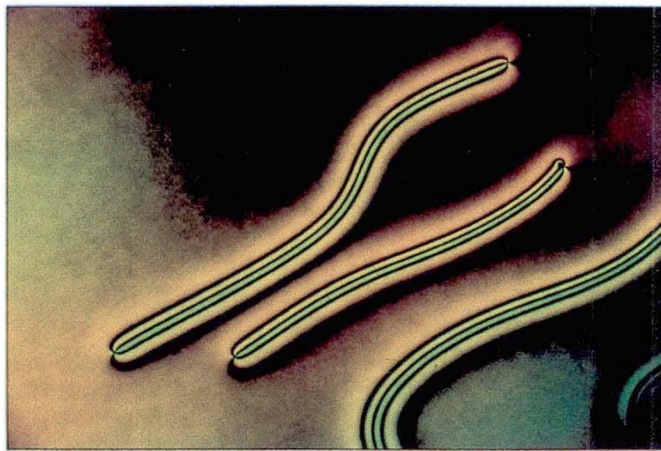

References:

1. M Kléman, *Points, Lines and Walls*, Wiley, Chichester (1983).
2. O D Lavrentovich and S S Rozhkov, *Pis'ma Zh. Eksp. Teor. Fiz.*, **47**, 210 (1988)/*JETP Lett.*, **47**, 255 (1988).
3. O D Lavrentovich and V M Pergamenschchik, *Mol. Cryst. & Liq. Cryst.*, **179**, 125 (1990).
4. O D Lavrentovich and Yu A Nastishin, *Europhys. Lett.*, **12**, 135 (1990).
5. M J Press and A S Arrott, *J. Phys. (Paris), Coll.*, **36**, C1-177 (1975).
6. D W Allender, G P Crawford and J W Doane, *Phys. Rev. Lett.*, **67**, 1442 (1991).
7. O D Lavrentovich, *Phys. Scr.*, **T39**, 394 (1991).
8. A Sparavigna, L Komitov and A Strigazzi, *Mol. Cryst. & Liq. Cryst.*, in press.
9. V M Pergamenschchik, *Ukrainian Phys. Zhurn.*, in press.