



Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl20>

Photochemical Method of Device Fabrication Starting from Molecular Crystals

Toshio Naito ^a, Hideyuki Sugawara ^b, Tamotsu Inabe ^b, Takeshi Miyamoto ^c, Hironobu Niimi ^c & Kiyotaka Asakura ^c

^a Creative Research Initiative "Sousei" (CRIS), Hokkaido University, Kita-Ku, Sapporo, Hokkaido, Japan

^b Division of Chemistry, Graduate School of Science, Hokkaido University, Kita-Ku, Sapporo, Hokkaido, Japan

^c Catalysis Research Center (CRC), Hokkaido University, Kita-Ku, Sapporo, Hokkaido, Japan

Version of record first published: 31 Jan 2007

To cite this article: Toshio Naito, Hideyuki Sugawara, Tamotsu Inabe, Takeshi Miyamoto, Hironobu Niimi & Kiyotaka Asakura (2006): Photochemical Method of Device Fabrication Starting from Molecular Crystals, *Molecular Crystals and Liquid Crystals*, 455:1, 311-316

To link to this article: <http://dx.doi.org/10.1080/15421400600699012>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.



Photochemical Method of Device Fabrication Starting from Molecular Crystals

Toshio Naito

Creative Research Initiative “Sousei” (CRIS), Hokkaido University,
Kita-Ku, Sapporo, Hokkaido, Japan

Hideyuki Sugawara

Tamotsu Inabe

Division of Chemistry, Graduate School of Science, Hokkaido University,
Kita-Ku, Sapporo, Hokkaido, Japan

Takeshi Miyamoto

Hironobu Niimi

Kiyotaka Asakura

Catalysis Research Center (CRC), Hokkaido University, Kita-Ku,
Sapporo, Hokkaido, Japan

The conductivity of a silver salt of N,N'-dicyanoquinonediimine irreversibly varied in approximate proportion to an illumination of a wide range of wavelengths. Depending on the illumination conditions, four different states (β , γ , δ , and ϵ) were obtained with different structures. The β structure is in particular important, where the formal charge of the N,N'-dicyanoquinonediimine molecules continuously decreased to -0.4 – -0.35 with retaining the crystal structure, when we kept the temperature $< 155^{\circ}\text{C}$ during the illumination. The non-illuminated area of the sample retained its original electrical property with a well-defined interface, which enabled a fabrication of a junction-structure in the single crystal.

Keywords: charge-transfer; doping; molecular semiconductor-metal junction; N,N'-dicyanoquinonediimine; photo-induced phenomena

We would like to thank Prof. Tooru Atake at Tokyo Institute of Technology for valuable discussion on the thermal analyses, and also thank Dr. Miho Sasaki at Rigaku Corporation for the XRD-DSC measurements.

Address correspondence to Toshio Naito, Creative Research Initiative “Sousei” (CRIS), Hokkaido University, Kita 21, Nishi 10, Kita-ku, Sapporo, Hokkaido 001-0021, Japan. E-mail: tnaito@mail.cris.hokudai.ac.jp

INTRODUCTION

Recently we reported on a new method of persistent electrical resistivity control of the molecular materials containing photosensitive chemical species [1]. At present, the chemistry of this method is considered to be approximately similar to the silver halides photography. A silver salt of an organic π -acceptor molecular radical anion, $\text{Ag}(\text{DM})_2$ ($\text{DM} = 2,5$ -dimethyl- N,N' -dicyanoquinonediimine; Fig. 1), is utilized instead of silver bromide. In the crystal of $\text{Ag}(\text{DM})_2$, the planar radical-anion species of DM stack to form a columnar structure [2]. The unpaired electrons on the radical-anion species delocalize along these columns, resulting in metallic conduction. Similar to AgBr , exposure to ultraviolet-visible (UV-Vis) light of $\text{Ag}(\text{DM})_2$ leads to a partial charge transfer from the π -acceptor molecules to the silver ions in the solid state. This charge transfer corresponds to decrease of the π -electrons in number on the DM radical-anion species. Because the electrical conductivity is solely dependent on the π -electrons on the DM radical-anion species in $\text{Ag}(\text{DM})_2$, such charge transfer results in the decrease of conductivity of this material. What is more, illumination on a limited part of the sample resulted in the change in conduction only at the illuminated part; the rest of the sample retained the original metallic conduction. Such a scenario is supported by X-ray photoelectron spectra (XPS) (Ag, N), and Raman spectra (C=C and C=N stretching modes) [1]. In combination with photolithography or light-focusing techniques, these findings might open a new way to control electrical properties of a particular part of a molecular solid, which would lead to fabrication of devices with junction-structures. In fact, using this method we demonstrated that one could produce an energy barrier in a single crystal of $\text{Ag}(\text{DM})_2$, which indeed exhibited rectifying behavior; i.e., characteristic behavior to diodes [1]. In addition to the semiconductor phase, we have found several

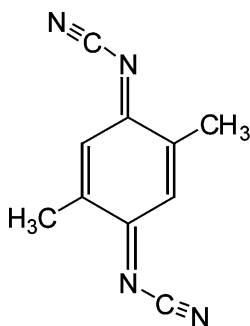


FIGURE 1 Molecular structure of DM.

phases created according to the illumination time and power. Therefore we must understand the properties and structures of these new phases and their formation mechanism in order to establish and develop this method to control electrical conductivities with as high spatial resolution as possible. In this brief communication we investigated the heat effects and wavelength dependence in addition to the characterization of several phases.

EXPERIMENTAL

We used two light sources depending on the experiment. One (light source A) was a UV-Vis Fiber Light Source L7893 equipped with a 5 W-tungsten halogen lamp (400–1100 nm) and a 30 W-D₂ lamp (200–400 nm), and with optical fiber of 800 μm in core diameter (numerical aperture = 0.22) (Hamamatsu Photonics K. K.). Both of the lamps could be turned on/off independently, but the power of light could not be varied. The end of the fiber was placed as close to the surface as possible ($< 150 \mu\text{m}$). The output of the incident beam at the end of the fiber is typically $0.1\text{--}0.2 \mu\text{W cm}^{-2} \text{ nm}^{-1}$ at 300–550 nm, $0.2\text{--}1 \mu\text{W cm}^{-2} \text{ nm}^{-1}$ at 200–300 and 550–1100 nm. In a typical run we used both of the 5 W-tungsten halogen and the 30 W-D₂ lamps, when the power was $\sim 3 \text{ mW}$ at the end of the fiber. The typical value of the fluctuation of the output during continuous illumination is 0.004% and the drift $0.3\% \text{ h}^{-1}$. The other (light source B) was a Hg/Xe lamp (200 W; Hamamatsu Photonics K. K.) with a multimode optical fiber (1 m-length, $\phi = 5 \text{ mm}$, numerical aperture = 0.22) (Supercure-203S UV Light Source; San-Ei Electric). This light source was also equipped with a removable filter and an aluminum mirror for cutting off the light with wavelengths shorter than $\sim 250 \text{ nm}$ and longer than $\sim 800 \text{ nm}$, respectively. This could minimize heat involved in the irradiation of the sample. The power of light of this light source could be varied continuously up to $\sim 300 \text{ mW}$ at the end of the fiber. The maximum power depended on the wavelength. When UV light of 200–250 nm was required, the filter was removed. During the illumination with the light source B, the sample was set in a copper or brass stage as a heat reservoir, and the temperature was continuously monitored. An anomalous deviation ($> 0.1 \text{ K}$) from the room temperature (RT) was not observed.

RESULTS AND DISCUSSION

Optically “Doped” States without Heating Effects

We obtained four different kinds of resultant states depending on the illumination conditions as shown in Table 1. Including the pristine

TABLE 1 Different States Derived from the Pristine (α -) $\text{Ag}(\text{DM})_2$ by Illumination or Thermally Treatments

States	Colors	Crystallinity	Chemical formula	Properties	Typical conditions of sampling
α -	Dark blue	Crystalline	$\text{Ag}(\text{DM})_2$	Metallic	—
β -	Dark blue	Crystalline	$\text{Ag}(\text{DM})_2$	Semiconducting	368–700 nm 200 mW cm^{-2} , 30 min, $< 155^\circ\text{C}$
γ -	Brown	Amorphous	$\text{Ag}(\text{DM})_2$	Insulating	$155^\circ\text{C} \leq$
δ -	Black	Amorphous ¹	$\text{Ag}(\text{DM})_n$; $n \leq 2$	— ⁴	$155 \leq T (^\circ\text{C}) \leq \sim 200$
ε -	White	Amorphous ²	Ag^3	— ⁴	$\sim 200^\circ\text{C} \leq$

¹With small crystallites of bulk Ag dispersed homogeneously.

²Aggregation of small (< 100 nm) crystallites of bulk Ag.

³Trace amount of C ($< 3\%$), H ($< 0.3\%$) and N ($< 1\%$) were detected as a contamination.

⁴Conducting behavior is yet to be measured.

material, let us tentatively call these series of states α , β , γ , δ and ε , respectively. All the states should involve charge transfer (redox) reaction between the Ag ions and the DM species based on their characterizations. As for the production of these states, no dependences on the wavelengths of illumination were observed. This is consistent with the results of an optical study, where no evident charge transfer bands between the Ag ions and the DM species were observed in temperature-dependent polarized reflectance spectra [3].

The β -state occurred after illumination of $\text{Ag}(\text{DM})_2$ in the pristine (α -) state below 155°C . The β -state turned out to be produced through purely optical processes, i.e. photochemical reactions, and not accessible with any thermal treatment [4]. The β -state shared the appearances (SEM photographs), X-ray diffraction (XRD) pattern, elemental analyses (C, H, N(%)) and IR spectra (Fig. 2) with the α -state, though it exhibited different electrical behavior, Raman shifts and XPS. The N1s XPS peak in the β -state had a small shoulder corresponding to the charge transfer. The amount of charge transfer evaluated from XPS was consistent with that of Raman shift. While $\text{Ag}(\text{DM})_2$ in the α -state exhibited metallic electrical behavior down to ~ 100 K, that in the β -state exhibited semiconducting behavior. Generally, the longer the illumination lasted, the higher the resistivity became. Judging from the Raman shifts, the formal charge of the DM species appeared to approach ~ -0.40 – -0.35 , where the illumination effects might saturate. After illumination ceased, the new semiconducting β -state lasted more than a half year, and it was never transformed into the α -state again. There should be small but definite structural differences between the α - and the β -states, which may

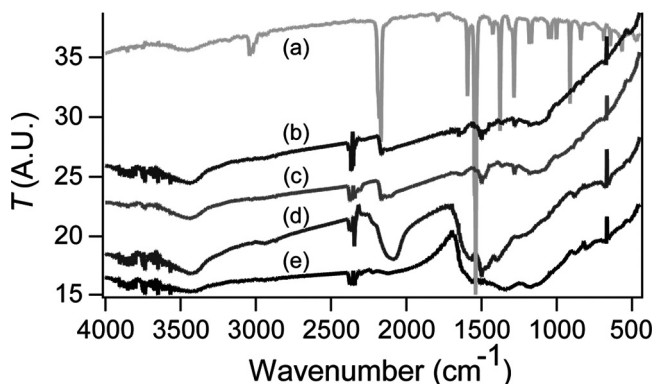


FIGURE 2 IR spectra in KBr pellets of (a) isolated neutral DM species, (b) α -, (c) β -, (d) γ -, and (e) δ - $\text{Ag}(\text{DM})_2$, respectively. (See COLOR PLATE VIII)

make this transformation irreversible. Further detailed study is now in progress.

Other Related States

When the α -state $\text{Ag}(\text{DM})_2$ was heated at 155°C , it suddenly turned into a brown amorphous solid (γ -state). This state was a diamagnetic insulator. A series of detailed chemical, thermal, structural and spectroscopic analyses of the amorphous process proved that this transformation was a structural transition rather than a decomposition. Through the amorphization, not only the original well-defined shape of the single crystals of the α -state, but also the mass of the sample, chemical stoichiometry and the molecular structure of the DM species were retained. The amorphization occurred sharply at 155°C irrespective of the atmosphere (under air or under dry nitrogen). The amorphous solid contained metal particles (X-ray absorption fine structures), but was insoluble to organic solvents. Phase separation did not occur to form bulk silver and neutral DM powder by any procedure. Comparison of IR and high resolution solid state NMR spectra clearly indicated that the neutral DM species had a different structure from the isolated neutral DM crystals.

When the α -state $\text{Ag}(\text{DM})_2$ was heated at $\sim 160^\circ\text{C}$ or strongly illuminated, it turned into a black solid (δ -state) or white solid (ε -state). Both of them were nearly amorphous; the XRD powder patterns of them showed only broad and small peaks corresponding to the reflections of bulk silver. However we could not find clear differences in

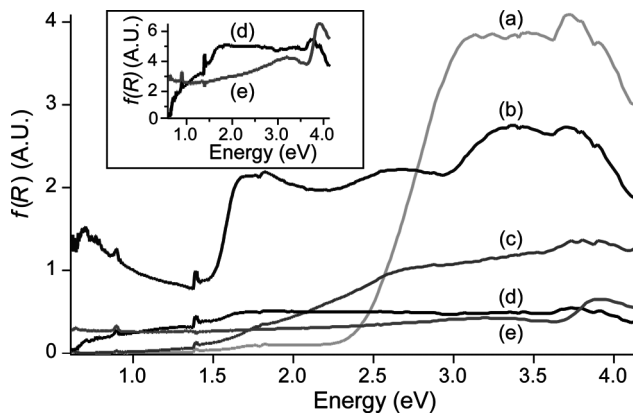


FIGURE 3 Diffuse scattering spectra of (a) isolated neutral DM species, (b) α -, (c) γ -, (d) δ -, and (e) ε -Ag(DM)₂, respectively. The inset shows (d) and (e) spectra with $f(R)$ enlarged by 10 times. (See COLOR PLATE IX)

production conditions of these two states yet. It was difficult to convert one of the two states to the other by any procedure. The δ -state contained small particles of bulk silver with 9 nm in the average diameter, and was still rich in the DM species (IR and elemental analysis), which nearly corresponded to the original stoichiometry (2:1). The ε -state was an aggregation of almost pure bulk silver particles (~ 65 nm ϕ) with a contamination of organic substances. The ε -state is considered to be produced by heating and decomposition of Ag(DM)₂. Diffuse scattering spectra (Fig. 3) suggested that the δ -state should be insulating, while the ε -state should be metallic.

REFERENCES

- [1] Naito, T., Inabe, T., Niimi, H., & Asakura, K. (2004). *Adv. Mater.*, **16**, 1786.
- [2] Kato, R., Kobayashi, H., Kobayashi, A., Mori, T., & Inokuchi, H. (1987). *Chem. Lett.*, **16**, 1579; Hünig, S. (1995). *J. Mater. Chem.*, **5**, 1469.
- [3] Yakushi, K., et al. (1990). *Mol. Cryst. Liq. Cryst.*, **181**, 217.
- [4] Naito, T., Sugawara, H., Inabe, T., Kitajima, Y., Miyamoto, T., Niimi, H., & Asakura, K. *J. J. Low Temp. Phys.*, in press.