

Microscopic mechanisms of spin-dependent electric polarization in 3d oxides

A. S. Moskvin¹ and S.-L. Drechsler²

¹*Department of Theoretical Physics, Ural State University, 620083 Ekaterinburg, Russia*

²*Leibniz Institut für Festkörper- und Werkstofforschung Dresden, D-01171, Dresden, Germany*

(Received 17 April 2008; revised manuscript received 28 May 2008; published 1 July 2008)

We address a systematic microscopic theory of spin-dependent electric polarization in 3d oxides starting with a generic three-site two-hole cluster. A perturbation scheme realistic for 3d oxides is applied which implies the quenching of orbital moments by low-symmetry crystal field, strong intra-atomic correlations, the *dp*-transfer effects, and rather small spin-orbital coupling. An effective spin operator of the electric-dipole moment is deduced incorporating both nonrelativistic $\propto(\hat{s}_1 \cdot \hat{s}_2)$ and relativistic $\propto[\mathbf{s}_1 \times \mathbf{s}_2]$ terms. The nonrelativistic electronic polarization mechanism related to the effects of the redistribution of the local on-site charge density due to *pd* covalency and exchange coupling is believed to govern the multiferroic behavior in 3d oxides. The relativistic exchange-dipole moment is mainly stems from the nonrelativistic one due to the perturbation effect of Dzyaloshinsky-Moriya coupling and is estimated to be a weak contributor to the electric polarization observed in the most of 3d multiferroics.

DOI: [10.1103/PhysRevB.78.024102](https://doi.org/10.1103/PhysRevB.78.024102)

PACS number(s): 77.80.-e, 75.80.+q, 71.70.Gm, 71.15.Rf

I. INTRODUCTION

Strong coupling of magnetism and ferroelectricity was recently uncovered in rare-earth manganites with the general formula $RMnO_3$ and RMn_2O_5 , where R is a rare-earth ion or Y (see, e.g., Ref. 1 and review articles^{2,3}). In magnetically ordered state below T_N , these *ferroelectric magnets*, or *multiferroics*, exhibit an exceptionally strong sensitivity to an applied magnetic field, which induces reversals and sudden flops of the electric polarization vector, and results in a strong enhancement of dielectric constant. Vice versa also an applied electric-field affects the magnetic properties such as the helicity.

Since Astrov's⁴ discovery of magnetoelectric effect in Cr_2O_3 , there were proposed several microscopic mechanisms of magnetoelectric coupling;² however, the multiferroicity have generated an impressive revival of the activity in this field. Currently two essentially different spin structures of net electric polarization in crystals are considered: (i) a bilinear *nonrelativistic symmetric* spin coupling,⁵⁻⁸

$$\mathbf{P}_s = \sum_{mn} \mathbf{\Pi}_{mn}^s (\mathbf{S}_m \cdot \mathbf{S}_n), \quad (1)$$

or (ii) a bilinear *relativistic antisymmetric* spin coupling,⁹⁻¹¹

$$\mathbf{P}_a = \sum_{mn} [\mathbf{\Pi}_{mn}^a \times [\mathbf{S}_m \times \mathbf{S}_n]], \quad (2)$$

respectively. The effective dipole moments $\mathbf{\Pi}_{mn}^{s,a}$ depend on the m, n orbital states and the mn bonding geometry.

If the first term stems somehow or other from a spin isotropic Heisenberg exchange interaction (see, e.g., Refs. 5 and 12), the second term does from antisymmetric Dzyaloshinsky-Moriya (DM) coupling. Namely, the second, or "spin-current," term is at present frequently considered to be one of the leading mechanisms of multiferroicity.^{9-11,13-16} However, there are notable exceptions, in particular, the manganites RMn_2O_5 — $HoMnO_3$ —where a ferroelectric polarization can appear without any indication of magnetic chiral symmetry breaking,^{6,7} and delafossite $CuFe_{1-x}Al_xO_2$,

where the helimagnetic ordering generates a spontaneous electric polarization \parallel to the helical axis,¹⁷ in sharp contrast with the prediction of the spin-current model.

Recent observations of multiferroic behavior concomitant the incommensurate spin-spiral ordering in chain cuprates $LiCuVO_4$ (Refs. 18–20) and $LiCu_2O_2$ (Ref. 21) challenge the multiferroic community. At first sight, these cuprates seem to be prototypical examples of 1D spiral-magnetic ferroelectrics, revealing the *relativistic* mechanism of "ferroelectricity caused by spin currents."⁹ However, both systems reveal a mysterious behavior with conflicting results obtained by different groups. Indeed, Yasui *et al.*¹⁹ claimed that $LiCuVO_4$ reveals clear deviations from the predictions of spin-current models,^{9,10} while Schrettle *et al.*²⁰ assured its applicability. In contrast to $LiCuVO_4$, $LiCu_2O_2$ shows a behavior which is obviously counterintuitive within the framework of spiral-magnetic ferroelectricity.²¹ It is worth noting that at variance with Park *et al.*,²¹ Naito *et al.*¹⁸ did not find any evidence for ferroelectric anomalies in $LiCu_2O_2$.

The ferroelectric anomaly in $LiVCuO_4$ reveals a magnitude comparable to that of the multiferroic $Ni_3V_2O_8$ where the magnetic ordering drives the electric polarization $P_b \approx 10^2 \mu C/m^2$ (Ref. 22) that represents a typical magnitude of polarization induced by magnetic reordering in multiferroics. However, such an anomalously strong magnetoelectric effect seems to be an unexpected feature for a system with e_g -holes and a nearly perfect highly symmetric chain structure with the edge-shared CuO_4 plaquettes, which both are unfavorable for a strong spin-electric coupling. Thus the giant magnetoelectric effect in the title cuprate raises fundamental questions about its microscopic origin.

Microscopic quantum theory of ME effect has not yet been fully developed, although several scenarios for particular materials have been proposed based on the effective spin Hamiltonian.^{7,9,11} In a recent paper, Katsura *et al.*⁹ presented a mechanism of the giant ME effect theoretically derived "in terms of a microscopic electronic model for noncollinear magnets." The authors derived the expression for the electric-dipole moment for the spin pair as follows:

$$\mathbf{P}_{ij} = a[\mathbf{R}_{ij} \times [\mathbf{S}_i \times \mathbf{S}_j]], \quad (3)$$

where \mathbf{R}_{ij} denotes the vector connecting the two sites i and j , $\mathbf{S}_{i,j}$ are spin moments, and a is an exchange-relativistic parameter. It is worth noting that the mechanism also implies the *uniform* polarization accompanying the spin-density wave. However, the original “spin-current” model by Katsuma *et al.*⁹ and its later versions^{14–16} seem to be questionable as the authors proceed with an unrealistic scenario. Indeed, when addressing a generic centrosymmetric M_1 -O- M_2 system, they groundlessly assume an effective Zeeman field to align noncollinearly the spins of $3d$ electrons and to provide a nonzero value of the two-site spin current $[\mathbf{S}_1 \times \mathbf{S}_2]$. To justify their approach, the authors^{9,14–16} were forced to assume a colossal magnitude of this fictitious field resulting in an enormous Zeeman splitting of several eV. Second, Katsuma *et al.*⁹ started with an unrealistic for $3d$ -oxides strong spin-orbital coupling limit for t_{2g} electrons,²³ which formally implies $\lambda \gg U$ and a full neglect of the low-symmetry crystal field and orbital quenching effect.^{24,25} The authors^{9,14–16} did heavily (up to 2 orders of magnitude) overestimate the numerical value of the overlap dipole matrix element $I(\mathbf{R}_{dp}) = \int d_{yz}(\mathbf{r}) y p_z(\mathbf{r} + \mathbf{R}_{dp}) d\mathbf{r}$, which defines maximal value of respective electric-dipole moments. It seems that the authors ignore the well developed techniques to proceed with pd covalency, exchange, and spin-orbital coupling in $3d$ oxides.

Alternative mechanism of giant magnetoelectricity based on the antisymmetric DM type magnetoelastic coupling was proposed recently by Sergienko and Dagotto.¹¹ However, here we meet with a “weak” contributor. Indeed, the minimal value of γ parameter ($\gamma = d\mathbf{D}/d\mathbf{R}$) needed to explain experimental phase transition in multiferroic manganites is 2 orders of magnitude larger than the reasonable microscopic estimations.¹¹

In our opinion, a misunderstanding exists regarding the relative role of the off-center ionic displacements (lattice effects) and electronic contributions to a resultant electric polarization. Many authors consider the giant multiferroicity requires the existence of sizeable atomic displacements and structural distortions.^{26,27} One would expect a transition to a structure with polar symmetry to occur at the onset of ferroelectricity, but neutron-diffraction studies thus far have failed to find direct evidence of such changes.²⁸ Earlier synchrotron x-ray studies found some evidence of lattice modulation in the ferroelectric phase of YMn_2O_5 ,²⁹ though the atomic displacements seem to be extremely small. Other structural works have not reported any signature of atomic displacements ~ 0.001 Å at the ferroelectric phase transition, which can explain the polarization observed in this family of compounds. This questions the microscopic model by Harris *et al.*²⁶ supposing the dominant role of the displacement derivatives of the exchange integrals, especially because the Bloch’s rule $-\frac{\partial \ln J}{\partial \ln R} \approx 10$ (Ref. 30) points to magnitudes of these derivatives as insufficient to explain the ~ 0.001 Å displacements. However, several phonons in TbMn_2O_5 exhibit clear correlations to the ferroelectricity of these materials.³¹ The signatures of the loss of inversion symmetry in the ferroelectric phase were found by the appearance of a infrared-active phonon that was only Raman active in the paraelectric

phase. A seeming contradiction we think is a result of an oversimplified approach to the lattice dynamics. Indeed, the effects of nuclear displacements and electron polarization should be described on equal footing, e.g., in frames of the well-known shell model of Dick and Overhauser³² widely used in lattice dynamics. In frames of the model the ionic configuration with filled electron shells is considered to be composed of an outer spherical shell of $2(2l+1)$ electrons and a core consisting of the nucleus and the remaining electrons. In an electric field the rigid shell retains its spherical charge distribution but moves bodily with respect to the core. The polarizability is made finite by a harmonic restoring force of spring constant k , which acts between the core and shell. The shells of two ions repel one another and tend to become displaced with respect to the ion cores because of this repulsion. Shell and core displacements may be of comparable magnitude. The conventional shell model does not take into account the spin and orbital degrees of freedom; hence, it cannot describe the multiferroic effects. In fact, the displacements of both the atomic core and electron shell would depend on the spin surroundings producing the synergetic effect of spin-dependent electric polarization. Obviously, this effect manifests itself differently in neutron and x-ray diffraction experiments. Sorting out two contributions is a key issue in the field.

Size of the macroscopic polarization \mathbf{P} in nonmagnetic ferroelectrics computed by modern *ab initio* band-structure methods agrees exceptionally well with the ones observed experimentally. However, state-of-the art *ab initio* computations for different multiferroics—manganites HoMnO_3 ,³³ TbMn_2O_5 ,³⁴ and HoMn_2O_5 (Ref. 35) and spin-spiral chain cuprates LiCuVO_4 and LiCu_2O_2 Ref. 36—yield data spread within 1–2 orders of magnitude with absolutely ambiguous and unreasonable values of polarization. Indeed, the basic starting points of the current versions of such spin-polarized approaches as the local spin-density approximation (LSDA) exclude any possibility to obtain a reliable quantitative estimation of the spin-dependent electric polarization in multiferroics. Basic drawback of the spin-polarized approaches is that these start with a local-density functional in the form (see, e.g., Ref. 37)

$$\mathbf{v}(\mathbf{r}) = v_0[n(\mathbf{r})] + \Delta v[n(\mathbf{r}), \mathbf{m}(\mathbf{r})] \left(\hat{\sigma} \cdot \frac{\mathbf{m}(\mathbf{r})}{|\mathbf{m}(\mathbf{r})|} \right),$$

where $n(\mathbf{r}), \mathbf{m}(\mathbf{r})$ are the electron and spin magnetic densities, respectively, and $\hat{\sigma}$ is the Pauli matrix, which imply the presence of a large fictitious local *one-electron* spin-magnetic field $\propto (v^\uparrow - v^\downarrow)$, where $v^{\uparrow,\downarrow}$ are the on-site LSDA spin-up and spin-down potentials. Magnitude of the field is considered to be governed by the intra-atomic Hund exchange, while its orientation does by the effective molecular or interatomic exchange fields. Despite the supposedly spin nature of the field, it produces an unphysically giant spin-dependent rearrangement of the charge density that cannot be reproduced within any conventional technique operating with spin Hamiltonians. Furthermore, a direct link with the orientation of the field makes the effect of the spin configuration onto the charge distribution to be unphysically large. Similar ef-

fects cannot be reproduced in frames of any conventional Heisenberg model. In general, the LSDA method to handle a spin degree of freedom is absolutely incompatible with a conventional approach based on the spin-Hamiltonian concept. There are some intractable problems with a match making between the conventional formalism of a spin-Hamiltonian and LSDA approach to the exchange and exchange-relativistic effects. Visibly plausible numerical results for different exchange and exchange-relativistic parameters reported in many LSDA investigations (see, e.g., Refs. 38 and 39) evidence only a potential capacity of the LSDA based models for semiquantitative estimations, rather than for reliable quantitative data. It is worth noting that for all of these “advantageous” instances, the matter concerns the handling of certain classical Néel-type spin configurations (ferromagnetic, antiferromagnetic, spiral, etc.) and search for a compatibility with a mapping made with a conventional quantum spin Hamiltonian. It is quite another matter when one addresses the search of the charge-density redistribution induced by a spin configuration. In such a case the straightforward application of the LSDA scheme can lead to an unphysical overestimation of the effects or even to qualitatively incorrect results due to an unphysical effect of a breaking of spatial symmetry induced by a spin configuration. As an example, we refer to the papers by Picozzi *et al.*³³ and Xiang and Whangbo³⁶ where the authors made use of the *first-principles* LSDA calculations to study the microscopic origin of ferroelectricity induced by magnetic order in orthorhombic HoMnO_3 and in quasi-1D cuprates LiCu_2O_2 and LiCuVO_4 , respectively. The calculated total nonrelativistic polarization of the AFM- E phase in HoMnO_3 exceeds the experimentally measured one by more than 3 orders of magnitude. In terms of a conventional scheme the AFM- E ordering turns out to be accompanied by a colossal exchange striction of the order of several percents that exceeds all the thinkable magnitudes (see Table I in Ref. 33). The relativistic LSDA calculations for the optimized structures of quasi-1D cuprates³⁶ yield the results that disagree with experiment both quantitatively and qualitatively. Again we see an unphysically strong overestimation of the spin-induced electric polarization. Interestingly, that the making use of experimental centrosymmetric structures leads to a strong suppression by order of magnitude of the calculated polarizations, clearly confirming the unphysically strong LSDA overestimation of spin-induced structural and charge-density distortions. Summarizing, we should emphasize two weak points of so-called *first-principles calculations*, which appear as usual to be well forgotten in the literature. First, these approaches imply the spin configuration induces immediately the appropriate kinematic breaking of spatial symmetry that makes the symmetry-breaking effect of a spin configuration unphysically large. Conventional schemes imply just opposite, however, a physically reasonable picture when the charge and orbital anisotropies induce a spin anisotropy. Second, these neglect quantum fluctuations, which restrict drastically their applicability to a correct description of the high-order perturbation effects. Overall, the LSDA approach seems to be more or less justified for a semiquantitative description of exchange coupling effects for materials with a classical Néel-type collinear magnetic order. However, it can lead to erro-

neous results for systems and effects where the symmetry-breaking and quantum fluctuations are of a principal importance such as: (i) noncollinear spin configurations, in particular, quantum $s=1/2$ magnets, (ii) relativistic effects, such as the symmetric spin anisotropy, antisymmetric DM coupling, and (iii) spin-dependent electric polarization. Indeed, a correct treatment of these high-order perturbation effects needs in a correct account both of local symmetry and of quantum fluctuations (see, e.g., Ref. 40).

It is worth noting that the spin-current scenario by Katsura *et al.*⁹ starts with the same LSDA-like assumption of unphysically large symmetry-breaking spin-magnetic field. Surprisingly, despite the problems with the model validation and quantitative estimations the spin-current mechanism is currently addressed to be responsible for the emergence of ferroelectric polarization in new multiferroics such as orthorhombic RMnO_3 , $\text{Ni}_3\text{V}_2\text{O}_8$, MnWO_4 , CoCr_2O_4 , and CuFeO_2 , where the inversion symmetry breaking is related to noncollinear spiral-magnetic structures.¹³ “Ferroelectricity caused by spin-currents” has established itself as the leading paradigm for both theoretical and experimental investigations in the field of strong multiferroic coupling. However, a “rule” that chiral symmetry needs to be broken in order to induce a ferroelectric moment at a magnetic phase transition is questionable. Moreover, there are increasing doubts whether weak exchange-relativistic coupling can generate giant electric polarization observed in multiferroics. Thus we may assert that a true microscopic mechanism of giant magnetoelectric effect is still missing.

Below we propose a systematic standard microscopic theory of spin-dependent electric polarization, which implies the derivation of effective spin operators for nonrelativistic and relativistic contributions to electric polarization of the generic three-site two-hole cluster such as $\text{Cu}_1\text{-O-Cu}_2$ and does not imply any fictitious Zeeman fields to align the spins. We make use of conventional well-known approaches to account for the pd -covalent effects, intra-atomic correlations, crystal field, and spin-orbital coupling. Despite the description is focused on $\text{Cu}_1\text{-O-Cu}_2$ clusters typical for different cuprates, the generalization of the results on the $\text{M}_1\text{-O-M}_2$ clusters in other $3d$ oxides is trivial. To the best of our knowledge such a conventional microscopic approach to the magnetoelectric coupling in multiferroics was not yet realized.

The paper is organized as follows: In Sec. II we consider the effects of pd covalency and spin-orbital coupling in a three-site two-hole $\text{Cu}_1\text{-O-Cu}_2$ cluster. Nonrelativistic and relativistic mechanisms of spin-dependent electric polarization with local and nonlocal terms are discussed in Secs. III and VI, respectively. In Sec. V we address an alternative approach to nonrelativistic mechanism of spin-dependent electric polarization induced by a parity-breaking exchange interaction. In Sec. VI we show a lack of the spin-dependent electric polarization effects for an isolated CuO_2 chain.

II. THREE-SITE TWO-HOLE $\text{M}_1\text{-O-M}_2$ CLUSTER

Before proceeding with electric polarization effects, we address the generic three-site $\text{M}_1\text{-O-M}_2$ cluster, which forms

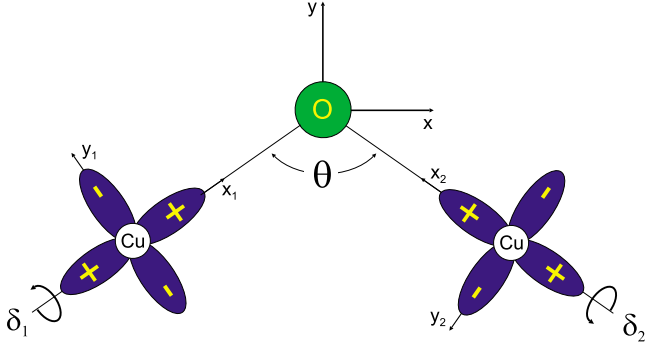


FIG. 1. (Color online) Geometry of the three-center (Cu-O-Cu) two-hole system with ground Cu $3d_{x^2-y^2}$ states.

a basic element of crystalline and electron structure for $3d$ oxides. A realistic perturbation scheme needed to describe the active M $3d$ and O $2p$ electron states implies the strong intra-atomic correlations, the comparable effect of crystal field, the quenching of orbital moments by low-symmetry crystal field, account for the dp transfer up to the fourth order effects, and rather small spin-orbital coupling. To this end we make use of a technique suggested in Refs. 40 and 41 to derive the expressions for the copper and oxygen spin-orbital contributions to Dzyaloshinsky-Moriya coupling in copper oxides. For illustration, below we address a typical for cuprates the three-site ($\text{Cu}_1\text{-O-Cu}_2$) two-hole system with a tetragonal Cu on-site symmetry and ground Cu $3d_{x^2-y^2}$ states (see Fig. 1), which conventional bilinear spin Hamiltonian is written in terms of the hole spins as follows:

$$\hat{H}_s(12) = J_{12}(\hat{\mathbf{s}}_1 \cdot \hat{\mathbf{s}}_2) + \mathbf{D}_{12} \cdot [\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2] + \hat{\mathbf{s}}_1 \vec{\mathbf{K}}_{12} \hat{\mathbf{s}}_2, \quad (4)$$

where $J_{12} > 0$ is an exchange integral, \mathbf{D}_{12} is a Dzyaloshinsky vector, and $\vec{\mathbf{K}}_{12}$ is a symmetric second-rank tensor of the anisotropy constants. Hereafter we will denote $J_{12} = J$, $\vec{\mathbf{K}}_{12} = \vec{\mathbf{K}}$, $\mathbf{D}_{12} = \mathbf{D}$, respectively.

For a composite two $s=1/2$ spin system, one should consider three types of the vector order parameters,^{40,41}

$$\hat{\mathbf{S}} = \hat{\mathbf{s}}_1 + \hat{\mathbf{s}}_2; \quad \hat{\mathbf{V}} = \hat{\mathbf{s}}_1 - \hat{\mathbf{s}}_2; \quad \hat{\mathbf{T}} = 2[\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2], \quad (5)$$

with a kinematic constraint

$$\hat{\mathbf{S}}^2 + \hat{\mathbf{V}}^2 = 3\hat{\mathbf{I}}; \quad (\hat{\mathbf{S}} \cdot \hat{\mathbf{V}}) = 0; \quad (\hat{\mathbf{T}} \cdot \hat{\mathbf{V}}) = 6i; \quad [\hat{\mathbf{T}} \times \hat{\mathbf{V}}] = \hat{\mathbf{S}}. \quad (6)$$

Here $\hat{\mathbf{S}}$ is a net spin of the pair, the $\hat{\mathbf{V}}$ operator describes the effect of local staggered (antiferromagnetic) order or staggered spin polarization, while the $\hat{\mathbf{T}}$ operator may be associated with a pair spin current. The both $\hat{\mathbf{T}}$ and $\hat{\mathbf{V}}$ operators change the net spin multiplicity with slightly different matrix elements,

$$\langle 00 | \hat{T}_m | 1n \rangle = -\langle 1n | \hat{T}_m | 00 \rangle = i\delta_{mn},$$

$$\langle 00 | \hat{V}_m | 1n \rangle = \langle 1n | \hat{V}_m | 00 \rangle = \delta_{mn}, \quad (7)$$

where we made use of Cartesian basis for the three $S=1$ states. The eigenstates of the operators \hat{V}_n and \hat{T}_n with non-zero eigenvalues ± 1 form Néel doublets $\frac{1}{\sqrt{2}}(|00\rangle \pm |1n\rangle)$ and DM doublets $\frac{1}{\sqrt{2}}(|00\rangle \pm i|1n\rangle)$, respectively. The Néel doublets correspond to classical collinear antiferromagnetic spin configurations, while the DM doublets correspond to quantum spin configurations, which sometimes are associated with a rectangular 90° spin ordering in the plane orthogonal to the Dzyaloshinsky vector.

It should be noted that the spin Hamiltonians can be reduced to within a constant to a spin operator acting in a net spin space,

$$\hat{H}_S = \frac{1}{4}J(\hat{\mathbf{S}}^2 - \hat{\mathbf{V}}^2) + \frac{1}{2}(\mathbf{D} \cdot \hat{\mathbf{T}}) + \frac{1}{4}\hat{\mathbf{s}}_1 \vec{\mathbf{K}} \hat{\mathbf{s}}_2 - \frac{1}{4}\hat{\mathbf{V}} \vec{\mathbf{K}} \hat{\mathbf{V}}. \quad (8)$$

Hereafter we assume a tetragonal symmetry at Cu sites with local coordinate systems, as shown in Fig. 1. The global xyz coordinate system is chosen so as the $\text{Cu}_1\text{-O-Cu}_2$ plane coincides with the xy plane, the x axis is directed along the $\text{Cu}_1\text{-Cu}_2$ bond. In such a case the basic unit vectors $\mathbf{x}, \mathbf{y}, \mathbf{z}$ can be written in local systems of the Cu_1 and Cu_2 sites as follows:

$$\mathbf{x} = \left(\sin \frac{\theta}{2}, -\cos \frac{\theta}{2} \cos \delta_1, -\cos \frac{\theta}{2} \sin \delta_1 \right),$$

$$\mathbf{y} = \left(\cos \frac{\theta}{2}, \sin \frac{\theta}{2} \cos \delta_1, \sin \frac{\theta}{2} \sin \delta_1 \right), \quad \mathbf{z} = (0, \sin \delta_1, \cos \delta_1)$$

for the Cu_1 , while for the Cu_2 site θ, δ_1 should be replaced by $-\theta, \delta_2$, respectively.

We start with the construction of spin-singlet and spin-triplet wave functions for our three-center two-hole system taking account of the p - d hopping, on-site hole-hole repulsion, and crystal-field effects for excited configurations $\{n\}$ (011, 110, 020, 200, 002) with different hole occupations of Cu_1 , O, and Cu_2 sites, respectively. The p - d hopping for Cu-O bond implies a conventional Hamiltonian

$$\hat{H}_{pd} = \sum_{\alpha\beta} t_{pd\alpha\beta} \hat{p}_\alpha^\dagger \hat{d}_\beta + \text{H.c.}, \quad (9)$$

where \hat{p}_α^\dagger creates a hole in the α state on the oxygen site, while \hat{d}_β annihilates a hole in the β state on the copper site; $t_{pd\alpha\beta}$ is a pd -transfer integral ($t_{p_x d_{x^2-y^2}} = \frac{\sqrt{3}}{2} t_{p_z d_z} = t_{pd\sigma} > 0, t_{p_y d_{xy}} = t_{pd\pi} > 0$).

For basic 101 configuration with two $d_{x^2-y^2}$ holes localized on its parent sites, we arrive at a perturbed wave function as follows:

$$\Psi_{101;SM} = \eta_S \left[\Phi_{101;SM} + \sum_{\Gamma\{n\} \neq 101} c_{\{n\}} ({}^{2S+1}\Gamma) \Phi_{\{n\};\Gamma SM} \right], \quad (10)$$

where the summation runs both on different configurations and different orbital Γ states,

$$\eta_S = \left(1 + \sum_{\{n\}\Gamma} |c_{\{n\}}(2S+1\Gamma)|^2 \right)^{-1/2}, \quad (11)$$

is a normalization factor. It is worth noting that the probability amplitudes or hybridization parameters, $c_{\{011\}}, c_{\{110\}} \propto t_{pd}, c_{\{200\}}, c_{\{020\}}, c_{\{002\}} \propto t_{pd}^2$. For instance,

$$c_{s,t}(dp_x) = -\frac{\sqrt{3}}{2} \frac{t_{pd\sigma}}{E_{s,t}(dp_x)} \sin \frac{\theta}{2}, \quad (12)$$

$$c_{s,t}(dp_y) = -\frac{\sqrt{3}}{2} \frac{t_{pd\sigma}}{E_{s,t}(dp_y)} \cos \frac{\theta}{2}, \quad (13)$$

where $c_{s,t}(dp) = c_{110}(dp), c_{s,t}(pd) = c_{011}(dp)$ are probability amplitudes for different singlet (c_s) and triplet (c_t) 110 ($\text{Cu}_1 3d_{x^2-y^2} \text{O } 2p_{x,y}$) and 011 ($\text{O } 2p_{x,y} \text{Cu}_2 3d_{x^2-y^2}$) configurations in the ground-state wave function, respectively; $c_{s,t}(dp_x) = -c_{s,t}(p_x d), c_{s,t}(dp_y) = c_{s,t}(p_y d)$, and $t_{dp\sigma}$ is a hole dp -transfer integral. The energies $E_{s,t}(dp_{x,y})$ are those for singlet and triplet states of $dp_{x,y}$ configurations, respectively: $E_{s,t}(dp_{x,y}) = \epsilon_{x,y} + K_{dp_{x,y}} \pm I_{dp_{x,y}}$, where $K_{dp_{x,y}}$ and $I_{dp_{x,y}}$ are Coulomb and exchange dp -integrals, respectively. It is worth noting that the energies $\epsilon_{x,y}$ accommodate both the pd transfer energy Δ_{pd} and crystal-field effects: $\epsilon_{x,y} = \Delta_{pd} + \delta\epsilon_{x,y}$. To account for orbital effects for $\text{Cu}_{1,2} 3d$ holes and the covalency induced mixing of different orbital states for 101 configuration, we should introduce an effective exchange Hamiltonian

$$\hat{H}_{ex} = \frac{1}{2} \sum_{\alpha\beta\gamma\delta\mu\mu'} J(\alpha\beta\gamma\delta) \hat{d}_{1\alpha\mu}^\dagger \hat{d}_{2\beta\mu'}^\dagger \hat{d}_{2\gamma\mu} \hat{d}_{1\delta\mu'} + \text{H.c.} \quad (14)$$

Here $\hat{d}_{1\alpha\mu}^\dagger$ creates a hole in the α th $3d$ orbital on Cu_1 site with spin projection μ . Exchange Hamiltonian (14) involves both spinless and spin-dependent terms; however, it preserves the spin multiplicity of Cu_1 -O- Cu_2 system. Exchange parameters $J(\alpha\beta\gamma\delta)$ are of the order of t_{pd}^4 . The conventional exchange integral can be written as follows:

$$J = \sum_{\{n\},\Gamma} [|c_{\{n\}}(3\Gamma)|^2 E_{3\Gamma}(\{n\}) - |c_{\{n\}}(1\Gamma)|^2 E_{1\Gamma}(\{n\})]. \quad (15)$$

To account for relativistic effects in the three-site cluster one should incorporate the spin-orbital coupling both for $3d$ and $2p$ holes. Local spin-orbital coupling is taken as follows:

$$\begin{aligned} V_{so} &= \sum_i \xi_{nl}(\mathbf{I}_i \cdot \mathbf{s}_i) = \frac{\xi_{nl}}{2} [(\hat{\mathbf{I}}_1 + \hat{\mathbf{I}}_2) \cdot \hat{\mathbf{S}} + (\hat{\mathbf{I}}_1 - \hat{\mathbf{I}}_2) \cdot \hat{\mathbf{V}}] \\ &= \hat{\Lambda}^S \cdot \hat{\mathbf{S}} + \hat{\Lambda}^V \cdot \hat{\mathbf{V}}, \end{aligned} \quad (16)$$

with a single-particle constant $\xi_{nl} > 0$ for electrons and $\xi_{nl} < 0$ for holes. We make use of orbital matrix elements: for $\text{Cu } 3d$ holes $\langle d_{x^2-y^2} | l_x | d_{yz} \rangle = \langle d_{x^2-y^2} | l_y | d_{xz} \rangle = i, \langle d_{x^2-y^2} | l_z | d_{xy} \rangle = -2i, \langle i | l_j | k \rangle = -i\epsilon_{ijk}$ with $\text{Cu } 3d_{yz} = |1\rangle, 3d_{xz} = |2\rangle$, and $3d_{xy} = |3\rangle$, and for $\text{O } 2p$ holes $\langle p_i | l_j | p_k \rangle = i\epsilon_{ijk}$. Free cuprous Cu^{2+} ion is described by a large spin-orbital coupling with $|\xi_{3d}| \cong 0.1$ eV (see, e.g., Ref. 42), though its value may be significantly reduced in oxides. Information regarding the ξ_{2p} value for the oxygen O^{2-} ion in oxides is scant if any. Usu-

ally one considers the spin-orbital coupling on the oxygen to be much smaller than that on the copper, and therefore may be neglected.^{43,44} However, even for a free oxygen atom the electron-spin-orbital coupling turns out to reach of appreciable magnitude: $\xi_{2p} \cong 0.02$ eV,⁴⁵ while for the oxygen O^{2-} ion in oxides one expects the visible enhancement of spin-orbital coupling due to a larger compactness of $2p$ wave function.⁴⁶ If we account for $\xi_{nl} \propto \langle r^{-3} \rangle_{nl}$ and compare these quantities for copper and oxygen ($\langle r^{-3} \rangle_{3d} \approx 6-8$ a.u. and $\langle r^{-3} \rangle_{2p} \approx 4$ a.u., respectively⁴⁶), we arrive at a maximum factor of 2 difference in ξ_{3d} and ξ_{2p} (see also Ref. 47).

The Dzyaloshinsky-Moriya coupling

$$\hat{H}_{DM} = \mathbf{D}_{12} \cdot [\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2] = \frac{1}{2} (\mathbf{D} \cdot \hat{\mathbf{T}}) \quad (17)$$

can be addressed to be a result of a projection of the spin-orbital operator $\hat{V}_{SO} = \hat{V}_{SO}(\text{Cu}_1) + \hat{V}_{SO}(\text{O}) + \hat{V}_{SO}(\text{Cu}_2)$ on the ground-state singlet-triplet manifold.⁴⁰ Remarkably that the net Dzyaloshinsky vector \mathbf{D}_{12} has a particularly local structure to be a superposition of partial contributions of different ions ($i=1,0,2$) and ionic configurations $\{n\} = 101, 110, 011, 200, 020, 002$

$$\mathbf{D} = \sum_{i,\{n\}} \mathbf{D}_i^{\{n\}}. \quad (18)$$

The partial contributions $\mathbf{D}_i^{\{n\}}$ are analyzed in detail in Ref. 40.

III. NONRELATIVISTIC MECHANISM OF SPIN-DEPENDENT ELECTRIC POLARIZATION: LOCAL AND NONLOCAL TERMS

Projecting electric-dipole moment $\mathbf{P} = |e|(\mathbf{r}_1 + \mathbf{r}_2)$ on the spin singlet or triplet ground state of two-hole system, we arrive at an effective electric polarization of three-center system $\langle \mathbf{P} \rangle_S = \langle \Psi_{101;SM} | \mathbf{P} | \Psi_{101;SM} \rangle$ to consist of local and nonlocal terms: $\mathbf{P} = \mathbf{P}^{\text{local}} + \mathbf{P}^{\text{nonlocal}}$, which accommodate the diagonal and nondiagonal on the ionic configurations matrix elements, respectively. The local contribution describes the redistribution of the local on-site charge density and can be written as follows:

$$\begin{aligned} \langle \mathbf{P} \rangle_S^{\text{local}} &= |e| |\eta_S|^2 \left[(\mathbf{R}_1 + \mathbf{R}_2 + (\mathbf{R}_1 + \mathbf{R}_O) \sum_{\Gamma} |c_{110}(S\Gamma)|^2 \right. \\ &\quad + (\mathbf{R}_O + \mathbf{R}_2 \sum_{\Gamma} |c_{011}(S\Gamma)|^2 + 2\mathbf{R}_O \sum_{\Gamma} |c_{020}(S\Gamma)|^2 \\ &\quad \left. + 2\mathbf{R}_1 \sum_{\Gamma} |c_{200}(S\Gamma)|^2 + 2\mathbf{R}_2 \sum_{\Gamma} |c_{002}(S\Gamma)|^2 \right] - \mathbf{P}_0, \end{aligned} \quad (19)$$

where $\mathbf{P}_0 = |e|(\mathbf{R}_1 + \mathbf{R}_2)$ is a bare purely ionic two-hole dipole moment. This dipole moment incorporates both the large ($\propto t_{pd}^2$) and small ($\propto t_{pd}^4$) contributions. Obviously, the net local electric polarization can be expressed as a sum of local dipole moments,

$$\langle \mathbf{P} \rangle_S^{\text{local}} = \sum_i \langle \mathbf{P}_i \rangle_S^{\text{local}},$$

though, on the other hand, it is easy to show that it depends only on \mathbf{R}_{ij} vectors ($\mathbf{R}_{10}, \mathbf{R}_{20}, \mathbf{R}_{12}$). To this end one should carefully proceed with the normalization factor in Eq. (19). It

$$\langle \mathbf{P} \rangle_S^{\text{nonlocal}} = 2|e||\eta_S|^2 \sum_{i=x,y} [c_S(p_i d) \langle 2p_i | \mathbf{r} | 3d_{x^2-y^2}^{(1)} \rangle + c_S(dp_i) \langle 2p_i | \mathbf{r} | 3d_{x^2-y^2}^{(2)} \rangle], \quad (20)$$

or

$$\langle P_x \rangle_{s,t} = -\frac{\sqrt{3}}{2} |e| (\cos^2 \delta_2 - \cos^2 \delta_1) \sin \theta \langle 2p_y | y | 3d_{x^2-y^2} \rangle t_{pd\sigma} \left[\frac{\cos \frac{\theta}{2}}{E_{s,t}(dp_x)} - \frac{\sin \frac{\theta}{2}}{E_{s,t}(dp_y)} \right], \quad (21)$$

$$\langle P_y \rangle_{s,t} = -\sqrt{3} |e| t_{pd\sigma} \cos \frac{\theta}{2} \left[(\cos^2 \delta_1 + \cos^2 \delta_2) \langle 2p_y | y | 3d_{x^2-y^2} \rangle \sin^2 \frac{\theta}{2} \left(\frac{1}{E_{s,t}(dp_x)} + \frac{1}{E_{s,t}(dp_y)} \right) \langle 2p_y | x | 3d_{x^2-y^2} \rangle \left(\frac{\cos^2 \frac{\theta}{2}}{E_{s,t}(dp_y)} - \frac{\sin^2 \frac{\theta}{2}}{E_{s,t}(dp_x)} \right) \right], \quad (22)$$

where all the matrix elements are taken in local coordinates of Cu sites. For a symmetric d -orbitals arrangement with $\delta_1 = \delta_2$, the x component of electric polarization $\langle P_x \rangle_{s,t}$ turns into zero regardless the bonding angle θ , whereas the y component $\langle P_y \rangle_{s,t}$ turns into zero only if $\theta = \pi$, which is for collinear Cu-O-Cu bonding. It should be noted that both the partial and net nonlocal contributions to electric polarization lie in the Cu₁-O-Cu₂ plane and are believed to have the same symmetry properties.

Nominally, the nonlocal contribution to the electric-dipole moment is proportional to the pd transfer integral; however, actually the two-site dipole matrix elements indirectly are proportional to the pd overlap integral S_{pd} that in a sense equalizes the nonlocal and local terms. Let us address the problem of the two-site dipole matrix elements in more details because their correct estimation allows us to make a reliable conclusion regarding the relation between local and nonlocal terms, and the resultant effect itself. For instance, Katsura *et al.*⁹ did heavily (up to 2 orders of magnitude) overestimate the numerical value of the integral $I(\mathbf{R}_{dp}) = \int d_{yz}(\mathbf{r}) y p_z(\mathbf{r} + \mathbf{R}_{dp}) d\mathbf{r}$, which defines maximal value of respective electric-dipole moments. Indeed, the authors erroneously replaced the actually two-site integral by a respective one-site integral with the hydrogenlike $3d$ and $2p$ functions, localized on the same site. Nevertheless, their estimate $I \sim 1 \text{ \AA}$ was directly or indirectly used in more later papers.^{14–16} In fact this integral is estimated to be $I \approx R_{dp} S_{dp\pi}$, where R_{dp} is a cation-anion separation and $S_{dp\pi}$ is the $dp\pi$ overlap integral. Thus the actual electric polarization induced by the spin current is 1–2 orders of magnitude smaller than the authors estimations.

In Fig. 2 we demonstrate the results of numerical calculations of several two-site dipole matrix elements against $3d$

is worth noting that the net local electric polarization lies in the Cu₁-O-Cu₂ plane.

The nonlocal, or overlap contribution is related with non-diagonal two-site matrix elements of \mathbf{P} and in the lowest order with respect to a pd transfer integral can be written as follows:

metal-oxygen separation \mathbf{R}_{MeO} . For illustration we choose both relatively large integrals $\langle 3d_{z^2} | z | 2p_z \rangle$ governed by the Me $3d$ -O $2p$ σ bond and the relatively small ones $\langle 3d_{xz} | z | 2p_x \rangle$ and $\langle 3d_{xz} | x | 2p_z \rangle$ governed by the Me $3d$ -O $2p$ π bond. We make use of hydrogenlike radial-wave functions with the Clementi-Raimondi effective charges^{48,49} $Z_{\text{O}2p}^{\text{eff}} = 4.45$ and $Z_{\text{Me}3d}^{\text{eff}} = 10.53$. It is clearly seen that given typical cation-anion separations $\mathbf{R}_{\text{MeO}} \approx 4$ a.u., we arrive at values less than 0.1 a.u. even for the largest two-site integral. Reasonable estimate for the π bond integral from the paper by Katsura *et al.*⁹ should be $|I(\mathbf{R}_{dp})| \approx 0.01 \text{ \AA}$ that is 2 orders of magnitude less than that of the authors.

Relation between local and nonlocal contributions to electric polarization is believed to be determined by that of covalent and overlap effects. The local contribution is defined by pure covalent effects and prevails for large covalency, which is for

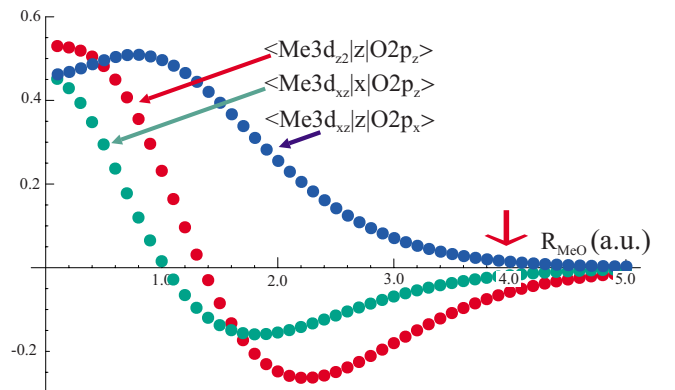


FIG. 2. (Color online) Two-site dipole matrix elements against Me $3d$ -O $2p$ separation. The arrow near 4 a.u. points to typical Me-O separations.

large t_{pd} and small E_{pd} , when $|t_{pd}/E_{pd}| > S_{pd}$. Neglecting the overlap effects we make the reliable estimates of nonlocal terms quite questionable.

Interestingly, the nonlocal, or overlap effects are usually missed in current calculations of electro-dipole transitions in 3d oxides, where one considers the electromagnetic field couples to the electrons via the standard Peierls phase transformation of the transfer integral,

$$\hat{t}_{ij} \rightarrow \hat{t}_{ij} e^{i(\Phi_j - \Phi_i)}, \quad (23)$$

$$(\Phi_j - \Phi_i) = -\frac{q}{\hbar c} \int_{\vec{R}_i}^{\vec{R}_j} \vec{A}(\vec{r}) d\vec{r}, \quad (24)$$

where \vec{A} is the vector potential, and integration runs over line binding the i and j sites (see, e.g., Ref. 50).

The effective electric polarization differs for the singlet and triplet pairings due to a respective singlet-triplet differ-

ence in the hybridization amplitudes $c_{\{m\}}(S\Gamma)$. Hence we may introduce an effective nonrelativistic *exchange-dipole* spin operator

$$\hat{\mathbf{P}}_s = \mathbf{\Pi}(\hat{\mathbf{s}}_1 \cdot \hat{\mathbf{s}}_2), \quad (25)$$

with an exchange-dipole moment

$$\mathbf{\Pi} = \langle \mathbf{P} \rangle_t - \langle \mathbf{P} \rangle_s, \quad (26)$$

which can be easily deduced from expressions (19) and (20).

Effective nonrelativistic exchange-dipole moment is determined by competitive local and nonlocal contributions of several configurations. To illustrate its common features, in particular, the crystal-field effects, the role played by correlations, and the bond geometry, we write out only one of the terms, that of local contribution of purely oxygen 020 configuration,

$$\mathbf{\Pi}_{020}^{\text{local}} = \frac{9|e|t_{pd\sigma}^4}{8} (\mathbf{R}_{01} + \mathbf{R}_{02}) \left[\frac{\sin^2 \theta}{8} \left(\frac{1}{\epsilon_x} + \frac{1}{\epsilon_y} \right)^2 \left[\frac{1}{E_t^2(p_x p_y)} - \frac{1}{E_s^2(p_x p_y)} \right] - \left\{ \left[\frac{\sin^2 \frac{\theta}{2}}{\epsilon_x E_s(p_x^2)} \right]^2 + \left[\frac{\cos^2 \frac{\theta}{2}}{\epsilon_y E_s(p_y^2)} \right]^2 \right\} \right], \quad (27)$$

where $E_s(p_{x,y}^2) = 2\epsilon_{x,y} + F_0 + \frac{4}{25}F_2$, $E_s(p_x p_y) = \epsilon_x + \epsilon_y + F_0 + \frac{1}{25}F_2$, and $E_t(p_x p_y) = \epsilon_x + \epsilon_y + F_0 - \frac{1}{5}F_2$ are the energies of the oxygen two-hole singlet (s) and triplet (t) configurations p_x^2, p_y^2 and $p_x p_y$, respectively, and F_0 and F_2 are the Slater integrals. We see that this vector is directed along the y axis regardless the $\delta_{1,2}$ angles and the resultant value depends strongly on the Cu₁-O-Cu₂ bond geometry and crystal-field effects. The latter determines the single hole energies both for O $2p$ and Cu $3d$ holes such as $\epsilon_{xy,xz}$ and $\epsilon_{x,y}$, which values are usually of the order of 1 and 1–3 eV,⁵¹ respectively. Given estimations for different parameters typical for cuprates⁵² ($t_{pd\sigma} \approx 1.5$ eV, $F_0 = 5$ eV, and $F_2 = 6$ eV), we can estimate a maximal value of $|\mathbf{\Pi}_{020}^{\text{local}}|_y$ as $0.01|e|\text{\AA} (\sim 10^3 \mu\text{C}/\text{m}^2)$. The local contributions to exchange-dipole moment seem to exceed the nonlocal ones, which are estimated as follows:

$$\mathbf{\Pi} \sim |e| \frac{t_{pd\sigma} t_{pd}}{E^2(pd)} \langle 2p_x | x | 3d_{x^2-y^2} \rangle \sim 0.001|e|\text{\AA}. \quad (28)$$

It is worth noting that for the collinear Cu₁-O-Cu₂ bonding both contributions vanish. As a whole, the exchange-dipole moment vanishes if the M₁-O-M₂ cluster has a center of symmetry.

Concluding the section it is worth to remind we addressed only the charge-density redistribution effects for Cu $3d$ and O $2p$ states and neglect a direct electronic polarization effects for the both metal and anion ions. These effects can be incorporated to the theory, if other orbitals, e.g., ns for oxygen ion, will be included to the initial orbital basis set. Al-

ternative approach may be applied to proceed with these effects if we turn to a generalized shell model.⁵³

IV. RELATIVISTIC MECHANISM OF SPIN-DEPENDENT ELECTRIC POLARIZATION

At variance with a scenario by Katsura *et al.*,⁹ we have applied a conventional procedure to derive an effective *spin operator* for a relativistic contribution to the electric-dipole moment in the three-site M₁-O-M₂ system like a technique suggested in Refs. 40 and 41 to derive expressions for the Cu and O spin-orbital contributions to the Dzyaloshinsky-Moriya coupling in cuprates.

The spin-orbital coupling V_{SO} for copper and oxygen ions drives the singlet-triplet mixing, which gives rise to a relativistic contribution to electric polarization deduced from an effective spin operator or an *exchange-relativistic-dipole* moment,

$$\hat{\mathbf{P}} = \frac{1}{2} \vec{\mathbf{\Pi}} \hat{\mathbf{T}} = \vec{\mathbf{\Pi}} [\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2], \quad (29)$$

where $\Pi_{ij} = -i \langle \Psi_{00} | P_i | \Psi_{1j} \rangle$ is an exchange-relativistic-dipole tensor. It is easy to see that this quantity has a clear physical meaning to be in fact a dipole matrix element for a singlet-triplet electro-dipole transition in our three-site cluster.^{54–56} First of all we should take into account the singlet-triplet mixing effects for the ground-state manifold, which are governed by Dzyaloshinsky-Moriya interactions,

$$\begin{aligned}\Phi_S &\rightarrow \Psi_S = \Phi_S + \frac{i}{2J}(\mathbf{D} \cdot \Phi_T), \\ \Phi_T &\rightarrow \Psi_T = \Phi_T + \frac{i}{2J}\mathbf{D}\Phi_S,\end{aligned}\quad (30)$$

where we make use of Cartesian vector to denote the spin triplet function. Then the components of the $\tilde{\mathbf{\Pi}}$ tensor can be found by projecting $\hat{\mathbf{P}}$ on the spin states

$$\Pi_{ij} = -i\langle \Psi_S | P_i | \Psi_{Tj} \rangle = (\langle \Phi_S | P_i | \Phi_S \rangle - \langle \Phi_T | P_i | \Phi_T \rangle) \frac{D_i}{J}, \quad (31)$$

In other words, we arrive at a simple form of exchange-relativistic-dipole moment as

$$\hat{\mathbf{P}} = -\frac{1}{J}\mathbf{\Pi}(\mathbf{D} \cdot [\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2]). \quad (32)$$

It is worth noting that this vector lies in $\text{Cu}_1\text{-O-Cu}_2$ plane and its direction does not depend on spin configuration. The singlet-triplet overlap density $\Psi_S^* \Psi_{Tj}$ in matrix element $\langle \Psi_S | P_i | \Psi_{Tj} \rangle$ has maxima at the points $\mathbf{R}_{1,2,3}$, where the spin-orbital coupling is localized. It means that we may pick up the leading local term in Eq. (32),

$$\hat{\mathbf{P}}^{\text{local}} = -\frac{1}{J} \sum_n \mathbf{\Pi}_n (\mathbf{D}_n \cdot [\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2]), \quad (33)$$

where $\mathbf{\Pi}_n$ and \mathbf{D}_n are local ($\text{Cu}_{1,2}, \text{O}$) contributions to the exchange-dipole moment $\mathbf{\Pi}$ and Dzyaloshinsky vector \mathbf{D} , respectively. For a rough estimate we may use a relation $D/J \sim \Delta g/g$, where g is the gyromagnetic ratio and Δg is its deviation from the value for a free electron.⁵⁷

Another contribution to $\Pi_{ij} = -i\langle \Psi_S | P_i | \Psi_{Tj} \rangle$ we obtain, if make use of singlet and triplet hybrid functions $\Psi_{101;SM}$ perturbed by spin-orbital coupling as follows:⁴⁰

$$\Pi_{ij} = -i \frac{\xi_{3d}}{2} \sum_{\alpha, \beta} \frac{\langle d_{x^2-y^2} | l_j | d_\beta \rangle}{\epsilon_\beta} \left[t_{p_\alpha d_\beta} \left(\frac{1}{E_t(dp_\alpha) - \epsilon_\beta} - \frac{1}{E_s(dp_\alpha) - \epsilon_\beta} \right) \langle 2p_\alpha | x_i | 3d_{x^2-y^2}^{(1)} \rangle + t_{p_\alpha d_{x^2-y^2}} \left(\frac{1}{E_t(dp_\alpha)} - \frac{1}{E_s(dp_\alpha)} \right) \langle 2p_\alpha | x_i | 3d_\beta^{(1)} \rangle \right]. \quad (38)$$

Thus we arrive at nonzero Π_{xz} and Π_{yz} components provided $d^* = d_{xy}$ and Π_{zy} component provided $d^* = d_{xz}$ if to account for the nonvanishing overlap dipole matrix elements $\langle 2p_\alpha | x_\alpha | 3d_{x^2-y^2} \rangle$ and $\langle 2p_x | z | 3d_{xz} \rangle$. A reasonable estimate for the maximal value of Π_{ij} can be made if we address relation (28): $|\Pi_{ij}| \sim 0.1 \mathbf{\Pi} \sim 10^{-4} |e| \text{\AA}$.

It should be noted that for the contribution of bare configurations other than that of ground-state 101 we may use a simplified expression,⁴⁰

$$\tilde{\Psi}_{101;SM} = \Phi_{101;SM} + \sum_{\{n\}\Gamma} c_{\{n\}\Gamma}^{(2S+1)\Gamma} \left[\Phi_{\{n\};\Gamma SM} - \sum_{S'M'\Gamma'} \frac{\langle \Phi_{\{n\};\Gamma'S'M'} | V_{so} | \Phi_{\{n\};\Gamma SM} \rangle}{E_{2S'+1\Gamma'}(\{n\}) - E_{2S+1\Gamma_0}(101)} \Phi_{\{n\};\Gamma'S'M'} \right]. \quad (39)$$

$$\begin{aligned}\tilde{\Psi}_{101;SM} &= \Psi_{101;SM} \\ &- \sum_{\{n\}S'\Gamma'} \frac{\langle \Psi_{\{n\};\Gamma'S'M'} | V_{so} | \Psi_{101;SM} \rangle}{E_{2S'+1\Gamma'}(\{n\}) - E_{2S+1\Gamma_0}(101)} \Psi_{\{n\};\Gamma'S'M'}.\end{aligned}\quad (34)$$

Notice that $\{n\}$ for the hybrid function $\Psi_{\{n\};\Gamma'S'M'}$ points only to a bare or generative ionic configuration.

For an illustration we address the $3d_{x^2-y^2} \rightarrow 3d^*$ excitations driven by $V_{SO}(\text{Cu}_1)$ within ground-state 101 configuration. The proper contribution to the singlet-triplet matrix element of \mathbf{P} can be written as follows:

$$\begin{aligned}\Pi_{ij} &= -i\langle \tilde{\Psi}_{101;00} | P_i | \tilde{\Psi}_{101;1j} \rangle \\ &= i\xi_{3d} \sum_{d^*} \frac{\langle d_{x^2-y^2} | \hat{l}_j | d^* \rangle}{\epsilon_{d^*}} (\langle \Psi_{1^*01;10} | P_i | \Psi_{101;10} \rangle \\ &\quad - \langle \Psi_{101;00} | P_i | \Psi_{1^*01;00} \rangle),\end{aligned}\quad (35)$$

where 1^*01 labels the 101 configuration with $d_{x^2-y^2}$ hole on Cu_1 site replaced by d^* hole with the energy ϵ_{d^*} . Interestingly the dipole matrix elements in brackets determine the transition probabilities for electro-dipole transition $d_{x^2-y^2} \rightarrow d^*$ on Cu_1 site induced by the covalent and exchange effects in the three-site cluster. Their difference can be related to a so-called exchange-dipole transition moment,¹²

$$\hat{\mathbf{P}}(d \rightarrow d^*) = \mathbf{\Pi}(d \rightarrow d^*)(\hat{\mathbf{s}}_1 \cdot \hat{\mathbf{s}}_2), \quad (36)$$

introduced first by Tanabe *et al.*⁵ to explain the magnon side bands in $3d$ magnetic insulators,

$$(\langle \Psi_{1^*01;10} | \mathbf{P} | \Psi_{101;10} \rangle - \langle \Psi_{101;00} | \mathbf{P} | \Psi_{1^*01;00} \rangle) = \mathbf{\Pi}(d_{x^2-y^2} \rightarrow d^*). \quad (37)$$

Interestingly the local contribution to the exchange-dipole transition moment vanishes due to the orthogonality conditions, whereas the nonlocal effects give rise both to the in-plane and out-of-plane components both of this vector and of the net relativistic electric polarization. Indeed, the nonlocal contribution of $d_{x^2-y^2} \rightarrow d^*$ spin-orbital excitations on Cu_1 site to the $\tilde{\mathbf{\Pi}}$ tensor can be written as follows:

However, on closer examination we arrive at vanishing contribution of these terms to exchange-relativistic-dipole moment.

Thus the Dzyaloshinsky-Moriya-type exchange-relativistic-dipole moment (32) is believed to be a dominant relativistic contribution to electric polarization in $\text{Cu}_1\text{-O-Cu}_2$ cluster. It is worth noting that the exchange-dipole moment operator (25) and exchange-relativistic-dipole moment operator (32) are obvious counterparts of the Heisenberg symmetric exchange and Dzyaloshinsky-Moriya antisymmetric exchange, respectively. Hence, the Moriya like relation $|\Pi_{ij}| \sim \Delta g/g |\mathbf{\Pi}|$ seems to be a reasonable estimation for the resultant relativistic contribution to electric polarization in $\text{M}_1\text{-O-M}_2$ clusters. At present, it is a difficult and, probably, hopeless task to propose a more reliable and so physically clear estimation. Taking into account the typical value of $\Delta g/g \sim 0.1$, we can estimate the maximal value of $|\Pi_{ij}|$ as $10^{-3}|e|\text{\AA}$ ($\sim 10^2 \mu\text{C}/\text{m}^2$) that points to the exchange-relativistic mechanism to be a weak contributor to a giant multiferroicity with ferroelectric polarization of the order of $10^3 \mu\text{C}/\text{m}^2$ as in TbMnO_3 ,¹ though it may be a noticeable contributor in, e.g., $\text{Ni}_3\text{V}_2\text{O}_8$.²²

V. PARITY BREAKING EXCHANGE COUPLING AND EXCHANGE-INDUCED ELECTRIC POLARIZATION

Along with many advantages of the three-site cluster model, it has a clear imperfection not uncovering a direct role played by exchange coupling as a driving force to induce a spin-dependent electric polarization. Below we will address an alternative approach starting with a spin center such as MeO_n cluster in $3d$ oxides exchange coupled with a magnetic surroundings. Then the magnetoelectric coupling can be related to the spin-dependent electric fields generated by spin surroundings in a magnetic crystal. In this connection we should point out some properties of exchange interaction that usually are missed in conventional treatment of Heisenberg exchange coupling. Following after paper by Tanabe *et al.*⁵ (see also Ref. 12), we start with a simple introduction to exchange-induced electric polarization effects.

Let address the one-particle (electron/hole) center in a crystallographically centrosymmetric position of a magnetic crystal. Then all the particle states can be of definite spatial parity, even (g) or odd (u), respectively. Having in mind the $3d$ centers we will assume the even-parity ground state $|g\rangle$. For simplicity we restrict ourselves by only one excited odd-parity state $|u\rangle$. The exchange coupling with surrounding spins can be written as follows:

$$\hat{V}_{ex} = \sum_n \hat{I}(\mathbf{R}_n)(\mathbf{s} \cdot \mathbf{S}_n), \quad (40)$$

where $\hat{I}(\mathbf{R}_n)$ is an orbital operator with a matrix

$$\hat{I}(\mathbf{R}_n) = \begin{pmatrix} I_{gg}(\mathbf{R}_n) & I_{gu}(\mathbf{R}_n) \\ I_{ug}(\mathbf{R}_n) & I_{uu}(\mathbf{R}_n) \end{pmatrix}. \quad (41)$$

The crystallographic centrosymmetry condition requires that

$$\sum_n I_{gu}(\mathbf{R}_n) = \sum_n I_{ug}(\mathbf{R}_n) = 0. \quad (42)$$

The parity-breaking off-diagonal part of exchange coupling can lift the center of symmetry and mix $|g\rangle$ and $|u\rangle$ states,

$$|g\rangle \rightarrow |g\rangle + c_{gu}|u\rangle, \quad (43)$$

where

$$c_{gu} = \Delta_{ug}^{-1} \sum_n I_{gu}(\mathbf{R}_n)(\mathbf{s} \cdot \mathbf{S}_n), \quad (44)$$

with $\Delta_{ug} = \epsilon_u - \epsilon_g$. In turn, it results in a nonzero electric-dipole polarization of the ground state,

$$\mathbf{P} = 2c_{gu} \langle g | e\mathbf{r} | u \rangle = \sum_n \mathbf{\Pi}_n (\mathbf{s} \cdot \mathbf{S}_n), \quad (45)$$

where $\mathbf{d} = e\mathbf{r}$ is a dipole moment operator,

$$\mathbf{\Pi}_n = 2I_{gu}(\mathbf{R}_n) \frac{\langle g | e\mathbf{r} | u \rangle}{\Delta_{ug}}. \quad (46)$$

It is easy to see that in frames of a mean-field approximation the nonzero dipole moment shows up only for spin-noncentrosymmetric surrounding, that is, if the condition $\langle \mathbf{S}(\mathbf{R}_n) \rangle = \langle \mathbf{S}(-\mathbf{R}_n) \rangle$ is broken. For isotropic bilinear exchange coupling this implies a spin frustration.

Kinetic contributions to conventional diagonal and unconventional off-diagonal exchange integrals can be obtained if one assumes that the surrounding spins are formed by a single electron localized in the same $|g\rangle$ state,

$$I_{gg}(n) = \frac{t_{gg}^2(n)}{\Delta_{gg}}, \quad (47)$$

$$I_{ug}(n) = \frac{1}{2} t_{gg}(n) t_{ug}(n) \left(\frac{1}{\Delta_{gg}} + \frac{1}{\Delta_{gg} - \Delta_{ug}} \right), \quad (48)$$

where t_{gg} is a transfer integral between ground $|g\rangle$ states of the neighboring ions, while t_{ug} is a transfer integral between ground $|g\rangle$ state of the neighboring ion and $|u\rangle$ state of the central ion, and Δ_{gg} is the energy of the charge transfer between ground $|g\rangle$ states of the neighboring ions.

It should be noted that at variance with DM-type mechanism the direction of the exchange-induced dipole moment for i, j pair does not depend on the direction of spins \mathbf{S}_i and \mathbf{S}_j . In other words, the spin-correlation factor $(\mathbf{S}_i \cdot \mathbf{S}_j)$ modulates a pre-existing dipole moment $\mathbf{\Pi}$ in which the direction and value depend on the $\text{Me}_i\text{-O-Me}_j$ bond geometry and orbitals involved in exchange coupling.

The net exchange induced polarization of the magnetic crystal depends both on crystal symmetry and spin structure. The allowed direction of the average \mathbf{P} in crystal can be unambiguously determined by symmetry analysis, for instance, \mathbf{P} should be parallel to all the mirror planes and glide planes.

The magnitude of off-diagonal exchange integrals can sufficiently exceed that of conventional diagonal exchange integral mainly due to a smaller value of the energy separa-

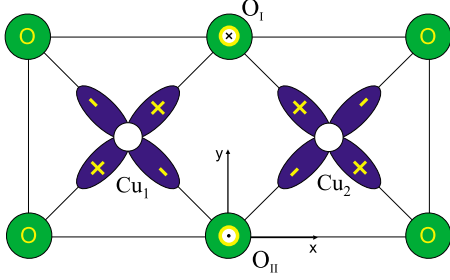


FIG. 3. (Color online) The fragment of a typical edge-shared CuO_2 chain. Note the antiparallel orientation of the oxygen Dzyaloshinsky vectors directed perpendicular to the chain plane.

tion $\Delta_{gg} - \Delta_{ug}$ as compared with Δ_{gg} and larger value of transfer integral t_{ug} as compared with t_{gg} due to the purely oxygen character of odd-parity $|u\rangle$ state. Given reasonable estimations for off-diagonal exchange integrals $I_{ug} \approx 0.1$ eV, g - u energy separation $\Delta_{gu} \approx 2$ eV, dipole matrix element $|\langle g | e\mathbf{r} | u \rangle| \approx 0.1$ Å, and spin function $|\langle (\mathbf{s} \cdot \mathbf{S}_n) \rangle| \approx 1$, we arrive at estimation of maximal value of electric polarization: $P \approx 10^4$ $\mu\text{C}/\text{m}^2$. This estimate points to exchange-induced electric polarization to be a potentially the most significant source of magnetoelectric coupling for new giant multiferroics.

It is worth noting that the exchange-induced polarization effect we consider is particularly strong for the $3d$ clusters such as MeO_n with the intensive low-lying electro-dipole allowed transition $|g\rangle \rightarrow |u\rangle$, which both initial and final states are coupled due to a strong exchange interaction with a spin surroundings. This simple rule may be practically used to seek new multiferroic materials.

The parity-breaking exchange coupling can produce a strong electric polarization of oxygen ions in $3d$ oxides, which can be written as follows:

$$\mathbf{P}_O = \sum_n \Pi_n \langle (\mathbf{S}_O) \cdot \mathbf{S}_n \rangle, \quad (49)$$

where \mathbf{S}_n are spins of surrounding $3d$ ions, and $\langle \mathbf{S}_O \rangle \propto \sum_n \vec{I}_n \mathbf{S}_n$ is a spin polarization of oxygen ion due to surrounding $3d$ ions with I_n as the exchange coupling tensor. It seems the oxygen exchange-induced electric polarization of purely electron origin is too little appreciated in the current pictures of multiferroicity in $3d$ oxides.

VI. LACK OF SPIN-DEPENDENT ELECTRIC POLARIZATION IN EDGE-SHARING CuO_2 CHAINS

According to the phenomenological theory of Mostovoy¹⁰ and microscopic model of Katsura *et al.*,⁹ the spin-spiral chain cuprates LiCuVO_4 and LiCu_2O_2 seem to be prototypical examples of 1D spiral-magnetic ferroelectrics revealing the relativistic mechanism of “ferroelectricity caused by spin currents.” Indeed, the net nonrelativistic polarization of a spin chain formed by $\text{Me } 3d$ ions even with no center of symmetry in between can be written as follows:⁵

$$\mathbf{P}_{\text{eff}} = \Pi \sum_{j=\text{even}} [(\mathbf{S}_j \cdot \mathbf{S}_{j+1}) - (\mathbf{S}_j \cdot \mathbf{S}_{j-1})]. \quad (50)$$

Hence for a simple plane spiral ordering, both the on-site and net polarizations vanish, while the spin-current mechanism^{9,10} directly points to a nonzero polarization concomitant spin-spiral order. However, a detailed analysis of relativistic effects for the system of e_g holes in a perfect chain structure of edge-shared CuO_4 plaquettes as in LiCuVO_4 shows that the in-chain spin current does not produce an electric polarization. First of all we should point to a high symmetry of $\text{Cu}_1\text{-O-Cu}_2$ bonds in edge-sharing CuO_2 chains (see Fig. 3) that results in a full cancellation of a net Dzyaloshinsky vector, though the partial oxygen contributions survive being of opposite sense.^{40,41} Cancellation of the Dzyaloshinsky-Moriya coupling in perfect edge-sharing CuO_2 chains implies immediately the same effect for the net exchange-relativistic-dipole moment \mathbf{P} . Indeed, the dominant contribution to the exchange-relativistic-dipole moment for isolated $\text{Cu}_1\text{-O-Cu}_2$ bonds is governed straightforwardly by the respective Dzyaloshinsky vectors; hence their cancellation for $\text{Cu}_1\text{-O}_I\text{-Cu}_2$ and $\text{Cu}_1\text{-O}_{II}\text{-Cu}_2$ bonds in edge-sharing CuO_2 chain geometry (see Fig. 3) leads to the vanishing of the exchange-relativistic electric polarization. It seems that small nonlocal terms addressed in Sec. IV could survive; however, the symmetry considerations point to their vanishing as well. Indeed, both the xz and yz components of the Π_{ij} tensor differ in sign for the $\text{Cu}_1\text{-O}_I\text{-Cu}_2$ and $\text{Cu}_1\text{-O}_{II}\text{-Cu}_2$ bonds, while the zy components differ in sign for the contribution of $V_{SO}(\text{Cu}_1)$ and $V_{SO}(\text{Cu}_2)$. Thus we may state that the edge-shared CuO_4 plaquettes chain arrangement appears to be robust regarding the proper spin-induced electric polarization both of the nonrelativistic and relativistic origins. It means that we should look for the origin of puzzling multiferroicity observed in LiCuVO_4 and LiCu_2O_2 somewhere within the out-of-chain stuff.^{58,59}

VII. CONCLUSION

We have considered a microscopic theory of spin-dependent electric polarization in $3d$ oxides starting with a generic three-site two-hole cluster. A perturbation scheme realistic for $3d$ oxides is applied, which implies the quenching of orbital moments by low-symmetry crystal field, strong intra-atomic correlations, the pd -transfer effects, and rather small spin-orbital coupling. An effective spin operator of the electric-dipole moment is deduced incorporating both nonrelativistic $\propto (\hat{\mathbf{s}}_1 \cdot \hat{\mathbf{s}}_2)$ and relativistic $\propto [\hat{\mathbf{s}}_1 \times \hat{\mathbf{s}}_2]$ terms. The nonrelativistic exchange-dipole moment is mainly governed by the effects of the redistribution of the local on-site charge density due to pd covalency and exchange coupling. The relativistic exchange-dipole moment is mainly stems from the nonrelativistic one due to the perturbation effect of Dzyaloshinsky-Moriya coupling and is estimated to be a weak contributor to the electric polarization observed in the most of $3d$ multiferroics. Our description is focused on $\text{Cu}_1\text{-O-Cu}_2$ clusters typical for different cuprates, however, the generalization of the results onto the $\text{M}_1\text{-O-M}_2$ clusters in other $3d$ oxides is trivial. The approach realized in the paper

has much in common with the mechanism of the bond- and site-centered charge order competition (see, e.g., Ref. 60) though we start with the elementary pd charge transfer rather than the dd charge transfer. An alternative approach to the derivation of the spin-dependent electric polarization is considered, which is based on the parity-breaking exchange coupling and exchange induced polarization. We point to the oxygen electric polarization effects due to an exchange-induced electric fields to be an important participant of the multiferroic phenomenon. In any case, the nonrelativistic electronic polarization mechanism is believed to govern the multiferroic behavior in $3d$ oxides.

It is shown that the perfect chain structure of edge-shared CuO_4 plaquettes as in LiCuVO_4 or LiCu_2O_2 appears to be robust regarding the proper spin-induced electric polarization both of nonrelativistic and relativistic origin. In other words, in contrast with the predictions of the model by Katsura

et al.,⁹ the in-chain spin current does not produce an electric polarization. Hence the puzzling multiferroicity observed in LiCuVO_4 and LiCu_2O_2 (Refs. 18 and 21) originates from an out-of-chain stuff. Clearly, the model approach applied can provide only a semiquantitative description of magnetoelectric effects in $3d$ oxides. More correct account for the overlap, or nonorthogonality effects and those produced by non-magnetic surroundings of the three-site two-hole cluster are needed.

ACKNOWLEDGMENTS

RFBR is acknowledged for financial support through Grants No. 06-02-17242, No. 07-02-96047, and No. 08-02-00633. A.S.M. would like to thank Leibniz-Institut für Festkörper- und Werkstofforschung Dresden, where part of this work was done, for hospitality.

-
- ¹T. Kimura, N. Goto, H. Shintani, T. Arima, and Y. Tokura, *Nature (London)* **426**, 55 (2003); N. Hur, S. Park, P. A. Sharma, J. S. Ahn, S. Guha, and S.-W. Cheong, *ibid.* **429**, 392 (2004).
- ²M. Fiebig, *J. Phys. D* **38**, R123 (2005).
- ³D. I. Khomskii, *J. Magn. Magn. Mater.* **306**, 1 (2006).
- ⁴D. N. Astrov, *Zh. Eksp. Teor. Fiz.* **37**, 881 (1960) [*Sov. Phys. JETP* **10**, 628 (1960)].
- ⁵Y. Tanabe, T. Moriya, and S. Sugano, *Phys. Rev. Lett.* **15**, 1023 (1965).
- ⁶L. C. Chapon, P. G. Radaelli, G. R. Blake, S. Park, and S.-W. Cheong, *Phys. Rev. Lett.* **96**, 097601 (2006).
- ⁷I. A. Sergienko, C. Sen, and E. Dagotto, *Phys. Rev. Lett.* **97**, 227204 (2006).
- ⁸J. J. Betouras, G. Giovannetti, and J. van den Brink, *Phys. Rev. Lett.* **98**, 257602 (2007).
- ⁹H. Katsura, N. Nagaosa, and A. V. Balatsky, *Phys. Rev. Lett.* **95**, 057205 (2005).
- ¹⁰M. Mostovoy, *Phys. Rev. Lett.* **96**, 067601 (2006).
- ¹¹I. A. Sergienko and E. Dagotto, *Phys. Rev. B* **73**, 094434 (2006).
- ¹²V. V. Druzhinin and A. S. Moskvin, *Sov. Phys. Solid State* **11**, 1088 (1969).
- ¹³Shu Tanaka, Hosho Katsura, and Naoto Nagaosa, *Phys. Rev. Lett.* **97**, 116404 (2006).
- ¹⁴C. Jia, S. Onoda, N. Nagaosa, and J. H. Han, *Phys. Rev. B* **74**, 224444 (2006).
- ¹⁵C. Jia, S. Onoda, N. Nagaosa, and J. H. Han, *Phys. Rev. B* **76**, 144424 (2007).
- ¹⁶C. D. Hu, *Phys. Rev. B* **75**, 172106 (2007).
- ¹⁷T. Nakajima, S. Mitsuda, S. Kanetsuki, K. Prokes, A. Podlesnyak, H. Kimura, and Y. Noda, *J. Phys. Soc. Jpn.* **76**, 043709 (2007).
- ¹⁸Y. Naito, K. Sato, Y. Yasui, Yu. Kobayashi, Yo. Kobayashi, and M. Sato, *J. Phys. Soc. Jpn.* **76**, 023708 (2007).
- ¹⁹Y. Yasui, Y. Naito, K. Sato, T. Moyoshi, M. Sato, and K. Kakurai, *J. Phys. Soc. Jpn.* **77**, 023712 (2008).
- ²⁰F. Schrettle, S. Krohns, P. Lunkenheimer, J. Hemberger, N. Butgen, H.-A. Krug von Nidda, A. V. Prokofiev, and A. Loidl, *Phys. Rev. B* **77**, 144101 (2008).
- ²¹S. Park, Y. J. Choi, C. L. Zhang, and S.-W. Cheong, *Phys. Rev. Lett.* **98**, 057601 (2007).
- ²²G. Lawes, A. B. Harris, T. Kimura, N. Rogado, R. J. Cava, A. Aharony, O. Entin-Wohlman, T. Yildirim, M. Kenzelmann, C. Broholm, and A. P. Ramirez, *Phys. Rev. Lett.* **95**, 087205 (2005).
- ²³It is worth noting that in the later papers (see Refs. 14 and 16), the authors proceed with a more reasonable approach to the spin-orbital coupling.
- ²⁴The improper perturbation scheme in Ref. 9 generates an opinion that the “spin-current” mechanism has nothing to do with the Dzyaloshinsky-Moriya interaction (see, e.g. Ref. 25).
- ²⁵G. Nénert and T. T. M. Palstra, *J. Phys.: Condens. Matter* **19**, 406213 (2007).
- ²⁶A. B. Harris, T. Yildirim, A. Aharony, and O. Entin-Wohlman, *Phys. Rev. B* **73**, 184433 (2006).
- ²⁷C. R. dela Cruz, F. Yen, B. Lorenz, M. M. Gospodinov, C. W. Chu, W. Ratcliff, J. W. Lynn, S. Park, and S. W. Cheong, *Phys. Rev. B* **73**, 100406(R) (2006).
- ²⁸G. R. Blake, L. C. Chapon, P. G. Radaelli, S. Park, N. Hur, S.-W. Cheong, and J. Rodriguez-Carvajal, *Phys. Rev. B* **71**, 214402 (2005).
- ²⁹I. Kagomiya, S. Matsumoto, K. Kohn, Y. Fukuda, T. Shoubu, H. Kimura, Y. Noda, and N. Ikeda, *Ferroelectrics* **286**, 167 (2003).
- ³⁰D. Bloch, *J. Phys. Chem. Solids* **27**, 881 (1966).
- ³¹R. Valdés Aguilar, A. B. Sushkov, S. Park, S.-W. Cheong, and H. D. Drew, *Phys. Rev. B* **74**, 184404 (2006).
- ³²B. G. Dick and A. W. Overhauser, *Phys. Rev.* **112**, 90 (1958).
- ³³S. Picozzi, K. Yamauchi, B. Sanyal, I. A. Sergienko, and E. Dagotto, *Phys. Rev. Lett.* **99**, 227201 (2007).
- ³⁴C. Wang, G. Guo, and L. He, *Phys. Rev. Lett.* **99**, 177202 (2007).
- ³⁵G. Giovanetti and J. Van den Brink, arXiv:0802.0653 (unpublished).
- ³⁶H. J. Xiang and M.-H. Whangbo, *Phys. Rev. Lett.* **99**, 257203 (2007).
- ³⁷L. M. Sandratskii, *Phys. Rev. B* **64**, 134402 (2001).
- ³⁸V. V. Mazurenko and V. I. Anisimov, *Phys. Rev. B* **71**, 184434

- (2005).
- ³⁹V. V. Mazurenko, S. L. Skornyakov, A. V. Kozhevnikov, F. Mila, and V. I. Anisimov, *Phys. Rev. B* **75**, 224408 (2007).
- ⁴⁰A. S. Moskvin, *JETP* **104**, 911 (2007).
- ⁴¹A. S. Moskvin, *Phys. Rev. B* **75**, 054505 (2007).
- ⁴²W. Low, in *Paramagnetic Resonance in Solids*, Solid State Physics Suppl II (Academic, New York, 1960).
- ⁴³T. Yildirim, A. B. Harris, O. Entin-Wohlman, and A. Aharony, *Phys. Rev. Lett.* **73**, 2919 (1994); T. Yildirim, A. B. Harris, A. Aharony, and O. Entin-Wohlman, *Phys. Rev. B* **52**, 10239 (1995).
- ⁴⁴S. Tornow, O. Entin-Wohlman, and A. Aharony, *Phys. Rev. B* **60**, 10206 (1999).
- ⁴⁵G. Herzberg, *Proc. R. Soc. London, Ser. A* **248**, 309 (1958); L. Veseth, *J. Phys B* **16**, 2713 (1983).
- ⁴⁶S. Renold, S. Pliberšek, E. P. Stoll, T. A. Claxton, and P. F. Meier, *Eur. Phys. J. B* **23**, 3 (2001).
- ⁴⁷S. Kotochigova, Z. H. Levine, E. L. Shirley, M. D. Stiles, and C. W. Clark, *Phys. Rev. A* **55**, 191 (1997); **56**, 5191(E) (1997).
- ⁴⁸E. Clementi and D. I. Raimondi, *J. Chem. Phys.* **38**, 2686 (1963); E. Clementi, D. I. Raimondi, and W. P. Reinhardt, *ibid.* **47**, 1300 (1967).
- ⁴⁹We make use of Z_{Me3d}^{eff} typical for Mn^{3+} ion as in Ref. 14 to compare our calculations with the estimates made in Refs. 9, 14, and 16 for manganites.
- ⁵⁰K. H. Ahn and A. J. Millis, *Phys. Rev. B* **61**, 13545 (2000).
- ⁵¹A. S. Moskvin, R. Neudert, M. Knupfer, J. Fink, and R. Hayn, *Phys. Rev. B* **65**, 180512(R) (2002).
- ⁵²H. Eskes and G. A. Sawatzky, *Phys. Rev. B* **43**, 119 (1991).
- ⁵³A. S. Moskvin and Yu. D. Panov, *Phys. Rev. B* **68**, 125109 (2003).
- ⁵⁴Singlet-triplet transitions in the DM coupled pairs of $3d$ ions have been observed by far-infrared spectroscopy in α' - NaV_2O_5 (Ref. 55) and $SrCu_2(BO_3)_2$ (Ref. 56), though the author's interpretation was based on the phonon activated DM coupling mechanism.
- ⁵⁵T. R  m, D. H  vonen, U. Nagel, Y.-J. Wang, and R. K. Kremer, *Phys. Rev. B* **69**, 144410 (2004).
- ⁵⁶T. R  m, D. H  vonen, U. Nagel, J. Hwang, T. Timusk, and H. Kageyama, *Phys. Rev. B* **70**, 144417 (2004).
- ⁵⁷T. Moriya, *Phys. Rev. Lett.* **4**, 228 (1960); *Phys. Rev.* **120**, 91 (1960).
- ⁵⁸The unconventional multiferroic behavior of $LiCuVO_4$ and $LiCu_2O_2$ is related with a nonstoichiometry in these cuprates and an exchange-induced electric polarization on the Cu^{2+} centers substituting for Li ions in $LiCuVO_4$ and Cu^{1+} ions in $LiCu_2O_2$ (Ref. 59).
- ⁵⁹A. S. Moskvin and S.-L. Drechsler, *Europhys. Lett.* **81**, 57004 (2008); A. S. Moskvin, Yu. D. Panov, and S.-L. Drechsler, arXiv:0801.1975 (unpublished).
- ⁶⁰D. V. Efremov, J. van den Brink, and D. I. Khomskii, *Nat. Mater.* **3**, 853 (2004).