

Fermi surfaces, electron-hole asymmetry, and correlation kink in a three-dimensional Fermi liquid LaNiO_3

R. Eguchi,^{1,2,*} A. Chainani,¹ M. Taguchi,¹ M. Matsunami,¹ Y. Ishida,¹ K. Horiba,¹ Y. Senba,³ H. Ohashi,³ and S. Shin^{1,2}

¹RIKEN SPring-8 Center, Sayo-cho, Sayo-gun, Hyogo 679-5148, Japan

²Institute for Solid State Physics, University of Tokyo, Kashiwanoha, Kashiwa, Chiba 277-8581, Japan

³JASRI/SPring-8, Sayo-cho, Sayo-gun, Hyogo 679-5198, Japan

(Received 10 December 2008; revised manuscript received 3 February 2009; published 23 March 2009)

We report the three-dimensional (3D) momentum-resolved soft x-ray photoemission spectroscopy of the Fermi liquid LaNiO_3 . The out-of-plane and in-plane cuts of the 3D electron- and hole-Fermi surfaces (FSs) are observed by energy- and angle-dependent photoemission measurements. The energy bands forming the electron FS suggest an ω^2 dependence of the imaginary part of the self-energy and a “correlation kink” at an energy scale of 0.25 eV. In contrast, the bands which form nesting character hole FSs do not show kinks and match local-density approximation calculations. The results indicate a momentum-dependent mass renormalization, leading to electron-hole asymmetry in strongly correlated LaNiO_3 .

DOI: [10.1103/PhysRevB.79.115122](https://doi.org/10.1103/PhysRevB.79.115122)

PACS number(s): 71.18.+y, 71.30.+h, 79.60.-i

I. INTRODUCTION

Transition-metal perovskite oxides provide the widest range of correlation-derived phenomena such as superconductivity, metal-insulator transitions (MITs), magnetic ordering, colossal magnetoresistance, etc.¹ While momentum-resolved studies of the two-dimensional high- T_c cuprates and other low-dimensional correlated materials have revealed novel aspects of their electronic structure and Fermi surfaces (FSs),² there is no report of a FS study of a three-dimensional (3D) correlated oxide. Recent studies have established that oxide films with three-dimensional electronic structures are fertile ground for discovering novel properties for device applications, such as interfacial metallicity, carrier-controlled transparent ferromagnetism, giant thermoelectricity, etc.³⁻⁵ These engineered properties arise from correlated electrons, as evidenced from momentum (k)-averaged experiments of transport, magnetism, thermodynamics, etc. However, there is no momentum-resolved study to date showing an ω^2 dependence of the imaginary part of the self-energy for a 3D Fermi liquid.^{1,2,6} Among the perovskite oxides, the series $R\text{NiO}_3$ (R : rare earth) is well known to show interesting behavior such as MITs, spin, and charge orderings. LaNiO_3 with a trivalent Ni^{3+} ($t_{2g}^6 e_g^1$) is the reference material of the series, crystallizing in a 3D nearly cubic structure with a small rhombohedral distortion ($\beta=90.41^\circ$). It exhibits enhanced Pauli paramagnetic metal behavior down to low temperature (T). LaNiO_3 undergoes an oxygen vacancy-controlled correlated metal to antiferromagnetic insulator transition, while the other members (e.g., $R=\text{Pr}$, Nd , and Sm) show MIT as a function of T .^{7,8} The T -dependent MIT coupled antiferromagnetic transition results in a $(h/2\ 0\ 1/2)$ reflection due to charge order (more precisely, charge disproportionation of the type $\text{Ni}^{3+\delta}\text{-Ni}^{3-\delta}$) and not due to orbital ordering, as was recently characterized by resonant soft and hard x-ray scatterings.⁹ Interestingly, the magnetic susceptibility of the entire series in the metallic phase is that of an enhanced Pauli metal due to the NiO_3 array and far from a Stoner-type ferromagnetic instability.^{8,10} The specific heat and susceptibility data, as well as T^2 de-

pendence of resistivity of LaNiO_3 indicate that this compound is well described as a strongly correlated system close to a MIT.¹⁰⁻¹² An enhanced effective mass ($m^* \sim 10m_0$) is well established from thermopower and specific-heat measurements.^{11,12} Thus, LaNiO_3 is a genuine 3D Fermi liquid with correlated $3d$ electrons in a quarter-filled e_g band.

Bulk single-crystal growth of LaNiO_3 has not been possible to date. However, single crystalline epitaxial thin films have been successfully synthesized for device applications and provide a very suitable metallic template for electrical contacts to perovskite films.¹³ In a recent study, we succeeded in fabricating single crystalline epitaxial thin films and studying it by angle-integrated photoemission spectroscopy (PES).¹⁴ We reported the observation of a clear sharp $\text{Ni } 3d e_g$ derived peak at the Fermi level (E_F), which could not be detected in earlier studies.¹⁵ This peak gets gapped across the oxygen vacancy-controlled MIT in LaNiO_{3-x} . A narrow band at E_F is typical of correlated metals, but the momentum or angle-resolved PES is necessary to directly probe 3D FSs and renormalization of band dispersions. Such studies require an accurate determination of the in-plane and out-of-plane components of the momentum vector of an electron and are intrinsically difficult experiment for 3D systems requiring tunable photons from a synchrotron source. Recent studies have reported soft x-ray angle-resolved photoemission spectroscopy (ARPES) of elemental metals¹⁶ and correlated-electron systems.¹⁷ The role of nondirect transitions could be identified at high temperature in elemental metals. For f -electron systems, dispersive bands and even FS crossings have been identified. However, the momentum dependence of renormalized band dispersions due to electron-electron correlations has not been addressed. Here, we report the momentum-resolved PES of LaNiO_3 using soft x rays. The aim of the present work is to determine the FSs and the role of correlations in a 3D Fermi liquid.

Recent theory showed that kinks can appear in the band dispersion of 3D materials as a consequence of correlations based on dynamical mean-field theory in combination with the local-density approximation (LDA+DMFT) calculations.¹⁸ These calculations carried out for the case of

an energy dependent but momentum independent self-energy suggested consistency with low-energy ARPES of SrVO₃.¹⁹ Kinks are often found in systems with strong electron-phonon coupling within 100 meV below E_F , for example, as in high- T_c superconductors.²⁰ Moreover, kinks on a higher-energy scale, about 300–500 meV, were also reported in high- T_c superconductors.^{21,22} These anomalies suggest that kinks can occur due to a variety of reasons such as electron-phonon interaction, short-range Coulomb interaction, etc. Since LaNiO₃ is a strongly correlated metal, one may expect to see anomalies in its momentum-resolved electronic structure.

II. EXPERIMENTAL DETAILS

The LaNiO₃ thin films were grown on SrTiO₃ single-crystal substrates. A sintered stoichiometric LaNiO₃ pellet was used as an ablation target. A Nb-doped yttrium aluminum garnet laser was used in its frequency-tripled mode ($\lambda=355$ nm) at a repetition rate of 1 Hz. The SrTiO₃ substrates were annealed at 900 °C at an oxygen pressure of 1×10^{-4} Pa before deposition. The substrate temperature was set to 650 °C and the oxygen pressure was 10 Pa during the deposition. The LaNiO₃ films were subsequently annealed at 400 °C for 30 min at atmospheric pressure of oxygen to remove vacancies. After cooling the sample to below 100 °C and evacuating the growth chamber, the surface morphology and crystallinity of the fabricated LaNiO₃ films were checked by an *in situ* observation of reflection high-energy electron-diffraction (RHEED) patterns. Further details on the characterization are described in Ref. 14.

Soft x-ray ARPES experiments were carried out using a high-resolution synchrotron-radiation PES system with a Gammadata-Scienta SES2002 spectrometer combined with a pulse laser deposition chamber at undulator beamline BL17SU, SPring-8.²³ The ARPES measurements were carried out in a vacuum of 5×10^{-8} Pa, at 30 K to minimize nondirect-transition effects. The energy resolution was set to ~ 150 and 200 meV and the angular resolution was $\pm 0.2^\circ$, which corresponds to a momentum resolution of $\pm 0.043 \text{ \AA}^{-1}$ at $h\nu=630$ eV

The high-symmetry momentum points (Γ and X) and the Fermi crossings were accurately determined from energy-dependent normal-emission spectra and a free-electron final state, taking into account the photon momentum into consideration. Thus,

$$k_z = \sqrt{\frac{2m}{\hbar^2}(E_{\text{kin}} \cos^2 \theta + V_0) - k_{\perp h\nu}},$$

where k_z is the normal component of the momentum, m is the electron mass, E_{kin} is the kinetic energy of the electrons, $k_{\perp h\nu}$ is the component of the photon momentum perpendicular to the surface, and θ is the emission angle. An inner potential of $V_0=10$ eV was assumed to obtain consistent results. We required a photon momentum correction of $\sim 14\%$ and $\sim 15\%$ of $2\pi/c$ at 630 eV (Γ - X - Γ cut) and 710 eV (X - M - X cut), respectively, where c is the pseudocubic lattice parameter of LaNiO₃. The high-symmetry points were further calibrated

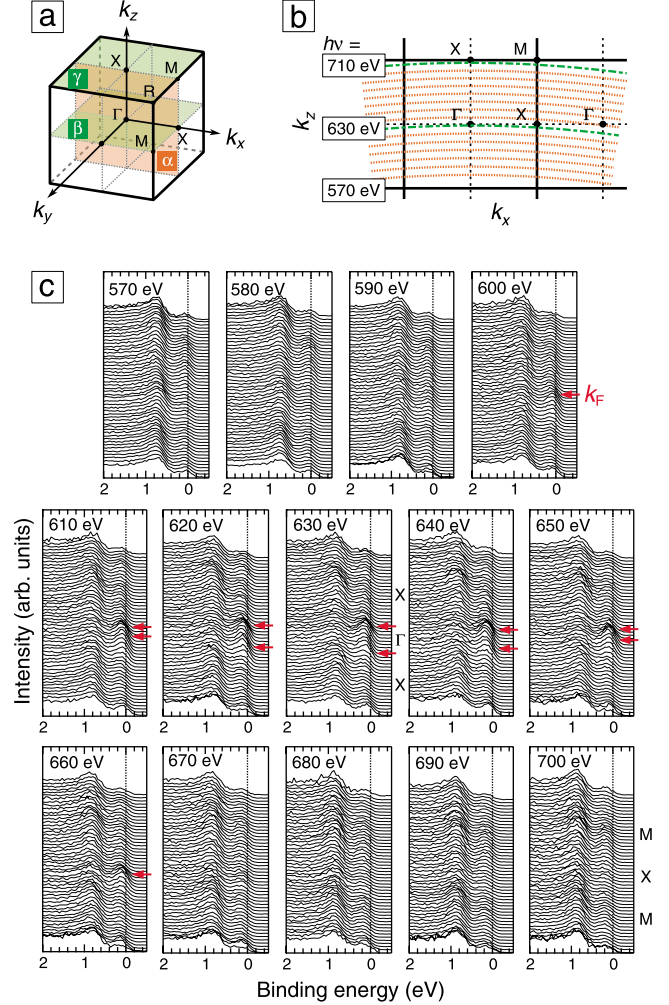


FIG. 1. (Color online) (a) The schematic of a cubic Brillouin zone. (b) The momentum space region of the ARPES measurements. (c) The EDCs at photon energies between $h\nu=570$ and 700 eV at normal emission.

by angle-dependent in-plane measurements at fixed photon energies. All the intensity maps shown in the paper are measured data over the displayed ranges and no symmetrization has been used to obtain the maps.

III. RESULTS AND DISCUSSION

Figures 1(a) and 1(b) show the schematic of a cubic Brillouin zone and the region in momentum space of the ARPES measurements reported here (15 cuts, using $h\nu=570$ –710 eV, steps of 10 eV). While bulk LaNiO₃ as well as thin-film LaNiO₃ show a small rhombohedral distortion and are not simple cubic, the band structure of rhombohedral LaNiO₃ is well explained by the zone folding of a cubic Brillouin zone into a rhombohedral Brillouin zone.²⁴ Hence, we adopt a pseudocubic notation for discussing the PES of LaNiO₃. Figure 1(c) shows the energy distribution curves (EDCs) at photon energies between $h\nu=570$ and 700 eV at normal-emission. EDCs at all photon energies show intense features with small dispersion around 0.8 eV, corresponding

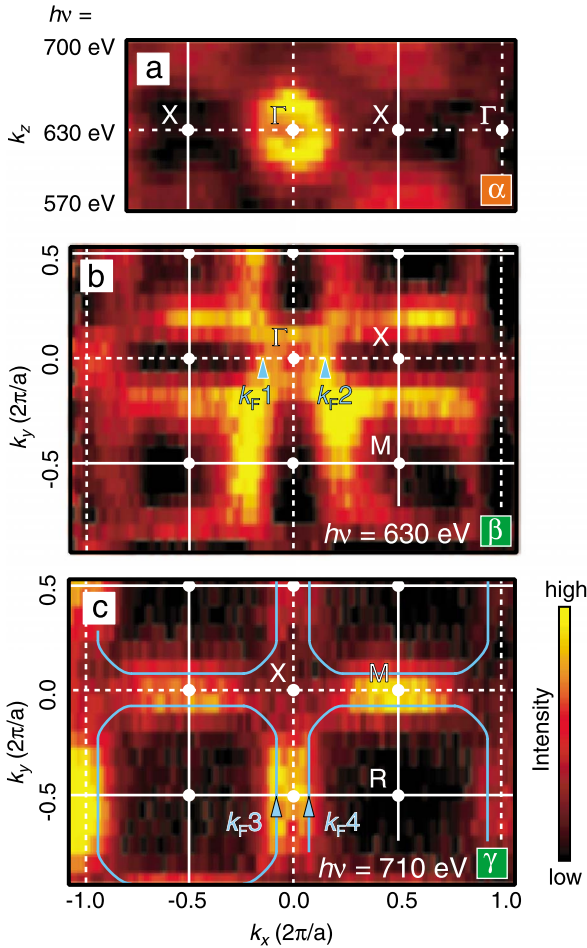


FIG. 2. (Color online) Fermi-surface mapping in (a) a vertical (k_z - k_x) plane “ α ” and (b) horizontal (k_x - k_y) planes “ β ” and (c) “ γ ” of Brillouin zone in Fig. 1(a). Solid white lines correspond to the cubic Brillouin zone and dotted white lines correspond to the high-symmetry lines. k_{F1} - k_{F4} indicate the MDC peak positions at E_F in Figs. 3(c) and 3(d). Blue (gray) lines show nesting character hole FSs. All the intensity maps are measured data over the displayed range and no symmetrization has been used to obtain the maps.

to the Ni $3d$ t_{2g} bands. In addition, EDCs for 600–660 eV clearly show a dispersive band crossing at the E_F (arrows) around the Γ point. This dispersive band originates in Ni $3d$ e_g states and forms a small electron pocket as predicted by the local-density approximation (LDA) band calculation. The band disappears for energies below 600 eV and above 660 eV photon energy and an increase in intensity is observed close to the M point at $h\nu=570$ and 700 eV.

Figure 2(a) shows the FS mapping in a vertical (k_z - k_x) plane “ α ” of Brillouin zone as shown in Fig. 1(a), which is obtained by a plot of the integrated intensity from -0.05 to 0.05 eV binding energy in EDCs. A small circle centered at Γ point is observed, while no intensity is observed around the X point. The existence of a nearly spherical small FS centered at Γ point, corresponding to the electron FS, was predicted by band calculations.²⁴ From photon energy (k_z)-dependent ARPES measurements, we can decide the photon energy tracing the Γ - X and X - M directions as shown in Fig. 1(b). In order to observe the in-plane cuts of the FSs,

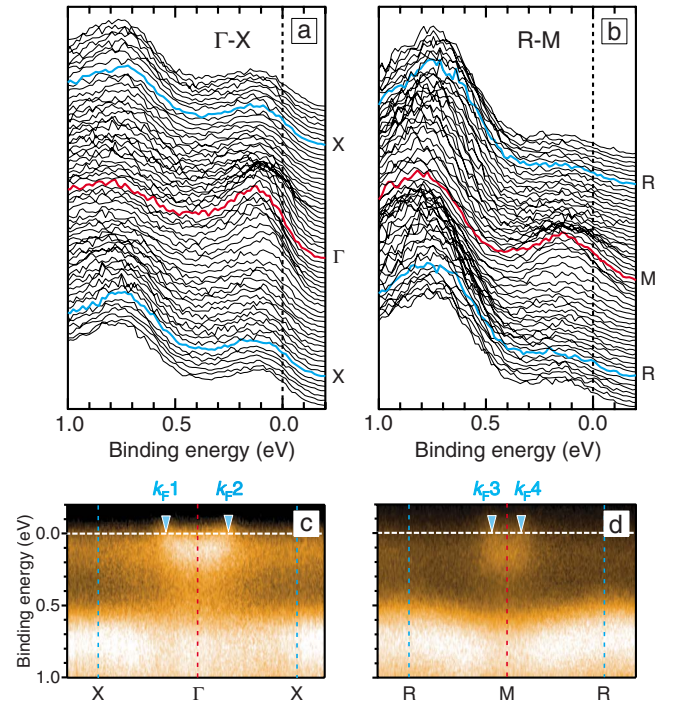


FIG. 3. (Color online) (a) and (b) EDCs along Γ - X and R - M direction, respectively. (c) and (d) The intensity maps of EDCs. k_{F1} - k_{F4} indicate the MDC peak positions at E_F .

we measured ARPES at a fixed photon energy of 630 eV ($k_z \sim 0$) and 710 eV ($k_z \sim \pi/c$). The FS mapping in horizontal (k_x - k_y) planes “ β ” and “ γ ” of Brillouin zone in Fig. 1(a) was obtained as shown in Figs. 2(b) and 2(c). In “ β ” plane, the small electron FS around Γ point is again observed. This result indicates that the 3D spherelike FS around Γ point can be observed by ARPES experimentally. The squarelike intense area around M points obtained from raw data without symmetrization corresponds to the projection of the hole FS centered at R point. In “ γ ” plane, no small FS is observed. Instead large FSs centered at R point were observed. From the complete data set of energy and angle-dependent FS maps, the experimental FS obtained by soft x-ray ARPES is in overall agreement with that predicted by the band calculation.²⁴ However, the actual band dispersions reveal an important difference in electron and hole FSs as discussed in the following.

In order to discuss the band structures forming these FSs, we measured the ARPES in the high-symmetry lines with detailed momentum steps and an energy resolution $\Delta E \sim 150$ meV. The EDCs [Figs. 3(a) and 3(b)] and the intensity plots [Figs. 3(c) and 3(d)] along Γ - X and R - M directions are shown in Fig. 3. The FS crossing k_F points are labeled as k_{F1} - k_{F4} . The intensity plots in both directions [Figs. 3(c) and 3(d)] show an intense feature around 0.0 – 0.2 eV at Γ and M points, corresponding to the electron band and the hole band derived from Ni $3d$ e_g states, respectively. While the band bottom at M point is around 0.25 eV, the band bottom at Γ point is not at 0.25 eV. The intensity remains in high binding-energy region (about 0.5 – 1.0 eV) at Γ point [Fig. 3(c)], indicating that the bands extend to high binding energies. Because the t_{2g} bands also appear above 0.5 eV at X point, the

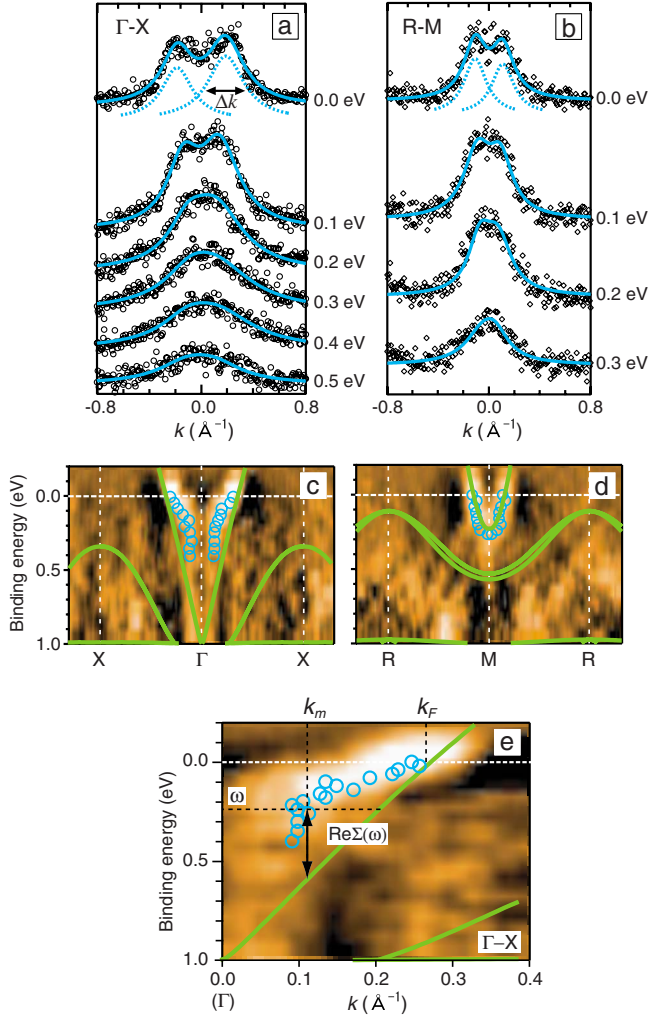


FIG. 4. (Color online) (a) and (b) MDCs with fitted spectra using two Lorentzians. (c) and (d) The intensity map of the second derivative MDCs with LDA band calculation [green (gray) lines]. The experimental band dispersion derived from the peak positions of second derivative MDCs is shown as the blue (gray) circles. (a) and (c) were measured along Γ - X direction, while (b) and (d) were measured along R - M direction. (e) Expanded view of the intensity map of the second derivative MDCs with LDA band calculation [green (gray) lines] in Γ - X direction.

band bottom is not clear. This behavior contrasts with the hole band at M point [Fig. 3(d)], in which there is no intensity around 0.3–0.5 eV at M point. Therefore, the electron band at the Γ point extends to at least 0.5 eV binding energy.

Figures 4(a) and 4(b) show the momentum distribution curves (MDCs) plotted in steps of 0.1 eV binding energy. We fitted the MDCs to two Lorentzians to estimate the MDC peak width. For the Γ centered electron FS, the mean-free path of carriers is obtained as $l=1/\Delta k \sim 3$ Å from the MDC width at E_F consistent with transport.¹² The mean-free path of the carriers around Γ point is smaller than that around M point. Moreover, to emphasize the band dispersion, we apply the second derivative for the MDCs and plot it as intensity map in Figs. 4(c) and 4(d). Blue (gray) circles indicate the peak positions of second derivative MDCs, corresponding to the experimental band dispersion. The theoretical band cal-

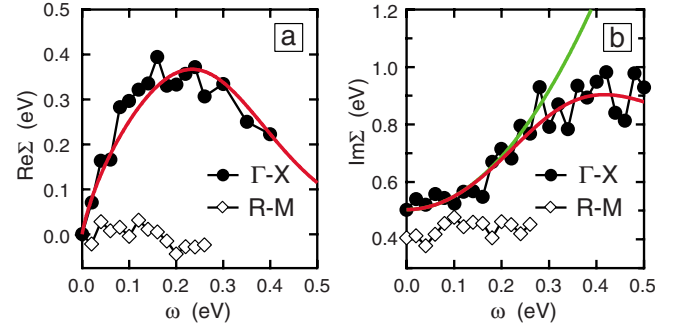


FIG. 5. (Color online) (a) $\text{Re } \Sigma(\omega)$ and (b) $\text{Im } \Sigma(\omega)$ obtained from the experiment (circles and squares) and a Kramers-Kronig analysis [red (black) lines]. Green (gray) line indicates $\text{Im } \Sigma(\omega)$ for a Fermi liquid.

ulation result is also plotted on the experimental intensity plot. The theoretical calculation was done using the LDA based full-potential linearized augmented plane-wave method²⁵ in the cubic symmetry with the lattice constant of $a=5.45/\sqrt{2}=3.85$ Å for the LaNiO_3 bulk crystal.⁷ From the comparison between the experimental and the calculated band dispersion, the band forming the electron FSs shows clear differences from the calculated band, while the band forming the hole FSs almost matches the calculated band dispersion. A clear kink structure at ~ 0.25 eV in the band forming the electron FS is observed in Fig. 4(e).

We have determined the real and imaginary parts of the self-energy [$\Sigma(\omega)$] from ARPES spectra, by neglecting its k dependence and approximating the bare band dispersion to be linear, as is the usual procedure.²¹ The $\text{Re } \Sigma(\omega)$ and $\text{Im } \Sigma(\omega)$ are derived from the widths Δk and peak positions k_m of the MDC peaks, and the bare velocity v_0 as shown in the following equation:

$$k_m = k_F + [\omega - \text{Re } \Sigma(\omega)]/v_0,$$

$$\Delta k = 2 \text{Im } \Sigma(\omega)/v_0.$$

The results of such an analysis are shown in Figs. 5(a) and 5(b). The $\text{Im } \Sigma(\omega)$ at E_F [$\text{Im } \Sigma(0) \sim 0.5$ eV] is rather high, along Γ - X . In contrast, the $\text{Re } \Sigma(\omega)$ at E_F is 0 along Γ - X , since the band crossing in experiment matches the band-structure calculations. The high $\text{Im } \Sigma(\omega)$ at E_F along Γ - X is assumed to be a constant in terms of an impurity scattering term. Although the $\text{Im } \Sigma(0)$ is large, a similar situation has been reported with $\text{Im } \Sigma(0) \sim 0.25$ eV for under-doped cuprates.²¹ Using an analytic function $\propto (a\omega)^2/[1+(a\omega)^4]$ to model the $\text{Im } \Sigma(\omega)$ of the Fermi liquid, we have checked the self-consistency between the $\text{Re } \Sigma(\omega)$ and $\text{Im } \Sigma(\omega)$ using the Kramers-Kronig relations [red (black) lines in Figs. 5(a) and 5(b)]. The behavior of $\text{Re } \Sigma(\omega)$ and $\text{Im } \Sigma(\omega)$ is remarkably similar to the high- T_c superconductors having the high-energy kink.^{21,22} The deviation from ω^2 behavior [green (gray) line in Fig. 5(b)] identifies the kink at 0.25 eV. The present results suggest a Fermi liquid behavior for LaNiO_3 , consistent with transport studies.^{10–12} The energy scale of 0.25 eV is very large and cannot be associated with a phonon energy scale in LaNiO_3 . The kink behavior leads to a picture

as was shown by LDA+DMFT calculations for strongly correlated-electron systems.¹⁸ On the other hand, the hole bands do not show a renormalization kink like the electron bands. This result indicates that the hole carriers do not have an enhanced effective mass like the electron carriers. The difference of the mean-free path between the electron and hole carriers is shown in the MDC width at E_F . LaNiO₃ is discussed in terms of a $t_{2g}^6 e_g^1$ state and shows n -type conductivity in Hall measurements.²⁶ In electron- and hole-doped $R_{1-x}A_x\text{NiO}_3$, it was found that a significant electron-hole asymmetry leads to the suppression of the MIT temperature by the extra carriers.²⁷

The mass-renormalization factor is estimated as $m^*/m_b \times m_b/m_0 = 3.3 \times 1.5 \approx 5$ from the experimental electron band, while thermodynamic studies indicate a value of ≈ 10 . It is noted that the possibility of a lower-energy interaction within 100 meV (for example, the electron-phonon interaction) cannot be ruled out. Unfortunately, the observation of such a small energy scale feature corresponding to the electron-phonon interaction is not possible presently with soft x-ray ARPES from the viewpoint of energy resolution. Nevertheless, the “correlation kink” at 0.25 eV originating in the strongly renormalized bands produce the sharp density of

states at the E_F and indicate the evidence of the mass enhancement in the electronic structure of LaNiO₃. The results indicate a momentum-dependent mass renormalization for the electron and hole bands near the E_F , leading to electron-hole asymmetry in this 3D Fermi liquid.

IV. CONCLUSION

In conclusion, we have directly observed the 3D FSs and the energy-band dispersion from energy- and angle-dependent PES measurements and determined $\text{Re } \Sigma(\omega)$ and $\text{Im } \Sigma(\omega)$ of LaNiO₃. The energy bands forming the electron FS suggest an ω^2 dependence of the $\text{Im } \Sigma(\omega)$ and a “correlation kink” at an energy scale of 0.25 eV. In contrast, the bands which form nesting character hole FSs do not show kinks and match local-density approximation calculations. The results indicate a momentum-dependent mass renormalization, leading to electron-hole asymmetry in strongly correlated LaNiO₃. Soft x-ray momentum-resolved PES applied to 3D epitaxial oxide films is expected to provide much needed insights into their electronic structure and exotic properties.

*ritsuko@spring8.or.jp

- ¹M. Imada, A. Fujimori, and Y. Tokura, *Rev. Mod. Phys.* **70**, 1039 (1998).
- ²A. Damascelli, Z. Hussain, and Z.-X. Shen, *Rev. Mod. Phys.* **75**, 473 (2003).
- ³A. Ohtomo and H. Y. Hwang, *Nature (London)* **427**, 423 (2004).
- ⁴J. Philip, A. Punnoose, B. I. Kim, K. M. Reddy, S. Layne, J. O. Holmes, B. Satpati, P. R. LeClair, T. S. Santos, and J. S. Moodera, *Nature Mater.* **5**, 298 (2006).
- ⁵H. Ohta, S.-W. Kim, Y. Mune, T. Mizoguchi, K. Nomura, S. Ohta, T. Nomura, Y. Nakanishi, Y. Ikuhara, M. Hirano, H. Hosono, and K. Koumoto, *Nature Mater.* **6**, 129 (2007).
- ⁶L. D. Landau, *Sov. Phys. JETP* **3**, 920 (1957).
- ⁷J. L. García-Muñoz, J. Rodríguez-Carvajal, P. Lacorre, and J. B. Torrance, *Phys. Rev. B* **46**, 4414 (1992).
- ⁸J.-S. Zhou, J. B. Goodenough, B. Dabrowski, P. W. Klamut, and Z. Bukowski, *Phys. Rev. Lett.* **84**, 526 (2000).
- ⁹J. E. Lorenzo, J. L. Hodeau, L. Paolasini, S. Lefloch, J. A. Alonso, and G. Demazeau, *Phys. Rev. B* **71**, 045128 (2005); V. Scagnoli, U. Staub, A. M. Mulders, M. Janousch, G. I. Meijer, G. Hammerl, J. M. Tonnerre, and N. Stojic, *ibid.* **73**, 100409(R) (2006).
- ¹⁰K. Sreedhar, J. M. Honig, M. Darwin, M. McElfresh, P. M. Shand, J. Xu, B. C. Crooker, and J. Spalek, *Phys. Rev. B* **46**, 6382 (1992).
- ¹¹X. Q. Xu, J. L. Peng, Z. Y. Li, H. L. Ju, and R. L. Greene, *Phys. Rev. B* **48**, 1112 (1993).
- ¹²K. P. Rajeev, G. V. Shivashankar, and A. K. Raychaudhuri, *Solid State Commun.* **79**, 591 (1991).
- ¹³P. Chen, S. Y. Xu, W. Z. Zhou, C. K. Ong, and D. F. Cui, *J. Appl. Phys.* **85**, 3000 (1999); A. Y. Dobin, K. R. Nikolaev, I. N. Krivorotov, R. M. Wentzcovitch, E. D. Dahlberg, and A. M.

Goldman, *Phys. Rev. B* **68**, 113408 (2003).

- ¹⁴K. Horiba, R. Eguchi, M. Taguchi, A. Chainani, A. Kikkawa, Y. Senba, H. Ohashi, and S. Shin, *Phys. Rev. B* **76**, 155104 (2007).
- ¹⁵S. R. Barman, A. Chainani, and D. D. Sarma, *Phys. Rev. B* **49**, 8475 (1994).
- ¹⁶Z. Hussain, S. Kono, R. E. Connelly, and C. S. Fadley, *Phys. Rev. Lett.* **44**, 895 (1980); C. Sondergaard, P. Hofmann, C. Schultz, M. S. Moreno, J. E. Gayone, M. A. Vicente Alvarez, G. Zampieri, S. Lizzit, and A. Baraldi, *Phys. Rev. B* **63**, 233102 (2001); N. Kamakura, Y. Takata, T. Tokushima, Y. Harada, A. Chainani, K. Kobayashi, and S. Shin, *ibid.* **74**, 045127 (2006).
- ¹⁷T. Claesson, M. Månsson, C. Dallera, F. Venturini, C. De Nadaï, N. B. Brookes, and O. Tjernberg, *Phys. Rev. Lett.* **93**, 136402 (2004); F. Venturini, J. C. Cezar, C. De Nadaï, P. C. Canfield, and N. B. Brookes, *J. Phys.: Condens. Matter* **18**, 9221 (2006); M. Yano, A. Sekiyama, H. Fujiwara, T. Saita, S. Imada, T. Muro, Y. Onuki, and S. Suga, *Phys. Rev. Lett.* **98**, 036405 (2007); S. Fujimori, Y. Saitoh, T. Okane, S. Fujimori, H. Yamagami, Y. Haga, E. Yamamoto, and Y. Onuki, *Nat. Phys.* **3**, 618 (2007).
- ¹⁸I. A. Nekrasov, K. Held, G. Keller, D. E. Kondakov, Th. Pruschke, M. Kollar, O. K. Andersen, V. I. Anisimov, and D. Vollhardt, *Phys. Rev. B* **73**, 155112 (2006); K. Byczuk, M. Kollar, K. Held, Y.-F. Yang, I. A. Nekrasov, Th. Pruschke, and D. Vollhardt, *Nat. Phys.* **3**, 168 (2007).
- ¹⁹T. Yoshida, K. Tanaka, H. Yagi, A. Ino, H. Eisaki, A. Fujimori, and Z.-X. Shen, *Phys. Rev. Lett.* **95**, 146404 (2005).
- ²⁰A. Lanzara, P. V. Bogdanov, X. J. Zhou, S. A. Kellar, D. L. Feng, E. D. Lu, T. Yoshida, H. Eisaki, A. Fujimori, K. Kishio, J.-I. Shimoyama, T. Nodak, S. Uchida, Z. Hussain, and Z.-X. Shen, *Nature (London)* **412**, 510 (2001).
- ²¹T. Valla, T. E. Kidd, W.-G. Yin, G. D. Gu, P. D. Johnson, Z.-H. Pan, and A. V. Fedorov, *Phys. Rev. Lett.* **98**, 167003 (2007).

- ²²W. Meevasana, X. J. Zhou, S. Sahrakorpi, W. S. Lee, W. L. Yang, K. Tanaka, N. Mannella, T. Yoshida, D. H. Lu, Y. L. Chen, R. H. He, Hsin Lin, S. Komiya, Y. Ando, F. Zhou, W. X. Ti, J. W. Xiong, Z. X. Zhao, T. Sasagawa, T. Kakeshita, K. Fujita, S. Uchida, H. Eisaki, A. Fujimori, Z. Hussain, R. S. Markiewicz, A. Bansil, N. Nagaosa, J. Zaanen, T. P. Devereaux, and Z.-X. Shen, *Phys. Rev. B* **75**, 174506 (2007).
- ²³K. Horiba, N. Kamakura, K. Yamamoto, K. Kobayashi, and S. Shin, *J. Electron Spectrosc. Relat. Phenom.* **144-147**, 1027 (2005); H. Ohashi, Y. Senba, H. Kishimoto, T. Miura, E. Ishiguro, T. Takeuchi, M. Oura, K. Shirasawa, T. Tanaka, M. Takeuchi, K. Takeshita, S. Goto, S. Takahashi, H. Aoyagi, M. Sano, Y. Furukawa, T. Ohata, T. Matsushita, Y. Ishizawa, S. Taniguchi, Y. Asano, Y. Harada, T. Tokushima, K. Horiba, H. Kitamura, T. Ishikawa, and S. Shin, *AIP Conf. Proc. No. 879* (AIP, New York, 2007), p. 523.
- ²⁴N. Hamada, *J. Phys. Chem. Solids* **54**, 1157 (1993).
- ²⁵P. Blaha, K. Schwarz, G. Madsen, D. Kvasnicka, and J. Luitz, *WIEN2K: An Augmented Plane Wave & Local Orbitals Program for Calculating Crystal Properties* (Karlheinz Schwarz Technical University Wien, Wien, Austria, 2001).
- ²⁶W. Noun, B. Berini, Y. Dumont, P. R. Dahoo, and N. Keller, *J. Appl. Phys.* **102**, 063709 (2007).
- ²⁷J. L. García-Muñoz, M. Suaaidi, M. J. Martínez-Lope, and J. A. Alonso, *Phys. Rev. B* **52**, 13563 (1995).