

Diamagnetic fluctuations in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$: Possible observation of phase correlations persisting above T_c

S. Salem-Sugui, Jr.,¹ J. Mosqueira,² and A. D. Alvarenga³¹*Instituto de Física, Universidade Federal do Rio de Janeiro, 21941-972 Rio de Janeiro, RJ, Brazil*²*LBTS, Universidade de Santiago de Compostela, Santiago de Compostela E-15782, Spain*³*Instituto Nacional de Metrologia Normalização e Qualidade Industrial, 25250-020 Duque de Caxias, RJ, Brazil*

(Received 4 May 2009; revised manuscript received 23 August 2009; published 22 September 2009)

We report on isofield curves of $\sqrt{-M}$ vs T , where M is the reversible magnetization, of $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$, $\text{YBa}_2\text{Cu}_3\text{O}_{6.65}$, and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ with the magnetic field, H , applied parallel to the c axis of the samples (and also parallel to the ab planes for YBaCuO). For temperatures close to the critical temperature, T_c , the quantity $\sqrt{-M}$ is proportional to the order parameter amplitude $|\psi|$. Curves of $\sqrt{-M}$ vs T allowed to study the asymptotic behavior of the form $(T_a - T)^m$ of $|\psi|$ near T_c , as a function of field. Results for the studied samples produced values of $T_a(H)$ lying above T_c , suggesting that the magnetic field gradually allows to probe a region of temperatures where phase correlations persist above T_c . The study performed here in YBaCuO samples allowed to study how phase correlations evolve with doping in the pseudogap region of YBaCuO . $\sqrt{-M}$ vs T curves for all samples show a rather large amplitude fluctuation with no phase correlation extending well above $T_a(H)$ which is interpreted in terms of a Gaussian Ginzburg-Landau approach with a *total-energy* cutoff in the fluctuation spectrum. Resulting values for the exponent m found for all samples, $0.5 < m < 0.7$, are interpreted as due to phase fluctuations of the d -wave pairing symmetry of the order parameter in the ab planes.

DOI: [10.1103/PhysRevB.80.094520](https://doi.org/10.1103/PhysRevB.80.094520)

PACS number(s): 74.25.Bt, 74.25.Ha, 74.72.Bk, 74.62.-c

I. INTRODUCTION

It is well-known that underdoped high- T_c superconductors exhibit superconducting fluctuations extending well above the superconducting temperature transition for zero magnetic field, T_c , in the pseudogap region.¹⁻³ Such diamagnetic fluctuations are thought to be due to amplitude fluctuations with no phase coherence⁴⁻⁶ where T_c represents the temperature at which phase coherence is lost.⁷ Based on Ref. 7, superconductors with a small superfluid density, as underdoped high- T_c superconductors, have a small phase stiffness and, as a consequence, phase fluctuations are important in the vicinity of T_c . More recently, a theoretical work which explicitly considers the effect of phase fluctuations on the phase diagram of a high- T_c superconductor with a d -wave order parameter symmetry was presented in Ref. 8. In this work a phase diagram is obtained for YBaCuO as a function of doping showing a new line lying above T_c (there denominated T_ϕ line) representing the temperature at which phase coherence is lost. This T_ϕ line represents a limited temperature region above T_c where phase correlations survive. The importance of phase fluctuations in d -wave coupling superconductors is also evidenced in another theoretical work presented in Ref. 9. These theoretical works of Refs. 7-9 do not consider an applied magnetic field, but most of the superconducting phenomena observed above T_c in these underdoped systems depend on the application of a magnetic field^{2,4,5,10,11} and the common thought regarding fluctuations above T_c is the existence of a state with vortices with no phase coherence.⁴⁻⁶ In a recent work,¹² which include some of us, it was shown that the asymptotic behavior of isofield $\sqrt{-M}$ vs T curves near T_c in two deoxygenated YBaCuO crystals supports the existence of a superconducting state with phase coherence persisting above T_c as predicted in Ref. 8 while results for an optimally doped YBaCuO crystal indicated that

phase coherence is controlled by the mean-field $T_c(H)$ in disagreement with theory predictions.^{7,8}

In this work, we address the issue of phase correlations above T_c in the high- T_c compounds $\text{YBa}_2\text{Cu}_3\text{O}_{6.65}$, $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$, and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ (Bi2212). Deoxygenated YBaCuO and Bi2212 systems exhibit the pseudogap phase^{1,2} and phase fluctuations may play an important role in the vicinity of T_c .⁷ Isofield magnetization curves, M vs T , were obtained for YBaCuO crystals with the magnetic field, H , applied parallel and perpendicular to the c axis while for Bi2212 we used previous obtained magnetization curves for $H \parallel c$ axis.¹¹ The YBaCuO crystals data complement a previous study performed in the vicinity of T_c on two deoxygenated samples¹² and verify (by studying another samples with $T_c = 92$ K) a result obtained in Ref. 12 for an optimally doped sample, where no phase correlations were observed above T_c . The work was motivated on the possibility of experimentally obtain a qualitative diagram showing the evolution of phase correlations with doping in YBaCuO . Other motivations were to obtain the extension in temperatures above T_c where phase correlations survive in Bi2212 and to study the large amplitude fluctuation observed well above T_c on the studied systems. We study isofield curves of $\sqrt{-M}$ vs T instead M vs T curves, since the quantity $\sqrt{-M}$ is directly proportional to the amplitude of the order parameter $|\psi|$ near T_c .¹³ The analysis is performed in two distinct regions of the isofield $\sqrt{-M}$ vs T curves. Below $T_c(H)$ the curves show an asymptotic behavior of the form $(T_a - T)^m$, where $T_a(H)$ is an apparent transition temperature representing the onset of phase correlations, and m is a fitting exponent. This analysis was motivated on the results of Ref. 14, which show that phase fluctuations have an effect on the superfluid density of states, reducing the gap in the vicinity of T_c . The region above $T_c(H)$, dominated by amplitude fluctuations, is analyzed following a Gaussian Ginzburg-Landau (GL) approach

developed in Refs. 15 and 16. We also present low isofield data for Bi2212 to demonstrate a similar crossing point to data at higher fields that suggests further theoretical work.

The paper is organized as follows: in Sec. II we present the experimental details, and in Sec. III the results and discussion. In Sec. III A, we discuss the crossing point of the Bi2212 curves, in Sec. III B the asymptotic behavior of the curves near T_c , in Sec. III C the effect of amplitude fluctuations above T_c , and finally in Sec. III D we present the phase diagram for the superconducting phase fluctuations in YBaCuO.

II. EXPERIMENTAL

We measured an optimally doped YBa₂Cu₃O_{6.95} single crystal with $T_c=92$ K and a deoxygenated YBa₂Cu₃O_{6.65} crystal with $T_c=61.5$ K. YBaCuO crystals used here were grown at Argonne National Laboratory by Boyd Veal.¹⁷ To fix the oxygen stoichiometry, the sample was held for 89 h at 520 °C in a flowing gas atmosphere consisting of 3.45 %O₂ in N₂. The gas mixture was continuously monitored during the heat treatment with a commercial zirconia cell. The sample was then quenched in a liquid nitrogen bath. This procedure fixes the oxygen stoichiometry at $x=6.65$, as discussed in Ref. 17. The 92 K sample was treated for 100 h at 480 °C plus 190 h at 400 °C in flowing O₂. The studied YBaCuO samples exhibited sharp, fully developed transitions, with a transition width $\Delta T_c \approx 1$ K. Magnetization curves obtained for YBaCuO samples studied here as obtained as a function of temperature for $H \approx 5$ Oe are presented in the inset of Fig. 1(a). We also include in this inset of Fig. 1(a) low field curves obtained for deoxygenated YBaCuO crystals of Ref. 12 from which results are used in this work. The temperature at the middle value of the transition is taken as T_c . Dimensions of the samples used here are on the order $1 \times 1 \times 0.2$ mm (the c axis being perpendicular to the largest plane of the samples) and their mass about 1 mg. For Bi₂Sr₂CaCu₂O_{8+x}, we used magnetization data recently obtained in a single crystal with $T_c=93$ K for $H \parallel c$ axis.¹¹ Magnetization measurements (isofield M vs T curves) were obtained by using a commercial magnetometer (Quantum Design) based on the superconducting quantum interference device (SQUID). All data were obtained after cooling the sample from a temperature above T_c in the presence of the earth magnetic field, to a desired temperature below T_c . After that, a magnetic field was applied reaching the desired value without overshooting, and data were obtained by heating the sample at fixed increments of temperature up to a temperature well above T_c . Magnetization data for YBaCuO crystals were obtained for both field directions, $H \parallel ab$ planes and $H \parallel c$ axis. Magnetization data was obtained up to 150 K for sample with $T_c=92$ K (for $H \parallel c$ axis only) and up to 110 K for sample with $T_c=61.5$ K. Figure 1 shows selected isofield magnetization curves as obtained for both samples with $H \parallel c$ axis. As shown in Figs. 1(a) and 1(b), background magnetization has a typical diamagnetic signal which increases with field. The same trend is followed for data with $H \parallel ab$ planes (not shown). The background magnetization due to the normal electrons, M_{back} , was obtained and re-

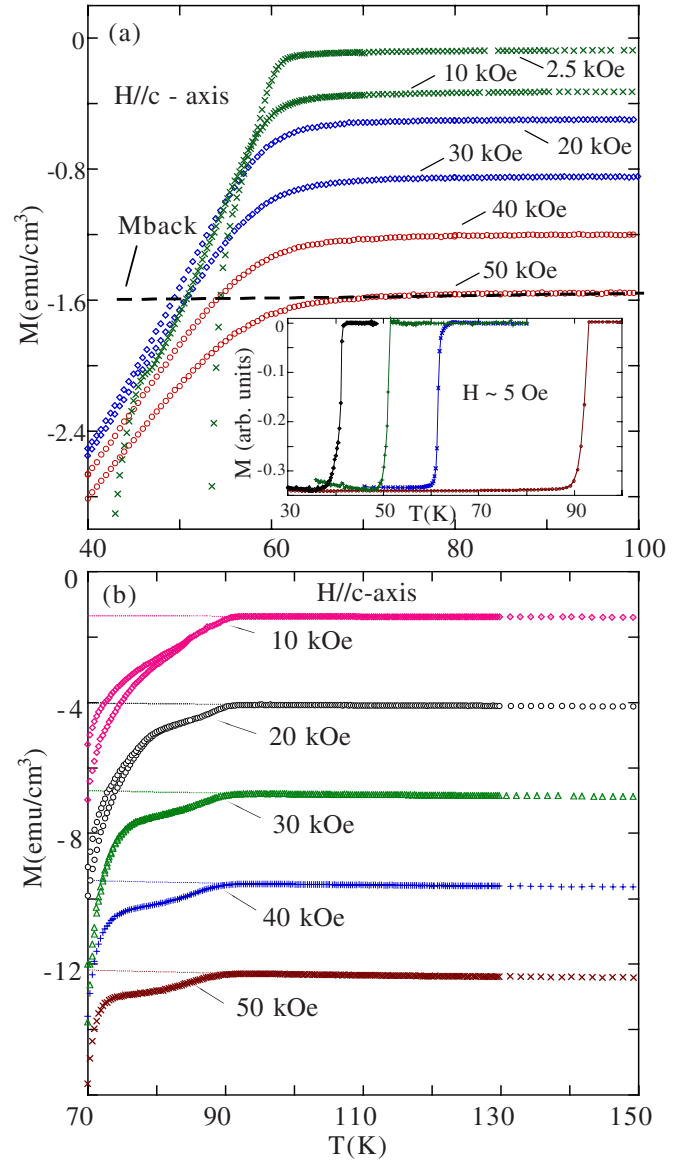


FIG. 1. (Color online) Selected isofield M vs T curves as obtained with $H \parallel c$ for: (a) the deoxygenated YBaCuO ($T_c=61.5$ K), where $M_{\text{back}}=-0.043-0.0293 \cdot H$ with H in kOe. (b) the optimally doped YBaCuO ($T_c=92$ K) where $M_{\text{back}}=c(H)/T+a(H)$ with $c(H)=(2.6+2.0 \cdot H) \cdot 10^{-4}$ and $a(H)=(44-8.9 \cdot H) \cdot 10^{-5}$ with H in kOe. Straight lines appearing below T_c on the curves of Fig. 1(b) represent extrapolation of the background magnetization. The inset of Fig. 1(a) displays the superconducting transitions of the YBaCuO crystals

moved for each data set by selecting data well above T_c and fitting to the form $M_{\text{back}}=c(H)/T+a(H)$.

III. RESULTS AND DISCUSSION

A. Crossing point of the Bi2212 curves

The isothermal magnetization curves of the studied systems are plotted as $\sqrt{-M}$ vs T and presented in Fig. 2 for YBa₂Cu₃O_{6.95}, Fig. 3 for YBa₂Cu₃O_{6.65}, and Fig. 4 for Bi₂Sr₂CaCu₂O_{8+x}. The common fact among the curves ob-

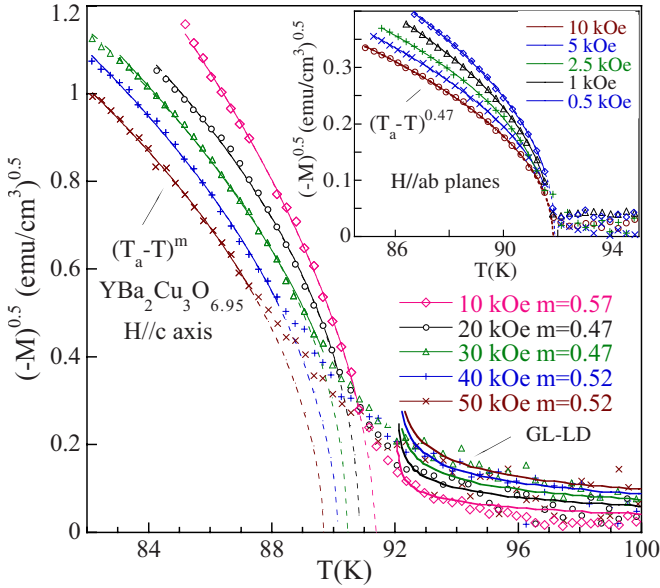


FIG. 2. (Color online) Isofield curves of $\sqrt{-M}$ vs T for the optimally doped YBaCuO ($T_c=92$ K) with $H\parallel c$. Dashed lines below T_c show the extrapolation of the fittings to $T_a(H)$. Solid lines above T_c represent fittings obtained from Eq. (5). Inset: optimally doped YBaCuO with $H\parallel ab$.

tained with field applied parallel to the c axis, is a crossing point appearing below T_c which defines a field independent magnetization for the corresponding set of curves. This crossing point, which occur for two-dimensional (2D) (Refs. 18–20) and three-dimensional (3D) (Refs. 20 and 21) sys-

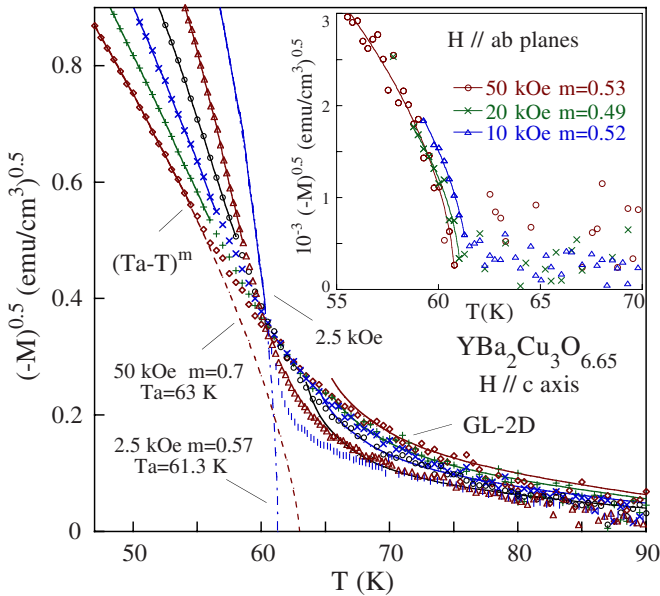


FIG. 3. (Color online) Selected Isofield curves of $\sqrt{-M}$ vs T for the deoxygenated YBaCuO ($T_c=61.5$ K) with $H\parallel c$ for fields $H=2.5, 10, 20, 30, 40,$ and 50 kOe. Dashed lines below 65 K shown the extrapolation of the fittings to $T_a(H)$ for fields $H=2.5$ and 50 kOe. Thicker dashed lines above T_c represent fittings of Eq. (4) to the data with $H=20, 30, 40,$ and 50 kOe. Inset: deoxygenated YBaCuO with $H\parallel ab$.

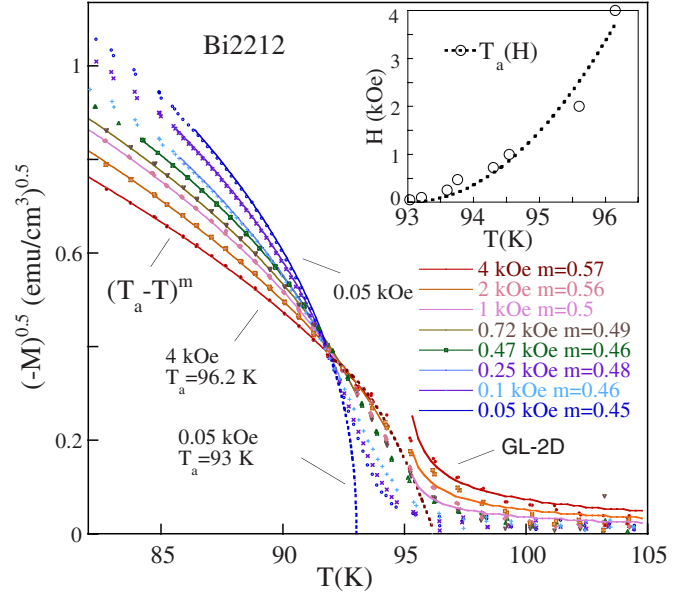


FIG. 4. (Color online) Isofield curves of $\sqrt{-M}$ vs T for Bi2212 with $H\parallel c$. Dashed lines show the extrapolation of the fittings to $T_a(H)$ for fields $H=0.05$ and 4 kOe. Solid lines above T_c represent fittings of Eq. (4) to the data with $H=1, 2,$ and 4 kOe. Inset: resulting H vs $T_a(H)$ diagram, where dashed line is only a guide to the eyes.

tems, are explained in terms of vortex fluctuations. We will not discuss this feature here, but we shall call the attention to the crossing point observed for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ in Fig. 4. An inspection of this figure shows that the crossing point is formed by curves obtained for magnetic fields from 50 Oe to 4 kOe. Previous works^{18,19} showing the same crossing point of magnetization curves in Bi2212 were obtained with fields in the kOe range (the lowest field in Ref. 18 is 1 kOe, while the lowest field here is 0.05 kOe). The fact that very low field curves also cross the same point defined by intermediate-high fields may deserve further considerations since the theory predicting the existence of this crossing point^{18–20} is worked out in the lowest-Landau-level approximation. On the other hand, the crossing point for a quasi-two-dimensional system is obtained in Ref. 19 from a critical fluctuation theory. Then, the fact that isothermal curves for much lower fields cross the same point in Fig. 4 suggests that this system, which is known to have a very large anisotropy ($\gamma \geq 100$) may have a two-dimensional characteristic in the vicinity of T_c even for very low fields,²² as observed in deoxygenated YBaCuO .²⁴ To check out this possibility, we estimate the value of the parameter defined in Ref. 23 $r = 8[\xi_{ab}^2(0)/\pi\gamma s]^2$ for Bi2212 with $T_c=93$ K, where γ is the anisotropy parameter which is assumed to be on the order of 100 , $\xi_{ab}^2(0) = \phi_0^2/2\pi T_c |dH_{c2}/dT|_{T_c}$ is the in-plane Ginzburg-Landau coherence length extrapolated to $T=0$ K, ϕ_0 is the flux quantum, and $s \sim 15$ Å (Ref. 18) the CuO_2 layers periodicity. The parameter r above coincides at $T=T_c$ for dirty systems with the same parameter first defined in Ref. 22 which carries important information about the dimensionality of the system. The calculated value is $r \approx 6 \times 10^{-5}$ where we used $\gamma=100$ and $\xi_{ab}(0)=13$ Å (which results from the

analysis of the fluctuation diamagnetism above T_c , see below). A plot of the reduced magnetic field $h \equiv H/H_{c2}(0)$ vs r is presented in Fig. 9 of Ref. 22, which helps to identify the dimensionality of fluctuations in a given system when the value of r is known, and also predicts whether a given system can exhibit a field-induced-dimensionality crossover (3D toward 2D) in the vicinity of T_c . An inspection on this figure suggests that a system with $r \approx 6 \times 10^{-5}$ may enter the superconducting region exhibiting two-dimensional fluctuations for very low fields, which explains the crossing point observed here in Bi2212.

B. Asymptotic behavior of the $\sqrt{-M}$ vs T curves near T_c

Near the upper critical field H_{c2} (Ref. 25) the magnetic induction B obtained from the Landau-Ginzburg equation is given by¹³

$$B = H - \frac{4\pi e\hbar}{mc} |\psi|^2, \quad (1)$$

where ψ is the order parameter and B is the magnetic induction. The magnetization $M = (B - H)/4\pi$ is

$$M = -\frac{e\hbar}{mc} |\psi|^2 \quad (2)$$

and follows that $\sqrt{-M}$ is directly proportional to the average amplitude of the order parameter. Then, the quantity $\sqrt{-M}$ can be expressed near T_c in the form $\sqrt{-M} \propto [T_c(H) - T]^m$ where $T_c(H)$ is the mean-field transition temperature. The mean-field value of the critical exponent is $m = 1/2$ for a s -wave BCS superconductor¹³ and for a d -wave superconductor within a Ginzburg-Landau theory.²⁶

Here, we study the presence of a phase-mediated transition by fitting to each curve the general scaling form $\sqrt{-M} \propto (T_a - T)^m$, where $T_a(H)$ is an apparent transition temperature representing the onset of phase correlations, and m is a fitting exponent. As already mentioned this fitting is motivated by the results of Ref. 14 which show that phase fluctuations of a d -wave order parameter have an effect on the superfluid density of states reducing the gap in the vicinity of T_c . The authors of Ref. 14 show that this is a direct result of the d -wave order parameter symmetry which presents a node and antinode where the effects of phase and amplitude fluctuations are distinct. This result implies that the temperature dependence of the gap near T_c is controlled by phase fluctuations. It is shown in Ref. 14 that the overall effect of phase fluctuations produces a change in the shape (temperature dependence) of the gap increasing the value of the exponent m .¹² The phase mediated behavior of interest here is within a region where $\sqrt{-M}$ should follow the typical asymptotic behavior of the superconducting gap near T_c , which in our curves occur below the region where exist a large amplitude fluctuation extending above T_c . The inflection point occurring very close to T_c , which is clearly visible in each curve, marks a crossover between high temperature amplitude fluctuations and lower temperature phase fluctuations. The inflection point for each curve occurs very close to the crossing point. The fitting is then performed in each

curve in a temperature window delimited at higher temperatures by the inflection point occurring near but below T_c , and at lower temperatures by the region where the magnetization show a linear dependence with temperature. The lower temperature cutoff lies within the region where the Abrikosov approximation above discussed is valid. The fitting is usually performed in a temperature window of 5–10 K. Results for the fitted values of $T_a(H)$ and m as obtained for each sample are presented in Figs. 2–4. For a better visualization we extrapolated some fittings toward the value of $T_a(H)$. It is important to note the anomalous enhancement of magnetization appearing above $T_a(H)$ in each curve, which is due to fluctuations of the amplitude of the order parameter with no phase coherence. Such fluctuations have been recently studied by using the Gaussian GL theory with a *total-energy* cutoff in the fluctuation spectrum to extend its applicability to high reduced temperatures.¹⁵ Here, we apply this approach to the data above T_c in Figs. 2–4 (see below).

Results of the analysis performed on the $\sqrt{-M}$ vs T curves (for $H \parallel c$ axis) of $\text{YBa}_2\text{Cu}_3\text{O}_{6.65}$, and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$, produced values of $T_a(H) > T_c$, with $dT_a(H)/dH > 0$ which support the scenario of a state with coherent phase persisting above T_c in these systems which are well-known to exhibit a pseudogap region.¹ Although $T_a(H)$ does not correspond to a true phase transition, it appears to control the scaling properties of the magnetization $M(T)$ in the asymptotic regime, just below the regime of strong amplitude fluctuations. Also, resulting values of the exponent m for $\text{YBa}_2\text{Cu}_3\text{O}_{6.65}$ are larger than the mean-field value $1/2$. Resulting values for the exponent m for the $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ and $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ crystals were enhanced slightly for $H \parallel \hat{c}$ relative to their mean-field values. Results for $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ crystal with $T_c = 92$ K confirmed the previous result of Ref. 12 with $T_a(H) \approx T_c(H)$ obtained in another single crystal with similar doping for both field directions, indicating the absence of phase coherence above T_c for the optimally doped crystal. It should be mentioned that this result is consistent with the fact that optimally doped YBaCuO does not show the pseudogap phase.¹ We mention that results for both YBaCuO samples for the direction $H \parallel ab$ (not shown) also produced values of $T_a(H) \approx T_c(H)$ in agreement with the mean-field behavior expected for $T_c(H)$. A possible explanation for the anomalous behavior of dT_a/dH and m in the underdoped YBaCuO sample as well in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ arises from the d -wave pairing symmetry of the order parameter. As discussed in Ref. 14, phase fluctuations of a d -wave order parameter can have a net effect on the superfluid density of states by reducing the gap in the vicinity of T_c . An inspection of Fig. 2 of Ref. 14 shows that the change in the shape of the gap near T_c , due to phase fluctuations, is accompanied by a change in the value of the fitting exponent m . In this picture, the dependence of m on H observed for $H \parallel c$ can be explained in terms of the order parameter symmetry which is likely to be d wave in the ab planes of the high- T_c systems. The presence of nodes or antinodes in the order parameter has definite consequences for the phase and amplitude fluctuations.¹⁴ It is important to mention that a value of $m \approx 1/2$ was found for all curves with $H \parallel ab$ for YBaCuO samples studied here and in Ref. 12. The observed anisotropy of the exponent m in YBaCuO , suggests that, in con-

trast to the effect observed in the gap for the coupling in the ab planes (which is probed when $H\parallel c$ axis), phase fluctuations have a minor effect in the gap for the coupling along the c -axis direction, which is probed when $H\parallel ab$ planes. This fact may suggest that the coupling along the c -axis direction in YBaCuO has a different symmetry (without nodes) than that in the ab planes, possibly s wave as suggested in Ref. 27. But, since magnetic field enhance fluctuation effects in high- T_c superconductors,²⁸ and YBaCuO is very anisotropic (mainly deoxygenated YBaCuO), experiments with much higher fields for $H\parallel ab$ (which are not available) would be necessary before to conclude for a different symmetry along the c -axis direction.

C. Effect of amplitude fluctuations on the $\sqrt{-M}$ vs T curves above T_c

We discuss below the large amplitude fluctuation observed above $T_a(H)$ in the $\sqrt{-M}$ vs T curves for all samples. These amplitude fluctuations with no phase coherence, which extend up to temperatures well above $T_a(H)$, can be interpreted in terms of the Gaussian GL theory by introducing a cutoff in the fluctuation spectrum to eliminate the contribution of the high-energy fluctuation modes.¹⁵ In the case of 2D high- T_c superconductors it is given by¹⁶

$$M = -\frac{k_B T N}{\phi_0 s} \left[-\frac{c}{2h} \psi\left(\frac{h+c}{2h}\right) - \ln \Gamma\left(\frac{h+\varepsilon}{2h}\right) + \ln \Gamma\left(\frac{h+c}{2h}\right) + \frac{\varepsilon}{2h} \psi\left(\frac{h+\varepsilon}{2h}\right) + \frac{c-\varepsilon}{2h} \right]. \quad (3)$$

Here, Γ and ψ are the gamma and digamma functions, $\varepsilon \equiv \ln(T/T_c)$ the reduced temperature, N the number of superconducting CuO_2 layers in their periodicity length, k_B the Boltzmann constant and $c \approx 0.5$ the total-energy cut-off constant.¹⁵ In the low magnetic field limit ($h \ll \varepsilon$) Eq. (3) may be approximated by

$$M = -\frac{k_B T N}{6\phi_0 s} h \left(\frac{1}{\varepsilon} - \frac{1}{c} \right). \quad (4)$$

In the case of superconductors moderately anisotropic, the fluctuation magnetization above T_c in the low magnetic field region may be calculated in the Lawrence-Doniach Ginzburg-Landau (GL-LD) approach. In presence of a total-energy cutoff it leads to²⁹

$$M = -\frac{k_B T N}{6\phi_0 s} h \left[\frac{1}{\varepsilon} \left(1 + \frac{4\xi_c^2(0)}{\varepsilon s^2} \right)^{-1/2} - \frac{1}{c} \right] \quad (5)$$

where $\xi_c(0)$ is the coherence length transverse to the CuO_2 layers. It is worth noting that in the 2D limit ($\xi_c(0) \ll s$) this expression reduces to Eq. (4), while in the 3D limit [$\xi_c(0) \gg s$] and in absence of a cutoff ($c \rightarrow \infty$), it reduces to the well known Schmidt result for 3D materials.³⁰

Due to their high $H_{c2}(0)$ values, the data above T_c for the highly anisotropic $\text{YBa}_2\text{Cu}_3\text{O}_{6.65}$ and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ were analyzed in terms of Eq. (4), while the moderately anisotropic $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ was studied in terms of Eq. (5). As shown in Figs. 2–4, the agreement with the data is good, the

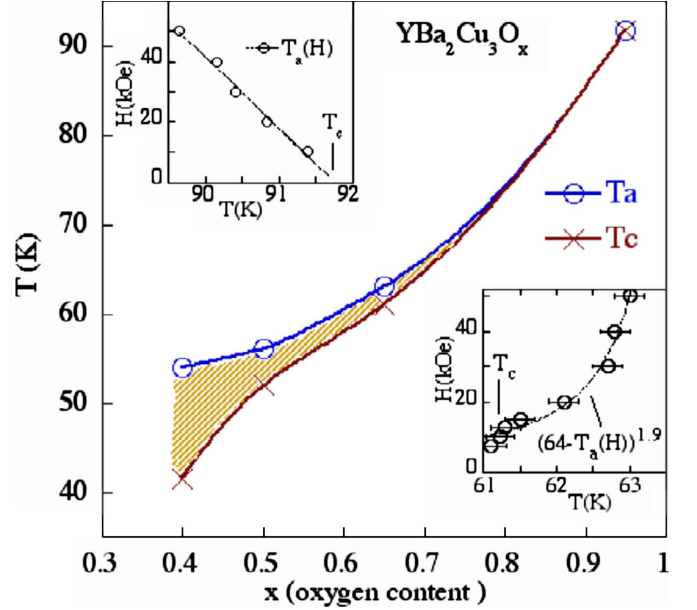


FIG. 5. (Color online) Phase diagram for YBaCuO where resulting values of $T_a(H)$ and T_c are plotted as a function of the oxygen content. The shadowed area represents the region above T_c where phase correlations persist. Top inset: H vs $T_a(H)$ diagram for the optimally doped crystal. Lower inset: H vs $T_a(H)$ diagram for the deoxygenated crystal.

resulting $\xi_{ab}(0)$ values being 15 Å for $\text{YBa}_2\text{Cu}_3\text{O}_{6.65}$, 13 Å for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$, and 6 Å [and $\xi_c(0)=1$ Å] for $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$. Taking into account the uncertainty in the fluctuations amplitude (mainly due to the normal-state background, a possible incomplete superconducting fraction,³¹ or the effect of possible T_c inhomogeneities),^{32,33} these values are well within the ones in the literature.³⁰

D. T - x phase diagram for the superconducting phase fluctuations in YBaCuO

We finally plot in Fig. 5 a diagram with values of T_c and $T_a(H=50$ kOe) as a function of the oxygen content for the YBaCuO samples studied here and in Ref. 12. The lower inset shows values of $T_a(H)$ as obtained for sample with $T_c=61.5$ K and the top inset shows the same plot for sample with $T_c=92$ K. As show in the lower inset of Fig. 5, values of $T_a(H)$ for sample with $T_c=61.5$ K obey a power-law behavior which tends to a field independent temperature $T_a=64$ K, which is 1 K above the value of $T_a(H)$ for $H=50$ kOe plotted in Fig. 5. This field independent temperature is probably related to the temperature T_ϕ defined in Ref. 8. For samples with $T_c=41$ and 52 K the plots of $T_a(H)$ vs H appearing in Ref. 12 are approximately linear and we also plot in Fig. 5 the corresponding values of $T_a(H)$ obtained for the highest field $H=50$ kOe. It might be possible that this linear behavior of $T_a(H)$ with field as observed for these two samples represents a low-intermediate field region which would give place to a power-law behavior (as observed for sample with $T_c=61.5$ K) for much higher fields. The shadowed region in Fig. 5 evidences the region above the $T_c(H)$ line where phase fluctuations were found to

be coherent, which agrees with the existence of a region of temperatures above T_c where phase coherence persists in YBaCuO as predicted in Ref. 8. Despite Fig. 5 here was obtained with an applied magnetic field (which gradually probes a temperature region above T_c where phase correlation persists) and Fig. 5 of Ref. 8 does not consider a magnetic field, it is interesting to compare both figures. A comparison between Fig. 5 here and Fig. 5 of Ref. 8 suggests that the qualitative behavior of the T_a line found here is more likely to be related to the T_1 line of Ref. 8 which values were extracted from specific heat measurements in YBaCuO (see Fig. 2 of Ref. 8) rather than with the T_ϕ line. The T_ϕ line appearing in Fig. 5 of Ref. 8 lies well above T_c even for the optimally doped sample, while our results obtained for two distinct optimally doped samples show in this case the onset of phase coherence coinciding with T_c . It is important to mention that the values of $T_a(H)$ plotted in Fig. 5 are much below the values of the T_1 line in Fig. 5 of Ref. 8. Since it appears that the literature lacks on specific heat measurements with field on deoxygenated YBaCuO, it should be considered the possibility that the T_1 line in Fig. 5 of Ref. 8 would tend to the T_ϕ line under an applied magnetic field. For the case of optimally doped ($T_c=92$ K) and slightly underdoped ($T_c=88$ K) YBaCuO crystals³⁴ the available data in the literature show that values of T_1 (the temperature T_1 defines a feature in the specific heat occurring above the anomaly as indicated in Ref. 8) seem to decrease with field following the shift in the anomaly to lower temperatures as field increases. We mention that the shadowed region in Fig. 5 is probably much larger than it appears, since we used values of $T_a(H=50$ kOe) and for samples with $T_c=41$ and

52 K the values of $T_a(H)$ are probably much below the values which would result if higher fields were available.

IV. CONCLUSIONS

In conclusion, we studied the effects of phase and amplitude fluctuations in isofield magnetization curves of the high- T_c systems $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ and $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$. The analysis of the asymptotic behavior of $\sqrt{-M}$ with temperature near T_c suggests, with the exception for optimally doped YBaCuO, that all studied systems show phase coherence persisting above T_c , where this region above T_c is gradually probed by the magnetic field. Results of this work allowed to study the evolution of the phase coherence region above T_c in the pseudogap region of YBaCuO. The results are in agreement with a theoretical prediction⁸ for high- T_c systems with a d -wave pairing along the ab planes, which exhibit a pseudogap above T_c . The large amplitude fluctuation observed for all systems is well explained in terms of uncorrelated fluctuations in a Gaussian Ginzburg-Landau theory with a total-energy cutoff in the fluctuation spectrum.

ACKNOWLEDGMENTS

We thank H. Beck for helpful suggestions and Boyd Veal who kindly provided the YBaCuO crystals. J.M. acknowledges financial support from the Spanish Ministerio de Educación y Ciencia (Grant No. FIS2007-63709), and the Xunta de Galicia (Grant No. 07TMT007304PR). A.D.A. acknowledges support from CNPq.

¹T. Timusk and B. Statt, Rep. Prog. Phys. **62**, 61 (1999).

²P. A. Lee, N. Nagaosa, and X.-G. Wen, Rev. Mod. Phys. **78**, 17 (2006).

³Z. Tesanović, Nat. Phys. **4**, 408 (2008).

⁴Y. Wang, L. Li, M. J. Naughton, G. D. Gu, S. Uchida, and N. P. Ong, Phys. Rev. Lett. **95**, 247002 (2005).

⁵Y. Wang, L. Li, and N. P. Ong, Phys. Rev. B **73**, 024510 (2006).

⁶L. Cabo, J. Mosqueira, and F. Vidal, Phys. Rev. Lett. **98**, 119701 (2007); N. P. Ong, Y. Wang, L. Li, and M. J. Naughton, *ibid.* **98**, 119702 (2007).

⁷V. J. Emery and S. A. Kivelson, Nature (London) **374**, 434 (1995).

⁸P. Curty and H. Beck, Phys. Rev. Lett. **91**, 257002 (2003).

⁹M. Mayr, G. Alvarez, C. Şen, and E. Dagotto, Phys. Rev. Lett. **94**, 217001 (2005).

¹⁰D. Li and B. Rosenstein, Phys. Rev. B **60**, 9704 (1999).

¹¹S. Salem-Sugui, Jr., M. M. Doria, A. D. Alvarenga, V. N. Vieira, P. F. Farinas, and J. P. Sinnecker, Phys. Rev. B **76**, 132502 (2007); M. M. Doria and S. Salem-Sugui, Jr., *ibid.* **78**, 134527 (2008).

¹²S. Salem-Sugui, Jr. and A. D. Alvarenga, Phys. Rev. B **77**, 104533 (2008).

¹³P. G. deGennes, *Superconductivity of Metals and Alloys* (Addison-Wesley, New York, 1989).

¹⁴H.-J. Kwon, Phys. Rev. B **59**, 13600 (1999); H.-J. Kwon and A.

T. Dorsey, *ibid.* **59**, 6438 (1999).

¹⁵F. Vidal, C. Carballeira, S. R. Currás, J. Mosqueira, M. V. Rammallo, J. A. Veira, and J. Viña, EPL **59**, 754 (2002), and references therein.

¹⁶C. Carballeira, J. Mosqueira, A. Revcolevschi, and F. Vidal, Physica C **384**, 185 (2003); The factor N in Eq. (3) was included to take into account that $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ and YBaCuO have more than one CuO_2 layers in their periodicity length, see, e.g., J. Mosqueira, E. G. Miramontes, C. Torron, J. A. Campa, I. Rasines, and F. Vidal, Phys. Rev. B **53**, 15272 (1996).

¹⁷B. W. Veal, A. P. Paulikas, H. You, H. Shi, Y. Fang, and J.-W. Downey, Phys. Rev. B **42**, 6305 (1990); J. D. Jorgensen, B. W. Veal, A. P. Paulikas, L. J. Nowicki, G. W. Crabtree, H. Claus, and W. K. Kwok, *ibid.* **41**, 1863 (1990); Samples of $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ from Argonne with same nominal content of oxygen, x , show reproducible values of T_c and of $T_c(H)$ independently of the sample batch, as attested by the samples with $x=0.35$ and $x=0.05$ measured here, which belongs to a newer batch, and two different samples with $x=0.35$ and $x=0.05$ from older batches measured in the past (see S. Salem-Sugui, Jr., L. Ghivelder, M. Friesen, K. Moloni, B. Veal, and P. Paulikas, *ibid.* **60**, 102 (1999) for $x=0.35$; S. Salem-Sugui, Jr. and E. Z. da Silva, Physica C **235-240**, 1919 (1994) for $x=0.05$).

¹⁸L. N. Bulaevskii, M. Ledvij, and V. G. Kogan, Phys. Rev. Lett. **68**, 3773 (1992).

- ¹⁹Z. Tesanović, L. Xing, L. Bulaevskii, Q. Li, and M. Suenaga, Phys. Rev. Lett. **69**, 3563 (1992).
- ²⁰B. Rosenstein, B. Y. Shapiro, R. Prozorov, A. Shaulov, and Y. Yeshurun, Phys. Rev. B **63**, 134501 (2001).
- ²¹E. Z. da Silva and S. Salem-Sugui, Jr., Physica C **257**, 173 (1996).
- ²²R. A. Klemm, M. R. Beasley, and A. Luther, Phys. Rev. B **8**, 5072 (1973).
- ²³R. R. Gerhardts, Phys. Rev. B **9**, 2945 (1974).
- ²⁴S. Salem-Sugui, Jr., A. D. Alvarenga, V. N. Vieira, and O. F. Schilling, Phys. Rev. B **73**, 012509 (2006).
- ²⁵A. Abrikosov, Zh. Eksp. Teor. Fiz. **32**, 1442 (1975) [Sov. Phys. JETP **5**, 1174 (1957)].
- ²⁶J.-H. Xu, Y. Ren, and C. S. Ting, Phys. Rev. B **52**, 7663 (1995).
- ²⁷J. Mannhart, H. Hilgenkamp, G. Hammerl, and C. W. Schneider, Phys. Scr., T **T102**, 107 (2002).
- ²⁸U. Welp, S. Fleshler, W. K. Kwok, R. A. Klemm, V. M. Vinokur, J. Downey, B. Veal, and G. W. Crabtree, Phys. Rev. Lett. **67**, 3180 (1991).
- ²⁹J. Mosqueira, C. Carballeira, M. V. Ramallo, C. Torrón, J. A. Veira, and F. Vidal, EPL **53**, 632 (2001).
- ³⁰M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, New York, 1996), Chap. 9.
- ³¹J. Mosqueira, J. A. Campá, A. Maignan, I. Rasines, A. Revcolevschi, C. Torrón, J. A. Veira, and F. Vidal, EPL **42**, 461 (1998); J. Mosqueira, M. V. Ramallo, A. Revcolevschi, C. Torrón, and F. Vidal, Phys. Rev. B **59**, 4394 (1999).
- ³²These inhomogeneities may increase the measured fluctuation diamagnetism in the temperature region from T_c up to $T_c + \Delta T_c$, ΔT_c being the transition width. This effect should be more pronounced in measurements performed under low fields [$H \ll H_{c2}(0)$], see, e.g., L. Cabo, F. Soto, M. Ruibal, J. Mosqueira, and F. Vidal, Phys. Rev. B **73**, 184520 (2006). By this reason, we have excluded from the analysis above T_c the data measured under the lowest magnetic fields in the 61.5 K YBCO and in the Bi2212 samples.
- ³³E. F. Skelton, A. R. Drew, M. S. Osofsky, S. B. Qadri, J. Z. Hu, T. A. Vanderah, J. L. Peng, and R. L. Greene, Science **263**, 1416 (1994).
- ³⁴M. B. Salamon, J. Shi, N. Overend, and M. A. Howson, Phys. Rev. B **47**, 5520 (1993).