

Interplay of instabilities in mounded surface growth

Buddhapriya Chakrabarti* and Chandan Dasgupta†

Centre for Condensed Matter Theory, Department of Physics, Indian Institute of Science, Bangalore 560012, India.

(Received 23 August 2004; published 9 February 2005)

We numerically study a one-dimensional conserved growth equation with competing linear (Ehrlich-Schwoebel) and nonlinear instabilities. As a control parameter is varied, this model exhibits a nonequilibrium phase transition between two mounded states, one of which exhibits slope selection and the other does not. The coarsening behavior of the mounds in these two phases is studied in detail. In the absence of noise, the steady-state configuration depends crucially on which of the two instabilities dominates the early time behavior.

DOI: 10.1103/PhysRevE.71.020601

PACS number(s): 81.10.Aj, 81.15.Hi, 05.70.Ln

The phenomenon of formation and coarsening of mounds in epitaxially grown thin films [1] is a subject of much recent experimental [2,3] and theoretical [4–6] interest. Traditionally, the formation of mounds has been attributed to the presence of an Ehrlich-Schwoebel (ES) step-edge barrier [7,8] that hinders the downward motion of atoms across the edge of a step. The ES mechanism is usually represented in continuum growth equations as a *linear* instability [9] that is controlled by higher-order nonlinear terms. In ES-type models, slope selection occurs (i.e., the slope of the mounds remains constant during coarsening) only if the “ES part” of the slope-dependent surface current has one or more stable zeros as a function of the slope.

In our earlier work [10,11] on a class of spatially discrete, conserved, one-dimensional (1D) models of epitaxial growth, we reported on a mechanism of mound formation and coarsening with slope selection that is different from the conventional ES mechanism. We studied the spatially discretized Lai–Das Sarma equation [12] of molecular beam epitaxy (MBE) growth and an atomistic model [13] that provides a discrete realization of the dynamics described by this equation, and found the occurrence of a *nonlinear* instability [14] in which isolated pillars or grooves grow in time if their height or depth exceeds a “critical” value. When this instability is controlled by the introduction of an infinite number of higher-order gradient nonlinearities, these models show, for a range of parameter values, the formation of mounds with well-defined slopes that remain constant during the coarsening process.

In most experimentally studied systems, however, it is believed that the ES step-edge barrier is present, although it may possibly be very weak. It is, therefore, important to understand how the behavior of our models would be modified when the ES mechanism is incorporated in their kinetics. To address this issue, we have studied, using numerical integration, a spatially discretized 1D growth equation in which a linear ES-type instability is present in conjunction with the

nonlinear instability mentioned above. The main results of this study are as follows. If the model parameters are such that the nonlinear instability is the dominant one, then the behavior of the system is similar to that found in our earlier studies [10,11]: it exhibits the formation of triangular mounds and power-law coarsening with slope selection. If, on the other hand, the linear instability is dominant, then the system exhibits a different kind of mounded state in which the mounds have a cusplike shape and they steepen during the coarsening process. We call these two mounded states “faceted” and “cusped,” respectively. As the parameters are changed, the system undergoes a *dynamical phase transition* from one of these mounded states to the other.

We study a spatially discretized 1D version of the fourth-order conserved growth equation, proposed in the context of MBE growth [9,12], in which the nonlinear instability [14] is controlled using a control function [10,11] of the form proposed by Politi and Villain [5] and a linear instability of the form proposed by Johnson *et al.* [2] to represent the ES effect is also included. Thus, the equation of motion of the interface height in appropriately nondimensionalized form is written as

$$\begin{aligned} \partial h_i / \partial t = & -\tilde{\nabla}^4 h_i + \lambda \tilde{\nabla}^2 [|\tilde{\nabla} h_i|^2 / (1 + c_1 |\tilde{\nabla} h_i|^2)] \\ & - \tilde{\nabla} [\tilde{\nabla} h_i / (1 + c_2 |\tilde{\nabla} h_i|^2)] + \eta_i(t), \end{aligned} \quad (1)$$

where h_i is the nondimensionalized height variable at lattice site i , and $\tilde{\nabla}$ and $\tilde{\nabla}^2$ are the lattice versions of the derivative and Laplacian operators, respectively, calculated using the nearest neighbors as outlined in our earlier papers [10,11]. In Eq. (1), c_1 , c_2 , and λ are constants (model parameters), and $\eta_i(t)$ represents uncorrelated random noise with zero mean and unit variance. Our results are based on the numerical integration of this equation in 1D, using a simple Euler scheme [14] in which the time evolution of the height variables is given by

$$\begin{aligned} h_i(t + \Delta t) = & h_i(t) + \Delta t [\tilde{\nabla}^2 (-\tilde{\nabla}^2 h_i(t) + \lambda \{ |\tilde{\nabla} h_i(t)|^2 / [1 \\ & + c_1 |\tilde{\nabla} h_i(t)|^2 \}] - \tilde{\nabla} \{ \tilde{\nabla} h_i(t) / [1 + c_2 |\tilde{\nabla} h_i(t)|^2 \}]] \\ & + \sqrt{\Delta t} \eta_i(t). \end{aligned} \quad (2)$$

In all our calculations, the value of the parameter c_2 was held

*Present address: Department of Physics, University of Massachusetts, Amherst, MA 01003. Electronic address: buddho@physics.umass.edu

†Electronic address: cdgupta@physics.iisc.ernet.in

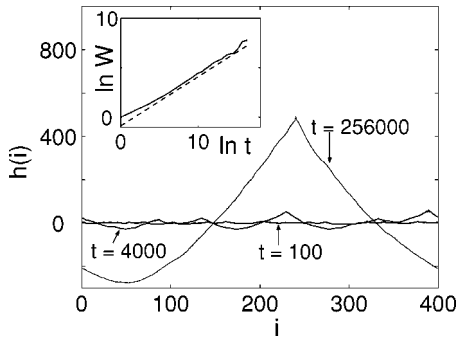


FIG. 1. The interface profiles at three different times ($t=100$, 4000 and 256 000) in a run with noise starting from a flat state for an $L=400$ sample with $\lambda=4.0$ and $c_1=0.05$. A double logarithmic plot of the interface width W as a function of time t , averaged over 15 runs for $L=1000$ samples in the presence of noise, and a power-law fit are shown in the inset.

fixed at unity, and c_1 and λ were varied. Our results are obtained for different system sizes, $40 \leq L \leq 1000$, with periodic boundary conditions. We do not find any significant L -dependence. We have used a time step $\Delta t=0.01$ for most of our studies and checked that very similar results are obtained with smaller values of Δt .

We first describe the results obtained in the absence of the noise term. In this case, we find that if the parameter c_1 is sufficiently small, then the long-time behavior of the interface depends on which of the instabilities dominates at early times. In order to characterize this, we considered initial configurations with a single pillar of height h_0 on an otherwise flat interface, and studied the long-time behavior as a function of h_0 . We find that when h_0 is sufficiently small, so that the nonlinear instability is not initiated, the linear instability dominates the time evolution and the resulting morphology is mounded without slope selection (“cusp” like), similar to the profiles shown in Fig. 1. If on the other hand h_0 is large enough to seed the nonlinear instability, then mounds with a “magic” slope (“faceted” morphology, similar to those shown in Fig. 2) result. The critical value of λ that separates these two kinds of behavior is approximately given by A/λ , $A \approx 21$, with a weak dependence on the parameter c_1 .

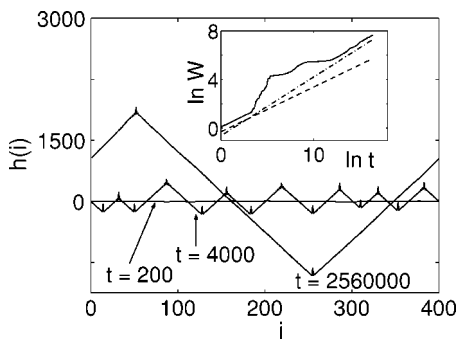


FIG. 2. Interface profiles at three different times ($t=200$, 4000 and 2 560 000) in a run starting from a flat state for an $L=400$ sample with $\lambda=4.0$ and $c_1=0.01$. A double logarithmic plot of the interface width W as a function of time t , averaged over 15 runs for $L=1000$ samples in the presence of noise, and power-law fits to the early- and late-time data are shown in the inset.

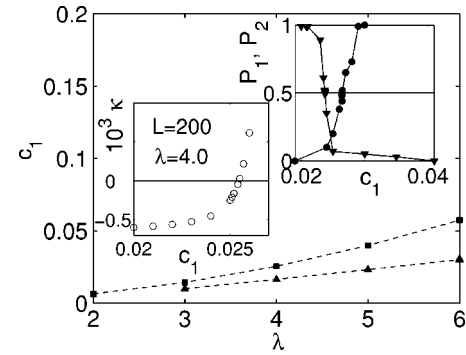


FIG. 3. Double logarithmic plots of the width W (full line) and the average of the maximum slope s_m (dash-dotted line) as a function of time t , for faceted growth with slope selection in the absence of noise. These data are for $\lambda=4.0$, $c_1=0.01$, and $L=800$, averaged over 20 initial conditions. In this case the growth exponent $\beta = 0.5 \pm 0.01$ (the dashed line is the best power-law fit) and the steepening exponent $\theta=0$.

This “bistable” behavior is found only if the control parameter c_1 is sufficiently small. Otherwise, the system evolves to the cusped morphology even if the initial configuration has a high central pillar. Thus, the faceted morphology is found in the zero-noise simulations only if $c_1 < c_1^{sp}(\lambda)$ [the superscript sp denotes “spinodal,” (see below)] and the initial configuration is sufficiently rough to seed the nonlinear instability. This behavior may be understood from a linear stability analysis. In both the faceted and cusped growths, the finite-sized system evolves, at long times, to a profile with a single mound that is a fixed point of the noiseless dynamics. Examples of such profiles (obtained from simulations with noise that slightly roughens the profiles) are shown in Figs. 1 and 2. These fixed points can also be obtained by calculating the h_i for which $g_i=0$ for all i , where g_i is the term multiplying Δt on the right-hand side of Eq. (2). The local stability of the faceted fixed point may be determined from a calculation of the eigenvalues of the matrix $M_{ij} = \partial g_i / \partial h_j$ evaluated at the fixed point. We find that the largest eigenvalue of this matrix crosses zero at a spinodal value, $c_1 = c_1^{sp}(\lambda)$ (see inset of Fig. 3), signaling an instability of the faceted profile. Thus, for $0 < c_1 < c_1^{sp}(\lambda)$, the dynamics of Eq. (2), without noise, admits two locally stable invariant profiles: a cusped profile without slope selection, and a faceted one with slope selection. Depending on the initial state, the no-noise dynamics takes the system to one of these two fixed points. For example, an initial state with one pillar on a flat background is driven by the no-noise dynamics to the cusped fixed point if the height of the pillar is smaller than a critical value (mentioned earlier), and to the faceted one otherwise. The dependence of c_1^{sp} on the nonlinearity parameter λ is shown in Fig. 3. Such a spinodal line does not exist for the cusped fixed point.

We have studied in detail the process of coarsening of the mounds in the two different (faceted and cusped) growth modes. In these simulations, the initial configuration is obtained by setting $h_i = h_0 r_i$ where r_i is a random number uniformly distributed between -1 and 1 . If $c_1 < c_1^{sp}$ and h_0 is sufficiently large to initiate the nonlinear instability, the sys-

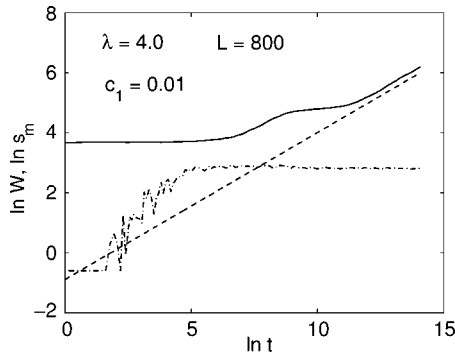


FIG. 4. Variation of width W (full line) and the average of the maximum slope, s_m (dash-dotted line) as a function of time t on a log-log scale for cusped growth in the absence of noise ($\lambda=4.0$, $c_1=0.05$, and $L=800$, averaged over 20 initial conditions). The growth exponent is $\beta=0.54\pm 0.02$, and the steepening exponent $\theta=0.2\pm 0.02$. The best power-law fits are shown by the dashed lines.

tem evolves to a faceted structure; a cusped structure is obtained otherwise. The results reported here were obtained from averages over 20 such runs with different initial configurations. In the region of parameter space, $0 < c < c_1^{sp}(\lambda)$, where the faceted phase is locally stable, the mounds coarsen in time with the slope of the mounds remaining constant. In this case, the average mound size $R(t)$ is obviously proportional to the interface width $W(t)$. As shown in Fig. 4, the interface width in this growth mode increases as a power law with time in the long-time coarsening regime, while the slope of the mounds remains constant in time. The exponent β that described this power-law coarsening behavior, $W(t) \propto R(t) \propto t^\beta$, is found to be close to 0.5. The coarsening of the mounds in the cusped regime [i.e., for $c_1 > c_1^{sp}(\lambda)$ and any initial configuration, and $c_1 < c_1^{sp}(\lambda)$ and sufficiently smooth initial configurations] is qualitatively different. In this growth mode, both the interface width and the average slope $s(t)$ of the cusplike mounds [as well as the maximum slope $s_m(t)$] to increase with time as power laws in the coarsening regime: $W(t) \propto t^\beta$, and $s(t) \propto t^\theta$. This implies that the average mound size also increases with time as a power law: $R(t) \propto t^n$ with $n = \beta - \theta$. This behavior is illustrated in Fig. 5. The values of the exponents are found to be $\beta=0.54\pm 0.02$ and $\theta=0.2\pm 0.02$, implying that the coarsening exponent is $n=0.34\pm 0.04$.

In the presence of noise, the steady state behavior is independent of the initial condition. When the control parameter c_1 is sufficiently large, the nonlinear instability is completely suppressed and the route to mounding is similar to the linear instability-dominated behavior mentioned above, the configurations being slightly roughened versions of their noiseless counterpart. This is illustrated in Fig. 1, where the interface profiles in a typical run starting from a flat state for $L=400$, $\lambda=4.0$, and $c_1=0.05$ are shown at times $t=100$ (early-time regime), $t=4000$ (coarsening regime) and $t=256\,000$ (steady state). The inset shows the interface width W as a function of t , averaged over 15 runs for $L=1000$ samples. The averaged data show $W \propto t^\beta$, $\beta=0.5\pm 0.01$ in the coarsening regime. The average slope of the mounded interface grows as $s(t) \propto t^\theta$, with $\theta=0.18\pm 0.02$ and hence the coarsening exponent is $n=0.32\pm 0.03$.

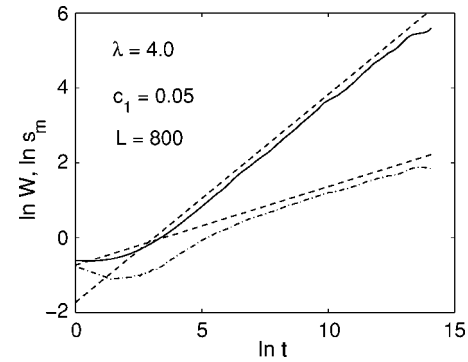


FIG. 5. Phase diagram for a $L=200$ system, where the critical values of the control parameter c_1 are shown as functions of λ . The critical value $c_1^{sp}(c_1^{cr})$ above which the faceted phase is unstable (metastable) is shown by squares (triangles). The dashed lines are guides to the eye. Left inset: The zero crossing of the largest eigenvalue κ of the stability matrix of the faceted fixed point as a function of c_1 ($\lambda=4.0$, $L=200$). Right inset: The probabilities P_1 (circles) and P_2 (inverted triangles) (see text) as functions of c_1 with $\lambda=5.0$ and $L=200$.

As the value of c_1 is decreased below a critical value holding λ fixed, the nonlinear instability dominates over the linear one. At early times in runs starting from a flat state, the interface is self-affine and the interface width shows power-law scaling with an exponent close to 0.37. As time progresses isolated pillars with height $h_0 > h_{min}$, where h_{min} is the minimum height of such a pillar above which the nonlinear instability is operative, make their appearance through random fluctuations. The time evolution of the interface beyond the point of occurrence of the instability is similar to that in the noiseless situation. In Fig. 2 we present snapshots of an $L=400$ sample for $\lambda=4.0$ and $c_1=0.01$ at different stages of growth: $t=200$ (before the onset of the instability), $t=4000$ (coarsening regime), and $t=2\,560\,000$ (steady state). The inset shows a plot of the interface width as a function of time, obtained by averaging over 15 runs for $L=1000$ samples. The averaged data show a power-law growth regime with an exponent of 0.37 ± 0.01 before the onset of the instability and a second power-law coarsening regime with $W \propto t^\beta$, $\beta=0.49\pm 0.02$.

A dynamical phase transition at $c_1 = c_1^{cr}(\lambda) < c_1^{sp}(\lambda)$ separates these two kinds of growth modes. To calculate $c_1^{cr}(\lambda)$, we start a system at the faceted fixed point and follow its evolution according to Eq. (2) for a long time (typically $t=10^4$) to check whether it reaches a cusped steady state. By repeating this procedure many times (typically 100 runs), the probability, $P_1(\lambda, c_1)$, of a transition to a cusped state is obtained. For fixed λ , P_1 increases rapidly from 0 to 1 as c_1 is increased above a critical value. Typical results for P_1 as a function of c_1 for $\lambda=5.0$ are shown in the right inset of Fig. 3. The value of c_1 at which $P_1=0.5$ provides an estimate of c_1^{cr} . Another estimate is obtained from a similar calculation of $P_2(\lambda, c_1)$, the probability that a flat initial state evolves to a faceted steady state. As expected, P_2 increases sharply from 0 to 1 as c_1 is decreased (see the right inset of Fig. 3), and the value of c_1 at which this probability is 0.5 is slightly lower than the value at which $P_1=0.5$. This difference reflects

finite-time hysteresis effects. The value of c_1^{cr} is taken to be the average of these two estimates, and the difference between the two estimates provides a measure of the uncertainty in the determination of c_1^{cr} . The phase boundary obtained this way is shown in Fig. 3, along with the results for c_1^{sp} .

The scaling behavior in the coarsening regime in the presence of noise is the same as that found in the noiseless case. The qualitative behavior in the faceted phase is similar to that found in our earlier work [10,11] on this model without the ES term. The ES term, however, has an important effect: it changes the coarsening exponent from 0.33 to 0.5. A model very similar to the one considered here was studied by Torcini and Politi [15] for parameter values deep in the cusped regime (small λ , large c_1). The mounded morphology we find in this regime is similar to that found in their study. Our results for the exponents θ and n are slightly different from the values ($\theta=n=1/4$) reported by them. This is probably due to crossover effects—we have found values of n closer to $1/4$ if smaller values of λ and/or larger values of c_1 are used.

In summary, we have shown that a nonlinear instability in

our spatially discrete growth model in which the linear ES instability is also present may, for appropriate parameter values, lead to mound formation with slope selection and power-law coarsening. This is qualitatively different from the behavior in the parameter regime where the ES instability dominates: the system exhibits mound formation in this regime also, but there is no slope selection. The coarsening exponent has different values in these two regimes which are separated by a line of first-order dynamical phase transitions. The ES part of the surface current in our model does not vanish for any nonzero value of the slope. Therefore, the slope selection we find in the regime where the nonlinear instability is dominant is qualitatively different from that in ES-type models and is a true example of nonlinear pattern formation. The noiseless version of our model exhibits an interesting dependence on initial conditions: the long-time behavior depends on whether the inhomogeneities in the initial configuration are sufficient to seed the nonlinear instability. Both kinds of mounding behavior found in this study have been observed in experiments, and our model may be relevant in the development of an understanding of these experimental observations.

-
- [1] J. Krug, *Adv. Phys.* **46**, 139 (1997).
 - [2] M. D. Johnson, C. Orme, A. W. Hunt, D. Graff, J. Sudijono, L. M. Sander, and B. G. Orr, *Phys. Rev. Lett.* **72**, 116 (1994).
 - [3] G. Apostolopoulos, J. Herfort, L. Daweritz, K. H. Ploog, and M. Luysberg, *Phys. Rev. Lett.* **84**, 3358 (2000), and references therein.
 - [4] M. Siegert and M. Plischke, *Phys. Rev. Lett.* **73**, 1517 (1994).
 - [5] P. Politi and J. Villain, *Phys. Rev. B* **54**, 5114 (1996).
 - [6] M. Rost and J. Krug, *Phys. Rev. E* **55**, 3952 (1997), and references therein.
 - [7] G. Ehrlich and F. G. Hudda, *J. Chem. Phys.* **44**, 1039 (1996).
 - [8] R. L. Schwoebel, *J. Appl. Phys.* **40**, 614 (1969).
 - [9] J. Villain, *J. Phys. I* **1**, 19 (1991).
 - [10] B. Chakrabarti and C. Dasgupta, *Europhys. Lett.* **61**, 547 (2003).
 - [11] B. Chakrabarti and C. Dasgupta, *Phys. Rev. E* **69**, 011601 (2004).
 - [12] Z. W. Lai and S. Das Sarma, *Phys. Rev. Lett.* **66**, 2348 (1991).
 - [13] J. M. Kim and S. Das Sarma, *Phys. Rev. Lett.* **72**, 2903 (1994).
 - [14] C. Dasgupta, J. M. Kim, M. Dutta, and S. Das Sarma, *Phys. Rev. E* **55**, 2235 (1997).
 - [15] A. Torcini and P. Politi, *Eur. Phys. J. B* **25**, 519 (2002).