

Compatibilization of immiscible polymer blends (PV/PVDF) by the addition of a third polymer (PMMA): analysis of phase morphology and mechanical properties

Noureddin Moussaïf, Robert Jérôme*

Center for Education and Research on Macromolecules (CERM), University of Liège, Institute of Chemistry, B6, Sart-Tilman, 4000 Liège, Belgium

Received 11 May 1998; received in revised form 7 July 1998; accepted 4 August 1998

Abstract

Compatibilization of the immiscible polycarbonate (PC)/polyvinylidene fluoride (PVDF) pair by a third homopolymer, i.e. polymethylmethacrylate (PMMA), was studied in relation to phase morphology and mechanical properties of the polyblends. Scanning electron microscopy showed a more regular and finer phase dispersion when the original PMMA content in PVDF exceeded 20 wt.%. The premixing of PVDF with ca. 40 wt.% PMMA also had a beneficial effect on mechanical properties, such as ultimate tensile strength, elongation at break, and notched impact strength. All these experimental results are consistent with the interfacial activity of PMMA in the PC/PVDF blends. © 1999 Elsevier Science Ltd. All rights reserved.

Keywords: Polymer blends; Polymethylmethacrylate; Polycarbonate

1. Introduction

Most polymer blends of commercial interest are multi-phase materials as a result of the thermodynamic immiscibility of the constitutive components. The usually high immiscibility of polymer pairs results in gross phase separation and poor interfacial adhesion, which requires these polyblends to be compatibilized. This situation explains why interface engineering has been a major research topic in the polymer blend area for the last decade [1,2].

The most general strategy for improving the compatibility of immiscible polymers is the use of block or graft copolymers, whose one block is identical or at least miscible with one blend component, and the second constituent block is identical to/or miscible with the second blend component. Depending on the molecular parameters, this type of copolymers exhibit interfacial activity and reinforce the interface [3–19].

The implementation of “reactive blending” has been a major progress in the blends compatibilization, as the in situ formation of the polymeric surfactant may significantly improve the economy of the blends processing [20–24]. In an alternative strategy, Fleischer and Koberstein have reported on the effective compatibilization of immiscible

polymers as result of non covalent although strong (e.g. ionic) interactions between the constitutive polymers through the interface [25].

Hobbs et al. have observed a substantial compatibilization upon the addition of a third polymeric component immiscible with each of the blended polymers but selected for a relatively low interfacial tension with each of them. The criteria for compatibilization are spreading coefficients so that the additive is selectively localized at the interface of the original two-phase polyblend [26]. As an extreme case of this third strategy, the compatibilization agent is completely miscible with the two components of the binary blend [27].

The major limitation of the first strategy is the very limited availability of block copolymers, that are anyway costly materials. The reactive blending can only be contemplated when the polymers to be blended can be modified by functional groups mutually reactive and stable under the processing conditions [23,24,28]. These prerequisites are not fulfilled in the specific case of polycarbonate (PC) and polyvinylidene fluoride (PVDF) blends, as no parent block or graft copolymer can be made available, and the appropriate functionalization of these polymers is not straightforward. In this work, polymethylmethacrylate (PMMA) has been considered as a potential compatibilizer for the PC/PVDF polyblends, as PMMA is known to be miscible with PVDF [29–31] and compatible with PC [32–34]. In

* Corresponding author.

E-mail address: rjerome@ulg.ac.be (R. Jérôme)

Table 1
Main characteristics and origin of the polymers used in this study

Polymers	Abbreviation	Commercial designation	Source	Molecular weight $M_w(10^{-3})$	M_w/M_n	T_g^b (°C)	Density (g cm^{-3}) 230 the 80/20°C
Polycarbonate	PC	Makrolon 3103	Bayer	58 ^a	1.7 ^a	150	1.09
Polymethylmethacrylate	PMMA	Diakon	ICI	60 ^a	1.6 ^a	118	1.08
Polyvinylidene fluoride	PVDF	Solef × 10N	Solvay	125	1.8	-45	1.7

^a Determined by SEC with a polystyrene calibration.

^b Determined by dynamic mechanical analysis (DMA) at 1 Hz.

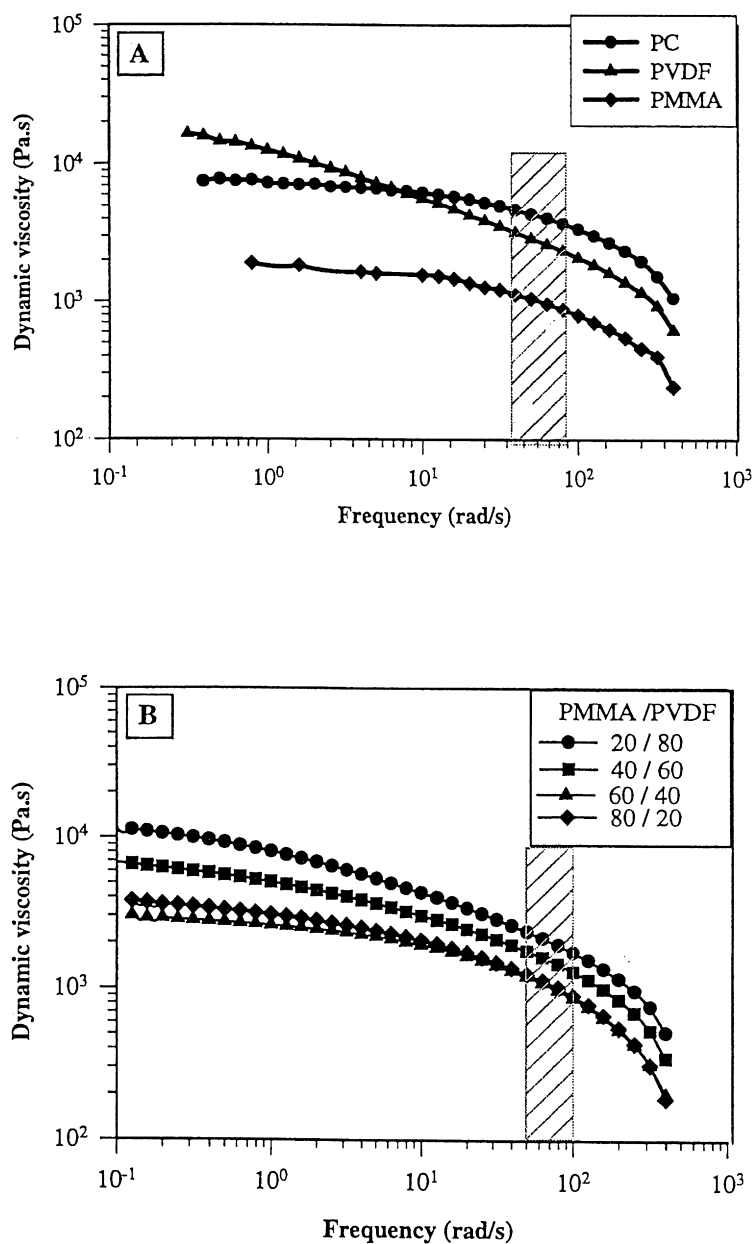


Fig. 1. (A) Frequency dependence of the dynamic viscosity at 235°C for PC, PVDF and PMMA. (B) Frequency dependence of the dynamic viscosity at 235°C for PVDF/PMMA blends.

Table 2
Viscosity and viscosity ratio for PC, PVDF, PMMA and homogeneous PVDF–PMMA blends of various compositions (235°C, 60 s⁻¹)

	Viscosity ⁻¹ (Pa s)	Viscosity ratio $\eta_{PC}/\eta_{(PMMA/PVDF)}$
PC	4020	–
PVDF	2600	1.55
PMMA	950	–
20 PMMA/80 PVDF	2170	1.85
40 PMMA/60 PVDF	1620	2.48
60 PMMA/40 PVDF	1100	3.65
80 PMMA/20 PVDF	1140	3.53

the extreme, PMMA might behave as a common “solvent” for PC and PVDF in the melt.

In a previous article, the ability of PMMA to decrease the PC/PVDF interfacial tension and to improve the PC/PVDF interfacial adhesion has been investigated [35]. Briefly, the PC/PVDF interfacial adhesion is steadily improved by the premixing of PVDF with increasing amounts of PMMA. This improvement tends however to level off when the PMMA concentration in PVDF exceeds 35 wt.% PMMA. In parallel, the interfacial tension between melted PC and PVDF is decreased down to a plateau value when PVDF is premixed with ca. 40 wt.% PMMA. These observations are thus consistent with the interfacial activity of PMMA in PC/PVDF blends.

This article deals with the beneficial effect that PMMA can have on the phase morphology and the mechanical properties of these polyblends.

2. Experimental

The main characteristics of the polymers used in this study are listed in Table 1. Blends were prepared by mixing the polymeric components in a Brabender mixing chamber (Plasti-corder) at 235°C, for 8 min, the rotation speed being 50 rpm. PC was first added and melted under mixing for 3 min, followed by the addition of PMMA and PVDF. Samples of PC, PVDF/PMMA and PC/PMMA/PVDF blends were prepared by compression molding at 220°C for 5 min and then quenched at room temperature still under pressure. The polymers were previously dried overnight in a vacuum oven at 120°C for PC and 70°C for PMMA.

Stress–strain curves were recorded with an Instron universal tensile tester (model DY 24) at a tensile rate of 20 mm min⁻¹, and yield strength (σ_y , MPa), ultimate tensile strength (σ_b , MPa) and elongation at break (ϵ_b , %) were reported as average values for at least five samples.

Charpy impact tests were carried out at room temperature with a 20 J hammer and notched samples. The impact energy was the average value for five samples of 50 mm length, 6 mm width, and 2 mm thickness, the notch depth being 0.35 mm.

Samples for tensile and impact testing were cut out from

2 mm thick plates prepared by compression molding at 220°C.

A Jeol JSM-840 A Scanning Electron Microscope (SEM) was used to observe fracture surfaces prepared at the liquid nitrogen temperature.

Image analysis was carried out using a Sun Sparc 10 working station equipped with a visilog noenis software (France).

3. Results and discussion

3.1. Effect of blend composition

The frequency dependence of the dynamic viscosity at 235°C for PC, PVDF and PMMA is shown in Fig. 1(A). According to Cox and Merz [36], these plots are equivalent to shear viscosity versus shear rate plots. The polycarbonate viscosity is high and essentially independent of frequency until 50 rad s⁻¹. In contrast, the viscosity of PVDF decreases upon increasing the frequency, so that the viscosity ratio for these two polymers at 235°C changes with the shear rate. In the whole frequency range (0.5–500 rad s⁻¹), PMMA is much less viscous than PC and PVDF at 235°C, which explains that the PVDF viscosity decreases with the PMMA content (at least until 60 wt.% PMMA) at high shear rates (50–100 s⁻¹) and 235°C (Fig. 1(B)).

The viscosity and viscosity ratio for PC, PVDF, PMMA and (PVDF–PMMA) blends at 235°C and a shear rate of 60 s⁻¹ are listed in Table 2.

According to a semi-empirical relationship by Wu [37], the phase inversion in a binary two-phase polyblend occurs at a composition that depends on the viscosity ratio (Eq. (1)).

$$\frac{\theta_2}{\theta_1} = 1.22 \left(\frac{\eta_2}{\eta_1} \right)^{0.29}, \quad (1)$$

where η_1 and η_2 are the viscosities for the phases 1 and 2, respectively; θ_1 and θ_2 are the volume fractions of these phases at the phase inversion.

For the type of mixing chamber and the mixing rate (50 rpm) used in this study, the maximum shear rate was estimated at approximately 60 s⁻¹. From Eq. (1) and the data in Table 1, the phase inversion (thus the dual-phase

Table 3
Composition at phase inversion (vol. Fraction PC)

Blends	θ_{PC}
PC/PVDF	0.48
PC/(80 PVDF–20 PMMA)	0.49
PMMA	
PC/(60 PVDF–40 PMMA)	0.51
PC/(40 PVDF–60 PMMA)	0.54
PC/(20 PVDF–80 PMMA)	0.54

continuity) should occur at $\theta_{PC} = 0.48$ for the PC/PVDF blends and at θ_{PC} in the range of 0.49–0.54 when the PMMA content in PVDF is increased from 20 to 80 wt.%. (Table 3).

Jordhano et al. have however questioned the validity of the semi-empirical Wu's equation [38], and proposed an exponent of 1 instead of 0.29 to the viscosity ratio. This disagreement is of course as important as the viscosity ratio is different from 1. In this study, as the PC/PVDF viscosity ratio at 235°C does not change too much with the PMMA content in PVDF (maximum by 2.3; Table 2), the phase inversion is predicted to occur in a comparable composition range for all the PC/(PVDF/PMMA) blends, whatever the equation used (Table 3).

The SEM observation of fracture surfaces is a qualitative way to confirm the phase morphology of polyblends. Figs. 2(a)–(d) and 3(a)–(h) illustrate the fracture surfaces for PC/PVDF blends and for PC/(PVDF–PMMA) blends

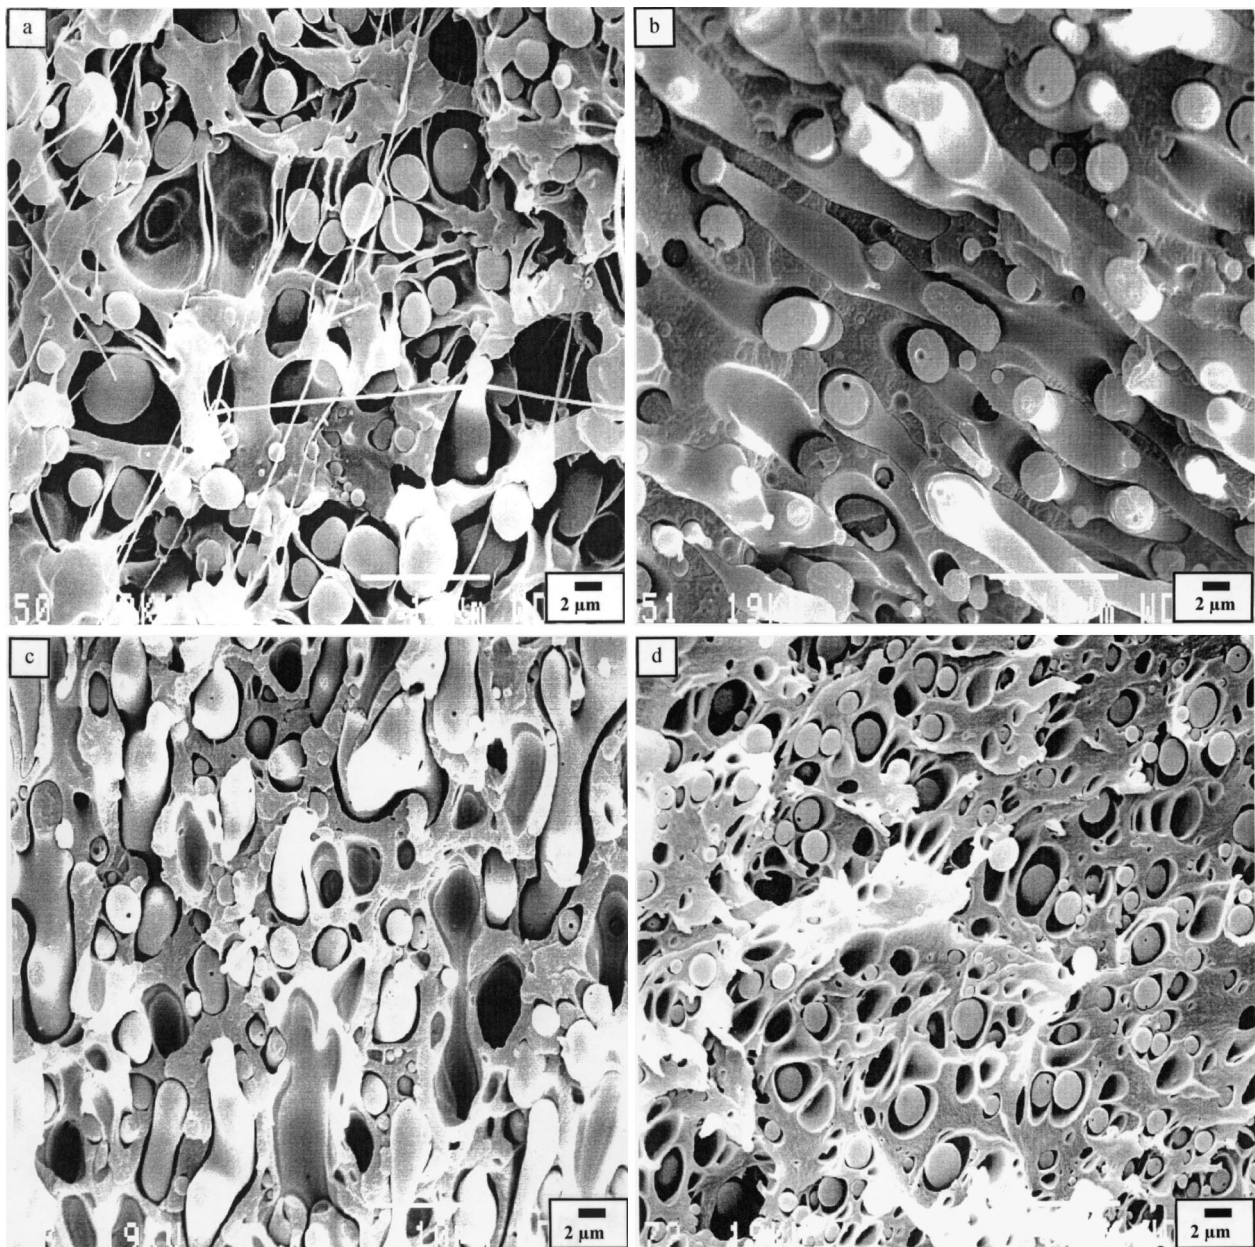


Fig. 2. Micrographs of fracture surfaces for different blend compositions of PC/PVDF (wt/wt.%), (a) 20/80, (b) 40/60, (c) 60/40 and (d) /80/20.

Table 4
Phase morphology of the PC/PVDF blends as analyzed by CHCl₃ extraction of PC

PC/PVDF	Extraction time (days)	Shape after extraction	Wt. % extracted PC ^a	Solvent aspect	Conclusions
20/80	15	Intact	0 (20)	Transparent	Dispersed morphology
40/60	15	Partially disintegrated	40.5 (40)	Cloudy solution	Co-continuous morphology
60/40	15	Partially disintegrated	62 (60)	Cloudy solution	Co-continuous morphology
80/20	15	Totally disintegrated	96 (80)	Very cloudy solution	Dispersed morphology

^a Theoretical values in parenthesis.

containing 20, 40, 60, and 80 wt.% PC. The phase morphology changes from dispersed phases of PC (Fig. 2(a)) to an apparently co-continuous morphology (Figs 2(b) and (c)) as the PC content is increased at the expense of the (PVDF/PMMA) component. Although SEM provides a 2-D observation of a 3-D situation, the phase inversion reasonably seems to occur between 40 and 60 wt.% PC (i.e. in the 43–65 vol% PC range). PC definitely forms the continuous phase of a dispersed type morphology when used at 80 wt.%. In order to confirm this preliminary investigation of the phase morphology, selective extractions of one polymeric component by a suitable solvent were carried out. In the case of complete extraction, the parent phase is continuous. If the original sample is not at all disintegrated as result of the complete extraction of one phase, the two phases are co-continuous. When the selective extraction of one phase remains uncomplete, this phase is at least partly dispersed [39,40]. In the specific case of the PC/PVDF and PC/(PVDF–PMMA) blends, PC and PMMA can be selectively dissolved by CHCl₃. The major observations are reported in Table 4 and Table 5 for the two series of blends under consideration. The 20/80 and 80/20 PC/PVDF blends have a typical phase dispersed morphology. Indeed, the 20 wt.% PC of the former blend cannot be extracted at all, whereas the 20 wt.% PVDF are collected as so small fragments upon dissolution of PC in the latter blend that their separation from the CHCl₃ solution is quite a problem. The co-continuity of the phases in the 40/60 and 60/40 PC/PVDF blends is close to 100% as the PC extraction is complete within the limits of inaccuracy because of contamination of the extraction solution by faint PVDF fragments. The

premixing of PVDF with increasing amounts of PMMA does not basically change the phase morphology of the co-continuous 40/60 and 60/40 PC/PVDF blends, as the (PC + PMMA) extraction is complete within the limits of experimental errors (Table 5). As a rule, the wt.% nonextracted polymer slightly exceeds the theoretical PVDF content, which more likely indicates that a small part of PMMA is not extracted from PVDF. For the 60/40 (80–20) PC/(PVDF–PMMA) blend, the residual solid fraction is much smaller than expected as a result of the very problematic separation of the solid residue from the CHCl₃ solution.

Fig. 2 shows that the dispersed domains are smaller in size when PVDF is the dispersed phase rather than PC. This observation may be explained, at least partly, by the difference in the melt viscosity of these two components, as the more viscous PC (dispersed) phase is more resistant to break-up than the PVDF one during melt mixing at 235°C [41].

The neat dispersed PC/PVDF blends show a phase morphology typical of highly immiscible polymers, with very large, coarse and irregular dispersed domains (Figs. 2(a) and (d)). More regular and finer dispersion is observed, when 10 wt % PMMA is premixed with PVDF in the 20/80 and 80/20 PC/PVDF blends. Indeed, the average particle size is then reduced up to four times (see Figs. 3(a)–(f)). Typical emulsification curves are shown in Fig. 4 for the 20/80 and 80/20 PC/PVDF blends added with PMMA.

It is worth comparing the average diameter observed for the dispersed domains to predictions based on various models. For newtonian polymers in a simple shear flow,

Table 5
Phase morphology of the PC/(PVDF–PMMA) blends as analyzed by CHCl₃ extraction of PMMA and PC

PC/(PVDF–PMMA)	Extraction time (days)	Shape after extraction	Wt. % nonextracted polymer (PVDF) ^a	Solvent aspect	Conclusions
40/60 (80–20)	15	Partially disintegrated	52 (48)	Cloudy solution	Co-continuous morphology
40/60 (60–40)	15	Partially disintegrated	38.5 (36)	Cloudy solution	Co-continuous morphology
40/60 (40–60)	15	Partially disintegrated	25 (24)	Cloudy solution	Co-continuous morphology
40/60 (20–80)	15	Partially disintegrated	13 (12)	Cloudy solution	Co-continuous morphology
60/40 (80–20)	15	Partially disintegrated	24 (32)	Cloudy solution	Co-continuous morphology
60/40 (60–40)	15	Partially disintegrated	25.5 (24)	Cloudy solution	Co-continuous morphology
60/40 (40–60)	15	Partially disintegrated	17.5 (16)	Cloudy solution	Co-continuous morphology
60/40 (20–80)	15	Partially disintegrated	8.5 (8.0)	Cloudy solution	Co-continuous morphology

^a Theoretical values in parenthesis.

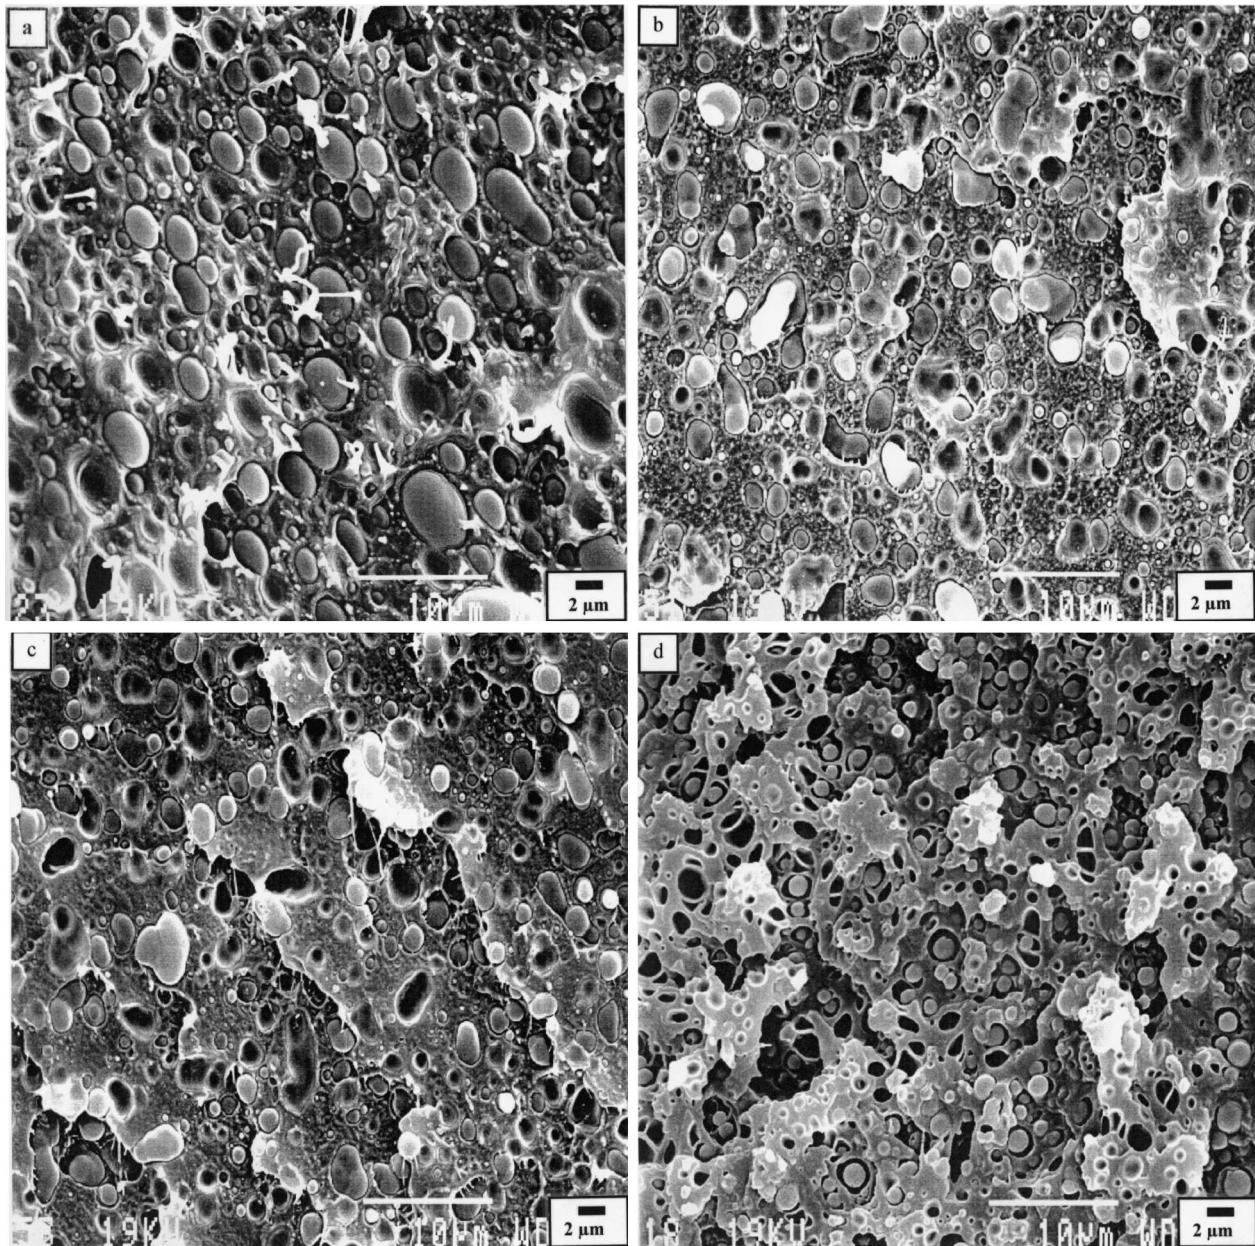


Fig. 3. Micrographs of fracture surfaces for different blend compositions of PC/(PMMA–PVDF) blends of various compositions. (a) 20/80 PC/(10PMMA–90PVDF), (b) 20/80 PC/(20PMMA–80PVDF), (c) 20/80 PC/(40PMMA–60PVDF), (d) 80/20 PC/(10PMMA–90PVDF), (e) 80/20 PC/(20PMMA–80PVDF), (f) 80/20 PC/(40PMMA–60PVDF), (g) 40/60 PC/(40PMMA–60PVDF), (h) 60/40 PC/(40PMMA–60PVDF).

particle breakup is expected to occur when the shear forces that deform the droplets exceeds the interfacial forces. On the basis of this force balance, Taylor [42–44] proposed to calculate the size of stable drops in dilute newtonian system by Eq. (2). Several authors have also discussed the effect that the viscosity ratio can have on the phase morphology of melt processed binary blends. In the case of polyamide/rubber blends, Wu [45] observed that the smallest particles were formed when the viscosity of the constitutive polymers were comparable ($\lambda = 1$). He also reported a good agreement between the final particle

diameter and values calculated from Eq. (3) over a wide range of polymer viscosities and interfacial tensions for low contents of dispersed phases (<15%). As particle coalescence was not taken into account in Eqs. (2) and (3), the predicted diameter must be considered as the lower limit value. Serpe et al. [46] further developed this type of equation by using the blend viscosity rather than the matrix viscosity and by considering a term of composition, thus coalescence effects (Eq. (4)). Using this modified viscosity ratio, Serpe confirmed Wu's equation for PE/PA6 blends.

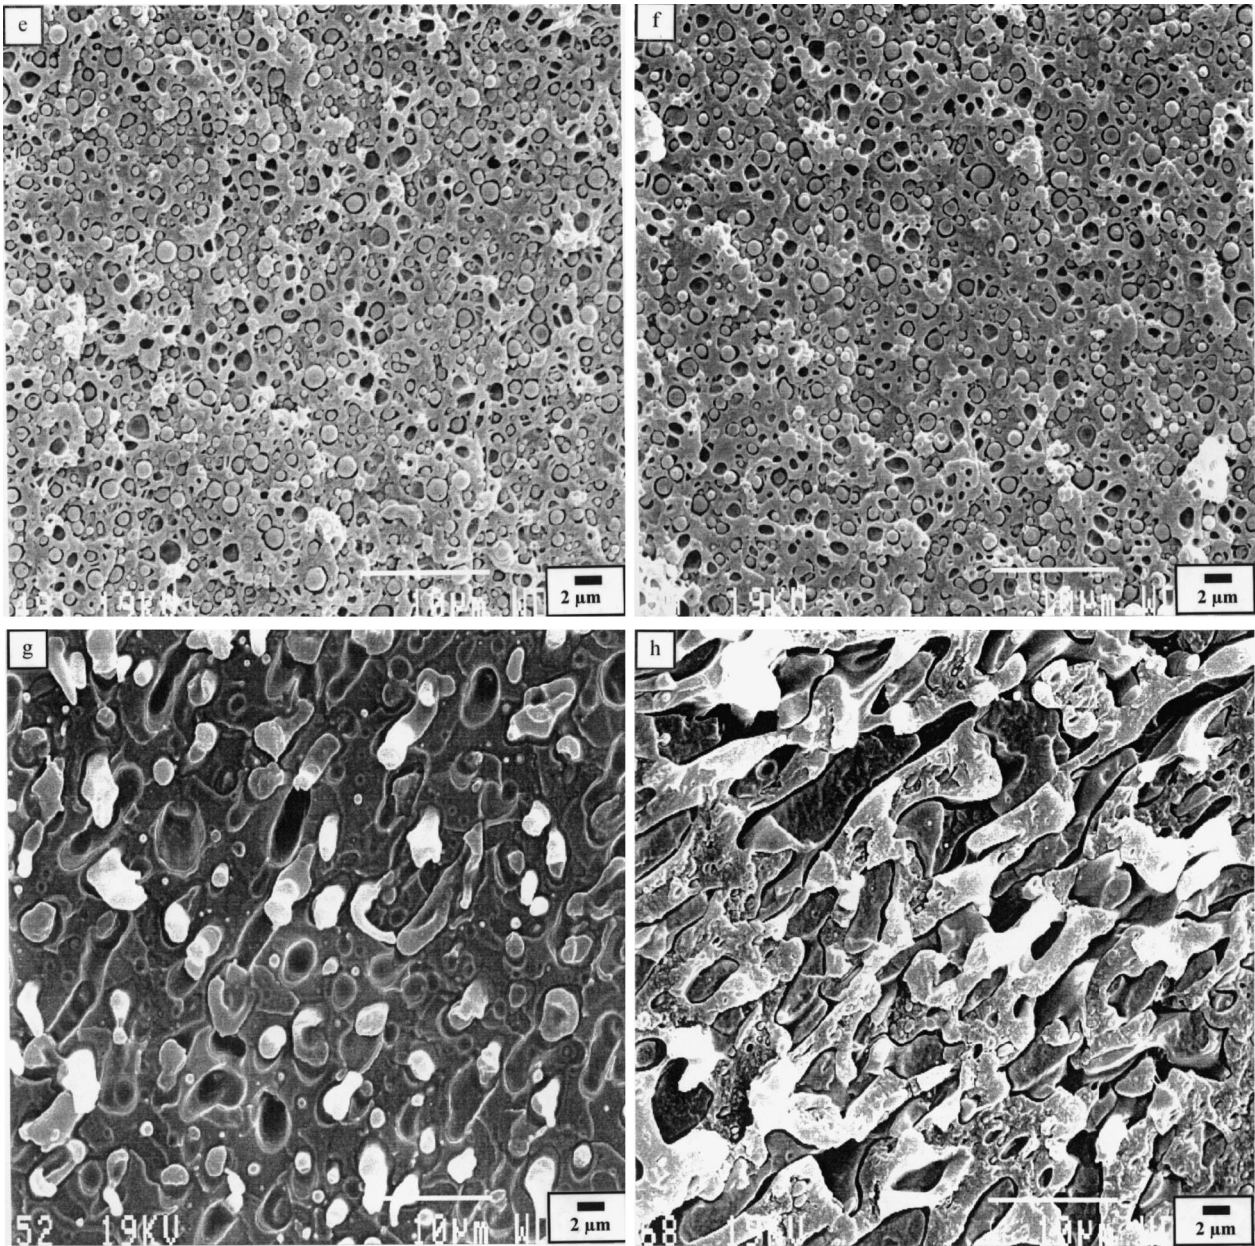


Fig. 3 (continued)

$$d_T = \frac{4\gamma_{1,2}(\lambda + 1)}{\dot{\gamma}\eta_m\left(\frac{19}{4}\lambda + 4\right)}, \quad (2)$$

$$d_{Wu} = \frac{4\gamma_{1,2}\lambda^{\pm 0.84}}{\dot{\gamma}\eta_m}, \quad (3)$$

with the λ exponent = + 0.84 for $\lambda > 1$ and -0.84 for $\lambda < 1$

$$d_s = \frac{4\gamma_{1,2}(\eta_d/\eta_b)^{\pm 0.84}}{\dot{\gamma}\eta_b(1 - (4\phi_d\phi_m)^{0.8})}, \quad (4)$$

where, $\gamma_{1,2}$ is the interfacial tension between components 1 and 2, η_d is the viscosity of the dispersed phase, η_m is the viscosity of the matrix, η_b is the viscosity of the blend, λ is the viscosity ratio ($= \eta_d/\eta_m$) ϕ volume fraction of the

Table 6
Interfacial tension between PC and PMMA/PVDF blends of different compositions at 220°C

Matrix	γ_{12} (dyn/cm ⁻¹)
PVDF	4.5 ± 0.6
20 PMMA / 80 PVDF	3.0 ± 0.5
40 PMMA / 60 PVDF	1.2 ± 0.5

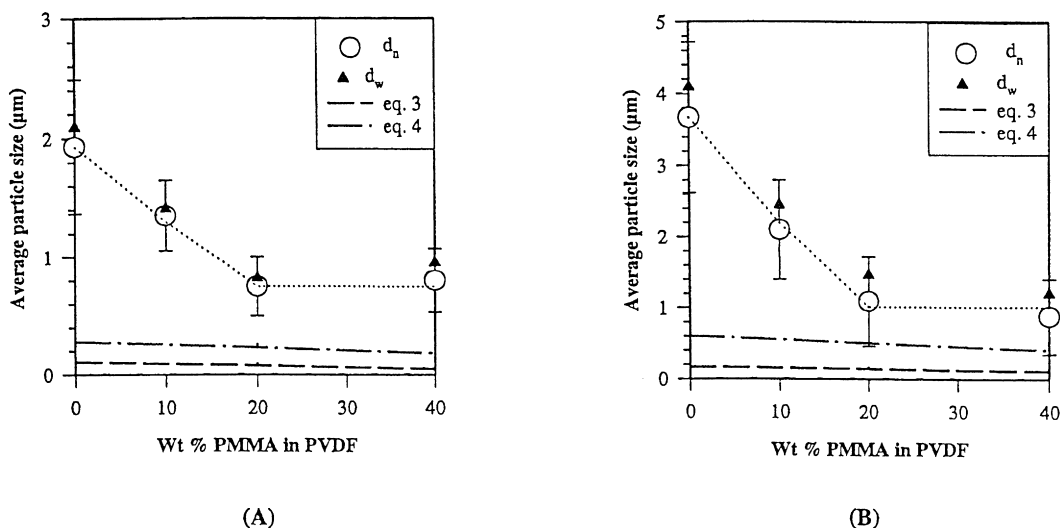


Fig. 4. Average particle diameter versus the PMMA content of the mixed PVDF/PMMA phase, for (A) the 80/20 PC/(PVDF-PAMMA) blends ($\lambda < 1$), (B) the 20/80 PC/(PVDF-PAMMA) blends ($\lambda > 1$).

dispersed phase (ϕ_d) and the matrix (ϕ_m) and $\dot{\gamma}$ is the shear rate.

The particle diameters were calculated from Eqs. (3) and (4) and compared to the experimental values in Fig. 4. As previously mentioned and in agreement with Refs. [47,48] the shear mixing rate was estimated at 60 s^{-1} , and the related viscosities and viscosity ratios are available in Table 2. The interfacial tensions, $\gamma_{1,2}$ have been measured by the imbedded fiber retraction method [49] as reported in Table 6.

The particle diameters calculated by Wu's equation (Eq. (3)) are much smaller than the experimental values, consistently with the fact that particle coalescence is not considered in Eq. (3) and with a non negligible content of the dispersed polymer (20 wt.%). Except for the neat PC/PVDF blends, the particle diameters calculated by the Serpe equation are in better agreement with experimental values, particularly in Fig. 4(B). The poor fitting of experimental theoretical data might, at least partly, result from coalescence during compression molding at 220°C for 5 min [50–52]. Nevertheless, Eqs. (3) and (4) cannot predict the sharp decrease in the particle diameter which occurs upon addition of small amounts of PMMA (20 wt.%) to PVDF, as the viscosity data are not changed very significantly. This observation more likely emphasizes the beneficial effect of PMMA, which decreases $\gamma_{1,2}$ to the point where the particles coalescence is significantly slowed down and in a finer phase dispersion is stabilized.

3.2. Mechanical properties

3.2.1. Neat PC/PVDF blends

In non compatibilized blends of immiscible polymers, the interfacial adhesion is usually not strong enough for stress to be efficiently transferred from one phase to another one

during yielding and/or fracture, thus resulting in poor mechanical properties. A previous article has reported that the PC/PVDF interfacial adhesion was improved by the addition of PMMA, that concentrated preferably in the PVDF rich phase, but also migrated to the PVDF/PC interface [35]. Measurement of the tensile properties of the PC/PVDF blends is another way to estimate how far interfacial adhesion, and thus the compatibilization effect, are improved by the addition of PMMA to PVDF. Tensile properties, particularly the elongation at break, ϵ_b , are indeed very sensitive to the strength of the interface, and they are routinely measured to evaluate the efficiency of compatibilization techniques [53,54]. The ultimate mechanical properties (σ_b , ϵ_b) and the yield strength (σ_y) of PC/PVDF blends are reported in Figs. 5(A) and (B).

Fig. 5(A) shows that the elongation at break, ϵ_b , is dramatically decreased in the whole composition range of the PC/PVDF blends compared to neat PC and PVDF. The dependence of the yield and ultimate tensile strength on the blend composition also shows a negative deviation with respect to the additivity rule (Fig. 5(B)). This general observation is consistent with a weak interfacial adhesion in the PC/PVDF blends.

3.2.2. PC/(PVDF/PMMA) ternary blends

In parallel to the investigation of the compatibilization activity of PMMA in the PC/PVDF binary blends, it is desirable to analyze the main physico-mechanical properties of the PVDF/PMMA blends. The degree of crystallinity and the melting temperature (T_m) of PVDF were measured by DSC as shown in Figs. 6(A) and (B). An S-shaped curve is a good description for the dependence of the PVDF crystallinity on the PMMA content (Fig. 6(A)). Beyond approximately 60 wt % PMMA in PVDF, all these blends are amorphous. In contrast, the melting temperature of PVDF

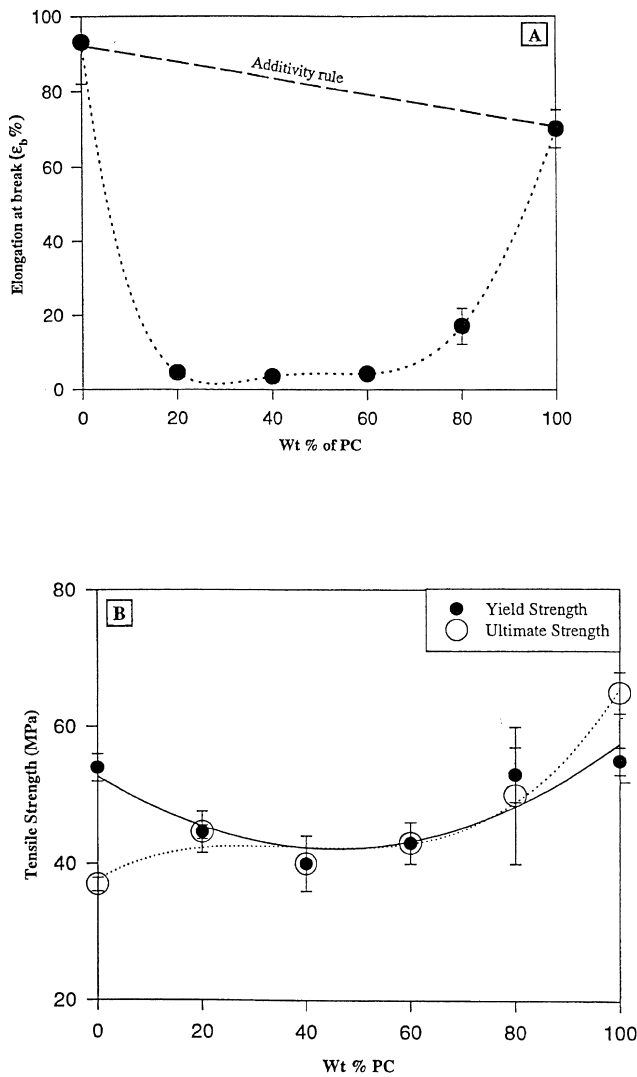


Fig. 5. (A) Dependence of the elongation at break on the PC content for the PC/PVDF blends. (B) Dependence of the yield and ultimate tensile strength on the PC content for the PC/PVDF blends.

linearly decreases when the PMMA content is increased up to 60 wt.%. Figs. 6(A) and (B) also confirm that the melting properties of PVDF in the PVDF/PMMA blends are not significantly modified by mixing these blends with PC, except for a smaller crystallinity at low PMMA contents (<40 wt.%) (Fig. 6(A)).

Fig. 7(A) shows how the elongation at break depends on the PMMA content in the PMMA/PVDF binary blends. Blends containing 20–40 wt % PMMA are ductile, whereas PMMA and PMMA/PVDF blends containing 60 wt.% PMMA and more are typically brittle.

Fig. 7(B) illustrates the dependence of the ultimate and yield strengths of the PMMA/PVDF blends on the blend composition. These data are in a qualitative agreement with observations reported by Noland et al. [55]. In order to explain the main characteristic features of Fig. 7, it is worth noting that the glass transition temperature (T_g)

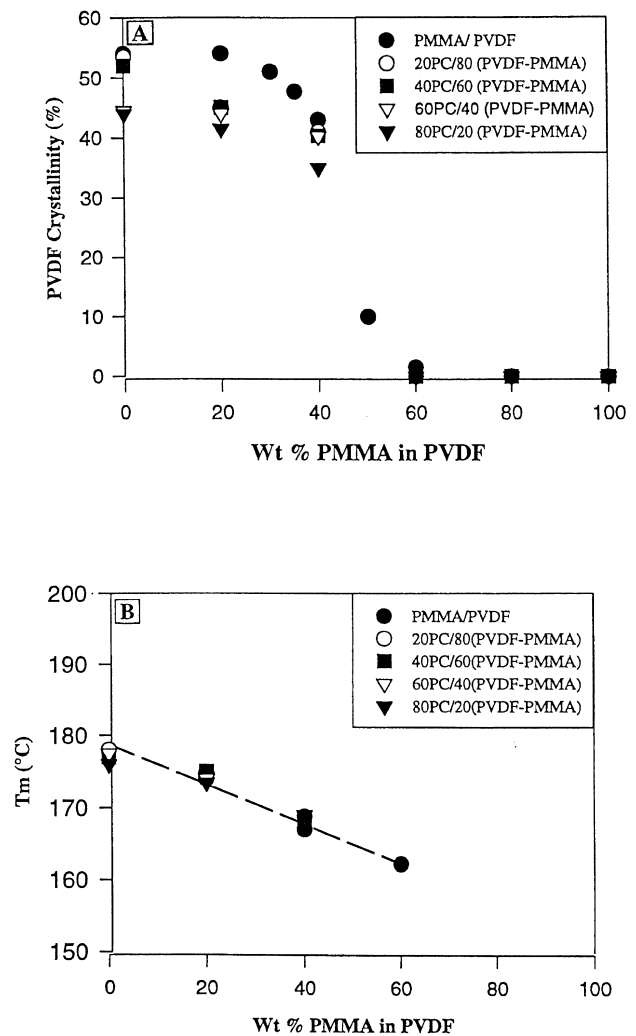


Fig. 6. (A) Crystallinity of PVDF versus the PMMA content in PVDF. (B). Melting temperature of PVDF versus the PMMA content in PVDF.

increases continuously from -40°C with the PMMA content and exceeds the testing temperature at approximately 10 wt.% PMMA contents. Thus when the PVDF/PMMA blends become predominantly amorphous [56–58].

Therefore, it is not surprising that both the yield and the ultimate tensile strengths start to decrease when PMMA is added with PVDF. This is the typical response when a liquid or a rubbery diluent (PVDF) is added to a glassy polymer (PMMA). However, tensile strengths pass through a minimum and then increase on further addition of PMMA. This behavior is consistent with a strengthening effect caused by crystallization of PVDF and, vitrification of the amorphous phase. Conversely, the elongation at break is very small for glassy PMMA and polyblends containing up to 40 wt.% PVDF. Upon further addition of PVDF, T_g falls in the range of the testing temperature and ϵ_b increases rapidly. However, the tendency is reversed when PVDF starts to crystallize.

Tensile properties of 20 PC/80 (PMMA–PVDF) blends versus the PMMA content in PVDF are shown in Figs. 8(A)

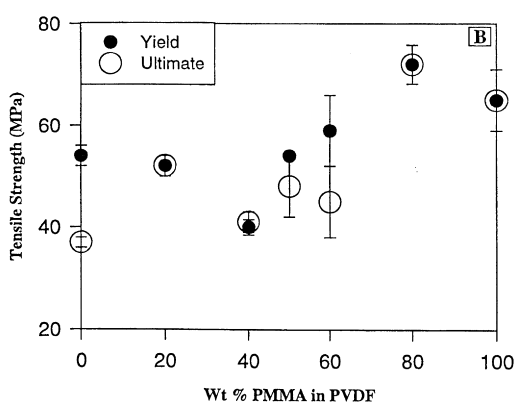
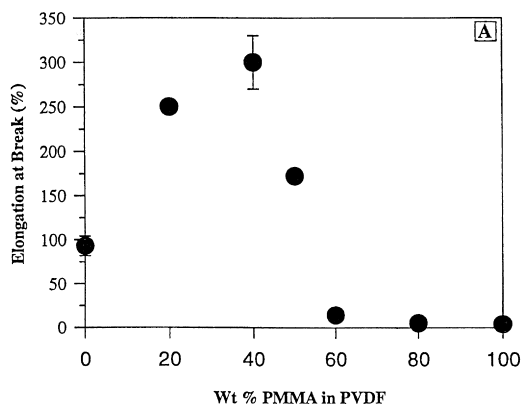


Fig. 7. (A) Elongation at break versus the PMMA content for PVDF/PMMA blends. (B) Yield and ultimate tensile strengths versus the PMMA content for PVDF/PMMA blends.

and (B). Upon dispersion of 20 wt.% PC, the tensile strengths at the yield point and at break for PVDF (Fig. 7(B)) merge to a unique value (45 MPa; Fig. 8(A)). However, when PVDF is premixed with PMMA, 20 wt.% PC have essentially no effect on the tensile strength of the PVDF/PMMA binary blends (comparison of Figs. 7(B) and 8(A)), which is an evidence for the PC/PVDF compatibilization by PMMA. Similarly, 20 wt.% PC make PVDF completely brittle (Fig. 8(B)). When PVDF is mixed with more than 20 wt.% PMMA, the elongation at break is remarkably increased, consistently with an improved interfacial adhesion. Beyond 40 wt.% PMMA in PVDF, a transition from a ductile to a brittle-like behavior is observed as was the case for the neat PVDF/PMMA blends (that form the matrix of the 20 PC/80 (PVDF/PMMA) blends) in this composition range.

In the case of the reverse composition for the ternary blends (80PC/20(PVDF–PMMA)), (Fig. 9(B)) brittleness is observed to dominate in absence of PMMA. Addition of 20 wt.% PMMA to PVDF remarkably increases the elongation at break, once again in line with an improved interfacial adhesion. Although the ductile behavior persists in the whole PVDF/PMMA composition range, some decrease is

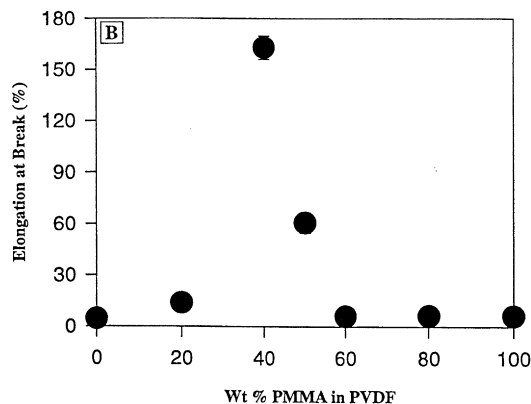
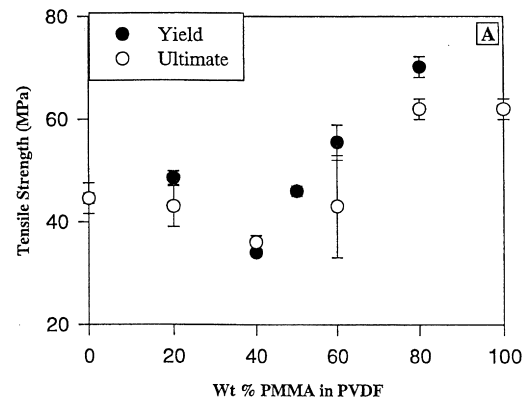


Fig. 8. (A) Yield and ultimate tensile strengths versus the PMMA content in PVDF for the 20/80 PC/(PVDF–PMMA) blends. (B) Elongation at break versus the PMMA content in PVDF for the 20/80 PC/(PVDF–PMMA) blends.

observed when the PMMA content in PVDF is 50 wt.% and higher, thus when the dispersed phase becomes amorphous and glassy. Although slightly improved by the addition of PMMA, the tensile strength (σ_y and σ_b) of these ternary blends (Fig. 9(A)) is basically independent of the PMMA content of the dispersed phase.

As a rule, the same qualitative observations are reported for ternary blends of a co-continuous two-phase morphology (Figs 10(A), (B) and 11(A), (B)) as for those with a dispersed phase morphology. In the absence of PMMA, the interface is weak and the ternary blends are brittle. The addition of 20 wt.% and more interestingly 40 wt.% PMMA to PVDF improves the ultimate mechanical properties of the 40/60 and 60/40 PC/(PVDF–PMMA) blends. The compatibilization efficiency of PMMA in PC/PVDF blends is thus convincingly supported by the general improvement of the mechanical behavior, and the usually observed transition from brittle to ductile blends.

3.3. Charpy impact strength properties

The Charpy impact strength confirms the brittleness of the PC/PVDF blends in the whole composition range

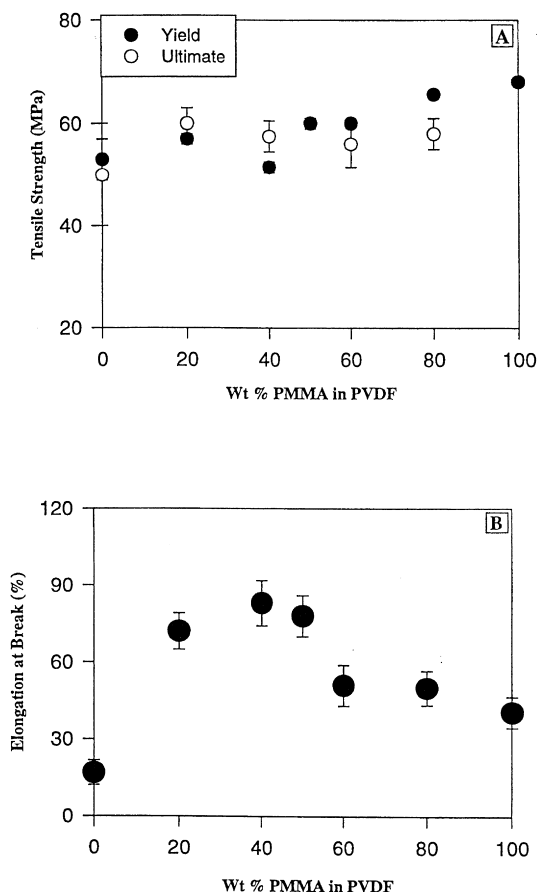


Fig. 9. (A) Yield ultimate tensile strengths versus the PMMA content in PVDF for the 80/20 PC/(PVDF–PMMA) blends. (B) Elongation at break versus the PMMA content in PVDF for the 80/20 PC/(PVDF–PMMA) blends.

(Fig. 12). Indeed, the ductility of PC (90 kJ m^{-2}) and PVDF (65 kJ m^{-2}) is rapidly lost when these two polymers are melt blended (less than 10 kJ m^{-2} , except for the 80/20 PC/PVDF blend). Fig. 13 shows the notched Charpy impact strength for ternary blends PC/(PMMA–PVDF) of a dispersed phase morphology. The addition of PMMA, which is intrinsically brittle (impact strength = 5 kJ m^{-2}), to the 80/20 PC/PVDF binary blend increases the impact strength particularly when 40 wt.% PMMA is mixed with PVDF. The same general curve is also observed for the reverse PC/PVDF composition (20/80), although the effect is comparatively faint. When PC is the matrix (80%), the addition of PMMA improves the impact strength whatever be the PVDF/PMMA composition. An improvement in the interfacial adhesion between the dispersed phase and the PC matrix is thought to be responsible for this beneficial effect, as the intrinsic ductility of PVDF is lost when mixed with PMMA (Fig. 14). This explanation is supported by the observation by Kunori and Ceil [59] that the PC ductility is adversely affected by the addition of 2 wt.% PS as a result of the weak PC/PS interfacial adhesion and possibly of a coarser phase morphology.

When PVDF is the matrix (80 wt.%), the addition of

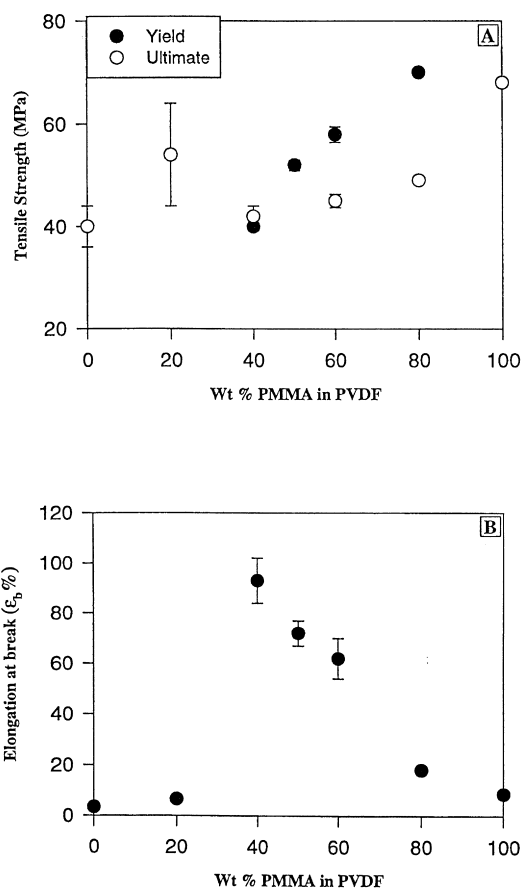


Fig. 10. (A) Yield and ultimate tensile strengths versus the PMMA content in PVDF for the 40/60 PC/(PVDF–PMMA) blends. (B) Elongation at break versus the PMMA content in PVDF for the 40/60 PC/(PVDF–PMMA) blends.

PMMA has no chance to improve the impact strength of the ternary blends (Fig. 13), as PVDF becomes rapidly brittle upon the addition of 20 wt.% PMMA (Fig. 14). The co-continuity in the 40/60 and 60/40 PC/(PVDF–PMMA) ternary blends (Fig. 15) does not basically change the situation observed in Fig. 13. The comparison would suggest that a randomly dispersed phase morphology is a favorable although not sufficient condition to impart toughness to a polymeric material [60]. Clearly the conclusions on the effect of PMMA on the PC/PVDF binary blends are at variance depending on the properties measured, i.e. tensile properties or Charpy impact strength. The origin for this discrepancy has to be found in the deformation speed, which is fast in the impact testing and comparatively slow when tensile properties are measured. The possible relaxation of the inclusions at low deformation speeds, can account for the plane strain permitting the failure ductility. At high speeds, this relaxation cannot occur leading to brittle failure in thick samples [61].

The results reported in this article confirm that the addition of a two-phase polymer blend by a third polymer miscible to one blend component and compatible to the second one may be a valuable strategy for the blend

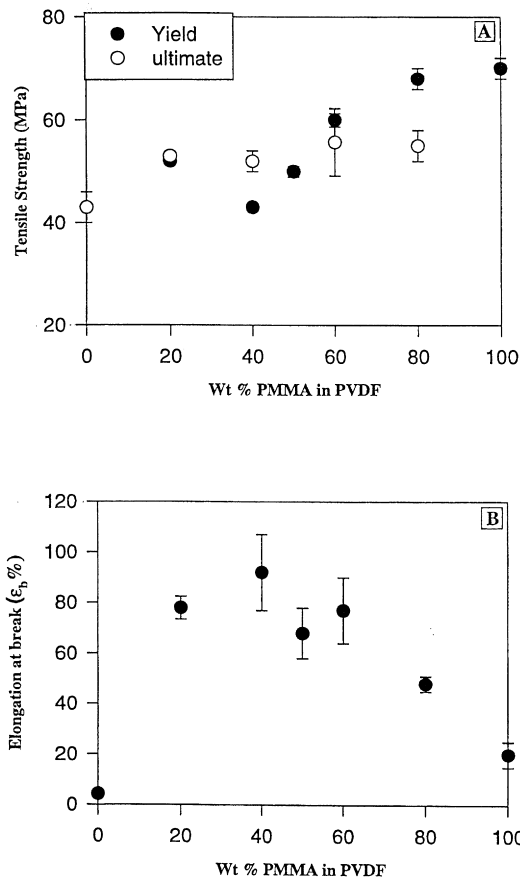


Fig. 11. (A) Yield ultimate tensile strengths versus the PMMA content in PVDF for the 60/40 PC/(PVDF-PMMA) blends. (B) Elongation at break versus the PMMA content in PVDF for the 60/40 PC/(PVDF-PMMA) blends.

compatibilization. Compared to the use of block or graft copolymers as interfacial agents, this strategy requires however a larger amount of the additive. This drawback may be largely compensated by the availability and the lower cost of a homopolymer (or random copolymer) compared to block or graft copolymers. The basic assumption for explaining the compatibilization efficiency of

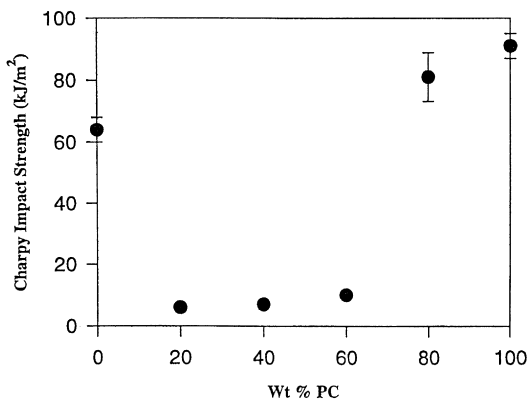


Fig. 12. Charpy impact strength versus the PC content for PC/PVDF blends.

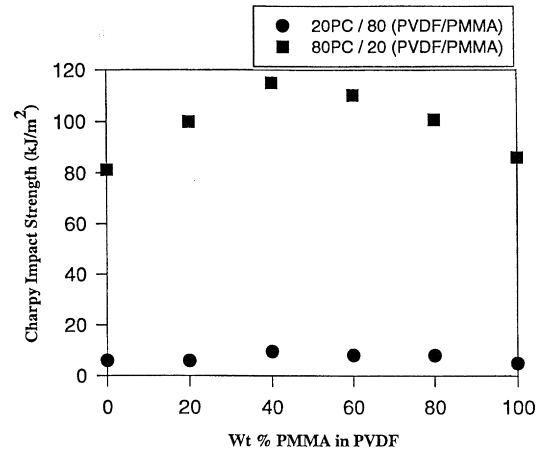


Fig. 13. Charpy impact strength versus the PMMA content in PVDF for PC/(PVDF-PMMA) blends.

PMMA in PC/PVDF blends is the migration of PMMA from the PVDF phase to the interface. The driving force for this migration may be identified by analogy with the well-known observation that the free surface of miscible blends is enriched with the component of the lower surface tension [62–64]. This phenomenon occurs provided that the free energy for setting up a composition gradient in the surface region is more than compensated by reducing the surface tension to a minimum. Quite similarly, the interfacial tension of PC/PVDF immiscible blends can be lowered by creating a PMMA/PVDF composition gradient on the PVDF side with accumulation of PMMA at the interface. The prerequisite is of course that the new PC/PMMA interfacial tension is smaller than the original PC/PVDF one. So the energy gained in substituting favorable (enthalpic) interactions for unfavorable ones at the interface must be higher than the energy cost associated with the rupture of favorable interactions in the bulk of each phase.

This condition is fulfilled in the PC/(PVDF-PMMA) system, as e.g. the PC/PMMA interfacial tension (0.6 dyn cm⁻¹) is smaller than the PC/PVDF one (4.5 dyn cm⁻¹). Further, PMMA is compatible to PC, in contrast to PVDF

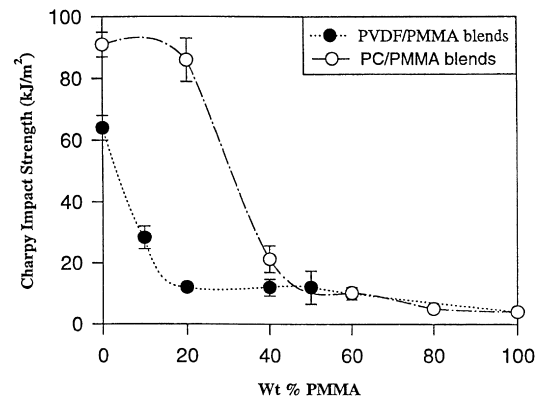


Fig. 14. Charpy impact strength versus the PMMA content for PC/PMMA and PVDF/PMMA blends.

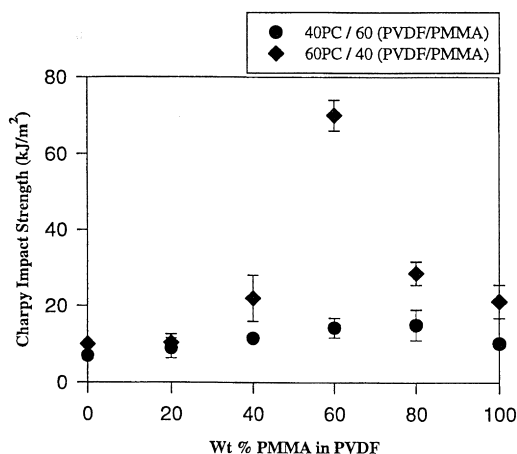


Fig. 15. Charpy impact strength versus the PMMA content in PVDF for PC/(PVDF-PMMA) blends.

which is highly immiscible to this component. The accumulation of PMMA at the PC/PVDF interface may have a favorable effect on the conformational entropy in the interfacial region. Indeed, two immiscible polymers, such as PVDF and PC, have to minimize their mutual interpenetration, and accordingly have a (more) collapsed conformation in the vicinity of the interface [65]. This is the primary cause for a weak interface in immiscible polymer blends. In case of substitution of PVDF by PMMA, conformations more favorable to molecular interpenetrations across the interface might develop in line with the PC/PMMA compatibility and account for the strengthening of the interface.

Finally, there is a direct analogy between the two-phase ternary blend analyzed in this study and the three-phase ternary blends investigated by Hobbs et al. [26]. The only difference is the miscibility of two of the three components, thus one of the three interfacial tensions which is zero. As in this study, the interfacial tension between primary components (PC and PVDF) is higher than that between PC and PMMA, the spreading coefficient (given by $\gamma_{PC/PVDF} - \gamma_{PC/PMMA} - \gamma_{PVDF/PMMA} = 3.9$) is positive, which is indeed predictive of interfacial activity.

4. Conclusions

This work has confirmed that immiscible PC/PVDF polymer blends could be compatibilized by the addition of a third polymer, PMMA. This polymeric additive has been selected for miscibility with one phase (PVDF) and a lower interfacial tension with the second phase compared to the original PC/PVDF interface. The required amount of PMMA is however rather large (20–40 wt.% with respect to PVDF) which is not prohibitive owing to the large availability and low cost of PMMA. The blend compatibilization is supported by a finer phase dispersion and improved tensile properties including elongation at break. The Charpy impact testing, which assumes conditions of fast

deformation, does not systematically conclude much improved performances. This observation is not a negative evidence for the blends compatibilization, but might merely indicate that PC is not an ideal toughening agent for PVDF (or PVDF/PMMA one phase blends) and viceversa.

Acknowledgements

The authors are very grateful to the ‘‘Services Fédéraux des Affaires Scientifiques, Techniques et Culturelles’’ in the framework of the ‘‘Pôles d’Attraction Interuniversitaires’’: PAI 4/11. N.M. is indebted to the ‘‘Ministère de l’Enseignement Supérieur de la Formation des Cadres et de la Recherche Scientifique du Maroc’’ for a fellowship. The authors also wish to thank Mr C. Pagnouille, Dr I. Luzinov and Dr Ph Maréchal for useful discussions, and Mrs S. Blacher for her collaboration in image analysis.

References

- [1] Teyssié Ph. *Macromol. Chem Macromol Symp* 1988;22:82.
- [2] Xanthos M. *Polym Eng Sci* 1988;28:392.
- [3] Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Phys Ed* 1989;27:775.
- [4] Heikens D, Barentsen W. *Polymer* 1977;18:69.
- [5] Fayt R, Jérôme R, Teyssié Ph. *Makromol Chem* 1986;187:837.
- [6] Fayt R, Jérôme R, Teyssié Ph. *Polym Eng Sci* 1987;27:328.
- [7] Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Phys Ed* 1982;20:2209.
- [8] Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Lett Ed* 1981;19:79.
- [9] Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Lett Ed* 1981;19:1269.
- [10] Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Lett Ed* 1986;24:25.
- [11] Brahim B, Ait-kadi A, Ajji A, Fayt R. *J Polym Sci, Polym Phys Ed* 1991;29:945.
- [12] Yoshida M, Ma JJ, Min K, White JL, Quirk RP. *Polym Eng Sci* 1990;30:30.
- [13] Petit D, Jérôme R, Teyssié Ph. *J Polym Sci Polym Chem Ed* 1979;17:2903.
- [14] McKay ID. *J Appl Polym Sci* 1991;42:281.
- [15] Xi X, Xiande M, Kegiang C. *Polym Eng Sci* 1987;27:391.
- [16] Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Chem Ed* 1989;27:2823.
- [17] Heuschen J, Vion JM, Jérôme R, Teyssié Ph. *Polymer* 1990;31:1473.
- [18] Ouhadi T, Fayt R, Jérôme R, Teyssié Ph. *J Polym Sci Polym Phys Ed* 1986;24:973.
- [19] Jo WH, Kim HC, Baik DH. *Macromolecules* 1991;24:2231.
- [20] Baker WE, Saleem M. *Polym Eng Sci* 1987;27:1634.
- [21] Triacca VJ, Ziaee S, Barlow JW, Keskkula H, Paul DR. *Polymer* 1991;32:1401.
- [22] Liu NC, Baker WE. *Adv. Polym Tech* 1992;11(4):249.
- [23] Xanthos M, Dagli SS. *Polym Eng Sci* 1991;31(13):929.
- [24] Curdo D, Valenza A, Lamantia FP. *J Appl Polym Sci* 1990;39:865.
- [25] Fleischer CA, Koberstein JT. *Polymer Prepr* 1992;31:541; *Polym Mater Sci Eng* 1991;67:94.
- [26] Hobbs SY, Dekkers MEJ, Watkins VH. *Polymer* 1988;29:1598.
- [27] Kwei TK, Frisch HC, Radigon W, Vogel S. *Macromolecules* 1977;10:157.
- [28] Liu NC, Baker WE. *Adv Polym Tech* 1992;11(4):249.
- [29] Tomura H, Saito H, Inoue T. *Macromolecules* 1992;25(5):1611.
- [30] Prud’Homme RE. *Polym Eng Sci* 1982;22:90.

- [31] Flory PJ. *J Am Chem Soc* 1965;87:1833.
- [32] Kim WN, Burns CM. *Macromolecules* 1987;20:1876.
- [33] Chiou JS, Barlow JW, Paul DR. *J Polym Sci Polym Phys Ed* 1987;25:1459.
- [34] Gardlund, ZG Polymer blend and composites in multiphase systems. In: Hans CD, editor. *Advances in Chemistry Series*; American Chemical Society Washington, DC, 1984.
- [35] Moussaif N, Maréchal Ph, Jérôme R. *Macromolecules* 1997;30:658.
- [36] Cox WP, Merz EH. *J Polym Sci* 1958;28:619.
- [37] Ho RM, Wu CH, Su AC. *Polym Eng Sci* 1990;30:511.
- [38] Jordhamo GM, Manson JA, Sperling LH. *Polym Eng Sci* 1986;26(8):517.
- [39] Utracki LA. *J Rheol* 1991;35:1615.
- [40] Lyngsae-Jorgensen L, Utracki LA. *Makromol Chem Macromol Sym* 1991;48/49:189.
- [41] Favis BD, Chalifoux JP. *Polymer* 1988;29:1761.
- [42] Taylor GI. *Proc Roy Soc Lond A* 1932;138:41.
- [43] Taylor GI. *Proc Roy Soc Lond A* 1932;146:501.
- [44] Sundararaj U, Macosko CW. *Macromolecules* 1995;28:2647.
- [45] Wu S. *Polym Eng Sci* 1987;27:335.
- [46] Serpe G, Jarrin J, Dawans F. *Polym Eng Sci* 1990;30:553.
- [47] Schramm G. *A practical approach to rheology and rheometry*. New York: Haake, 1995.
- [48] Porter RS. *Polym Eng Sci* 1967;7:45.
- [49] Moussaif N, Jérôme, R. Submitted to *macromolecular chemistry and physics*
- [50] Macosko CW, Guégan P, Khandpur AK, Nakayama A, Marechal P, Inoue T. *Macromolecules* 1996;29:5590.
- [51] Harrats Ch, Blacher S, Fayt R, Jérôme R, Teyssié Ph. *Polym Sci Polym Phys Ed* 1995;33:801.
- [52] Fortenly I, Kovar J. *J Polym Comp* 1988;9:119.
- [53] Paul DR. In: Paul DR, Newman S, editor. *Polymers blends*. Vol. 2, ch. 12, New York: Academic Press
- [54] Akkapedi MK, Van Buskirk B. *Polym. Sci. Eng.* 1992;67:317.
- [55] Noland JS, Hsu NNC, Saxon R, Schmith JM. In: Platzer NAJ, editor. *Multicomponent polymer systems*. *Advancies in chemistry series no. 99*, Washington, DC, 1971, pp. 15–29.
- [56] Paul DR, Altamirano JO. *Copolymers, polyblends and composites*. In: Platzer NAJ., editor. *Advances in chemistry series no. 142*; ACS: Washington DC, 1975, pp. 371–385.
- [57] Paul DR, Barlow JW, Bernstein RE, Wahrmund DC. *Polym Eng Sci* 1978;18:1225.
- [58] Nishi T, Wang TT. *Macromolecules* 1975;8:909.
- [59] Kunori T, Ceil PH. *J Macromol Sci, Phys part B* 1980;18(1):135.
- [60] Bucknall CB. In: Paul DR, Newman S, editor. *Polymer blends*. Vol. 2, ch. 12. New York: Academic Press.
- [61] Yee AF. *J Mater Sci* 1977;12:757.
- [62] Wu S. In: *Polymer interface and adhesion*. New York: Marcel Dekker, 1982.
- [63] Bahatia QS, Pan DH, Koberstein JT. *Macromolecules* 1988;21:2165.
- [64] Koberstein JT. In: *Encyclopedia of polymer science and engineering*. Vol.8, p. 237, New York: Wiley, 1987.
- [65] Utracki LA. In: *Polymer alloys and blends* Hanser, Munich, 1989.