

Erratum

Erratum to “Synthesis methods of fluorinated polyurethanes.
1. Effects on thermal and dynamic-mechanical behaviours”
[Polymer 42 (2001) 5589–5598][☆]

Claudio Tonelli^{a,*}, Giuseppe Ajroldi^b, Antonio Turturro^c, Antonio Marigo^d

^aAUSIMONT S.p.A., Research and Development Center, V. le Lombardia 20, I-20021 Bollate, Italy

^bVia A. Campiglio, 9, I-20133 Milan, Italy

^cDipartimento di Chimica e Chimica Industriale dell’Universita Á, via Dodecaneso 31, I-16146 Genova, Italy

^dDipartimento di Chimica Inorganica, Metallorganica e Analitica dell’Universita Á, via Loredan, 4, I-35131 Padova, Italy

The publisher regrets that there were errors present in the published version of the above article. We apologise for any inconvenience or embarrassment caused.

Table 5 and Fig. 4 should appear as shown.

Table 5
Transition temperatures and enthalpies of the FPU samples

Sample	w_h	T_1 (°C)	T_2 (°C)	T_3 (°C)	T_4 (°C)	ΔH_1 (J/g _h)	ΔH_2 (J/g _h)	ΔH_3 (J/g _h)	ΔH_4 (J/g _h)	T_c (°C)	ΔH_c (J/g _h)
S1-2000	0.203	130	151	186	–	–37.6–	–	1.5	–	89	26.4
S1-3100	0.137	132	145	173	–	–45.0–	–	3.0	–	94	29.7
S1-3800	0.119	120	–	180	–	–26.0–	–	4.6	–	88	13.5
S2-2000	0.276	91	–	179	–	4.0	–	52.9	–	98	15.0
S2-3100	0.200	–	–	175	–	–	–	25.5	–	85	8.8
SS-1000	0.286	70–100	156	175	215	2.8	–38.1–	–	2.4	108	29.8
SS-2000	0.205	70–110	–	–166–	215	7.2	–14.8–	–	4.7	95	15.5
SS-3100	0.156	70–120	–	–171–	218	21.8	–12.2–	–	3.6	98	19.2
SS-3800	0.130	70–140	–	–	215	22.3	–	–	33.1	96	11.5

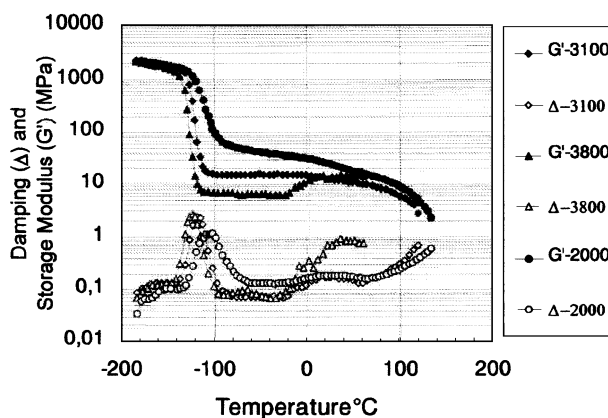


Fig. 4. Dynamic-mechanical spectra (G' and Δ vs T) for samples of S1 series.

[☆] PII of original article: S0032-3861(01)00020-9

* Corresponding author. Tel.: +39-02-3835-6485; fax: +39-02-3835-2152.

E-mail address: claudio.tonelli@ausimont.com (C. Tonelli).