

Polymer Communication

High-pressure atom transfer radical polymerization of methyl methacrylate for well-defined ultrahigh molecular-weight polymers

Toshihiko Arita, Yuzo Kayama, Kohji Ohno, Yoshinobu Tsujii, Takeshi Fukuda*

Institute for Chemical Research, Kyoto University, Uji, Kyoto 611-0011, Japan

ARTICLE INFO

Article history:

Received 25 January 2008

Received in revised form 7 March 2008

Accepted 15 March 2008

Available online 19 March 2008

Keywords:

High pressure

Living radical polymerization

Atom transfer radical polymerization

ABSTRACT

The feasibility of high-pressure atom transfer radical polymerization (ATRP) for synthesizing well-defined polymers of extraordinarily high molecular weights was demonstrated. ATRP of methyl methacrylate (MMA) under pressures up to 500 MPa was investigated at 60 °C. The addition of a small amount of a Cu(II)Cl₂/ligand complex along with the general benefits of high pressure of enhancing propagation and suppressing termination brought about an excellent control of polymerization even with an extremely low concentration of ATRP initiator. For example, there was produced PMMA with a number-average molecular weight M_n of 3.6×10^6 and a polydispersity index of 1.24, which had never been achieved by conventional ATRP.

© 2008 Elsevier Ltd. All rights reserved.

1. Introduction

Living (or controlled/living) radical polymerizations (LRPs) have attracted much attention as a powerful method to synthesize well-defined polymers with e.g., designed molecular weight, low polydispersity, and defined end group [1]. Mechanistically, LRP is distinguished from conventional free-radical polymerization (FRP) by the existence of a reversible activation process [1–3]. By thermal, photochemical, and/or chemical stimuli, the dormant chain P–X is activated to the polymer radical P[•], which undergoes propagation in the presence of monomer M until it is deactivated back to P–X, where P and X denote the polymer moiety and end-capping group, respectively. A sufficiently large number of activation–deactivation cycles is a requisite for low-polydispersity products. Like FRP, LRP also involves termination and chain transfer reactions producing dead chains. The number of dead chains increases with increasing polymerization time and hence with increasing number-average degree of polymerization, DP_n . To achieve low polydispersity, the total number of dead chains should be sufficiently smaller than that of living chains (dormant plus active chains). In other words, the target DP_n in LRP should be sufficiently small compared to that in the FRP carried out under equivalent conditions (the same radical and monomer concentrations and the same temperature and pressure), which limits the DP_n in LRP. If the target molecular weight is set equal to this upper limit, all chains will be dead at the end of polymerization with the controllability of LRP totally lost. Hence, unlike termination-free polymerizations such as living

anionic polymerization, it is difficult to access very high molecular weights by LRP (and FRP) under usual experimental conditions. We have firstly to seek for special experimental conditions that will give high molecular-weight polymers in FRP.

If we consider only propagation (rate constant k_p), termination (rate constant k_t) and chain transfer reactions as main elementary reactions in FRP, the kinetic chain length DP_{kin} , which is equal to DP_n in the complete absence of recombination in termination, is given by

$$DP_{kin} = \frac{k_p[M]}{k_t[P^{\bullet}] + S_{tr}} \quad (1)$$

In Eq. (1), S_{tr} is the proportionality coefficient defined by

$$R_{tr} = S_{tr}[P^{\bullet}] \quad (2)$$

where R_{tr} is the sum of the rates of chain transfer reactions (hence S_{tr} depends on the concentrations of all chain-transferable species). Clearly, a method to increase DP_{kin} is to carry out experiments at lower $[P^{\bullet}]$, as is well known and practically used. Other possibilities will be to enhance propagation (larger k_p) and/or suppress termination (smaller k_t) by some means or other. In this regard, high pressures are known to bring about a remarkable increase in polymerization rate R_p in FRP [5], as a result of increased k_p and decreased k_t [4]. For example, the activation volumes ΔV^{\ddagger} of propagation and termination of poly(methyl methacrylate) (PMMA) radical were reported to be $-16.7 \text{ cm}^3 \text{ mol}^{-1}$ [6] and $15 \text{ cm}^3 \text{ mol}^{-1}$ [4], respectively, calculating the enhancement in k_p by a factor of about 20 and suppression in k_t by a factor of about 15 at 500 MPa, relative to the values at the ambient pressure of about 0.1 MPa. Under the premise that the coefficient S_{tr} in Eq. (2) does

* Corresponding author.

E-mail address: fukuda@scl.kyoto-u.ac.jp (T. Fukuda).

not heavily depend on pressure, which is likely because chain transfer reactions would not accompany a large change in volume, high pressures are expected to give extraordinarily high molecular-weight polymers in FRP, hence in LRP. Recently, reversible addition–fragmentation chain transfer (RAFT) polymerizations under high pressures were reported [7–10]. Rzyayev and Penelle demonstrated the mentioned benefits of high pressure for improved R_p , DP_n and polydispersity, by successfully synthesizing PMMA with $M_n = 1.2 \times 10^6$ and polydispersity index (PDI) $M_w/M_n = 1.03$ (as determined by GPC-MALLS) at 500 MPa by dithiobenzoate-mediated RAFT polymerization [10], where M_n and M_w are number- and weight-average molecular weights, respectively.

In an attempt to explore the feasibility or possibility of LRP in synthesizing well-defined ultrahigh molecular-weight polymers, we in this communication give a report on the copper-catalyzed atom transfer radical polymerization [11] of methyl methacrylate (MMA) under pressures up to 500 MPa [12,13]. The reversible activation–deactivation in this system is mediated by the $Cu(I)X/L$ and $Cu(II)X_2/L$ complexes as shown in Scheme 1, where X and L represent a halogen and a ligand, respectively.

2. Experimental

2.1. Materials


MMA was obtained from Nacalai Tesque Inc., Japan and purified by passing through a column filled with activated basic alumina to remove inhibitor. Ethyl 2-bromoisobutyrate (EBIB) was used as received from Tokyo Chemical Industry Co., Ltd., Japan. 4,4'-Dinonyl-2,2'-bipyridine (dNbipy) was purchased from Aldrich and used without further purification. Copper(I) chloride ($Cu(I)Cl$) and copper(II) dichloride ($Cu(II)Cl_2$) were purchased from Wako Pure Chemicals, Japan.

2.2. Polymerization

All sample preparations were carried out in a glove box purged with argon, and all chemicals were deoxygenated by argon before the use in the glove box. The reaction mixture (ca. 1 mL) of MMA, EBIB, $Cu(I)Cl$, $Cu(II)Cl_2$ (if needed), and dNbipy was put into a sample bag made of poly(tetrafluoroethylene-co-hexafluoropropylene) (FEP) film and the bag was sealed by a heat sealer. The sample was further packed in a polyethylene-coated aluminum sheet to prevent oxygen contamination and put into the chamber, thermostated at 60 °C, of the high-pressure reaction system (HPS-700, Syn Corporation, Kyoto, Japan) and pressurized up to a prescribed pressure. After a prescribed time, the system was depressurized and an aliquot of the reaction mixture was taken out for NMR measurement to estimate monomer conversion and for GPC measurement to determine molecular weight and its distribution.

2.3. Measurements

Gel permeation chromatographic (GPC) analysis was carried out at 40 °C on a Shodex GPC-101 high-speed liquid chromatography system equipped with a guard column (Shodex GPC KF-G), two 30-cm mixed columns (Shodex GPC KF-806L, exclusion limit = 2×10^7), and a differential refractometer (Shodex RI-101).



Scheme 1. The mechanism of reversible activation in Cu-mediated ATRP.

Tetrahydrofuran (THF) was used as an eluent at a flow rate of 0.8 mL/min. The GPC system was basically calibrated by PMMA standards (Polymer Laboratories, $M_p = 2.00 \times 10^3$ – 1.64×10^6). The calibration was complemented by polystyrene standards (Polymer Laboratories, $M_p = 1.65 \times 10^3$ – 1.54×10^7) using the idea of universal calibration [14]. The M_n and PDI values were estimated by this calibration method, unless otherwise noted. Sample detection was also made with a multiangle laser light-scattering (MALLS) detector (Wyatt Technology DAWN EOS). 1H (300 MHz) NMR spectra were obtained on a JEOL/AL300 spectrometer.

3. Results and discussion

The ATRP runs of MMA in the presence of the activator $Cu(I)Cl/L_2$ complex ($[Cu(I)Cl/L_2]_0 = 14$ mM) were performed at 60 °C in a pressure range from 0.1 to 500 MPa. The concentration of ATRP initiator $[EBIB]_0$ was adjusted to 0.32 mM, corresponding to the target M_n of 3.0×10^6 (at full conversion). Thermal initiation of MMA was negligibly small under all studied conditions. Figs. 1 and 2 show the conversion index $\ln([M]_0/[M])$ vs. polymerization time t and the M_n and PDI of products vs. conversion c , respectively. As expected, the polymerization rate (estimated from the slope of the lines in Fig. 1) increased with increasing pressure. The figures also indicate that at the ambient pressure, the polymerization was not well controlled because of the extremely low initiator concentration, but elevated pressures resulted in better control with PDI effectively lowered even at high conversions. At 500 MPa, the polymerization was about 20 times faster than that at the ambient pressure, giving a polymer with $M_n = 5 \times 10^5$ and PDI = 1.25 at conversion 20%. However, the system gradually lost the control over M_n and PDI at higher conversions.

For improvement of the control, we added 0.31 mM of $Cu(II)Cl_2/L_2$ complex in the original feed as a deactivator and carried out the polymerization at 500 MPa. The closed symbols in Figs. 1 and 2 show the result. Clearly, the addition of the deactivator somewhat decreased the polymerization rate and lowered the PDI, giving a polymer with $M_n = 1.5 \times 10^6$ and PDI = 1.25 at conversion 60%. We then carried out a run in which the initiator concentration was lowered to 0.047 mM (target molecular weight = 2.0×10^7) with other conditions almost unchanged. The first-order plot of the monomer concentration $[M]$ ($\ln([M]_0/[M])$ vs. t) was confirmed to

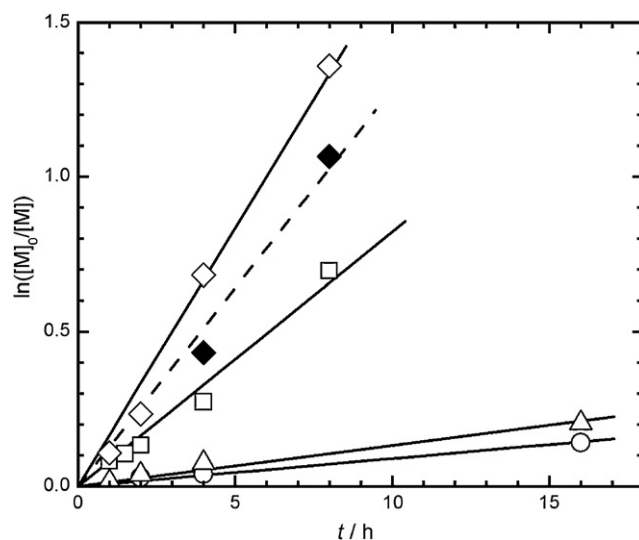


Fig. 1. Plot of $\ln([M]_0/[M])$ vs. t for the ATRP of MMA at a temperature of 60 °C and pressures of 0.1 (○), 30 (△), 300 (□), and 500 MPa (◇ and ◆); $[EBIB]_0 = 0.32$ mM, $[Cu(I)Cl/L_2]_0 = 14$ mM, $[Cu(II)Cl_2/L_2]_0 = 0$ (open symbols) and 0.31 mM (◆).

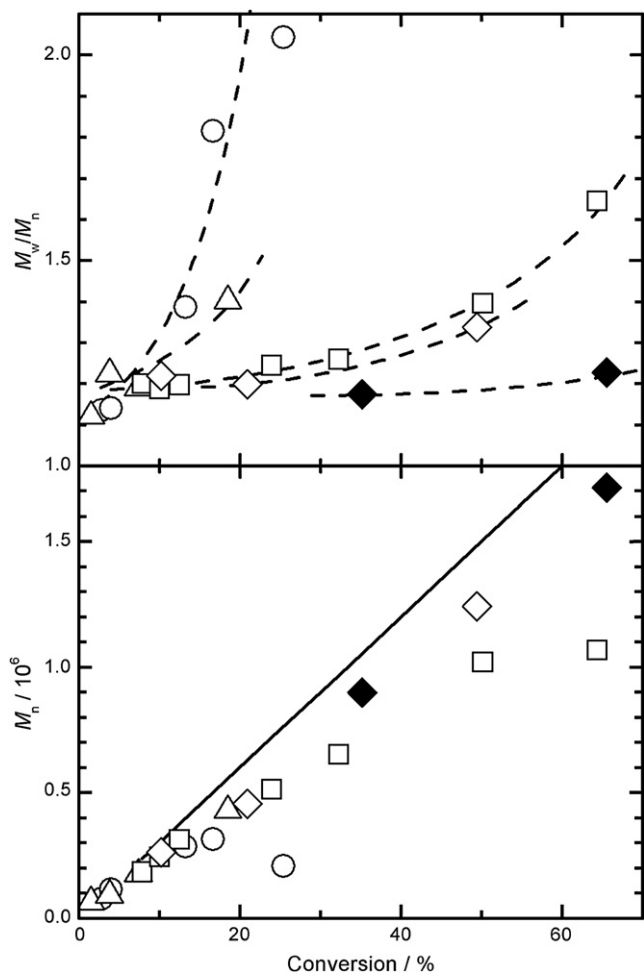


Fig. 2. Plots of number-average molecular weight, M_n , and polydispersity index, M_w/M_n , vs. conversion for the ATRP of MMA at a temperature of 60 °C and pressures of 0.1 (○), 30 (△), 300 (□), and 500 MPa (◇ and ◆); $[EBIB]_0 = 0.32$ mM, $[Cu(I)Cl/L_2]_0 = 14$ mM, $[Cu(II)Cl_2/L_2]_0 = 0$ (open symbols) and 0.31 mM (◆). The solid line indicates the theoretical values of M_n .

be linear, meaning that the polymerization rate (hence active chain concentration) was essentially constant (Fig. 3). Also notably, M_n increased linearly with conversion, in good agreement with the theoretical value, and the PDI was kept at a relatively low level (<1.3) at all studied conversions (Fig. 4).

This work of the deactivator is indeed noteworthy, while it was expectable from the kinetic theory for LRP systems including a sufficient amount of added deactivator [3]. Eqs. (22) and (25) in Ref. [3b] can be written in our case as

$$\ln([M]_0/[M]) = (k_p K_{AT} [EBIB]_0 [Cu(I)Cl/L_2]_0 / [Cu(II)Cl_2/L_2]_0) t \quad (3)$$

where K_{AT} ($=k_a/k_{da}$) is the equilibrium constant (cf. Scheme 1). The theory suggests that increased deactivator concentration keeps the active chain concentration $[P^*]$ at a lower constant level and hence decreases termination. In this connection, the Cu(I)Cl reagent used here was likely contaminated by a significant but not-precisely known amount of Cu(II)Cl₂ [15]. We believe that this was a main reason why those experiments with no Cu(II)Cl₂ added in the feed still gave reasonably good results. In the complete absence of added Cu(II) species in the polymerization with an extremely low concentration of ATRP initiator, the activation–deactivation quasi-equilibrium would be hardly or never achieved by the persistent radical effect [2] alone. Now to estimate the magnitude of the equilibrium constant K_{AT} , we use the value of k_p at 500 MPa as $1.7 \times 10^4 \text{ M}^{-1} \text{ s}^{-1}$ (calculated with the Arrhenius parameters for

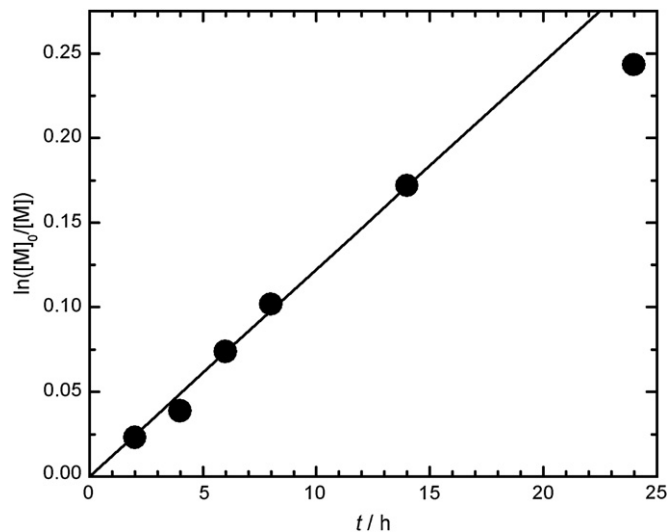


Fig. 3. Plot of $\ln([M]_0/[M])$ vs. t for the ATRP of MMA at 60 °C and 500 MPa; $[EBIB]_0 = 0.047$ mM, $[Cu(I)Cl/L_2]_0 = 14$ mM, $[Cu(II)Cl_2/L_2]_0 = 0.37$ mM.

ambient pressure [16] and the activation volume for a pressure range of 0.1–200 MPa at 30 °C [6]). Applying this k_p value along with the slope of the first-order plot in Fig. 3 to Eq. (3), we have $K_{AT} = 1 \times 10^{-7} - 3 \times 10^{-7}$ at 500 MPa, as a very crude estimate taking account of the Cu(II) species possibly contaminating Cu(I)Cl [15]. This K_{AT} value is of the same order of magnitude as that at the ambient pressure [17], suggesting that the pressure dependencies in the activation and deactivation reactions are insignificant, or at least similar in magnitude to each other, if any.

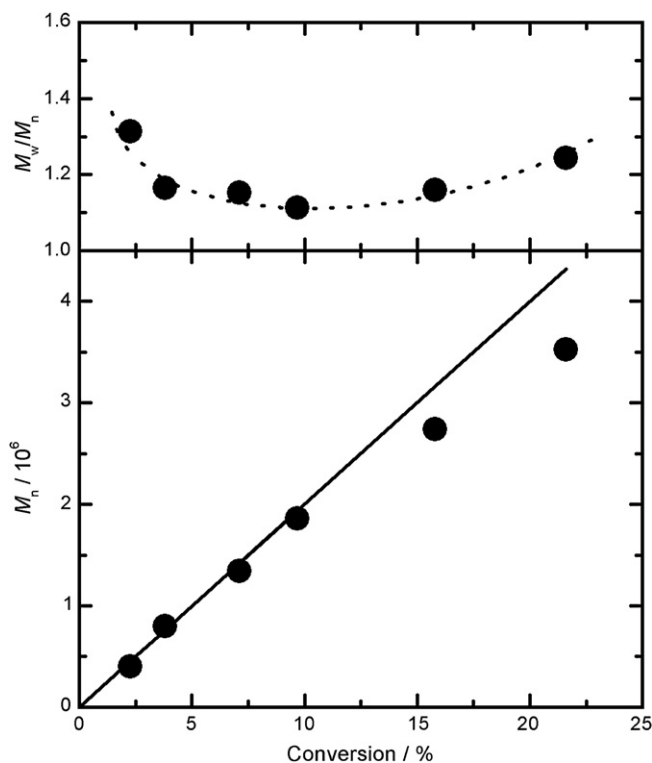


Fig. 4. Plots of number-average molecular weight, M_n , and polydispersity index, M_w/M_n , vs. conversion for the ATRP of MMA at 60 °C and 500 MPa; $[EBIB]_0 = 0.047$ mM, $[Cu(I)Cl/L_2]_0 = 14$ mM, $[Cu(II)Cl_2/L_2]_0 = 0.37$ mM. The solid line indicates the theoretical values of M_n .

The highest molecular weight achieved in this work was $M_n = 3.6 \times 10^6$ with PDI = 1.24. The PDI of this sample estimated by GPC-MALLS was 1.05, which is unexpectedly small compared to the calibration-method value. We believe that the calibration method was more reliable in our case, since the MALLS method was likely to have missed or underestimated low molecular-weight fractions because of their too weak MALLS signals. In any case, the achieved M_n value exceeds the highest molecular weight of PMMA standards commercially available (Polymer Standards Service GmbH, $M_w = 3.0 \times 10^6$, $M_w/M_n < 1.50$). This success not only demonstrates the feasibility and possibility of high-pressure ATRP as a standard method to synthesize well-defined polymers of still higher molecular weights but also opens up a new route to create concentrated polymer brushes [18] with extraordinarily large brush-layer thickness (of micrometer scale), by applying it to the surface-initiated graft polymerization. Such a study is in progress in our laboratory.

4. Conclusions

ATRP of MMA under pressures up to 500 MPa was investigated at 60 °C. In accord with the theoretical suggestion of ATRP kinetics, the addition of a proper amount of Cu(II)Cl₂ complex along with the general benefits of high pressure of enhancing propagation and suppressing termination brought about an excellent control of polymerization even with an extremely low concentration of ATRP initiator. For example, there was obtained a PMMA with $M_n = 3.6 \times 10^6$ and PDI = 1.24, demonstrating the feasibility and possibility of high-pressure ATRP for producing well-defined ultrahigh molecular-weight polymers, including those which are difficult to synthesize by any other methods than radical polymerization.

Acknowledgment

This work was supported in part by a Grant-in-Aid for Scientific Research (Grant-in-Aid 17002007 and 17685010) from the Ministry

of Education, Culture, Sports, Science, and Technology, Japan and by Industrial Technology Research Grant Program in 2004 from the New Energy and Industrial Technology Development Organization (NEDO) of Japan.

References

- [1] For reviews: (a) Matyjaszewski K, Davis TP, editors. Handbook of radical polymerization. New York: Wiley and Sons; 2002; (b) Matyjaszewski K, editor. ACS symposium series, vol. 685; 1998; Matyjaszewski K, editor. ACS symposium series, vol. 768; 2000; Matyjaszewski K, editor. ACS symposium series, vol. 854; 2003; Matyjaszewski K, editor. ACS symposium series, vol. 944; 2006; (c) Hawker CJ, Bosman AW, Harth E. Chem Rev 2001;101:3661–88; (d) Kamigaito M, Ando T, Sawamoto M. Chem Rev 2001;101:3689–746; (e) Moad G, Solomon DH. The chemistry of radical polymerization. Amsterdam: Elsevier; 2006; (f) Braunecker WA, Matyjaszewski K. Prog Polym Sci 2007;32:93–146.
- [2] Fischer H. Chem Rev 2001;101:3581–610.
- [3] (a) Fukuda T, Goto A, Ohno K. Macromol Rapid Commun 2000;21:151–61; (b) Goto A, Fukuda T. Prog Polym Sci 2004;29:329–85.
- [4] Beuermann S, Buback M. Prog Polym Sci 2002;27:191–254.
- [5] Sivergin YM. In: Kovarskii AL, editor. High-pressure chemistry and physics of polymers. Boca Raton: CRC; 1994. p. 195–264.
- [6] Beuermann S, Buback M, Russell GT. Macromol Rapid Commun 1994;15:351–5.
- [7] Monteiro MJ, Bussels R, Beuermann S, Buback M. Aust J Chem 2002;55:433–7.
- [8] Rzaev J, Penelle J. Macromolecules 2002;35:1489–90.
- [9] Arita T, Buback M, Janssen O, Vana P. Macromol Rapid Commun 2004;25:1376–81.
- [10] Rzaev J, Penelle J. Angew Chem Int Ed 2004;43:1691–4.
- [11] Matyjaszewski K, Xia JH. Chem Rev 2001;101:2921–90.
- [12] This work was presented in part at the 55th Autumn Meeting of the Society of Polymer Science, Japan (Toyama, Japan, September 20–22, 2006) and the ICR international symposium (Kyoto, Japan, June 11–13, 2007). (a) Arita T, Ohno K, Tsujii Y, Fukuda T. Polym Prep Jpn 2006;55:2782; (b) Fukuda T, Tsujii Y, Ohno K, Goto A. Proceedings of ICRIS'07; 2007. p. 17–20.
- [13] Very recently, Kwiatkowski et al. also succeeded in AGET ATRP of MMA under high pressure, where AGET represents the activator generated by electron transfer; Kwiatkowski P, Jurczak J, Pietrasik J, Jakubowski W, Muellerc L, Matyjaszewski K, private communication.
- [14] Grubestic Z, Rempp P, Benoit H. J Polym Sci Polym Lett Ed 1967;5:753–9.
- [15] The kinetic data at the ambient pressure suggest that the reagent Cu(I)Cl used here is contaminated by about 2 mol% of Cu(II) species.
- [16] Beuermann S, Buback M, Davis TP, Gilbert RG, Hutchinson RA, Kajiwar A, et al. Macromol Chem Phys 2000;201:1355–64.
- [17] Wang JL, Grimaud T, Matyjaszewski K. Macromolecules 1997;30:6507–12.
- [18] Tsujii Y, Ohno K, Yamamoto S, Goto A, Fukuda T. Adv Polym Sci 2006;197:1–45.