

# DSC study of precipitation in an Al–Mg–Mn alloy microalloyed with Cu

M.J. Starink\*, A. Dion

*Materials Research Group, School of Engineering Sciences, University of Southampton, Southampton SO171BJ, UK*

Received 12 November 2003; received in revised form 5 January 2004; accepted 5 January 2004

Available online 3 March 2004

## Abstract

Power compensation differential scanning calorimetry (DSC) has been employed to detect and analyse precipitation reactions in an Al–1.3Mg–0.4Mn and an Al–1.3Mg–0.4Mn–0.07Cu alloy in which very small amounts of precipitate, less than 0.3 at.%, are expected to form. Due to the very small heat effects, baseline instability and drift significantly interfere with the measurements. After repeated experiments and careful baseline correction it is demonstrated that in the Cu containing alloy, ageing at 170 °C causes the appearance of two endothermic effects: for 2 days ageing a small dissolution effect appears at about 230 °C, whilst for 7 and 21 days ageing a dissolution effect peaking appears at about 300 °C. The temperature range of the latter is consistent with S phase dissolution.

© 2003 Elsevier B.V. All rights reserved.

*Keywords:* DSC; Thermal analysis; Precipitation; 3xxx alloy; S phase

## 1. Introduction

Differential scanning calorimetry (DSC) and isothermal calorimetry are extensively used for the study of precipitation in heat treatable Al-based alloys [1]. Studies are conducted on alloys in which the amount of alloying elements that precipitate is typically in the range of 1–10 at.%. For instance, in commercial Al–Cu–Mg alloys (e.g. AA2024: Al–1.6 at.%Cu–1 at.%Mg) the amount of Cu and Mg atoms that precipitate to form S phase is about 2 at.% [2,3], in an Al–1 at.%Si alloy the amount of Si that precipitates is about 1 at.% [4], in commercial Al–Zn–Mg–Cu-based alloys the amount of precipitates is in the order of 4 to 7 at.% [5,6] (but these precipitates will contain some Al), in Al–Li–Cu–Mg alloys the amount of Li that precipitates to form  $\delta'$  phase (Al<sub>3</sub>Li) is about 2–3 at.% [7,8] and in Al–16 at.%Mg the amount of Mg atoms that precipitates to form  $\beta''$  (Al<sub>3</sub>Mg) phase is about 6 at.% [9]. The Al alloys with the smallest amount of precipitation which have been studied by calorimetry are probably the Al–4.7 at.%Mg–0.25 at.%Cu–0.14 at.%Si alloy, in which about 0.5 at.% of Cu and Mg are expected to combine to form S phase (Al<sub>2</sub>CuMg) [10,11]

and the Al–0.5 at.%Mn–0.3 at.%Fe-based AA3003 alloy in which most of the Mn and Fe is thought to form intermetallic Al, Mn and Fe containing precipitates [12]. As far as we are aware no attempts to detect or analyse precipitation with calorimetry have been reported for metallic alloys in which the total amount of precipitating alloying elements is less than 0.5 at.%.

The present paper reports work on a very dilute precipitation system: an Al–1.3 at.%Mg–0.4 at.%Mn alloy microalloyed with up to 0.07 at.%Cu. If S phase (Al<sub>2</sub>CuMg) forms in this alloy, the maximum volume fraction is determined mostly by the amount of Cu in the alloy. (The rod or lath shaped precipitates in Al–Cu–Mg alloys, which have often been indicated by S', are a slightly strained semi-coherent version of the (incoherent) S phase. In recent works [7,13,14] several researchers have thus decided to discontinue the use of the indication S'. This is thought to be appropriate, and for the present paper we will not use the term S' phase, and instead indicate all precipitates with the same structure as S phase.) The solubility of Cu in the Al rich phase at 170 °C in the presence of 1 at.%Mg is lower than 0.001 at.% (see Section 4) and hence is nearly negligible. Thus we can assume that all Cu is available for precipitation. The amount of S phase should be about  $4 \times 0.07$  at.%. Detecting this small amount of S phase is challenging because heat effects will be very small, causing equipment noise and baseline

\* Corresponding author. Tel.: +44-2380-595094; fax: +44-2380-593016.

E-mail address: [m.j.starink@soton.ac.uk](mailto:m.j.starink@soton.ac.uk) (M.J. Starink).

instabilities to interfere with the measurement. But analysis of these alloys is important because the small amounts of S phase can cause a small but significant strengthening and thus the present paper sets out to analyse the formation of precipitates in the Al–1.3 at.%Mg–0.4 at.%Mn alloy microalloyed with 0.07 at.%Cu.

The Al–1.3 at.%Mg–0.4 at.%Mn alloy is generally indicated as AA3104, and alloys like these, based on Al–Mg–Mn are generally considered to be non-heat treatable alloys. Currently, these alloys are widely used in packaging applications. Work hardening and solid solution strengthening are two effective ways to improve their strength, but it has been realised that precipitation induced by small additions of Cu can play a role in work hardening and cause precipitation hardening [15–17]. Another reason for the interest in these type of alloys is the new trend in the automobile industry to exploit new Al alloys as car body panels to reduce weight and thus reduce fuel consumption [18]. Al–Mg–Mn alloys of the 5XXX series (especially AA5182, AA5052) with Cu additions are very promising candidates for that application due to their excellent formability and good strength, moreover the precipitation induced by small Cu additions may also influence corrosion [19] and reduce recovery [20]. Therefore, it is important to understand the precipitation in these alloy systems and to quantitatively elucidate their mechanisms.

## 2. Experimental

Two alloys were investigated, an Al–1.3 at.%Mg–0.4 at.%Mn alloy and an Al–1.3 at.%Mg–0.4 at.%Mn–0.07 at.%Cu alloy (compositions in Table 1). The alloys were supplied by Alcan International, Banbury Labs, UK in the form of sheets. The sheet was produced through casting, homogenising, hot rolling in several passes, solution treatment to dissolve Cu, Mg and most of the Mn and subsequent cold deformation through cold rolling or stretching. The alloys were produced with varying levels of cold deformation. Samples with 2 and 5% cold deformation were deformed through stretching, whilst the 10% cold deformed samples were deformed by cold rolling. The samples were stored at room temperature for several weeks, and subsequently aged at 170 °C for 2, 7 or 21 days shown in Table 1.

All DSC experiments were conducted in a Perkin-Elmer Pyris 1 Calorimeter, which is a power compensation DSC [1,21]. Nitrogen was used as both a purge and protective gas. Prior to a day of performing DSC runs, a cleaning run was done to improve the repeatability. In analysing linear

heating experiments the baseline of the DSC needs to be carefully considered, as baselines will generally be temperature and time dependent [22], and a comparison of baselines measured confirmed that this was also the case for our instrument. Therefore the following procedure was followed. Before testing samples, a baseline run with empty sample holders was performed. This baseline run is later used to subtract from the experimental results to determine the baseline correction. This will thus provide the enthalpy changes related to the sample, taking account of a correction for (some of the) the imperfections of the DSC machine. A second baseline run was performed in the course of the day in such a manner that always a baseline run is available that was performed within 3 h of a DSC experiment on an actual sample. Occasionally a third baseline run was performed. For all alloy/ageing combinations two samples were tested. With at least two baselines available for each sample, at least four corrected experimental curves are available.

## 3. Results

Fig. 1 shows an example of the thermograms obtained after correction of the DSC run on the sample with a DSC run performed with empty sample holders. The sample studied here is the Al–1.3 at.%Mg–0.4 at.%Mn–0.07 at.%Cu 10% deformation sample aged for 21 days at 170 °C. These curves are dominated by continuous slope indicating an ever increasing endothermic effect. Superimposed on this there are common features in the form of endothermic effects around 300 and 470 °C. The continuous slope is thought to be due mostly to the difference in heat capacity of sample and reference, and also imperfections in the DSC measurement play a role as for this type of DSC the baseline (run with empty holders) varies with time [22]. The heat capacity of aluminium is in good approximation a linear function of the temperature and hence, in a first order correction we may correct the curves by subtracting a linear function, provided we can identify section(s) of the curve in which no reactions occur. For the present alloys we can expect that no significant reactions occur up to 200 °C, and hence we will apply the linear correction by fitting a linear function to the section of curves between 100 and 200 °C. DSC thermograms obtained after this linear correction are presented in Fig. 2, for the same alloy/ageing combinations as shown in Fig. 1. The latter figure shows that even though the samples and the experiments were nominally identical, there are differences between the four measurements of the heat evolution from the sample, and these differences increase as the temperature increases over 200 °C. Thus parts of the measurements are associated with a substantial level of uncertainty. Nevertheless, some effects are determined quite consistently. Firstly, all thermograms show a linear part up to about 200 °C, which is interpreted as indicating a temperature range where no reactions take place. Secondly, a distinct endothermic effect is present between about 210 and 350 °C, with a peak at

Table 1  
Composition of the two alloys studied

Alloy	Element (%)					
	Si	Fe	Cu	Mn	Mg	Zn
Al–1.3Mg–0.4Mn	0.19	0.19	0.07	0.44	1.34	0.01
Al–1.3Mg–0.4Mn–0.07Cu	0.19	0.19	0.00	0.44	1.34	0.00

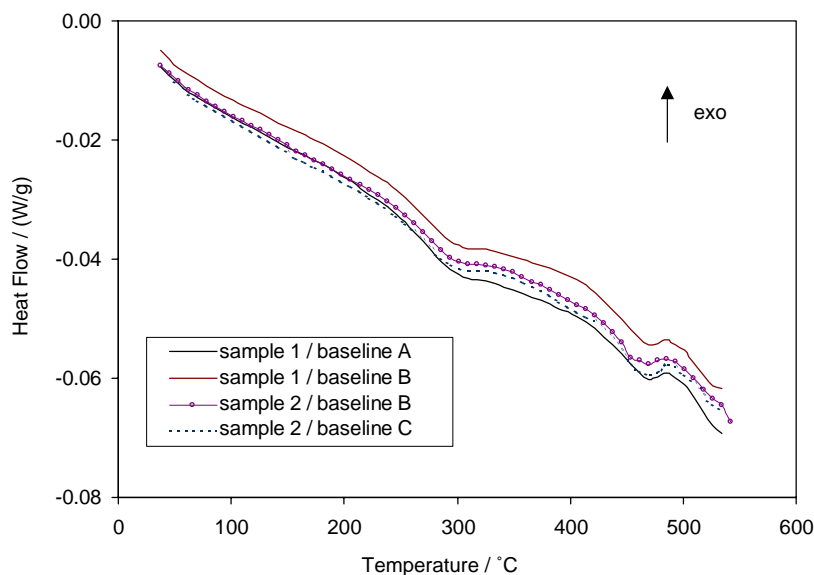


Fig. 1. Sample run minus baseline run of the Al-1.3 at.%Mg-0.4 at.%Mn-0.07 at.%Cu 10% deformation samples aged for 21 days at 170 °C. Four measurements are shown, which are formed from combinations of two DSC runs on the alloy samples and three different baselines.

300 °C. Thirdly, an endothermic effect with a peak at 460 °C is observed.

A similar analysis of repeatability of the DSC experiments after baseline correction and linear correction for heat capacity was performed for both alloys in the as cold-rolled condition and aged for 2, 7 and 21 days at 170 °C. The variations between nominally identical experiments were similar to the ones illustrated in Fig. 2. Nevertheless, some clear and consistent differences in the thermograms were observed. As an example, Fig. 3 compares several experiments on the Al-1.3 at.%Mg-0.4 at.%Mn-0.07 at.%Cu 10% deformation samples aged for 21 days at 170 °C, with experiments on

samples of the same composition and deformation, but aged for 2 days. The latter figure clearly shows that the endothermic effect with peak at about 300 °C has developed between 2 and 21 days ageing. Further evidence that the effect with peak at about 300 °C is caused by extended ageing (>2 days at 170 °C) can be obtained by subtracting a corrected DSC thermogram of an unaged or slightly aged sample from that of a sample aged for 21 days at 170 °C. We will term such a thermogram a comparative thermogram. Such a comparative thermogram for a sample aged 21 days is presented in Fig. 4, and compared in the same figure with two comparative thermograms for the same alloy aged 7 days at 170 °C, using

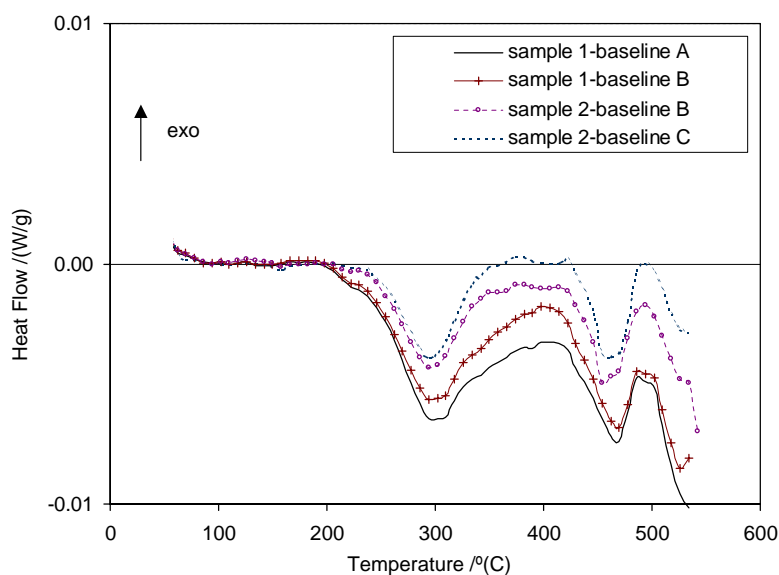


Fig. 2. Thermograms corrected for baseline run and heat capacity (linear function) of the Al-1.3 at.%Mg-0.4 at.%Mn-0.07 at.%Cu 10% deformation samples aged for 21 days at 170 °C. Four measurements are shown, which are formed by two samples and two baselines for each sample.

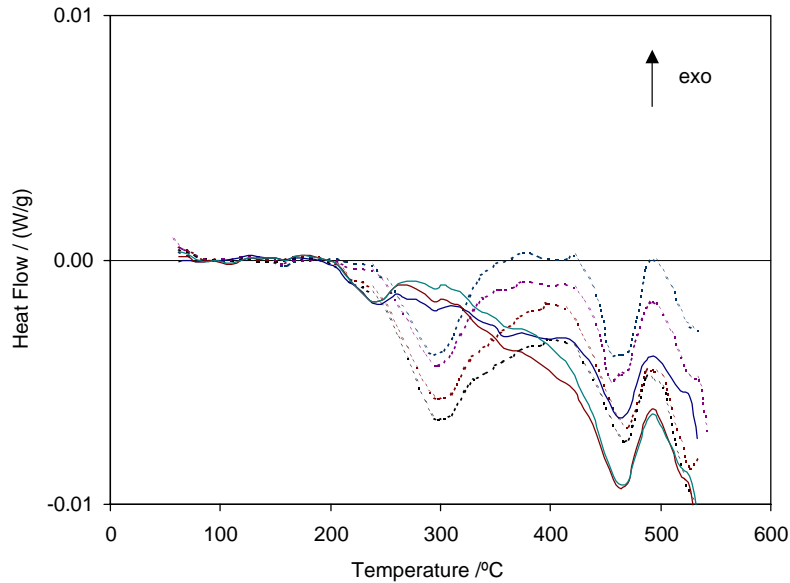


Fig. 3. Thermograms corrected for baseline run and heat capacity (linear function) of the Al–1.3 at.%Mg–0.4 at.%Mn–0.07 at.%Cu 10% deformation samples aged for 2 days (solid lines) and for 21 days (dotted lines) at 170 °C.

two different samples of the aged alloy, and a comparative thermogram for the same alloy aged 2 days at 170 °C. The curves of Al–1.3 at.%Mg–0.4 at.%Mn–0.07 at.%Cu samples aged for 7 and 21 days consistently show the endothermic effect with peak at about 300 °C as illustrated in Fig. 4. This confirms that this effect is caused by extended ageing (>2 days at 170 °C). This figure further shows that for 2 days ageing an endothermic peak at about 230 °C is present, whilst the effect peaking at 300 °C is absent. Fig. 4 also shows considerable variations in the heat effects beyond 320 °C, even

though ageing at 170 °C is unlikely to affect this part of the thermograms, and even for samples that are nominally identical. However none of the curves show any clear heat effect with a local minimum or maximum in the heat flow in this temperature range. Thus we must conclude that we can not reliably determine the thermograms beyond 320 °C. In Fig. 4, the endothermic effect with a peak at 460 °C, which was clearly distinguishable in Fig. 2 and Fig. 3, has disappeared. This indicates that ageing at 170 °C has not influenced the reaction(s) responsible for this effect.

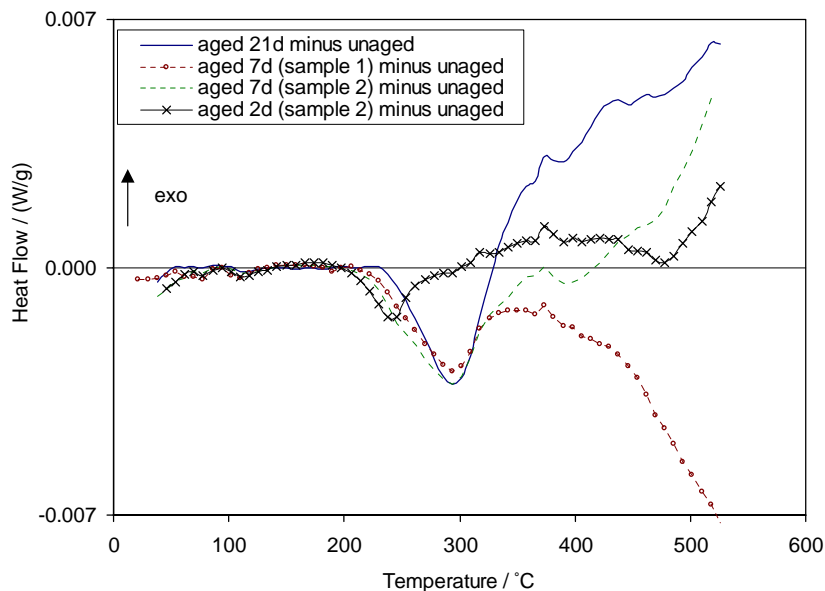


Fig. 4. Difference of a thermogram of the Al–1.3 at.%Mg–0.4 at.%Mn–0.07 at.%Cu 10% deformation samples aged for 21 days (dotted lines) at 170 °C and an unaged sample of the same alloy, compared with two measurements of the difference of a thermogram of the Al–1.3 at.%Mg–0.4 at.%Mn–0.07 at.%Cu 10% deformation samples aged for 7 days (dotted lines) at 170 °C and an unaged sample of the same alloy.

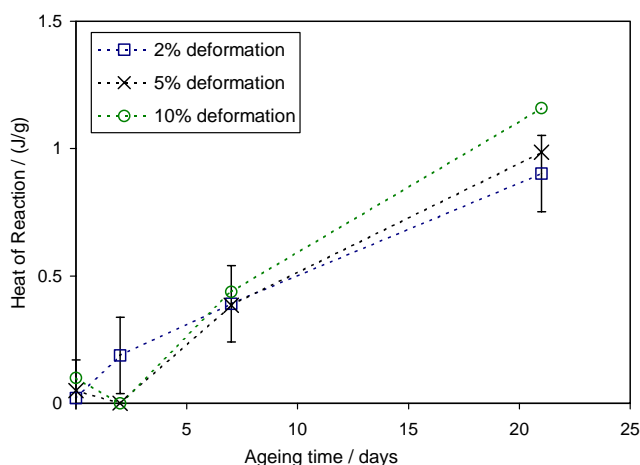


Fig. 5. Heat content of the exothermic effect with peak at 300 °C for the aged Al–1.3 at.% Mg–0.4 at.% Mn–0.07 at.% Cu with three levels of cold deformation.

The above analysis reveals the experimental limitations encountered while analysing Al alloys in which very small heat effects occur. However, it is equally clear that, through the present careful analysis and comparison of repeated experiments, certain small heat effects can be shown to be clearly reproducible, and suitable for analysis. The strongest reproducible effects caused by ageing are the endothermic effect with peak at 300 °C in samples aged for 7 and 21 days and the effect at about 230 °C in samples aged for 2 days. We have measured the heat contents of the endothermic effect with peak at 300 °C in our Al–1.3Mg–0.4Mn–0.07Cu and Al–1.3Mg–0.4Mn samples with three levels of cold deformation and four ageing conditions. We found that for the Cu free alloy in both aged and as cold worked conditions no significant heat effect could be observed. Also the as cold worked Al–1.3Mg–0.4Mn–0.07Cu showed no significant heat effect. In the aged Al–1.3Mg–0.4Mn–0.07Cu samples we could detect this endothermic heat effect and the magnitude is presented in Fig. 5. This figure shows a uniform increase of dissolution energies with ageing time, indicating the amount of precipitate increases with ageing time. The difference between our two alloys is in line with work on Al–3 at.% Mg–0.1 at.% Mn– $x$ Cu alloys which shows precipitation hardening for  $x > 0.08$  at.% and no precipitation hardening for  $x = 0$  [20].

#### 4. Discussion

In order to aid modelling and understanding of the DSC data of the present alloys, the solvi of S phase and Cu–Mg clusters in low Cu Al–Mg–Mn–Cu alloys is modelled using a regular solution model as presented before [23,24]. It is noted that in thermodynamic sense there is no difference between S phase and the phase that is usually indicated as S' as both have the same structure. The method assumes that solid solubility of elements A and B,  $c_A$ ,  $c_B$ , for phases of

the type  $M_m A_a B_b$  (M is the main constituent of the alloy), is given by [25]:

$$(c_A)^a (c_B)^b = c_1 \exp \left[ -\frac{\Delta H}{RT} \right] \quad (1)$$

where  $\Delta H$  is the enthalpy of formation of one ‘molecule’ of  $M_m A_a B_b$ ,  $R$  the gas constant,  $c_1$  is a (pre-exponential) constant.  $\Delta H$  and  $c_1$  are determined by fitting to data on S phase dissolution in Al–Mg–Cu alloys as obtained from DSC experiments [23,26] and for the clusters by data on cluster strengthening Al–Cu–Mg alloys from [27]. A graph for the solvus of S phase is given in Fig. 6. This figure indicates that S phase can form at 170 °C for alloys with very low copper content. In fact, for our alloys and other typical canstock alloys with about 1 at.% Mg, the Cu solubility is predicted to be less than 0.001 at.% at 170 °C and hence practically all copper that is dissolved after solution treatment can, in principle, precipitate to form S phase. One factor that could limit the amount of Cu available for S phase formation is the presence of Fe, which can combine in some alloys with Cu to form phases of the type  $Al_7 Cu_2 Fe$ . However, literature indicates that for the present alloys and other typical canstock alloys with Cu contents below 0.1 at.% no Al–Cu–Fe phases will form [28–30], and hence all Cu should be available for S phase formation. Similar calculations for Cu–Mg clusters indicate that the metastable solvus is well in excess of 170 °C and hence these clusters should not form in the present ageing treatments.

Fig. 6 further shows that for the present alloy with 0.07 at.% Cu and 1.3 at.% Mg, S phase dissolution during slow heating should be completed at about 310 °C. This corresponds very well with the temperature where the endothermic effect that appears in samples aged for 7 and 21 days is nearly completed, and hence the temperature

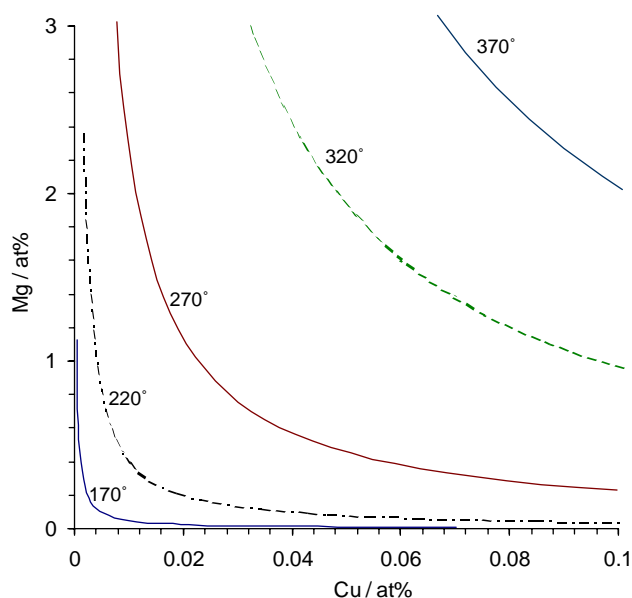


Fig. 6. Solvi of S phase at 170, 220, 270, 320 and 370 °C.

range of this effect is consistent with S phase dissolution. The latter indicates that the phase precipitating in our Al–1.3Mg–0.4Mn–0.07Cu alloy on extended ageing at 170 °C is either S phase or a Cu containing phase that has a solvus very similar to that of S phase. As S phase has been detected in aged Al–Mg–Cu alloys with Cu contents similar to the one in our Al–1.3Mg–0.4Mn–0.07Cu alloy [16], and no distinct dissolution effect was detected in this temperature range for the Cu-free alloy, it is very likely that the exothermic effect is due to dissolution of S phase. Conversely, the phase/structure that is dissolving in the endothermic effect at the lower temperature of 230 °C in the samples aged 2 days at 170 °C is clearly a phase/structure that is less stable than S phase. As noted in the previous paragraph, Cu–Mg clusters are expected to not be stable at 170 °C in our Al–1.3Mg–0.4Mn–0.07Cu alloy, and hence the phase/structure that is dissolving around 230 °C can not be Cu–Mg clusters. Instead, this phase/structure may be a structure termed GPBII zone or ordered zone [16] or a phase termed S'' which has been claimed to be present for several Al–Mg–Cu alloys with low Cu:Mg ratio [31], for instance in an Al–3.3 at.% Mg–0.18 at.% Cu alloy aged for 4 h at 180 °C in which the S'' phase was detected by high resolution electron microscopy [32]. In fact, a structure for a GPBII/S'' phase (orthorhombic with lattice parameters 0.4, 0.4 and 1.6 nm) was recently proposed by our group [31], and it was shown that diffraction and HREM data on alloys with Cu:Mg ratio close to 1 is consistent with this structure. Further investigations would be needed to confirm the presence of these structures/phases in the present low Cu alloys and to check whether any other precipitates are involved.

The 10% deformed samples aged for 21 days have a somewhat higher heat content for the S phase dissolution effect as compared to the samples with lower deformation (see Fig. 5). This deviation suggests that the high deformation levels (higher than 5%) enhance S phase formation rates after ageing for about 1 week. This could be due to the increased level of heterogeneous nucleation sites (such as dislocations) available for S phase formation or to enhanced diffusion of atoms along dislocations.

It is finally noted that the heat effects at temperatures in excess of 320 °C including the endothermic peak at about 470 °C are likely to be caused by the precipitation and subsequent dissolution of Mn containing phases (see e.g. [30]). The baseline variability and drift as illustrated in Figs. 2–4 proved too severe to provide a meaningful analysis of these effects.

## 5. Conclusions

DSC has been employed to detect and analyse precipitation reactions in an Al–1.3Mg–0.4Mn and an Al–1.3Mg–0.4Mn–0.07Cu alloy in which very small amounts of precipitate, less than 0.3 at.%, are expected to

form. It is shown that due to the very small heat effects, baseline instability and drift significantly interfere with the measurements, and multiple experiments and careful baseline correction are needed to detect and demonstrate reproducibility of effects. In the Cu containing alloy, ageing at 170 °C causes the appearance of two endothermic effects: for 2 days ageing a small dissolution effect at about 230 °C appears, whilst for 7 and 21 days ageing a dissolution peak at about 300 °C appears. The temperature range of the latter is consistent with S phase dissolution, whilst the former is thought to be due to a phase/structure that is less stable than S phase.

## Acknowledgements

The authors would like to thank Alcan International for providing the alloys and support for this work, and thank Drs G. Mahon, M. Hao and S. Court for their technical input.

## References

- [1] M.J. Starink, *Int. Mater. Rev.*, 2004. in press.
- [2] M.J. Starink, J. Yan, in: *Proceedings of First International Symposium on Metallurgical Modeling for Al Alloys*, ASM Materials Solutions, 12–15 October 2003, Pittsburgh, PA, USA, in press.
- [3] M.J. Starink, N. Gao, L. Davin, J. Yan, A. Cerezo, *Acta Mater.*, submitted for publication.
- [4] M.J. Starink, A.-M. Zahra, *Thermochim. Acta* 292 (1997) 159.
- [5] M.J. Starink, S.C. Wang, *Acta Mater.* 51 (2003) 5131.
- [6] A. Deschamps, A. Bigot, F. Livet, P. Auger, Y. Brechet, D. Blavette, *Philosoph. Mag.* 81 (2001) 2391.
- [7] M.J. Starink, P. Wang, I. Sinclair, P.J. Gregson, *Acta Mater.* 47 (1999) 3841.
- [8] M.J. Starink, P. Wang, I. Sinclair, P.J. Gregson, *Acta Mater.* 47 (1999) 3855.
- [9] M.J. Starink, A.-M. Zahra, *Phil. Mag. A* 76 (1997) 701.
- [10] P. Ratchev, B. Verlinden, P. De Smet, P. Van Houtte, *Scripta Mater.* 35 (1998) 1195.
- [11] P. Ratchev, B. Verlinden, P. De Smet, P. Van Houtte, *Acta Mater.* 46 (1998) 3523.
- [12] J.M. Howe, *Metall. Trans. A* 17A (1986) 593.
- [13] S.P. Ringer, K. Hono, I.J. Polmear, T. Sakurai, *Appl. Surf. Sci.* 94–5 (1996) 253.
- [14] A.K. Gupta, P. Gaunt, M.C. Chaturvedi, *Philos. Mag. A* 55 (1987) 375.
- [15] B. Verlinden, A.-M. Zahra, *Mater. Sci. Forum* 426 (2003) 423.
- [16] P.I. Gouma, D.J. Lloyd, M.J. Mills, *Mater. Sci. Eng. A* 319–321 (2001) 439.
- [17] Z. Zhu, M.J. Starink, in: *Proceedings of Ninth PG Conference in Eng. Mater.*, University of Southampton, Southampton, 2003.
- [18] G.B. Burger, A.K. Gupta, P.W. Jeffrey, D.J. Lloyd, *Mater. Charact.* 35 (1995) 23.
- [19] M.C. Carroll, P.I. Gouma, G.S. Dahen, M.J. Mills, *Mater. Sci. Eng. A* 319–321 (2001) 425.
- [20] S.A. Court, K.P. Hicklin, D.J. Lloyd, *Mater. Sci. Forum* 396–402 (2002) 1031.
- [21] C. Michaelsen, K. Barmak, T.P. Weihs, *Phys. D* 30 (1997) 3167.
- [22] C.Y. Zahra, A.-M. Zahra, *Thermochim. Acta* 276 (1996) 161.
- [23] M.J. Starink, P.J. Gregson, *Scr. Metall. Mater.* 33 (1995) 893.

- [24] M.J. Starink, P.J. Gregson, *Mater. Sci. Forum* 217–222 (1996) 673.
- [25] R.H. Brown, L.A. Willey, in: K.R. Van Horn (Ed.), *Aluminium: Properties, Physical Metallurgy and Phase Diagrams*, Vol. 1, ASM, Metals Park, OH, USA, 1967 p. 31.
- [26] P. Ratchev, B. Verlinden, A.-M. Zahra, *Mater. Sci. Forum* 331–337 (2000) 1095.
- [27] R.H. Beton, E.C. Rollason, *J. Inst. Metals* 86 (1957–1958) 77.
- [28] G.J. Marshall, *Mater. Sci. Forum* 217–220 (1996) 19.
- [29] R.G. Kamat, *J. Min. Met. Mater. Soc.* 48 (1996) 34.
- [30] Y.J. Li, L. Arnberg, *Mater. Sci. Eng. A* 347 (2003) 130.
- [31] S.C. Wang, M.J. Starink, in: *Proceedings of EMAG2003*, 3–5 September 2003, Oxford, UK.
- [32] L. Kovarik, P.I. Gouma, C. Kisielowski, S.A. Court, M.J. Mills, *Mater. Sci. Forum* 396–4 (2002) 845.