

X-Ray Studies in the System Ti–Hg–Zn

M. PUŠELJ and Z. BAN

Institute for Inorganic and Analytical Chemistry,
the University Zagreb, Yugoslavia(Z. Naturforsch. **25 a**, 315 [1970]; received 5 January 1970)

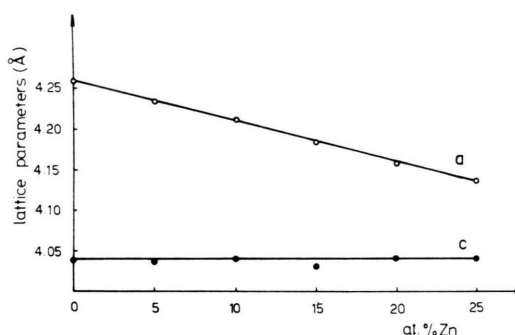
In a recent paper reported on part of the system Ti–Cu–Hg¹ a new phase TiCuHg₂ was found having the crystal structure B 32 (NaTl type). The most interesting but hitherto unexplained feature of this structure is the degree of filling of the unit cell (71%). In order to examine which one of the metals in the structure is eventually responsible for the formation of this particular phase, to which often a certain degree of ionic bonding is ascribed², we tried to prepare the isostructural compound TiZnHg₂. However, it turned out that its crystal structure belongs to the AuCu₃ (Ll₂) type ($a = 4.02 \pm 0.02$ Å), where all atoms are distributed statistically. We assume that the alternative configurations of the electron shells in the copper atom (3d¹⁰4s¹ or 3d⁹4s²) may be responsible for such a behaviour. Diffractometer data for this phase are given in Table I.

HKL	d_0	d_c	I_0	I_c
111	2.310	2.320	100	100
200	2.010	2.013	40	45
220	1.425	1.421	38	40
311	1.212	1.210	42	45
222	1.164	1.160	15	14
400	1.002	1.002	5	8
331	0.923	0.923	20	18
420	0.897	0.897	25	23
422	0.821	0.821	25	20

$\rho_x = 13.05$ g/cm³, $\rho_0 = 12.19$ g/cm³

Table I. Diffractometer data for TiZnHg₂ (CuK α -radiation) (Ll₂-type).

We also found that exactly 25% of titanium atoms in the TiHg phase (L I_0 -AuCu type)³ can be replaced by zinc, yielding thus a continuous series of solid solutions TiHg–Ti₃Hg₄Zn. It is interesting to notice that the zinc atoms tend to occupy preferentially positions parallel to the basal plane of the tetragonal unit cell of Ti₃Hg₄Zn ($a = 4.14 \pm 0.02$ Å, $c = 4.04 \pm 0.02$ Å). Since they are smaller than titanium atoms ($r_{Ti} = 1.47$ Å, $r_{Zn} = 1.34$ Å) parameter a decreases monotonously (Fig. 1) while c remains constant within the error limits. We were unable to find any sign of ordering between the zinc and titanium atoms in the

Fig. 1. The variation of the lattice parameters a and c in the series of solid solutions TiHg–Ti₃Hg₄Zn.

intermediary layer, even though an extensive series of experiments has been carried out. The relevant x-ray (film) data are given in Table II.

HKL	d_0	d_c	I_0	I_c
001	4.031	4.041	20	19
110	2.936	2.934	22	20
111	2.372	2.375	100	100
200	2.072	2.069	30	22
201	1.844	1.844	14	11
112	1.663	1.667	16	14
220	1.462	1.464	12	10
221	1.373	1.376	6	4
003	1.350	1.351	1	2.10 ⁻³
310	1.308	1.308	2	4
311	1.245	1.242	15	8
222	1.188	1.186	6	8
203	1.127	1.129	1	2
312	1.100	1.099	1	3
004	1.010	1.009	1	0.4
114	0.995	0.954	1	2
311	0.948	0.948	6	2
420	0.924	0.923	3	1
422	0.845	0.844	5	2

$\rho_x = 12.15$ g/cm³ $\rho_0 = 11.80$ g/cm³

Table II. X-ray data for Hg₄ZnTi₃ (CuK α -radiation).

Samples were prepared by heating mixtures of the elements in Vycor tubes filled with purified and dried argon (0.5 at.) at temperatures ranging from 400–700 °C, depending on composition. Densities were determined pycnometrically at least three times for each particular sample, using decalin, CCl₄ and CH₂J₂. The observed discrepancies must be ascribed to the pasty nature of the samples and the very pronounced tendency towards decomposition, during extended aging at room temperature.

Reprints request to Dr. Z. BAN, Institute for Inorganic and Analytical Chemistry, University of Zagreb, Zagreb, Jugoslavien, Ul. Soc. Rev. 8.

¹ M. PUŠELJ and Z. BAN, Croat. Chem. Acta **41**, 79 [1969].² E. ZINTL and F. HUSEMANN, Z. Physik. Chem. Leipzig (B) **21**, 138 [1933].³ I. PIETROKOWSKY, Trans. AIME **200**, 219 [1954].

Dieses Werk wurde im Jahr 2013 vom Verlag Zeitschrift für Naturforschung in Zusammenarbeit mit der Max-Planck-Gesellschaft zur Förderung der Wissenschaften e.V. digitalisiert und unter folgender Lizenz veröffentlicht: Creative Commons Namensnennung-Keine Bearbeitung 3.0 Deutschland Lizenz.

Zum 01.01.2015 ist eine Anpassung der Lizenzbedingungen (Entfall der Creative Commons Lizenzbedingung „Keine Bearbeitung“) beabsichtigt, um eine Nachnutzung auch im Rahmen zukünftiger wissenschaftlicher Nutzungsformen zu ermöglichen.

This work has been digitalized and published in 2013 by Verlag Zeitschrift für Naturforschung in cooperation with the Max Planck Society for the Advancement of Science under a Creative Commons Attribution-NoDerivs 3.0 Germany License.

On 01.01.2015 it is planned to change the License Conditions (the removal of the Creative Commons License condition “no derivative works”). This is to allow reuse in the area of future scientific usage.