

Self-diffusion of Tin in a liquid Tin-Lead alloy at the Eutectic Composition

D. H. Kurlat, M. Rosen, and G. Quintana

Departamento de Física, Facultad de Ingeniería (UNBA),
Buenos Aires, Argentina

(Z. Naturforsch. 31a, 1024 [1976];
received May 5, 1976)

By the shear cell technique, the self-diffusion coefficient (D_{Sn}) of tin in a liquid Sn–38.1 wt% Pb alloy has been measured in the temperature range 466 to 786 K. The slope of the D_{Sn} vs. T curve decreases up to about 573 K, where it gets constant. This behaviour may be explained by the cluster hypothesis.

A shear cell, as first used by Nachtrieb^{1,2} for liquid metals (Hg, Ga), has been employed. It was made of graphite to avoid bubble formation and chemical reactions and for ease of handling. The cell consisted of ten disks, mounted coaxially; each one was 0.5 cm thick, with three off center capillary holes of 1 mm diameter.

Before a diffusion experiment was begun, the capillaries of the two last disks – which contained the Sn radiotracer – were misaligned with respect

to the others. The run was started by aligning the holes, and finished by rotating each disk so as to section the liquid thread. By measuring the specific activity in each capillary section the diffusion profile was obtained.

The solution of Fick's equation with the boundary conditions $\partial c / \partial x = 0$ for $x = 0, L$ and the starting condition $c = c_0$ for $0 < x < h$ and $c = 0$ for $h < x < L$ is given e. g. in³. In our case $h = 1$ cm, $L = 5$ cm. The solution of this problem has been tabulated by Stefan and Kawalki⁴.

The radiotracer was Sn^{113} (half-life 112 days). Tin and lead were 4 N purity. All the operations were performed under Argon (1 atm) with previous degassing under 10^{-4} mm Hg. The temperature was controlled with a P.I.D. thermoregulator and measured with chromel-alumel thermocouples. A small positive temperature gradient (≤ 0.2 K/cm) avoided convective effects (thermodiffusion was considered negligible).

The filling of the capillaries was made by plunging the disks into the respective liquids and forcing the liquids to enter the capillaries by means of pressurized Argon (2–3 atm). The results are shown in Figure 1.

Measurements of the viscosity as a function of temperature^{5,6} in liquid Sn–38.1 wt% Pb (eutectic composition) show a soft change in slope near 623 K. Taking into account Ubbelohde's theory⁷, Kumar⁸ explains this behaviour as due to the presence of clusters (pseudo-molecules) in the liquid. This hypothesis may also explain our findings. Between T_{melting} and 573 K, relatively small changes in temperature produce dissociation of the clusters and the diffusion flow is largely increased. Above 573 K the liquid is "monomeric" and the variation of the self-diffusion coefficient with temperature is smaller.

Acknowledgments

The authors express their consideration to the National Research Council of Argentina (CONICET) for financial support.

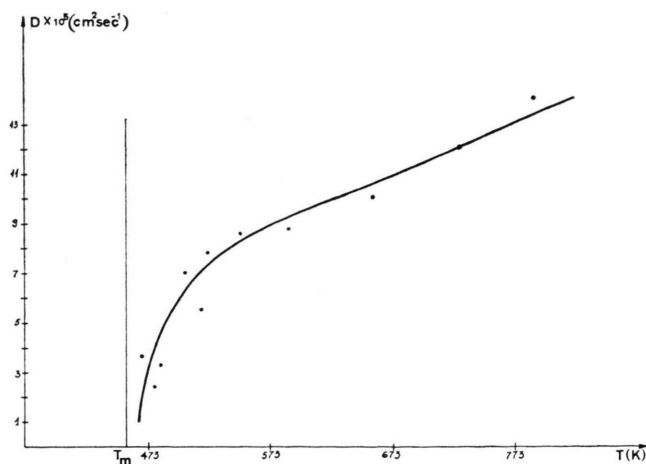


Fig. 1. Self-diffusion coefficient of tin in the liquid Sn–Pb eutectic alloy as a function of temperature.

- ¹ N. H. Nachtrieb and J. Petit, J. Chem. Phys. **24** (N 4), 746 [1956].
- ² N. H. Nachtrieb and J. Petit, J. Chem. Phys. **24** (N 5), 1027 [1956].
- ³ Y. Adda et J. Philibert, La Diffusion dans les Solides, Bibliothèque des Sciences et Techniques Nucleaires, p. 156.
- ⁴ H. Jost, Diffusion in Solid, Liquid, Gases, Academic Press, New York 1952.

- ⁵ H. J. Fisher and A. Phillips, Trans. TMS–AIME **200**, 1060 [1954].
- ⁶ M. Shiraishi, Y. Ogino, and A. Adachi, Technology Reports of the Osaka University **22**, No 1062 [1972].
- ⁷ E. McLaughlin and A. R. Ubbelohde, Trans. Faraday Soc. **56**, 988 [1960].
- ⁸ R. Kumar, M. Singh, and C. S. Sivaramakrishnan, Trans. TMS–AIME **239**, 1219 [1967].



Dieses Werk wurde im Jahr 2013 vom Verlag Zeitschrift für Naturforschung in Zusammenarbeit mit der Max-Planck-Gesellschaft zur Förderung der Wissenschaften e.V. digitalisiert und unter folgender Lizenz veröffentlicht: Creative Commons Namensnennung-Keine Bearbeitung 3.0 Deutschland Lizenz.

Zum 01.01.2015 ist eine Anpassung der Lizenzbedingungen (Entfall der Creative Commons Lizenzbedingung „Keine Bearbeitung“) beabsichtigt, um eine Nachnutzung auch im Rahmen zukünftiger wissenschaftlicher Nutzungsformen zu ermöglichen.

This work has been digitalized and published in 2013 by Verlag Zeitschrift für Naturforschung in cooperation with the Max Planck Society for the Advancement of Science under a Creative Commons Attribution-NoDerivs 3.0 Germany License.

On 01.01.2015 it is planned to change the License Conditions (the removal of the Creative Commons License condition "no derivative works"). This is to allow reuse in the area of future scientific usage.